

**ASME B18.8.2-2020**

**[Revision of ASME B18.8.2-2000 (R2010)]**

# **Taper Pins, Dowel Pins, Straight Pins, Grooved Pins, and Spring Pins (Inch Series)**

---

ASMENORMDOC.COM : Click to view the full PDF of ASME B18.8.2-2020

**AN AMERICAN NATIONAL STANDARD**



**The American Society of  
Mechanical Engineers**

**ASME B18.8.2-2020**  
[Revision of ASME B18.8.2-2000 (R2010)]

# **Taper Pins, Dowel Pins, Straight Pins, Grooved Pins, and Spring Pins (Inch Series)**

---

ASMENORMDOC.COM : Click to view the full PDF of ASME B18.8.2-2020

**AN AMERICAN NATIONAL STANDARD**



**The American Society of  
Mechanical Engineers**

Two Park Avenue • New York, NY • 10016 USA

Date of Issuance: December 21, 2020

This Standard will be revised when the Society approves the issuance of a new edition.

ASME issues written replies to inquiries concerning interpretations of technical aspects of this Standard. Interpretations are published on the Committee web page and under <http://go.asme.org/InterpsDatabase>. Periodically certain actions of the ASME B18 Committee may be published as Cases. Cases are published on the ASME website under the B18 Committee Page at <http://go.asme.org/B18committee> as they are issued.

Errata to codes and standards may be posted on the ASME website under the Committee Pages to provide corrections to incorrectly published items, or to correct typographical or grammatical errors in codes and standards. Such errata shall be used on the date posted.

The B18 Committee Page can be found at <http://go.asme.org/B18committee>. There is an option available to automatically receive an e-mail notification when errata are posted to a particular code or standard. This option can be found on the appropriate Committee Page after selecting "Errata" in the "Publication Information" section.

ASME is the registered trademark of The American Society of Mechanical Engineers.

This code or standard was developed under procedures accredited as meeting the criteria for American National Standards. The Standards Committee that approved the code or standard was balanced to assure that individuals from competent and concerned interests have had an opportunity to participate. The proposed code or standard was made available for public review and comment that provides an opportunity for additional public input from industry, academia, regulatory agencies, and the public-at-large.

ASME does not "approve," "rate," or "endorse" any item, construction, proprietary device, or activity.

ASME does not take any position with respect to the validity of any patent rights asserted in connection with any items mentioned in this document, and does not undertake to insure anyone utilizing a standard against liability for infringement of any applicable letters patent, nor assume any such liability. Users of a code or standard are expressly advised that determination of the validity of any such patent rights, and the risk of infringement of such rights, is entirely their own responsibility.

Participation by federal agency representative(s) or person(s) affiliated with industry is not to be interpreted as government or industry endorsement of this code or standard.

ASME accepts responsibility for only those interpretations of this document issued in accordance with the established ASME procedures and policies, which precludes the issuance of interpretations by individuals.

No part of this document may be reproduced in any form,  
in an electronic retrieval system or otherwise,  
without the prior written permission of the publisher.

The American Society of Mechanical Engineers  
Two Park Avenue, New York, NY 10016-5990

Copyright © 2020 by  
THE AMERICAN SOCIETY OF MECHANICAL ENGINEERS  
All rights reserved  
Printed in U.S.A.

# CONTENTS

|                                                                                                |           |
|------------------------------------------------------------------------------------------------|-----------|
| Foreword .....                                                                                 | v         |
| Committee Roster .....                                                                         | vii       |
| Correspondence With the B18 Committee .....                                                    | viii      |
| <b>1 Introduction .....</b>                                                                    | <b>1</b>  |
| <b>2 General Data for Pins .....</b>                                                           | <b>1</b>  |
| <b>3 General Data for Taper Pins .....</b>                                                     | <b>2</b>  |
| <b>4 General Data for Hardened Ground Machine Dowel Pins .....</b>                             | <b>5</b>  |
| <b>5 General Data for Hardened Ground Production Dowel Pins .....</b>                          | <b>9</b>  |
| <b>6 General Data for Unhardened Ground Dowel Pins .....</b>                                   | <b>11</b> |
| <b>7 General Data for Straight Pins .....</b>                                                  | <b>14</b> |
| <b>8 General Data for Grooved Pins, Grooved Drive Studs, and Grooved T-Head Cotter Pins ..</b> | <b>16</b> |
| <b>9 General Data for Spring Pins .....</b>                                                    | <b>27</b> |
| <b>Nonmandatory Appendices</b>                                                                 |           |
| A Recommended Hole Specifications for Taper Pins .....                                         | 34        |
| B Double Shear Testing of Pins .....                                                           | 38        |
| C Type B, C, and D Grooved Pin Dimensions .....                                                | 39        |
| D Conversion Table for SAE and UNS Material Specifications .....                               | 40        |
| <b>Figures</b>                                                                                 |           |
| 4.2.1.1-1 Point Concentricity .....                                                            | 7         |
| A-1-1 Step Drill Selection .....                                                               | 36        |
| A-1-2 Drill Diameter Examples .....                                                            | 37        |
| B-1-1 Typical Pin Shear Test Fixtures .....                                                    | 38        |
| <b>Tables</b>                                                                                  |           |
| 3.1.1-1 Dimensions of Taper Pins .....                                                         | 3         |
| 3.5.3-1 Standard Sizes and Lengths of Taper Pins .....                                         | 4         |
| 4.1.1-1 Dimensions of Hardened Ground Machine Dowel Pins .....                                 | 6         |
| 4.3.3-1 Preferred Sizes and Lengths of Hardened Ground Machine Dowel Pins .....                | 7         |
| 4.9.1-1 Suggested Hole Sizes for Standard Series Pins .....                                    | 8         |
| 5.1.1-1 Dimensions of Hardened Ground Production Dowel Pins .....                              | 9         |
| 5.3.3-1 Preferred Sizes and Lengths of Hardened Ground Production Dowel Pins .....             | 10        |
| 5.8.1-1 Suggested Hole Diameters for Hardened Ground Production Dowel Pins .....               | 11        |
| 6.1.1-1 Dimensions of Unhardened Ground Dowel Pins .....                                       | 12        |
| 6.3.3-1 Preferred Sizes and Lengths of Unhardened Ground Dowel Pins .....                      | 13        |
| 6.8-1 Suggested Hole Diameters for Unhardened Ground Dowel Pins .....                          | 14        |
| 7.1.1-1 Dimensions of Chamfered and Square End Straight Pins .....                             | 15        |

|         |                                                                                           |    |
|---------|-------------------------------------------------------------------------------------------|----|
| 8.2.1-1 | Dimensions of Grooved Pins . . . . .                                                      | 17 |
| 8.2.1-2 | Dimensions of Round-Head Grooved Drive Studs . . . . .                                    | 19 |
| 8.2.1-3 | Dimensions of Grooved T-Head Cotter Pins . . . . .                                        | 20 |
| 8.2.2-1 | Expanded Diameters for Grooved Pins Made From Low Carbon or Alloy Steel . . . . .         | 21 |
| 8.2.2-2 | Expanded Diameters for Grooved Pins Made From Corrosion Resistant Steel and Monel . . . . | 22 |
| 8.5.3-1 | Standard Sizes and Lengths of Grooved Pins . . . . .                                      | 24 |
| 8.5.3-2 | Pilot Length Dimensions for Round-Head Grooved Drive Studs . . . . .                      | 25 |
| 8.5.3-3 | Groove Length Dimensions for Grooved T-Head Cotter Pins . . . . .                         | 26 |
| 8.7-1   | Minimum Performance Requirements of Grooved Pins . . . . .                                | 26 |
| 8.8-1   | Recommended Hole Sizes for Unplated Grooved Pins . . . . .                                | 26 |
| 8.8-2   | Recommended Hole Sizes for Unplated Grooved Drive Studs . . . . .                         | 27 |
| 9.4.2-1 | Tolerance on Length of Spring Pins . . . . .                                              | 28 |
| 9.4.3-1 | Practical Sizes and Lengths of Coiled- and Slotted-Type Spring Pins . . . . .             | 29 |
| 9.4.4-1 | Dimensions of Slotted-Type Spring Pins . . . . .                                          | 30 |
| 9.4.4-2 | Dimensions of Coiled-Type Spring Pins . . . . .                                           | 31 |
| 9.6-1   | Hardness Requirements for Slotted- and Coiled-Type Spring Pins . . . . .                  | 33 |
| A-1-1   | Drill Chart . . . . .                                                                     | 35 |
| C-1     | Dimensions of Grooved Pins . . . . .                                                      | 39 |
| D-1     | Conversion Table for SAE and UNS Material Specifications . . . . .                        | 40 |

ASMENORMDOC.COM : Click to view the full PDF of ASME B18.8.2-2020

# FOREWORD

The need for a standard covering machine pins was recognized by industry as far back as March, 1926, when the Sectional Committee on the Standardization of Machine Pins was organized under the procedure of the American Standards Association (later the United States of America Standards Institute and as of October 6, 1969, the American National Standards Institute, Inc.), with the Society of Automotive Engineers and the American Society of Mechanical Engineers as joint sponsors.

For the next year or two an effort was made via correspondence to develop a basis on which a standard for straight, taper, split, and dowel pins might be established. This correspondence exposed a distinct difference of opinion on the part of the manufacturers and users of taper machine pins, which seemed to discourage the members of the committee from attempting standardization on any of the types of pins within its scope. The sponsor organization made frequent efforts to revive this project through letters and the distribution of technical literature on this general subject, without avail.

In December, 1941, during its periodic review of Society-sponsored standards, the ASME Standardization Committee decided that reviving the project was unlikely and voted (subject to acceptance by the sponsors) to suggest to the ASA the transfer of this project to Sectional Committee B5 on the Standardization of Small Tools and Machine Tool Elements. The sponsors agreed and on July 7, 1942, the ASA sanctioned this action and Sectional Committee B43 was discharged and the project was officially transferred to Sectional Committee B5.

At its meeting in December, 1942, Sectional Committee B5 voted to enlarge its scope to include machine pins. Technical Committee No. 23 was subsequently established and charged with the responsibility for technical content of standards covering machine pins. This group held its first meeting on November 30, 1943, at which time a subgroup on Correlation and Recommendations was appointed and it was voted to include clevis pins in addition to the other pin types already under consideration. Several drafts were prepared by the subgroup, distributed for critical comment to users, manufacturers, and general interests and revised and resubmitted for comments. This action finally resulted in acceptance by Technical Committee 23 of a draft dated November, 1945. Proofs of the draft, with a date of October, 1946 were distributed to the members of Sectional Committee B5 for letter ballot approval. After the approval of the Sectional Committee, the proposal was next approved by the sponsor bodies, and presented to the American Standards Association for approval as an American Standard. This designation was granted on July 7, 1947.

Following the issuance of the standard it became apparent that the table on cotter pins needed revision. Accordingly in 1953 a proposed revision was submitted to the Sectional Committee. After attaining Sectional Committee and sponsor approval this revision was approved by the American Standards Association on July 9, 1954 as ASA B5.20-1954.

In 1956 and 1957, in response to requests from industry, extensive changes were incorporated into a proposed revision. These included revisions to chamfer values and tolerances on straight pins and unhardened ground dowel pins; revisions to under-head-to-hole, pin end dimensions, and hole size tolerances on clevis pins; addition of chisel point to cotter pin end-styles; and the incorporation of coverage on grooved pins. Following Sectional Committee and sponsor approvals, this revision was adopted by the American Standards Association on March 25, 1958, as ASA B5.20-1958.

In late 1961, Sectional Committee B5 suggested that Sectional Committee B18 on the standardization of bolts, nuts, rivets, screws, and similar fasteners assume jurisdiction over standards for pins. Recognizing that the bulk of the products covered in the ASA B5.20 standards were fastener rather than machine oriented, this recommendation was supported by the B18 Committee and officially endorsed by the sponsor organizations. Consequently this Committee, at the September 14, 1962 meeting, decreed that Subcommittee 23\* should be formed to review and update the pin standard.

At the initial meeting, held on June 3, 1964, Subcommittee 23\* decided to add standards for spring pins and to establish seven subgroups, each of which would have technical responsibility for specific pin products, and to publish respective products under separate cover as projects were completed.

Over several years, work by Subgroups 2, 3, 4, 5, and 6 culminated in a proposal for revising the standards covering taper, dowel, straight, and grooved pins and including coverage for spring pins (which was approved through letter ballot by Subcommittee 8 on February 24, 1977). After acceptance by American National Standards Committee B18 and the sponsor organizations, this document was submitted to the American National Standards Institute for approval as an American National Standard. Approval was granted on April 5, 1978 and the standard was published under the designation ANSI B18.8.2, superseding in part the coverage provided in ASA B5.20-1958.

---

\* As of April 1, 1966 Subcommittee 23 was redesignated Subcommittee 8.

The B18.8.2-1978 edition was reaffirmed without change in 1989. The 1995 edition of B18.8.2 contained significant changes to the 1989 edition of B18.8.2 and was developed by the American Society of Mechanical Engineers B18 Committee on Fasteners. ASME B18.8.2-2000 was approved by the American National Standards Institute on June 22, 2000, and reaffirmed in 2010.

In 2017, the committee agreed to revise this Standard. The technical request prompting the revision began with some confusion in the industry regarding the diameter ( $A$ ) of grooved pins. This revision clarifies that this dimension may be affected during the grooving process and shall not be cause for rejection. ASME B18.8.2-2020 was initially approved by ANSI as an American National Standard on April 16, 2020. However, publication was postponed to allow the committee to remove unrelated dimensions from Table C-1. ASME B18.8.2-2020 was again approved by ANSI as an American National Standard on October 30, 2020.

ASMENORMDOC.COM : Click to view the full PDF of ASME B18.8.2 2020

# ASME B18 COMMITTEE

## Standardization of Bolts, Nuts, Rivets, Screws, Washers, and Similar Fasteners

(The following is the roster of the Committee at the time of approval of this Standard.)

### STANDARDS COMMITTEE OFFICERS

**W. Guth**, *Chair*  
**J. Medcalf**, *Vice Chair*  
**A. L. Guzman Rodriguez**, *Secretary*

### STANDARDS COMMITTEE PERSONNEL

**T. Anderson**, Bay Bolt  
**L. Borowski**, Greenslade and Co., Inc.  
**S. Brahimi**, Industrial Fasteners Institute  
**B. Cao**, Infasco  
**V. Cartina**, Hi-Performance Fastening Systems  
**L. Claus**, NNI Training and Consulting, Inc.  
**A. P. Cockman**, Consultant  
**D. S. George**, Michigan Metal Coating  
**W. Guth**, Electric Boat Corp.  
**A. L. Guzman Rodriguez**, The American Society of Mechanical Engineers  
**J. Medcalf**, Field Fastener  
**M. Q. Muhammad**, Defense Logistics Agency — Troop Support  
**J. P. Nash**, Caterpillar, Inc.  
**F. J. Perry**, John Deere  
**C. B. Williamson**, Fastenal Co.

**J. F. McCarrick**, *Alternate*, Defense Supply Center — Philadelphia  
**M. Byrne**, *Contributing Member*, General Fasteners Co.  
**D. A. Clever**, *Contributing Member*, Consultant  
**R. W. Davidson**, *Contributing Member*, Endries International, Inc.  
**J. J. Grey**, *Contributing Member*, Fastener Consulting Services, Inc.  
**J. C. Jennings**, *Contributing Member*, Naval Surface Warfare Center — Philadelphia  
**M. Kaindle**, *Contributing Member*, Aztech Locknut Co.  
**D. Korneffel**, *Contributing Member*, Cadenas PARTsolutions  
**M. D. Prasad**, *Contributing Member*, Global M&F Solutions, Inc.  
**J. J. Stoczanskyj**, *Contributing Member*, Beacon Fasteners and Components, Inc.  
**R. D. Strong**, *Contributing Member*, Lear Corp.  
**C. G. Vertullo**, *Contributing Member*, Carver Engineering and Manufacturing, Inc.  
**C. J. Wilson**, *Contributing Member*, Consultant

### SUBCOMMITTEE 8 — MACHINE PINS

**A. Barry**, *Chair*, Consultant  
**J. F. Koehl**, SPIROL International Corp.  
**R. Lund**, Fastenal Co.  
**D. A. Thonus**, Fastar, Inc.

**C. G. Vertullo**, Carver Engineering and Manufacturing, Inc.  
**C. J. Wilson**, Consultant  
**D. Clever**, *Contributing Member*, Consultant



# CORRESPONDENCE WITH THE B18 COMMITTEE

**General.** ASME Standards are developed and maintained with the intent to represent the consensus of concerned interests. As such, users of this Standard may interact with the Committee by requesting interpretations, proposing revisions or a case, and attending Committee meetings. Correspondence should be addressed to:

Secretary, B18 Standards Committee  
The American Society of Mechanical Engineers  
Two Park Avenue  
New York, NY 10016-5990  
<http://go.asme.org/Inquiry>

**Proposing Revisions.** Revisions are made periodically to the Standard to incorporate changes that appear necessary or desirable, as demonstrated by the experience gained from the application of the Standard. Approved revisions will be published periodically.

The Committee welcomes proposals for revisions to this Standard. Such proposals should be as specific as possible, citing the paragraph number(s), the proposed wording, and a detailed description of the reasons for the proposal, including any pertinent documentation.

**Proposing a Case.** Cases may be issued to provide alternative rules when justified, to permit early implementation of an approved revision when the need is urgent, or to provide rules not covered by existing provisions. Cases are effective immediately upon ASME approval and shall be posted on the ASME Committee web page.

Requests for Cases shall provide a Statement of Need and Background Information. The request should identify the Standard and the paragraph, figure, or table number(s), and be written as a Question and Reply in the same format as existing Cases. Requests for Cases should also indicate the applicable edition(s) of the Standard to which the proposed Case applies.

**Interpretations.** Upon request, the B18 Standards Committee will render an interpretation of any requirement of the Standard. Interpretations can only be rendered in response to a written request sent to the Secretary of the B18 Standards Committee.

Requests for interpretation should preferably be submitted through the online Interpretation Submittal Form. The form is accessible at <http://go.asme.org/InterpretationRequest>. Upon submittal of the form, the Inquirer will receive an automatic e-mail confirming receipt.

If the Inquirer is unable to use the online form, he/she may mail the request to the Secretary of the B18 Standards Committee at the above address. The request for an interpretation should be clear and unambiguous. It is further recommended that the Inquirer submit his/her request in the following format:

|                         |                                                                                                                                                                                                                                                                                                                       |
|-------------------------|-----------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------|
| Subject:                | Cite the applicable paragraph number(s) and the topic of the inquiry in one or two words.                                                                                                                                                                                                                             |
| Edition:                | Cite the applicable edition of the Standard for which the interpretation is being requested.                                                                                                                                                                                                                          |
| Question:               | Phrase the question as a request for an interpretation of a specific requirement suitable for general understanding and use, not as a request for an approval of a proprietary design or situation. Please provide a condensed and precise question, composed in such a way that a "yes" or "no" reply is acceptable. |
| Proposed Reply(ies):    | Provide a proposed reply(ies) in the form of "Yes" or "No," with explanation as needed. If entering replies to more than one question, please number the questions and replies.                                                                                                                                       |
| Background Information: | Provide the Committee with any background information that will assist the Committee in understanding the inquiry. The Inquirer may also include any plans or drawings that are necessary to explain the question; however, they should not contain proprietary names or information.                                 |

Requests that are not in the format described above may be rewritten in the appropriate format by the Committee prior to being answered, which may inadvertently change the intent of the original request.

Moreover, ASME does not act as a consultant for specific engineering problems or for the general application or understanding of the Standard requirements. If, based on the inquiry information submitted, it is the opinion of the Committee that the Inquirer should seek assistance, the inquiry will be returned with the recommendation that such assistance be obtained.

ASME procedures provide for reconsideration of any interpretation when or if additional information that might affect an interpretation is available. Further, persons aggrieved by an interpretation may appeal to the cognizant ASME Committee or Subcommittee. ASME does not “approve,” “certify,” “rate,” or “endorse” any item, construction, proprietary device, or activity.

**Attending Committee Meetings.** The B18 Standards Committee regularly holds meetings and/or telephone conferences that are open to the public. Persons wishing to attend any meeting and/or telephone conference should contact the Secretary of the B18 Standards Committee. Future Committee meeting dates and locations can be found on the Committee Page at <http://go.asme.org/B18committee>.

ASMENORMDOC.COM : Click to view the full PDF of ASME B18.8-2020

INTENTIONALLY LEFT BLANK

ASMENORMDOC.COM : Click to view the full PDF of ASME B18.8.2 2020

# TAPER PINS, DOWEL PINS, STRAIGHT PINS, GROOVED PINS, AND SPRING PINS (INCH SERIES)

## 1 INTRODUCTION

### 1.1 Scope

**1.1.1** This Standard covers the dimensional and general data for taper pins, dowel pins, straight pins, grooved pins, and spring pins. Also included are appendices providing supplementary information for the drilling of holes for taper pins and the testing of pins in double shear.

**1.1.2** The inclusion of dimensional data in this Standard is not intended to imply that all the products described are stock production sizes. Consumers should consult with manufacturers concerning lists of stock production sizes.

### 1.2 Comparison With ISO Standards

Since these are inch fastener standards, there are no comparable ISO standards.

### 1.3 Dimensions

Unless otherwise specified, all dimensions are in inches. All dimensions shall apply before coating. Symbols specifying geometric characteristics are in accord with ASME Y14.5.

### 1.4 Options

Where specified, options shall be at the discretion of the manufacturer unless otherwise agreed upon by the manufacturer and purchaser. Special materials, coatings, lubrication, or packaging requirements shall be specified by the purchaser.

### 1.5 Terminology

For definitions of terminology not specified in this Standard, refer to ASME B18.12.

### 1.6 Referenced Standards

The following is a list of publications referenced in this Standard. The latest edition shall be used.

ASME B18.8.1, Clevis Pins and Cotter Pins (Inch Series)  
ASME B18.12, Glossary of Terms for Mechanical Fasteners  
ASME B18.18, Quality Assurance for Fasteners

ASME B18.24, Part Identifying Number (PIN) Code System for B18 Fastener Products

ASME B46.1, Surface Texture (Surface Roughness, Waviness, and Lay)

ASME Y14.5, Dimensioning and Tolerancing

Publisher: The American Society of Mechanical Engineers (ASME), Two Park Avenue, New York, NY 10016-5990 (www.asme.org)

### 1.7 Related Standards

Standards for clevis pins and cotter pins, inch series are published in ASME B18.8.1.

### 1.8 Part Identifying Number

For a Part Identifying Number, refer to ASME B18.24.

## 2 GENERAL DATA FOR PINS

### 2.1 Types of Pins

**2.1.1 Taper Pins.** Taper pins shall have a uniform taper over the pin length with both ends crowned. Most sizes are supplied in both commercial and precision classes, the latter having generally tighter tolerances and being more closely controlled in manufacture. Dimensions for both classes are given in [Table 3.1.1-1](#).

**2.1.2 Dowel Pins.** The following three varieties of dowel pins are covered.

**2.1.2.1 Hardened Ground Machine Dowel Pins.** This variety of hardened dowel pins shall have ground cylindrical sides with one end pointed slightly to enter mating drive-fit holes and the other end rounded or crowned for driving purposes. They are available in standard and over-size diameter series to satisfy initial and replacement requirements, respectively. Dimensions for both series are given in [Table 4.1.1-1](#).

**2.1.2.2 Hardened Ground Production Dowel Pins.** This variety of hardened dowel pin shall have ground cylindrical sides with both ends rounded sufficiently to enable the pin to be pressed into drive-fit holes. Dimensions are given in [Table 5.1.1-1](#).

**2.1.2.3 Unhardened Ground Dowel Pins.** This variety of dowel pin shall have ground cylindrical sides with both ends chamfered. Dimensions are given in [Table 6.1.1-1](#).

**2.1.3 Straight Pins.** Straight pins shall have unground, straight cylindrical sides with both ends definitely chamfered on chamfered straight pins and with both ends having broken corners or being slightly chamfered on square end straight pins. Dimensions are given in [Table 7.1.1-1](#).

**2.1.4 Grooved Pins.** Grooved pins shall have unground, straight cylindrical sides with three or more swaged or extruded grooves equally spaced around the periphery to displace material beyond the basic pin diameter. Both ends of the pin are normally crowned or chamfered. Several types of grooved pins are available, including headed versions, grooved drive studs, and grooved T-head cotter pins, to satisfy various design considerations. Upon installation, the material displaced by the grooves is forced back into the grooves and reacts against the sides of the hole to promote retention of the pin or stud. Dimensions of the various types of groove pins are given in [Tables 8.2.1-1](#) through [8.2.2-2](#), grooved drive studs are shown in [Table 8.2.1-2](#), and grooved T-head cotter pins are covered in [Tables 8.2.1-3](#) and [8.5.3-3](#).

**2.1.5 Spring Pins.** Spring pins shall have straight cylindrical sides with both ends chamfered. They are available in two basic types, reflecting slotted construction and coiled construction, and the latter in standard duty, heavy duty, and light duty series to suit various design requirements. Slotted-type spring pins having a single wall and coiled-type spring pins having multiple walls are formed or wrapped from strip stock to a diameter larger than basic and hardened in accordance with [para. 9.6](#). Upon installation the pin diameters contract and the spring reaction against the sides of the hole tends to retain the pin. Dimensions of slotted-type spring pins and coiled-type spring pins are given in [Tables 9.4.4-1](#) and [9.4.4-2](#), respectively.

### 3 GENERAL DATA FOR TAPER PINS

#### 3.1 Diameters

**3.1.1 Major Diameter.** The major diameter,  $A$ , of both commercial and precision classes of pins, specified in [Table 3.1.1-1](#), is the diameter at the large end and is the basis for the pin size.

**3.1.2 Diameter at Small End.** The diameter at the small end of pins,  $B$ , is a function of the length and should be specified as a reference dimension for determining drilled hole size. (See [Nonmandatory Appendix A](#).) It shall be computed by multiplying the nominal length of pin by the factor 0.02083 and subtracting the result from the basic pin diameter.

#### 3.2 Ends

Both ends of commercial and precision class pins shall be crowned with a spherical radius as specified in [Table 3.1.1-1](#).

#### 3.3 Taper

**3.3.1 Commercial Class.** The taper on diameter of commercial class taper pins shall be  $0.250 \pm 0.006$  in./ft (12.00 in.) of length.

**3.3.2 Precision Class.** The taper on diameter of precision class taper pins shall be  $0.250 \pm 0.004$  in./ft (12.00 in.) of length.

#### 3.4 Concavity and Convexity

Pins shall be straight within the following limits. Refer to the illustration in [Table 3.1.1-1](#).

| Pin Class  | Concavity and Convexity Limits for Nominal Pin Length |                           |               |
|------------|-------------------------------------------------------|---------------------------|---------------|
|            | Up to 2 in.,<br>incl.                                 | Over 2 to 4 in.,<br>incl. | Over<br>4 in. |
| Commercial | 0.001                                                 | 0.002                     | 0.004         |
| Precision  | 0.0005                                                | 0.001                     | 0.002         |

#### 3.5 Length

**3.5.1 Measurement.** The length of taper pins shall be measured, parallel to the axis of pin, between the points of intersection of the crown with the diameter at the ends of the pin.

**3.5.2 Tolerance on Length.** The tolerance on length of taper pins shall be  $\pm 0.010$  in. for both commercial and precision classes.

**3.5.3 Standard Lengths.** The standard sizes and lengths in which taper pins are normally available are depicted in [Table 3.5.3-1](#). Precision class pins are not produced in size numbers 11 through 14. Where other size-length combinations may be required, manufacturers should be consulted.


#### 3.6 Surface Roughness

The surface roughness over the length of pins shall not exceed  $63 \mu\text{in.}$  (arithmetical average) on commercial class pins nor  $32 \mu\text{in.}$  (arithmetical average) on precision class pins. Refer to ASME B46.1. For pins having additive finishes, these limits shall apply prior to plating or coating.

#### 3.7 Materials

Unless otherwise specified, taper pins shall be made from SAE 1211 steel, or cold drawn SAE 1212 or SAE 1213 steel, or equivalents, and no mechanical property requirements shall apply.

Table 3.1.1-1 Dimensions of Taper Pins

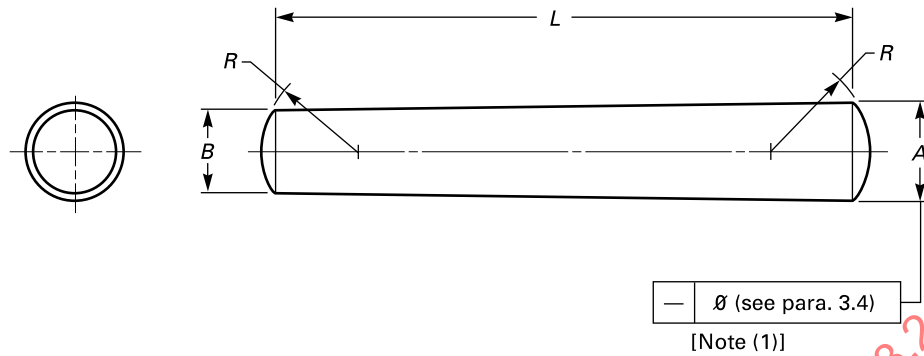

| Pin Size Number and<br>Basic Pin Diameter<br>[Note (2)] |        | Major Diameter (Large End), <i>A</i> |        |                            |          | End Crown Radius, <i>R</i> |       |
|---------------------------------------------------------|--------|--------------------------------------|--------|----------------------------|----------|----------------------------|-------|
|                                                         |        | Commercial Class                     |        | Precision Class [Note (3)] |          |                            |       |
|                                                         |        | Max.                                 | Min.   | Max.                       | Min.     | Max.                       | Min.  |
| 7/0                                                     | 0.0625 | 0.0638                               | 0.0618 | 0.0635                     | 0.0625   | 0.072                      | 0.052 |
| 6/0                                                     | 0.0780 | 0.0793                               | 0.0773 | 0.0790                     | 0.0780   | 0.088                      | 0.068 |
| 5/0                                                     | 0.0940 | 0.0953                               | 0.0933 | 0.0950                     | 0.0940   | 0.104                      | 0.084 |
| 4/0                                                     | 0.1090 | 0.1103                               | 0.1083 | 0.1100                     | 0.1090   | 0.119                      | 0.099 |
| 3/0                                                     | 0.1250 | 0.1263                               | 0.1243 | 0.1260                     | 0.1250   | 0.135                      | 0.115 |
| 2/0                                                     | 0.1410 | 0.1423                               | 0.1403 | 0.1420                     | 0.1410   | 0.151                      | 0.131 |
| 0                                                       | 0.1560 | 0.1573                               | 0.1553 | 0.1570                     | 0.1560   | 0.166                      | 0.146 |
| 1                                                       | 0.1720 | 0.1733                               | 0.1713 | 0.1730                     | 0.1720   | 0.182                      | 0.162 |
| 2                                                       | 0.1930 | 0.1943                               | 0.1923 | 0.1940                     | 0.1930   | 0.203                      | 0.183 |
| 3                                                       | 0.2190 | 0.2203                               | 0.2183 | 0.2200                     | 0.2190   | 0.229                      | 0.209 |
| 4                                                       | 0.2500 | 0.2513                               | 0.2493 | 0.2510                     | 0.2500   | 0.260                      | 0.240 |
| 5                                                       | 0.2890 | 0.2903                               | 0.2883 | 0.2900                     | 0.2890   | 0.299                      | 0.279 |
| 6                                                       | 0.3410 | 0.3423                               | 0.3403 | 0.3420                     | 0.3410   | 0.351                      | 0.331 |
| 7                                                       | 0.4090 | 0.4103                               | 0.4083 | 0.4100                     | 0.4090   | 0.419                      | 0.399 |
| 8                                                       | 0.4920 | 0.4933                               | 0.4913 | 0.4930                     | 0.4920   | 0.502                      | 0.482 |
| 9                                                       | 0.5910 | 0.5923                               | 0.5903 | 0.5920                     | 0.5910   | 0.601                      | 0.581 |
| 10                                                      | 0.7060 | 0.7073                               | 0.7053 | 0.7070                     | 0.7060   | 0.716                      | 0.696 |
| 11                                                      | 0.8600 | 0.8613                               | 0.8593 | Note (2)                   | Note (2) | 0.870                      | 0.850 |
| 12                                                      | 1.0320 | 1.0333                               | 1.0313 | Note (2)                   | Note (2) | 1.042                      | 1.022 |
| 13                                                      | 1.2410 | 1.2423                               | 1.2403 | Note (2)                   | Note (2) | 1.251                      | 1.231 |
| 14                                                      | 1.5230 | 1.5243                               | 1.5223 | Note (2)                   | Note (2) | 1.533                      | 1.513 |

## GENERAL NOTES:

- (a) For additional requirements, refer to [section 3](#).  
 (b) Reference ASME Y14.5M.

## NOTES:

- (1) — = straightness; ø = diameter  
 (2) Where specifying nominal pin size in decimals, zeros preceding decimal and in the fourth decimal place shall be omitted.  
 (3) Precision Class pins are not produced in size numbers 11 through 14.

Table 3.5.3-1 Standard Sizes and Lengths of Taper Pins

| Nominal Length | Pin Size Number |     |     |     |     |     |     |     |     |     |     |     |     |     |     |     |     |        |        |        |        |
|----------------|-----------------|-----|-----|-----|-----|-----|-----|-----|-----|-----|-----|-----|-----|-----|-----|-----|-----|--------|--------|--------|--------|
|                | 7/0             | 6/0 | 5/0 | 4/0 | 3/0 | 2/0 | 0   | 1   | 2   | 3   | 4   | 5   | 6   | 7   | 8   | 9   | 10  | 11 (1) | 12 (1) | 13 (1) | 14 (1) |
| 1/4            | X               | X   | X   | X   | X   | ... | ... | ... | ... | ... | ... | ... | ... | ... | ... | ... | ... | ...    | ...    | ...    | ...    |
| 3/8            | X               | X   | X   | X   | X   | ... | ... | ... | ... | ... | ... | ... | ... | ... | ... | ... | ... | ...    | ...    | ...    | ...    |
| 1/2            | X               | X   | X   | X   | X   | X   | X   | ... | ... | ... | ... | ... | ... | ... | ... | ... | ... | ...    | ...    | ...    | ...    |
| 5/8            | X               | X   | X   | X   | X   | X   | X   | ... | ... | ... | ... | ... | ... | ... | ... | ... | ... | ...    | ...    | ...    | ...    |
| 3/4            | X               | X   | X   | X   | X   | X   | X   | X   | X   | X   | X   | ... | ... | ... | ... | ... | ... | ...    | ...    | ...    | ...    |
| 7/8            | X               | X   | X   | X   | X   | X   | X   | X   | X   | X   | X   | ... | ... | ... | ... | ... | ... | ...    | ...    | ...    | ...    |
| 1              | X               | X   | X   | X   | X   | X   | X   | X   | X   | X   | X   | X   | ... | ... | ... | ... | ... | ...    | ...    | ...    | ...    |
| 1 1/4          | ...             | X   | X   | X   | X   | X   | X   | X   | X   | X   | X   | X   | X   | X   | X   | X   | ... | ...    | ...    | ...    | ...    |
| 1 1/2          | ...             | X   | X   | X   | X   | X   | X   | X   | X   | X   | X   | X   | X   | X   | X   | X   | X   | ...    | ...    | ...    | ...    |
| 1 3/4          | ...             | ... | ... | X   | X   | X   | X   | X   | X   | X   | X   | X   | X   | X   | X   | X   | X   | ...    | ...    | ...    | ...    |
| 2              | ...             | ... | ... | X   | X   | X   | X   | X   | X   | X   | X   | X   | X   | X   | X   | X   | X   | X      | X      | ...    | ...    |
| 2 1/4          | ...             | ... | ... | ... | ... | X   | X   | X   | X   | X   | X   | X   | X   | X   | X   | X   | X   | X      | X      | ...    | ...    |
| 2 1/2          | ...             | ... | ... | ... | ... | X   | X   | X   | X   | X   | X   | X   | X   | X   | X   | X   | X   | X      | X      | ...    | ...    |
| 2 3/4          | ...             | ... | ... | ... | ... | X   | X   | X   | X   | X   | X   | X   | X   | X   | X   | X   | X   | X      | X      | ...    | ...    |
| 3              | ...             | ... | ... | ... | ... | ... | X   | X   | X   | X   | X   | X   | X   | X   | X   | X   | X   | X      | X      | X      | X      |
| 3 1/4          | ...             | ... | ... | ... | ... | ... | ... | ... | ... | X   | X   | X   | X   | X   | X   | X   | X   | X      | X      | X      | X      |
| 3 1/2          | ...             | ... | ... | ... | ... | ... | ... | ... | ... | X   | X   | X   | X   | X   | X   | X   | X   | X      | X      | X      | X      |
| 3 3/4          | ...             | ... | ... | ... | ... | ... | ... | ... | ... | X   | X   | X   | X   | X   | X   | X   | X   | X      | X      | X      | X      |
| 4              | ...             | ... | ... | ... | ... | ... | ... | ... | ... | X   | X   | X   | X   | X   | X   | X   | X   | X      | X      | X      | X      |
| 4 1/4          | ...             | ... | ... | ... | ... | ... | ... | ... | ... | ... | ... | X   | X   | X   | X   | X   | X   | X      | X      | X      | X      |
| 4 1/2          | ...             | ... | ... | ... | ... | ... | ... | ... | ... | ... | ... | X   | X   | X   | X   | X   | X   | X      | X      | X      | X      |
| 4 3/4          | ...             | ... | ... | ... | ... | ... | ... | ... | ... | ... | ... | X   | X   | X   | X   | X   | X   | X      | X      | X      | X      |
| 5              | ...             | ... | ... | ... | ... | ... | ... | ... | ... | ... | ... | X   | X   | X   | X   | X   | X   | X      | X      | X      | X      |
| 5 1/4          | ...             | ... | ... | ... | ... | ... | ... | ... | ... | ... | ... | X   | X   | X   | X   | X   | X   | X      | X      | X      | X      |
| 5 1/2          | ...             | ... | ... | ... | ... | ... | ... | ... | ... | ... | ... | X   | X   | X   | X   | X   | X   | X      | X      | X      | X      |
| 5 3/4          | ...             | ... | ... | ... | ... | ... | ... | ... | ... | ... | ... | X   | X   | X   | X   | X   | X   | X      | X      | X      | X      |
| 6              | ...             | ... | ... | ... | ... | ... | ... | ... | ... | ... | ... | X   | X   | X   | X   | X   | X   | X      | X      | X      | X      |
| 6 1/4          | ...             | ... | ... | ... | ... | ... | ... | ... | ... | ... | ... | ... | ... | X   | X   | X   | X   | X      | X      | X      | X      |
| 6 1/2          | ...             | ... | ... | ... | ... | ... | ... | ... | ... | ... | ... | ... | ... | X   | X   | X   | X   | X      | X      | X      | X      |
| 6 3/4          | ...             | ... | ... | ... | ... | ... | ... | ... | ... | ... | ... | ... | ... | X   | X   | X   | X   | X      | X      | X      | X      |
| 7              | ...             | ... | ... | ... | ... | ... | ... | ... | ... | ... | ... | ... | ... | X   | X   | X   | X   | X      | X      | X      | X      |
| 7 1/4          | ...             | ... | ... | ... | ... | ... | ... | ... | ... | ... | ... | ... | ... | X   | X   | X   | X   | X      | X      | X      | X      |
| 7 1/2          | ...             | ... | ... | ... | ... | ... | ... | ... | ... | ... | ... | ... | ... | X   | X   | X   | X   | X      | X      | X      | X      |
| 7 3/4          | ...             | ... | ... | ... | ... | ... | ... | ... | ... | ... | ... | ... | ... | X   | X   | X   | X   | X      | X      | X      | X      |
| 8              | ...             | ... | ... | ... | ... | ... | ... | ... | ... | ... | ... | ... | ... | X   | X   | X   | X   | X      | X      | X      | X      |
| 8 1/4          | ...             | ... | ... | ... | ... | ... | ... | ... | ... | ... | ... | ... | ... | ... | ... | ... | ... | ...    | X      | X      | X      |
| 8 1/2          | ...             | ... | ... | ... | ... | ... | ... | ... | ... | ... | ... | ... | ... | ... | ... | ... | ... | ...    | X      | X      | X      |
| 8 3/4          | ...             | ... | ... | ... | ... | ... | ... | ... | ... | ... | ... | ... | ... | ... | ... | ... | ... | ...    | X      | X      | X      |
| 9              | ...             | ... | ... | ... | ... | ... | ... | ... | ... | ... | ... | ... | ... | ... | ... | ... | ... | ...    | X      | X      | X      |
| 9 1/4          | ...             | ... | ... | ... | ... | ... | ... | ... | ... | ... | ... | ... | ... | ... | ... | ... | ... | ...    | ...    | X      | X      |
| 9 1/2          | ...             | ... | ... | ... | ... | ... | ... | ... | ... | ... | ... | ... | ... | ... | ... | ... | ... | ...    | ...    | X      | X      |
| 9 3/4          | ...             | ... | ... | ... | ... | ... | ... | ... | ... | ... | ... | ... | ... | ... | ... | ... | ... | ...    | ...    | X      | X      |
| 10             | ...             | ... | ... | ... | ... | ... | ... | ... | ... | ... | ... | ... | ... | ... | ... | ... | ... | ...    | ...    | X      | X      |

**Table 3.5.3-1 Standard Sizes and Lengths of Taper Pins (Cont'd)**

| Nominal Length                 | Pin Size Number |     |     |     |     |     |     |     |     |     |     |     |     |     |     |     |     |        |        |        |        |
|--------------------------------|-----------------|-----|-----|-----|-----|-----|-----|-----|-----|-----|-----|-----|-----|-----|-----|-----|-----|--------|--------|--------|--------|
|                                | 7/0             | 6/0 | 5/0 | 4/0 | 3/0 | 2/0 | 0   | 1   | 2   | 3   | 4   | 5   | 6   | 7   | 8   | 9   | 10  | 11 (1) | 12 (1) | 13 (1) | 14 (1) |
| 10 <sup>1</sup> / <sub>4</sub> | ...             | ... | ... | ... | ... | ... | ... | ... | ... | ... | ... | ... | ... | ... | ... | ... | ... | ...    | ...    | X      | X      |
| 10 <sup>1</sup> / <sub>2</sub> | ...             | ... | ... | ... | ... | ... | ... | ... | ... | ... | ... | ... | ... | ... | ... | ... | ... | ...    | ...    | X      | X      |
| 10 <sup>3</sup> / <sub>4</sub> | ...             | ... | ... | ... | ... | ... | ... | ... | ... | ... | ... | ... | ... | ... | ... | ... | ... | ...    | ...    | X      | X      |
| 11                             | ...             | ... | ... | ... | ... | ... | ... | ... | ... | ... | ... | ... | ... | ... | ... | ... | ... | ...    | ...    | X      | X      |
| 11 <sup>1</sup> / <sub>4</sub> | ...             | ... | ... | ... | ... | ... | ... | ... | ... | ... | ... | ... | ... | ... | ... | ... | ... | ...    | ...    | ...    | X      |
| 11 <sup>1</sup> / <sub>2</sub> | ...             | ... | ... | ... | ... | ... | ... | ... | ... | ... | ... | ... | ... | ... | ... | ... | ... | ...    | ...    | ...    | X      |
| 11 <sup>3</sup> / <sub>4</sub> | ...             | ... | ... | ... | ... | ... | ... | ... | ... | ... | ... | ... | ... | ... | ... | ... | ... | ...    | ...    | ...    | X      |
| 12                             | ...             | ... | ... | ... | ... | ... | ... | ... | ... | ... | ... | ... | ... | ... | ... | ... | ... | ...    | ...    | ...    | X      |
| 12 <sup>1</sup> / <sub>4</sub> | ...             | ... | ... | ... | ... | ... | ... | ... | ... | ... | ... | ... | ... | ... | ... | ... | ... | ...    | ...    | ...    | X      |
| 12 <sup>1</sup> / <sub>2</sub> | ...             | ... | ... | ... | ... | ... | ... | ... | ... | ... | ... | ... | ... | ... | ... | ... | ... | ...    | ...    | ...    | X      |
| 13                             | ...             | ... | ... | ... | ... | ... | ... | ... | ... | ... | ... | ... | ... | ... | ... | ... | ... | ...    | ...    | ...    | X      |

GENERAL NOTE: Standard reamers are available for pins shown above heavy lines.

NOTE: (1) Precision-class pins are not produced in size numbers 11 through 14.

### 3.8 Finishes

Unless otherwise specified, taper pins shall be furnished unplated or uncoated. A lightweight oil may be used to inhibit corrosion in transportation. Other finishes, where required, shall be subject to agreement between the manufacturer and purchaser.

### 3.9 Workmanship

Taper pins shall be free from burrs, seams, scratches, or nicks and any other defects affecting their serviceability.

### 3.10 Hole Sizes

Under most circumstances, holes for taper pins require taper reaming. Recommended practices covering the preparation of holes for installation of taper pins are contained in [Nonmandatory Appendix A](#).

### 3.11 Designation

**3.11.1** Taper pins shall be designated by the following data, in the sequence shown: product name (noun first), including class; size number (or decimal equivalent); length (fraction or three-place decimal equivalent); material, and protective finish, if required. See the following examples:

EXAMPLES:

- (1) Pin, Taper (Commercial Class) No. 0 × 3/44, Steel
- (2) Pin, Taper (Precision Class) 0.219 × 1.750, Steel, Zinc Plated

## 4 GENERAL DATA FOR HARDENED GROUND MACHINE DOWEL PINS

### 4.1 Diameters

**4.1.1 Size.** Hardened ground machine dowel pins are furnished in two diameter series: Standard Series having basic diameters 0.0002 in. over the nominal diameter, intended for initial installations; and Oversize Series having basic diameters 0.001 in. over the nominal diameter, intended for replacement use. For both series, the diameter shall be ground, or ground and lapped, to within ±0.0001 in. of the respective basic diameters, as specified in [Table 4.1.1-1](#).

**4.1.2 Roundness.** The outer periphery of hardened ground machine dowel pins shall conform to true round about the longitudinal axis of the pin within 0.0001 in., when measured with equipment that will detect a lobed surface.


### 4.2 Ends

**4.2.1 End Contours.** The ends of hardened ground machine dowel pins shall be reasonably flat and perpendicular to the axis of pin. One end of pin shall be pointed and the other end crowned to the dimensions specified in [Table 4.1.1-1](#). On the pointed end, the edge formed by the surface of point and the end of pin may be slightly rounded or broken.

**4.2.1.1 Point Concentricity.** For pins having nominal lengths equal to four times the basic pin diameter or longer, the concentricity between the diameter of point and the pin diameter shall be such that the minimum length of point on the pin is not less than 0.010 in. (see [Figure 4.2.1.1-1](#)).



Table 4.1.1-1 Dimensions of Hardened Ground Machine Dowel Pins

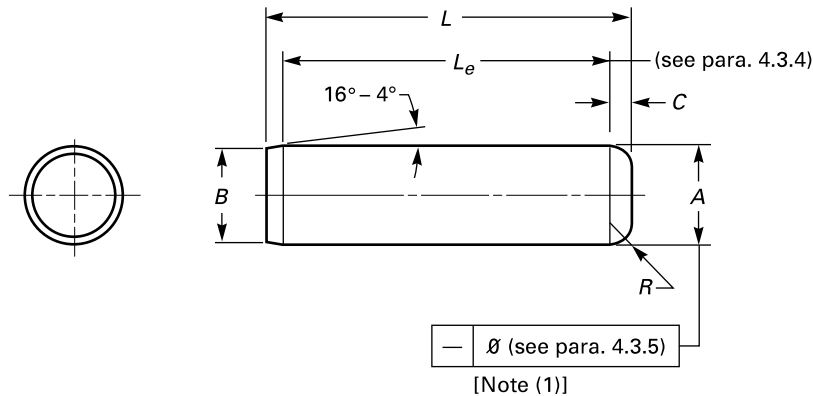

| Nominal Size or<br>Nominal Pin Diameter<br>[Note (2)] |        | Pin Diameter         |        |        |                      |        |        | Point<br>Diameter, <i>B</i> |       | Maximum<br>Crown<br>Height,<br><i>C</i> | Minimum<br>Crown<br>Radius,<br><i>R</i> |
|-------------------------------------------------------|--------|----------------------|--------|--------|----------------------|--------|--------|-----------------------------|-------|-----------------------------------------|-----------------------------------------|
|                                                       |        | Standard Series Pins |        |        | Oversize Series Pins |        |        |                             |       |                                         |                                         |
|                                                       |        | Basic                | Max.   | Min.   | Basic                | Max.   | Min.   | Max.                        | Min.  |                                         |                                         |
| $\frac{1}{16}$                                        | 0.0625 | 0.0627               | 0.0628 | 0.0626 | 0.0635               | 0.0636 | 0.0634 | 0.058                       | 0.048 | 0.020                                   | 0.008                                   |
| $\frac{5}{64}$ [Note (3)]                             | 0.0781 | 0.0783               | 0.0784 | 0.0782 | 0.0791               | 0.0792 | 0.0790 | 0.074                       | 0.064 | 0.026                                   | 0.010                                   |
| $\frac{3}{32}$                                        | 0.093  | 0.0940               | 0.0941 | 0.0939 | 0.0948               | 0.0949 | 0.0947 | 0.089                       | 0.079 | 0.031                                   | 0.012                                   |
| $\frac{1}{8}$                                         | 0.1250 | 0.1252               | 0.1253 | 0.1251 | 0.1260               | 0.1261 | 0.1259 | 0.120                       | 0.110 | 0.041                                   | 0.016                                   |
| $\frac{5}{32}$ [Note (3)]                             | 0.1562 | 0.1564               | 0.1565 | 0.1563 | 0.1572               | 0.1573 | 0.1571 | 0.150                       | 0.140 | 0.052                                   | 0.020                                   |
| $\frac{3}{16}$                                        | 0.1875 | 0.1877               | 0.1878 | 0.1876 | 0.1885               | 0.1886 | 0.1884 | 0.180                       | 0.170 | 0.062                                   | 0.023                                   |
| $\frac{1}{4}$                                         | 0.2500 | 0.2502               | 0.2503 | 0.2501 | 0.2510               | 0.2511 | 0.2509 | 0.240                       | 0.230 | 0.083                                   | 0.031                                   |
| $\frac{5}{16}$                                        | 0.3125 | 0.3127               | 0.3128 | 0.3126 | 0.3135               | 0.3136 | 0.3134 | 0.302                       | 0.290 | 0.104                                   | 0.039                                   |
| $\frac{3}{8}$                                         | 0.3750 | 0.3752               | 0.3753 | 0.3751 | 0.3760               | 0.3761 | 0.3759 | 0.365                       | 0.350 | 0.125                                   | 0.047                                   |
| $\frac{7}{16}$                                        | 0.4375 | 0.4377               | 0.4378 | 0.4376 | 0.4385               | 0.4386 | 0.4384 | 0.424                       | 0.409 | 0.146                                   | 0.055                                   |
| $\frac{1}{2}$                                         | 0.5000 | 0.5002               | 0.5003 | 0.5001 | 0.5010               | 0.5011 | 0.5009 | 0.486                       | 0.471 | 0.167                                   | 0.063                                   |
| $\frac{5}{8}$                                         | 0.6250 | 0.6252               | 0.6253 | 0.6251 | 0.6260               | 0.6261 | 0.6259 | 0.611                       | 0.595 | 0.208                                   | 0.078                                   |
| $\frac{3}{4}$                                         | 0.7500 | 0.7502               | 0.7503 | 0.7501 | 0.7510               | 0.7511 | 0.7509 | 0.735                       | 0.715 | 0.250                                   | 0.094                                   |
| $\frac{7}{8}$                                         | 0.8750 | 0.8752               | 0.8753 | 0.8751 | 0.8760               | 0.8761 | 0.8759 | 0.860                       | 0.840 | 0.293                                   | 0.109                                   |
| 1                                                     | 1.0000 | 1.0002               | 1.0003 | 1.0001 | 1.0010               | 1.0011 | 1.0009 | 0.980                       | 0.960 | 0.333                                   | 0.125                                   |


## GENERAL NOTES:

- (a) For additional requirements, refer to section 4.  
 (b) Reference ASME Y14.5.

## NOTES:

- (1) — = straightness;  $\varnothing$  = diameter  
 (2) Where specifying nominal size as basic diameter, zeros preceding decimal and in the fourth decimal place shall be omitted.  
 (3) Nonpreferred sizes, not recommended for use in new designs.

Figure 4.2.1.1-1 Point Concentricity

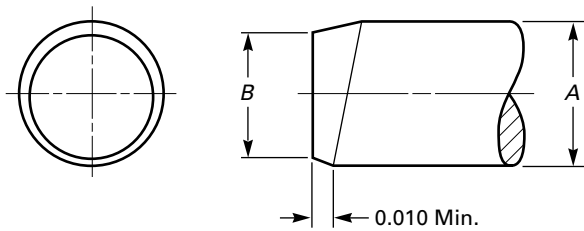

### 4.3 Length

**4.3.1 Measurement.** The length of hardened ground machine dowel pins shall be measured overall from end to end, parallel to the axis of pin.

**4.3.2 Tolerance on Length.** The tolerance on the length of hardened ground machine dowel pins shall be  $\pm 0.01$  in.

**4.3.3 Preferred Lengths.** The preferred sizes and lengths in which hardened ground machine dowel pins are normally available are depicted in Table 4.3.3-1. Other sizes and lengths are produced as required by the purchaser.

**4.3.4 Effective Length.** The effective length,  $L_e$ , is that portion of the pin length bounded by the length of point on one end and the radius of crown on the other. On dowel pins, when the effective length is less than 75% of the overall length of pin, it is necessary to deviate from the specified dimensions by reducing the crown radius and height, or increasing the point angle, or both, to maintain 75%.

**4.3.5 Straightness.** Machine dowel pins shall be straight over the effective length within an accumulative total of 0.0005 in. per inch of length for nominal lengths, up to and including 4 in., and within 0.002 in. total for all nominal lengths over 4 in.

### 4.4 Surface Roughness

The surface roughness on hardened ground machine dowel pins shall not exceed 8  $\mu$ in. (arithmetical average) on the effective length nor 125  $\mu$ in. (arithmetical average) on all other surfaces. Refer to ASME B46.1. For pins having additive finishes, these limits shall apply prior to coating or plating.

Table 4.3.3-1 Preferred Sizes and Lengths of Hardened Ground Machine Dowel Pins

| Nominal Length | Nominal Size |      |     |      |     |      |     |      |     |     |     |     |     |
|----------------|--------------|------|-----|------|-----|------|-----|------|-----|-----|-----|-----|-----|
|                | 1/16         | 3/32 | 1/8 | 3/16 | 1/4 | 5/16 | 3/8 | 7/16 | 1/2 | 5/8 | 3/4 | 7/8 | 1   |
| 3/16           | X            | ...  | ... | ...  | ... | ...  | ... | ...  | ... | ... | ... | ... | ... |
| 1/4            | X            | ...  | ... | ...  | ... | ...  | ... | ...  | ... | ... | ... | ... | ... |
| 5/16           | X            | X    | ... | ...  | ... | ...  | ... | ...  | ... | ... | ... | ... | ... |
| 3/8            | X            | X    | X   | ...  | ... | ...  | ... | ...  | ... | ... | ... | ... | ... |
| 1/2            | X            | X    | X   | X    | X   | X    | X   | ...  | ... | ... | ... | ... | ... |
| 5/8            | X            | X    | X   | X    | X   | X    | X   | ...  | ... | ... | ... | ... | ... |
| 3/4            | X            | X    | X   | X    | X   | X    | X   | ...  | X   | ... | ... | ... | ... |
| 7/8            | ...          | X    | X   | X    | X   | X    | X   | X    | ... | ... | ... | ... | ... |
| 1              | ...          | X    | X   | X    | X   | X    | X   | X    | X   | ... | ... | ... | ... |
| 1 1/4          | ...          | ...  | X   | X    | X   | X    | X   | X    | X   | X   | ... | ... | ... |
| 1 1/2          | ...          | ...  | X   | X    | X   | X    | X   | X    | X   | X   | X   | ... | ... |
| 1 3/4          | ...          | ...  | X   | X    | X   | X    | X   | X    | X   | X   | X   | ... | ... |
| 2              | ...          | ...  | X   | X    | X   | X    | X   | X    | X   | X   | X   | X   | X   |
| 2 1/4          | ...          | ...  | ... | ...  | X   | X    | X   | X    | X   | X   | X   | ... | ... |
| 2 1/2          | ...          | ...  | ... | ...  | X   | X    | X   | X    | X   | X   | X   | X   | X   |
| 3              | ...          | ...  | ... | ...  | ... | ...  | X   | X    | X   | X   | X   | X   | X   |
| 3 1/2          | ...          | ...  | ... | ...  | ... | ...  | ... | ...  | X   | X   | X   | X   | X   |
| 4              | ...          | ...  | ... | ...  | ... | ...  | ... | ...  | X   | X   | X   | X   | X   |
| 4 1/2          | ...          | ...  | ... | ...  | ... | ...  | ... | ...  | ... | X   | X   | X   | X   |
| 5              | ...          | ...  | ... | ...  | ... | ...  | ... | ...  | ... | X   | X   | X   | X   |
| 5 1/2          | ...          | ...  | ... | ...  | ... | ...  | ... | ...  | ... | ... | X   | X   | ... |
| 6              | ...          | ...  | ... | ...  | ... | ...  | ... | ...  | ... | ... | X   | X   | X   |

## 4.5 Material and Heat Treatment

**4.5.1 Steel.** Hardened ground machine dowel pins shall be made from any carbon or alloy steel capable of being heat treated to a core hardness of Rockwell C50 minimum and having sulfur and phosphorus content not in excess of 0.05% and 0.04%, respectively.

**4.5.2 Heat Treatment.** Pins shall be hardened by quenching in oil from the austenizing temperature and tempering to meet the following conditions.

**4.5.2.1 Case-Hardened Pins.** Pins shall be case hardened to a minimum total case depth of 0.010 in. for nominal pin sizes  $\frac{5}{32}$  in., or smaller, and 0.015 in. for nominal pin sizes  $\frac{3}{16}$  in., and larger. The case shall have a minimum surface hardness of Rockwell C70, or equivalent, and the core hardness shall be Rockwell C47 to C58. The microstructure shall be tempered martensite.

**4.5.2.2 Through-Hardened Pins.** At manufacturer's option, pins smaller than  $\frac{1}{8}$  in. nominal size may be through hardened to a hardness of Rockwell C50 to C58. However, in no instance shall the hardness of the pin surface be softer than that of the core. The microstructure shall be tempered martensite.

## 4.6 Finishes

Unless otherwise specified, machine dowel pins shall be furnished with a ground (as processed) finish or with black oxide coating at the option of the manufacturer. A lightweight oil may be used to inhibit corrosion during transportation. Other protective or decorative finishes, where required, shall be subject to agreement between the manufacturer and purchaser. However, where a finish applied to carbon or alloy steel pins is such that it might produce hydrogen embrittlement, the pins shall be baked for a suitable time at a temperature that will obviate such embrittlement. Baking shall be accomplished as soon as possible following the plating or coating operation inasmuch as delay is detrimental to achieving the desired results. Where additive-type finishes are used, the tabulated dimensions and tolerances shall apply to the pins prior to application of the plating or coating, unless otherwise specified by the purchaser.

## 4.7 Workmanship

Dowel pins shall be free from detrimental burrs, cracks, seams, or nicks and other defects affecting their serviceability or properties.

## 4.8 Designation

**4.8.1** Hardened ground machine dowel pins shall be designated by the following data, in the sequence shown: product name (noun first), including pin series; nominal pin diameter (fraction or decimal equivalent); length

(fraction or decimal equivalent); material; and protective finish, if required. See examples below.

### EXAMPLES:

- (1) Pin, Hardened Ground Machine Dowel — Standard Series,  $\frac{3}{8} \times 1\frac{1}{2}$ , Steel, Phosphate Coated
- (2) Pin, Hardened Ground Machine Dowel — Oversize Series, 0.6250  $\times$  2.500, Steel

## 4.9 Application Information

**4.9.1 Hole Sizes.** Because of the wide variety of materials in which dowel pins are used and of the many design requirements which must be considered, it is not possible to provide hole size recommendations that will be suitable for all applications. However, the suggested hole sizes in Table 4.9.1-1 have been commonly used for press-fitting standard series machine dowel pins into material such as mild steels and cast iron. In soft materials such as aluminum or zinc die castings, hole size limits are usually decreased by 0.0005 in. to increase the press fit.

Holes for oversize series machine dowel pins may best be determined by the user to suit the particular application.


**4.9.2 Design Calculations.** For design calculations, the shear strength of these standard pins should be based on the values listed in para. 4.9.1.

**4.9.3 Responsibility for Modification.** The manufacturer shall not be held responsible for product malfunctions that are due to plating or other modifications when

**Table 4.9.1-1 Suggested Hole Sizes for Standard Series Pins**

| Nominal Pin Size | Suggested Hole Diameter for Standard Series Pins |        | Single-Shear Load Carbon or Alloy Steel Calculated, lb |
|------------------|--------------------------------------------------|--------|--------------------------------------------------------|
|                  | Max.                                             | Min.   |                                                        |
| $\frac{1}{16}$   | 0.0625                                           | 0.0620 | 400                                                    |
| $\frac{5}{64}$   | 0.0781                                           | 0.0776 | 620                                                    |
| $\frac{3}{32}$   | 0.0937                                           | 0.0932 | 900                                                    |
| $\frac{1}{8}$    | 0.1250                                           | 0.1245 | 1,600                                                  |
| $\frac{5}{32}$   | 0.1562                                           | 0.1557 | 2,500                                                  |
| $\frac{3}{16}$   | 0.1875                                           | 0.1870 | 3,600                                                  |
| $\frac{1}{4}$    | 0.2500                                           | 0.2495 | 6,400                                                  |
| $\frac{5}{16}$   | 0.3125                                           | 0.3120 | 10,000                                                 |
| $\frac{3}{8}$    | 0.3750                                           | 0.3745 | 14,350                                                 |
| $\frac{7}{16}$   | 0.4375                                           | 0.4370 | 19,550                                                 |
| $\frac{1}{2}$    | 0.5000                                           | 0.4995 | 25,500                                                 |
| $\frac{5}{8}$    | 0.6250                                           | 0.6245 | 39,900                                                 |
| $\frac{3}{4}$    | 0.7500                                           | 0.7495 | 57,000                                                 |
| $\frac{7}{8}$    | 0.8750                                           | 0.8745 | 78,000                                                 |
| 1                | 1.0000                                           | 0.9995 | 102,000                                                |

Table 5.1.1-1 Dimensions of Hardened Ground Production Dowel Pins

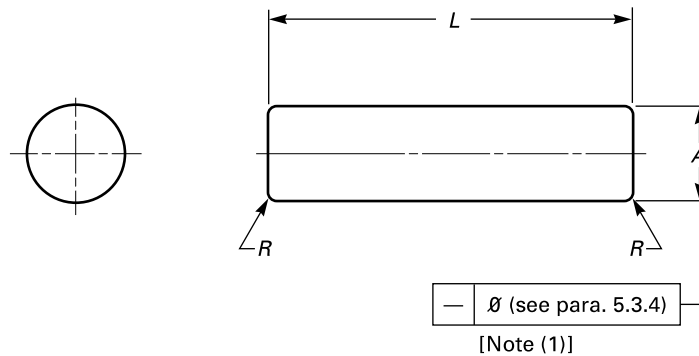

| Nominal Size or Nominal Pin Diameter [Note (2)] |        | Pin Diameter, <i>A</i> |        |        | Corner Radius, <i>R</i> |       |
|-------------------------------------------------|--------|------------------------|--------|--------|-------------------------|-------|
|                                                 |        | Basic                  | Max.   | Min.   | Max.                    | Min.  |
| $\frac{1}{16}$                                  | 0.0625 | 0.0627                 | 0.0628 | 0.0626 | 0.020                   | 0.010 |
| $\frac{3}{32}$                                  | 0.0938 | 0.0939                 | 0.0940 | 0.0938 | 0.020                   | 0.010 |
| $\frac{7}{64}$                                  | 0.1094 | 0.1095                 | 0.1096 | 0.1094 | 0.020                   | 0.010 |
| $\frac{1}{8}$                                   | 0.1250 | 0.1252                 | 0.1253 | 0.1251 | 0.020                   | 0.010 |
| $\frac{5}{32}$                                  | 0.1562 | 0.1564                 | 0.1565 | 0.1563 | 0.020                   | 0.010 |
| $\frac{3}{16}$                                  | 0.1875 | 0.1877                 | 0.1878 | 0.1876 | 0.020                   | 0.010 |
| $\frac{7}{32}$                                  | 0.2188 | 0.2189                 | 0.2190 | 0.2188 | 0.020                   | 0.010 |
| $\frac{1}{4}$                                   | 0.2500 | 0.2502                 | 0.2503 | 0.2501 | 0.020                   | 0.010 |
| $\frac{5}{16}$                                  | 0.3125 | 0.3127                 | 0.3128 | 0.3126 | 0.020                   | 0.010 |
| $\frac{3}{8}$                                   | 0.3750 | 0.3752                 | 0.3753 | 0.3751 | 0.020                   | 0.010 |

## GENERAL NOTES:

- (a) For additional requirements, refer to [section 5](#).  
 (b) Reference ASME Y14.5M.

## NOTES:

- (1) — = straightness;  $\varnothing$  = diameter  
 (2) Where specifying nominal pin size in decimals, zeros preceding decimal and in the fourth decimal place shall be omitted.

such plating or modification is not accomplished under their control or direction.

**4.9.4 Installation Warning.** Pins should not be installed by striking or hammering and, when installing with a press, a shield should be used and safety glasses worn.

## 5 GENERAL DATA FOR HARDENED GROUND PRODUCTION DOWEL PINS

### 5.1 Diameter

**5.1.1 Size.** Hardened ground production dowel pins have basic diameters which are 0.0002 in. over the nominal pin diameter. The diameter shall be ground, or ground and lapped, to within  $\pm 0.0001$  in. of the basic diameter as specified in [Table 5.1.1-1](#).

**5.1.2 Roundness.** The outer periphery of hardened ground production dowel pins shall conform to true round about the longitudinal axis of pin within 0.0001 in., when measured with equipment that will detect a lobed surface.

### 5.2 Ends

The ends of hardened ground production dowel pins shall be reasonably flat and perpendicular to the axis of pin. The corners at both ends of pins shall be rounded as defined in [Table 5.1.1-1](#) and the accompanying figure.

### 5.3 Length

**5.3.1 Measurement.** The length of hardened ground production dowel pins shall be measured overall from end to end, parallel to the axis of pin.

**Table 5.3.3-1 Preferred Sizes and Lengths of Hardened Ground Production Dowel Pins**

| Nominal Length | Nominal Size |      |      |     |      |      |      |     |      |     |
|----------------|--------------|------|------|-----|------|------|------|-----|------|-----|
|                | 1/16         | 3/32 | 7/64 | 1/8 | 5/32 | 3/16 | 7/32 | 1/4 | 5/16 | 3/8 |
| 3/16           | x            | x    | x    | x   | x    | x    | ...  | ... | ...  | ... |
| 1/4            | x            | x    | x    | x   | x    | x    | x    | x   | ...  | ... |
| 5/16           | x            | x    | x    | x   | x    | x    | x    | x   | x    | ... |
| 3/8            | x            | x    | x    | x   | x    | x    | x    | x   | x    | x   |
| 7/16           | x            | x    | x    | x   | x    | x    | x    | x   | x    | x   |
| 1/2            | x            | x    | x    | x   | x    | x    | x    | x   | x    | x   |
| 9/16           | x            | x    | x    | x   | x    | x    | x    | x   | x    | x   |
| 5/8            | x            | x    | x    | x   | x    | x    | x    | x   | x    | x   |
| 11/16          | x            | x    | x    | x   | x    | x    | x    | x   | x    | x   |
| 3/4            | x            | x    | x    | x   | x    | x    | x    | x   | x    | x   |
| 13/16          | x            | x    | x    | x   | x    | x    | x    | x   | x    | x   |
| 7/8            | x            | x    | x    | x   | x    | x    | x    | x   | x    | x   |
| 15/16          | x            | x    | x    | x   | x    | x    | x    | x   | x    | x   |
| 1              | x            | x    | x    | x   | x    | x    | x    | x   | x    | x   |
| 1 1/8          | ...          | x    | x    | x   | x    | x    | x    | x   | x    | x   |
| 1 1/4          | ...          | x    | x    | x   | x    | x    | x    | x   | x    | x   |
| 1 3/8          | ...          | x    | x    | x   | x    | x    | x    | x   | x    | x   |
| 1 1/2          | ...          | x    | x    | x   | x    | x    | x    | x   | x    | x   |
| 1 5/8          | ...          | x    | x    | x   | x    | x    | x    | ... | ...  | ... |
| 1 3/4          | ...          | x    | x    | x   | x    | x    | x    | x   | x    | x   |
| 1 7/8          | ...          | x    | x    | x   | x    | x    | x    | ... | ...  | ... |
| 2              | ...          | x    | x    | x   | x    | x    | x    | x   | x    | x   |
| 2 1/4          | ...          | ...  | ...  | ... | ...  | ...  | ...  | x   | x    | x   |
| 2 1/2          | ...          | ...  | ...  | ... | ...  | ...  | ...  | x   | x    | x   |
| 3              | ...          | ...  | ...  | ... | ...  | ...  | ...  | ... | ...  | x   |

**5.3.2 Tolerance on Length.** The tolerance on the length of hardened ground production dowel pins shall be  $\pm 0.010$  in.

**5.3.3 Preferred Lengths.** The preferred sizes and lengths in which hardened ground production dowel pins are normally available are depicted in [Table 5.3.3-1](#). Other sizes and lengths are produced as required by the purchaser.

**5.3.4 Straightness.** Production dowel pins shall be straight over that portion of the pin length not affected by the rounded ends within an accumulative total of 0.0005 in. per inch of length for nominal lengths, up to and including 4 in., and within 0.002 in. total for all nominal lengths over 4 in.

## 5.4 Surface Roughness

The surface roughness on hardened ground production dowel pins shall not exceed 8  $\mu$ in. (arithmetical average) over the cylindrical portion of the pin length nor 125  $\mu$ in. (arithmetical average) on all other surfaces. Refer to ASME

B46.1. For pins having additive finishes, these limits shall apply prior to coating or plating.

## 5.5 Material and Heat Treatment

**5.5.1 Steel.** Hardened ground production dowel pins shall be made from carbon steel having a sulfur and phosphorus content not in excess of 0.05% and 0.04%, respectively.

**5.5.2 Heat Treatment.** Pins shall be case hardened to a minimum total case depth of 0.010 in. for nominal pin sizes  $5/32$  in., or smaller, and 0.02 in. for nominal pin sizes  $3/16$  in., and larger. Pins shall be quenched in oil from the austenizing temperature and tempered to provide a minimum case hardness of Rockwell C58, or equivalent, and a core hardness of Rockwell C50 to C55. The microstructure shall be tempered martensite.

## 5.6 Finishes

Unless otherwise specified, production dowel pins shall be furnished with a ground (as processed) finish, unplated or uncoated. Protective or decorative finishes, where required, shall be subject to agreement between the manufacturer and purchaser. However, where a finish applied to pins is such that it might produce hydrogen embrittlement, the pins shall be baked for a suitable time at a temperature that will obviate such embrittlement. Baking shall be accomplished as soon as possible following the plating or coating operation inasmuch as delay is detrimental to achieving the desired results. Where additive-type finishes are used, the tabulated dimensions and tolerances shall apply to the pins prior to application of the plating or coating, unless otherwise specified by the purchaser.

## 5.7 Workmanship

Dowel pins shall be free from burrs, cracks, seams, scratches, and nicks, and any other defects affecting their serviceability.

## 5.8 Application Information

**5.8.1 Hole Sizes.** Because of the wide variety of materials in which dowel pins are used and the many design requirements which must be considered, it is not possible to provide hole size recommendations that will be suitable for all applications. However, the suggested hole sizes tabulated in [Table 5.8.1-1](#) have been commonly used for press-fitting production dowel pins into materials such as mild steels and cast iron. In soft materials, such as aluminum or zinc die castings, hole size limits are usually decreased by 0.0005 in. to increase the press fit.

**5.8.2 Design Calculations.** For design calculations, the shear strength of these standard pins should be based on the values listed in [para. 5.8.1](#).

**Table 5.8.1-1 Suggested Hole Diameters for Hardened Ground Production Dowel Pins**

| Nominal Pin Sizes | Suggested Hole Diameter |        | Single-Shear Load Calculated, lb |
|-------------------|-------------------------|--------|----------------------------------|
|                   | Max.                    | Min.   |                                  |
| $\frac{1}{16}$    | 0.0625                  | 0.0620 | 395                              |
| $\frac{3}{32}$    | 0.0937                  | 0.0932 | 700                              |
| $\frac{7}{64}$    | 0.1094                  | 0.1089 | 950                              |
| $\frac{1}{8}$     | 0.1250                  | 0.1245 | 1,300                            |
| $\frac{5}{32}$    | 0.1562                  | 0.1557 | 2,050                            |
| $\frac{3}{16}$    | 0.1875                  | 0.1870 | 2,950                            |
| $\frac{7}{32}$    | 0.2188                  | 0.2183 | 3,800                            |
| $\frac{1}{4}$     | 0.2500                  | 0.2495 | 5,000                            |
| $\frac{5}{16}$    | 0.3125                  | 0.3120 | 8,000                            |
| $\frac{3}{8}$     | 0.3750                  | 0.3745 | 11,500                           |

## 5.9 Designation

**5.9.1** Hardened ground production dowel pins shall be designated by the following data in the sequence shown: product name (noun first); nominal pin diameter (fraction or decimal equivalent); length (fraction or decimal equivalent); material, and protective finish, if required. See the following examples:

EXAMPLES:

- (1) Pin, Hardened Ground Production Dowel,  $\frac{1}{8} \times \frac{3}{4}$ , Steel, Phosphate Coated
- (2) Pin, Hardened Ground Production Dowel, 0.375  $\times$  1.500, Steel

## 6 GENERAL DATA FOR UNHARDENED GROUND DOWEL PINS

### 6.1 Diameter

**6.1.1 Size.** Unhardened ground dowel pins are normally produced by grinding the outside diameter of commercial wire or rod material to size. Consequently, the maximum diameters of the pins, as specified in Table 6.1.1-1, are below the minimum commercial stock sizes by graduated amounts from 0.0005 in. on the  $\frac{1}{16}$  in. nominal pin size to 0.0028 in. on the 1 in. nominal pin size.

**6.1.2 Roundness.** The outer periphery of unhardened ground dowel pins shall conform to true round about the longitudinal axis of pin within 0.00025 in., when measured with equipment that will detect a lobed surface.

### 6.2 Ends

The ends of unhardened ground dowel pins shall be reasonably flat and perpendicular to the axis of pin. The corners at both ends of pins shall be chamfered to the dimensions given in Table 6.1.1-1 and the accompa-

nying figure. The contour of the chamfer surface shall be optional providing the juncture of the chamfer with the outside diameter of the pin permits the pin to be pressed into a hole of the respective minimum suggested hole size (see para. 6.8) in AA 2011-T3 aluminum material without shaving the hole sides.

### 6.3 Length

**6.3.1 Measurement.** The length of unhardened ground dowel pins shall be measured overall from end to end, parallel to the axis of pin.

**6.3.2 Tolerance on Length.** The tolerance on length of unhardened ground dowel pins shall be  $\pm 0.010$  in.

**6.3.3 Preferred Lengths.** The preferred sizes and lengths in which unhardened and ground dowel pins are normally available are depicted in Table 6.3.3-1. Other sizes and lengths are produced as required by the purchaser.

**6.3.4 Straightness.** Unhardened ground dowel pins shall be straight over that portion of the pin length bounded by the end chamfers within an accumulative total of 0.0005 in. per inch of pin length.

### 6.4 Surface Roughness

The surface roughness on unhardened ground dowel pins shall not exceed 32  $\mu$ in. (arithmetical average) over the cylindrical portion of the pin length nor 250  $\mu$ in. (arithmetical average) on all other surfaces. Refer to ASME B46.1. For pins having additive finishes, these limits shall apply prior to coating or plating.


### 6.5 Materials

**6.5.1 Steel.** Unhardened ground dowel pins shall be made from carbon steel optional with the manufacturer but having a maximum hardness of Rockwell C32 for nominal pin sizes up to and including  $\frac{1}{8}$  in.; Rockwell C23 for nominal sizes over  $\frac{1}{8}$  in. to  $\frac{1}{2}$  in., inclusive; and Rockwell B95 for all larger nominal pin sizes.

**6.5.2 Brass.** Brass pins, when specified, shall be made from ASTM B16 (half hard) or SAE CA 360 (half hard), or equivalent, copper alloys.

**6.5.3 Shear Strength.** Unhardened ground dowel pins shall have a single shear strength of 64,000 psi minimum for pins made from steel and 40,000 psi minimum when made from brass. They shall be capable of withstanding the minimum double shear loads specified in Table 6.1.1-1 for the respective materials when tested in accordance with the double shear testing of pins set forth in Nonmandatory Appendix B. The holes in test fixtures shall conform with the maximum pin diameter within a tolerance of +0.0001 in. and -0.0003 in.

Table 6.1.1-1 Dimensions of Unhardened Ground Dowel Pins

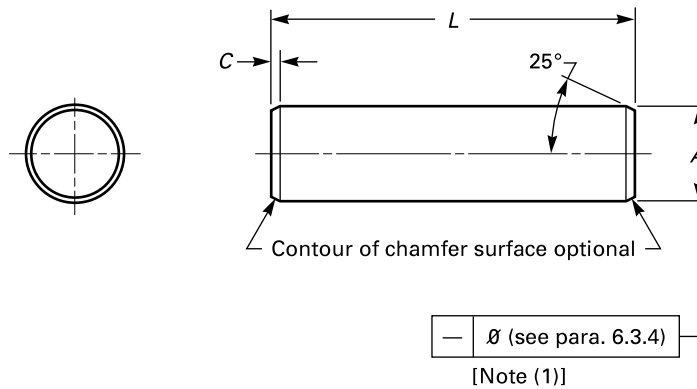

| Nominal Size or<br>Basic Pin Diameter<br>[Note (2)] |        | Pin Diameter,<br>$A$ |        | Chamfer Length,<br>$C$ |       | Minimum Double-Shear Load, lb,<br>for Material Type |        |
|-----------------------------------------------------|--------|----------------------|--------|------------------------|-------|-----------------------------------------------------|--------|
|                                                     |        | Max.                 | Min.   | Max.                   | Min.  | Carbon Steel                                        | Brass  |
| $\frac{1}{16}$                                      | 0.0625 | 0.0600               | 0.0595 | 0.025                  | 0.005 | 350                                                 | 220    |
| $\frac{3}{32}$                                      | 0.0938 | 0.0912               | 0.0907 | 0.025                  | 0.005 | 820                                                 | 510    |
| $\frac{7}{64}$ [Note (3)]                           | 0.1094 | 0.1068               | 0.1063 | 0.025                  | 0.005 | 1,130                                               | 710    |
| $\frac{1}{8}$                                       | 0.1250 | 0.1223               | 0.1218 | 0.025                  | 0.005 | 1,490                                               | 930    |
| $\frac{5}{32}$                                      | 0.1562 | 0.1535               | 0.1530 | 0.025                  | 0.005 | 2,350                                               | 1,470  |
| $\frac{3}{16}$                                      | 0.1875 | 0.1847               | 0.1842 | 0.025                  | 0.005 | 3,410                                               | 2,130  |
| $\frac{7}{32}$                                      | 0.2188 | 0.2159               | 0.2154 | 0.025                  | 0.005 | 4,660                                               | 2,910  |
| $\frac{1}{4}$                                       | 0.2500 | 0.2470               | 0.2465 | 0.025                  | 0.005 | 6,120                                               | 3,810  |
| $\frac{5}{16}$                                      | 0.3125 | 0.3094               | 0.3089 | 0.040                  | 0.020 | 9,590                                               | 5,990  |
| $\frac{3}{8}$                                       | 0.3750 | 0.3717               | 0.3712 | 0.040                  | 0.020 | 13,850                                              | 8,650  |
| $\frac{7}{16}$                                      | 0.4375 | 0.4341               | 0.4336 | 0.040                  | 0.020 | 18,900                                              | 11,810 |
| $\frac{1}{2}$                                       | 0.5000 | 0.4964               | 0.4959 | 0.040                  | 0.020 | 24,720                                              | 15,450 |
| $\frac{5}{8}$                                       | 0.6250 | 0.6211               | 0.6206 | 0.055                  | 0.035 | 38,710                                              | 24,190 |
| $\frac{3}{4}$                                       | 0.7500 | 0.7548               | 0.7453 | 0.055                  | 0.035 | 55,840                                              | 34,900 |
| $\frac{7}{8}$                                       | 0.8750 | 0.8705               | 0.8700 | 0.070                  | 0.050 | 76,090                                              | 47,550 |
| 1                                                   | 1.0000 | 0.9952               | 0.9947 | 0.070                  | 0.050 | 99,460                                              | 62,160 |

## GENERAL NOTES:

(a) For additional requirements, refer to [section 6](#)

(b) Reference ASME Y14.5M

## NOTES:

(1) — = straightness;  $\varnothing$  = diameter

(2) Where specifying nominal pin size in decimals, zeros preceding decimal and in the fourth decimal place shall be omitted.

(3) Nonpreferred sizes, not recommended for use in new designs.



**Table 6.3.3-1 Preferred Sizes and Lengths of Unhardened Ground Dowel Pins**

| Nominal Length  | Nominal Size   |                |               |                |                |                |               |                |               |                |               |               |               |               |     |
|-----------------|----------------|----------------|---------------|----------------|----------------|----------------|---------------|----------------|---------------|----------------|---------------|---------------|---------------|---------------|-----|
|                 | $\frac{1}{16}$ | $\frac{3}{32}$ | $\frac{1}{8}$ | $\frac{5}{32}$ | $\frac{3}{16}$ | $\frac{7}{32}$ | $\frac{1}{4}$ | $\frac{5}{16}$ | $\frac{3}{8}$ | $\frac{7}{16}$ | $\frac{1}{2}$ | $\frac{5}{8}$ | $\frac{3}{4}$ | $\frac{7}{8}$ | 1   |
| $\frac{1}{4}$   | X              | X              | X             | X              | X              | X              | X             | ...            | ...           | ...            | ...           | ...           | ...           | ...           | ... |
| $\frac{5}{16}$  | X              | X              | X             | X              | X              | X              | X             | X              | ...           | ...            | ...           | ...           | ...           | ...           | ... |
| $\frac{3}{8}$   | X              | X              | X             | X              | X              | X              | X             | X              | X             | ...            | ...           | ...           | ...           | ...           | ... |
| $\frac{7}{16}$  | X              | X              | X             | X              | X              | X              | X             | X              | X             | X              | ...           | ...           | ...           | ...           | ... |
| $\frac{1}{2}$   | X              | X              | X             | X              | X              | X              | X             | X              | X             | X              | X             | ...           | ...           | ...           | ... |
| $\frac{9}{16}$  | X              | X              | X             | X              | X              | X              | X             | X              | X             | X              | ...           | ...           | ...           | ...           | ... |
| $\frac{5}{8}$   | X              | X              | X             | X              | X              | X              | X             | X              | X             | X              | X             | X             | ...           | ...           | ... |
| $\frac{11}{16}$ | X              | X              | X             | X              | X              | X              | X             | X              | X             | ...            | ...           | ...           | ...           | ...           | ... |
| $\frac{3}{4}$   | X              | X              | X             | X              | X              | X              | X             | X              | X             | X              | X             | X             | X             | ...           | ... |
| $\frac{13}{16}$ | X              | X              | X             | X              | X              | X              | X             | X              | X             | ...            | ...           | ...           | ...           | ...           | ... |
| $\frac{7}{8}$   | X              | X              | X             | X              | X              | X              | X             | X              | X             | X              | X             | X             | X             | X             | ... |
| $\frac{15}{16}$ | X              | X              | X             | X              | X              | X              | X             | X              | X             | X              | ...           | ...           | ...           | ...           | ... |
| 1               | X              | X              | X             | X              | X              | X              | X             | X              | X             | X              | X             | X             | X             | X             | X   |
| $1\frac{1}{8}$  | ...            | X              | X             | X              | X              | X              | X             | X              | X             | X              | X             | X             | ...           | ...           | ... |
| $1\frac{1}{4}$  | ...            | X              | X             | X              | X              | X              | X             | X              | X             | X              | X             | X             | X             | X             | X   |
| $1\frac{3}{8}$  | ...            | X              | X             | X              | X              | X              | X             | X              | X             | X              | X             | X             | ...           | ...           | ... |
| $1\frac{1}{2}$  | ...            | X              | X             | X              | X              | X              | X             | X              | X             | X              | X             | X             | X             | X             | X   |
| $1\frac{5}{8}$  | ...            | ...            | X             | X              | X              | X              | ...           | ...            | ...           | ...            | ...           | ...           | ...           | ...           | ... |
| $1\frac{3}{4}$  | ...            | ...            | X             | X              | X              | X              | X             | X              | X             | X              | X             | X             | X             | X             | X   |
| $1\frac{7}{8}$  | ...            | ...            | X             | X              | X              | X              | ...           | ...            | ...           | ...            | ...           | ...           | ...           | ...           | ... |
| 2               | ...            | ...            | X             | X              | X              | X              | X             | X              | X             | X              | X             | X             | X             | X             | X   |
| $2\frac{1}{4}$  | ...            | ...            | ...           | ...            | ...            | ...            | X             | X              | X             | X              | X             | ...           | ...           | ...           | ... |
| $2\frac{1}{2}$  | ...            | ...            | ...           | ...            | ...            | ...            | X             | X              | X             | X              | X             | X             | X             | X             | X   |
| 3               | ...            | ...            | ...           | ...            | ...            | ...            | ...           | ...            | ...           | ...            | X             | X             | X             | X             | X   |
| $3\frac{1}{2}$  | ...            | ...            | ...           | ...            | ...            | ...            | ...           | ...            | ...           | ...            | ...           | X             | X             | X             | X   |
| 4               | ...            | ...            | ...           | ...            | ...            | ...            | ...           | ...            | ...           | ...            | ...           | X             | X             | X             | X   |

## 6.6 Finishes

Unless otherwise specified, unhardened ground dowel pins shall be furnished with a natural (as processed) finish, unplated or uncoated. Other protective or decorative finishes, where required, shall be subject to agreement between the manufacturer and purchaser. Where additive-type finishes are used, the tabulated dimensions and tolerances shall apply to the pins prior to application of the plating or coating, unless otherwise specified by the purchaser.

## 6.7 Workmanship

Dowel pins shall be free from burrs, seams, sharp edges, and any other defects affecting their serviceability.

## 6.8 Hole Sizes

Because of the wide variety of materials in which dowel pins are used and of the many design requirements that must be considered, it is not possible to provide hole size recommendations that will be suitable for all applications.

However, experience has indicated that the suggested hole sizes tabulated in Table 6.8-1 are satisfactory for press-fitting pins into mild steels and cast and malleable irons. In soft materials such as aluminum alloys or zinc die castings, hole size limits are usually decreased by 0.0005 in. to increase the press fit.

## 6.9 Designation

Unhardened ground dowel pins shall be designated by the following data, in the sequence shown: product name (noun first); nominal pin diameter (fraction or decimal equivalent); length (fraction or decimal equivalent); material; and protective finish, if required. See examples below.

EXAMPLES:

- (1) Pin, Unhardened Ground Dowel,  $\frac{1}{8} \times \frac{3}{4}$ , Steel
- (2) Pin, Unhardened Ground Dowel, 0.250  $\times$  2.500, Steel, Zinc Plated



**Table 6.8-1 Suggested Hole Diameters for Unhardened Ground Dowel Pins**

| Nominal Pin Size | Suggested Hole Diameter |        |
|------------------|-------------------------|--------|
|                  | Max.                    | Min.   |
| $\frac{1}{16}$   | 0.0595                  | 0.058  |
| $\frac{3}{32}$   | 0.0907                  | 0.0892 |
| $\frac{7}{64}$   | 0.1062                  | 0.1047 |
| $\frac{1}{8}$    | 0.1217                  | 0.1202 |
| $\frac{5}{32}$   | 0.1528                  | 0.1513 |
| $\frac{3}{16}$   | 0.184                   | 0.1825 |
| $\frac{7}{32}$   | 0.2151                  | 0.2136 |
| $\frac{1}{4}$    | 0.2462                  | 0.2447 |
| $\frac{5}{16}$   | 0.3085                  | 0.307  |
| $\frac{3}{8}$    | 0.3708                  | 0.3693 |
| $\frac{7}{16}$   | 0.4331                  | 0.4316 |
| $\frac{1}{2}$    | 0.4954                  | 0.4939 |
| $\frac{5}{8}$    | 0.6200                  | 0.6185 |
| $\frac{3}{4}$    | 0.7446                  | 0.7431 |
| $\frac{7}{8}$    | 0.8692                  | 0.8677 |
| 1                | 0.9938                  | 0.9923 |

## 7 GENERAL DATA FOR STRAIGHT PINS

### 7.1 Diameter

**7.1.1 Size.** The diameter of both chamfered and square end straight pins shall conform to that of the commercial wire or rod from which the pins are made. The tolerances specified in Table 7.1.1-1 are applicable to carbon steel and some deviations in the diameter limits may be necessary for pins made from other materials.

### 7.2 Ends

**7.2.1 General.** The ends of straight pins shall be flat and reasonably perpendicular to the axis of pin. Cut-off nibs not protruding more than 0.01 in. beyond pin ends shall be permissible.

**7.2.2 Chamfered Straight Pins.** The corners of both ends of chamfered straight pins shall be chamfered to the dimensions specified in Table 7.1.1-1. The contour of the chamfer surface shall be optional.

**7.2.3 Square End Straight Pins.** The corners of both ends of square end straight pins shall be broken with a radius or chamfer conforming to the specified limits.

### 7.3 Length

**7.3.1 Measurement.** The length of straight pins shall be measured overall from end to end, parallel to the axis of pin, excluding cut-off nibs where they exist.

**7.3.2 Tolerance on Length.** The tolerance on length shall be  $\pm 0.01$  in.

**7.3.3 Length Increments.** Lengths shall be as specified by the purchaser. However, it is recommended that nominal pin lengths be limited to increments of not less than 0.062 in.

**7.3.4 Straightness.** Pins shall be straight over the entire length within a total runout equivalent to 0.001 in. per inch of length.

### 7.4 Materials

**7.4.1 Steel.** Straight pins are normally made from cold drawn steel wire or rod having a maximum carbon content of 0.28%. Unless otherwise agreed upon between the manufacturer and purchaser, no mechanical property requirements shall apply.

**7.4.2 Other Materials.** Where required, pins may also be made from corrosion resistant steel, brass, or other metals, having chemical and mechanical properties as agreed upon between the manufacturer and purchaser.

### 7.5 Finishes

Unless otherwise specified, straight pins shall be furnished with a natural (as processed) finish, unplated or uncoated. Other finishes, where required, shall be subject to agreement between the manufacturer and purchaser. Where additive-type finishes are used, the tabulated dimensions and tolerances shall apply to the pins prior to application of the plating or coating, unless otherwise specified by the purchaser.

### 7.6 Workmanship


Straight pins shall be free from peripheral burrs, excessive cut-off nibs, seams, scale, sharp edges and any other defects affecting their serviceability.

### 7.7 Designation

Straight pins shall be designated by the following data, in the sequence shown: product name (noun first); nominal size (fraction or decimal equivalent); length (fraction or decimal equivalent); material; and protective finish, if required. See examples below.

EXAMPLES:

- (1) Pin, Chamfered Straight,  $\frac{1}{8} \times 1.500$ , Steel
- (2) Pin, Square End Straight,  $0.250 \times 2.250$  Steel, Zinc Plated

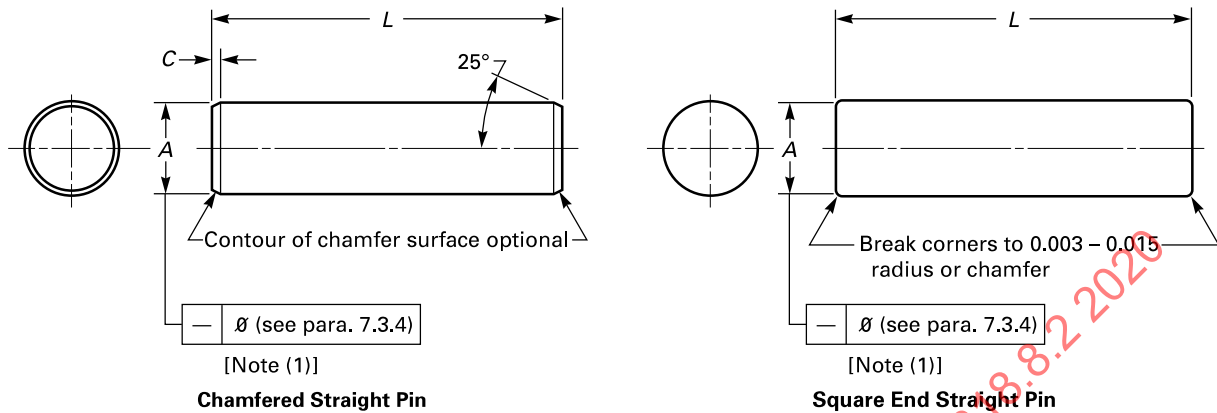**Table 7.1.1-1 Dimensions of Chamfered and Square End Straight Pins**

| Nominal Size or Basic Pin Diameter [Note (2)] |        | Pin Diameter, A |        | Chamfer Length, C |       |
|-----------------------------------------------|--------|-----------------|--------|-------------------|-------|
|                                               |        | Max.            | Min.   | Max.              | Min.  |
| $\frac{1}{16}$                                | 0.0625 | 0.0625          | 0.0605 | 0.025             | 0.005 |
| $\frac{3}{32}$                                | 0.0938 | 0.0937          | 0.0917 | 0.025             | 0.005 |
| $\frac{7}{64}$                                | 0.1094 | 0.1094          | 0.1074 | 0.025             | 0.005 |
| $\frac{1}{8}$                                 | 0.1250 | 0.1250          | 0.1230 | 0.025             | 0.005 |
| $\frac{5}{32}$                                | 0.1563 | 0.1562          | 0.1542 | 0.025             | 0.005 |
| $\frac{3}{16}$                                | 0.1875 | 0.1875          | 0.1855 | 0.025             | 0.005 |
| $\frac{7}{32}$                                | 0.2188 | 0.2187          | 0.2167 | 0.025             | 0.005 |
| $\frac{1}{4}$                                 | 0.2500 | 0.2500          | 0.2480 | 0.025             | 0.005 |
| $\frac{5}{16}$                                | 0.3125 | 0.3125          | 0.3105 | 0.040             | 0.020 |
| $\frac{3}{8}$                                 | 0.3750 | 0.3750          | 0.3730 | 0.040             | 0.020 |
| $\frac{7}{16}$                                | 0.4375 | 0.4375          | 0.4355 | 0.040             | 0.020 |
| $\frac{1}{2}$                                 | 0.5000 | 0.5000          | 0.4980 | 0.040             | 0.020 |
| $\frac{5}{8}$                                 | 0.6250 | 0.6250          | 0.6230 | 0.055             | 0.035 |
| $\frac{3}{4}$                                 | 0.7500 | 0.7500          | 0.7480 | 0.055             | 0.035 |
| $\frac{7}{8}$                                 | 0.8750 | 0.8750          | 0.8730 | 0.055             | 0.035 |
| 1                                             | 1.0000 | 1.0000          | 0.9980 | 0.055             | 0.035 |

**GENERAL NOTES:**

- (a) For additional requirements, refer to [section 7](#).  
 (b) Reference ASME Y14.5.

**NOTES:**

- (1) — = straightness; Ø = diameter  
 (2) Where specifying nominal pin size in decimals, zeros preceding decimal and in the fourth decimal place shall be omitted.

## 8 GENERAL DATA FOR GROOVED PINS, GROOVED DRIVE STUDS, AND GROOVED T-HEAD COTTER PINS

### 8.1 Heads of Grooved Drive Studs and T-Head Cotter Pins

**8.1.1 Bearing Surface.** The bearing surface of head on round-head grooved drive studs and grooved T-head cotter pins, shall be flat and perpendicular with the axis of pin (determined over a distance from under the head equivalent to 1.5 times the basic diameter) within 2 deg.

**8.1.2 Head Position.** The axis of head on round-head grooved drive studs and grooved T-head cotter pins shall be located at true position with respect to the axis of the shank within a tolerance zone having a diameter equivalent to 12% of the maximum head diameter or 0.02 in., whichever is greater.

**8.1.2.1 Eccentricity** shall be equal to one-half of the full or total indicator reading.

### 8.2 Diameters

**8.2.1 Size.** The pin diameter and shank diameter,  $A$ , specified in [Tables 8.2.1-1](#), [8.2.1-2](#), and [8.2.1-3](#), respectively, conform with that of the commercial wire from which the pins and studs are fabricated and is the basis for the product size. Inspection of this dimension on finished (grooved) product shall not be cause for rejection.

**8.2.2 Expanded Diameter.** The expanded diameter,  $B$ , specified in [Tables 8.2.1-2](#), [8.2.1-3](#), [8.2.2-1](#), and [8.2.2-2](#) represents the diameter over the crests of raised ridges formed by the material displaced when grooves are produced. It is dependent upon the depth, shape, and length of the grooves and the pin material. Conformance of expanded diameters to minimum and maximum dimensions shall be determined by the use of GO and NO GO plain ring gages, respectively.

**8.2.3 Tolerances.** The tolerances specified in [Table 8.2.1-1](#) are applicable to carbon steel pins made from wire. Deviations in the diameter limits may be necessary for pins made from other material or from bar stock as agreed to by the manufacturer and the purchaser.

### 8.3 Grooves

**8.3.1 Grooved Pins and Drive Studs.** Grooved pins and drive studs shall have three grooves equally spaced on the diameter. All grooves in any pin or stud shall be of uniform depth, shape, and length and the crests shall be free from tears, burrs, or other irregularities, over the entire length of groove. Grooves shall be aligned with axis of pin or stud and, unless otherwise specified, shall be parallel, oval, or tapered and of length as designated for the respective pin

types. For Types H and E grooved pins having groove lengths equal to 0.125 in. or shorter, the grooves shall be parallel instead of tapered or oval as depicted in the illustrations in [Table 8.2.1-1](#).

**8.3.2 Grooved T-Head Cotter Pins.** Grooved T-head cotter pins shall have three grooves equally spaced on the diameter. Deformation of the shank diameter between the grooves is permitted; however, this may cause high insertion pressures. Where high insertion pressures cannot be tolerated, a solution should be negotiated between the user and the supplier.

**8.3.3 Groove Length.** The groove length shall not vary more than  $\pm 0.03$  in.

### 8.4 Ends

**8.4.1 Grooved Pins.** Except for nominal lengths of  $\frac{1}{4}$  in. or shorter, on which ends are neither crowned nor chamfered, both ends of grooved pins shall be crowned or chamfered as specified for the respective types. Pins made from alloy steel shall have a chamfer on both ends conforming with that specified for Type F pins in lieu of crowned ends. At the manufacturers' option, the ends of pins in nominal sizes up to and including  $\frac{1}{4}$  in. may be tumbled to provide rounded corners equivalent to a 0.015 in.  $\pm$  0.005 in. radius.

**8.4.2 Chamfered Ends.** Chamfered ends shall be 35 deg  $\pm$  5 deg.

**8.4.3 Grooved Drive Studs.** The ends of grooved drive studs shall have a definite chamfer.

**8.4.4 Grooved T-Head Cotter Pins.** The ends of grooved T-head cotter pins may have square, rounded, or chamfered corners conforming to manufacturer's practices.

### 8.5 Length


**8.5.1 Measurement.** The length of grooved pins, drive studs, and T-head cotter pins shall be measured, parallel to the axis of product as defined in the following:

(a) *Grooved Pins.* The length of grooved pins with chamfered, radiussed, or sheared ends shall be measured overall from end to end. The length of grooved pins with crowned ends shall be measured at  $L + 2E$ .

(b) *Grooved Drive Studs and T-Head Cotter Pins.* The length of round-head grooved drive studs and grooved T-head cotter pins shall be measured from the extreme end of the shank to the bearing surface of the head.

**8.5.2 Tolerance on Length.** The tolerance on length of grooved pins and grooved drive studs shall be  $\pm 0.01$  in. The tolerance on length of grooved T-head cotter pins shall be  $\pm 0.031$  in.

Table 8.2.1-1 Dimensions of Grooved Pins

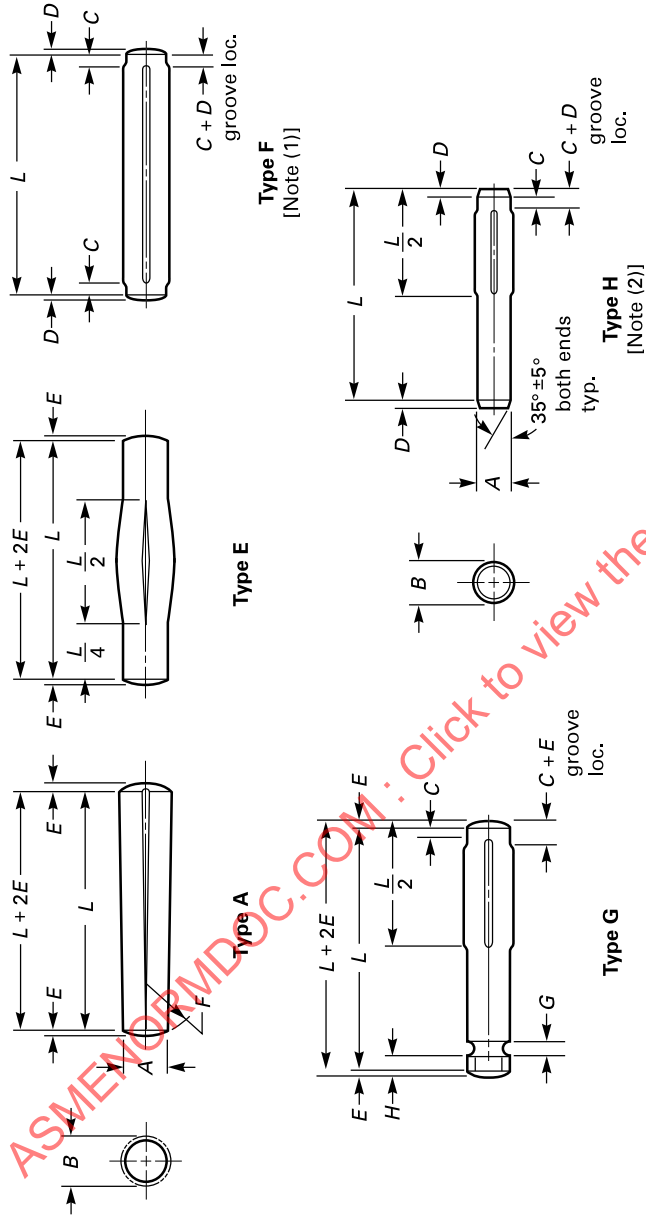

| Nominal<br>Size or<br>Basic Pin<br>Diameter<br>[Note (3)] | Pin Diameter,<br>A |        | Refer-<br>ence<br>Pilot<br>Length,<br>C | Minimum<br>Chamfer<br>Length,<br>D | Nominal<br>Crown<br>Height,<br>E | Crown<br>Radius, F<br>[Note (4)] |       | Neck Width,<br>G |       | Shoulder<br>Length,<br>H |       | Refer-<br>ence<br>Neck<br>Radius,<br>J |       | Neck<br>Diameter,<br>K |       |
|-----------------------------------------------------------|--------------------|--------|-----------------------------------------|------------------------------------|----------------------------------|----------------------------------|-------|------------------|-------|--------------------------|-------|----------------------------------------|-------|------------------------|-------|
|                                                           | Max.               | Min.   |                                         |                                    |                                  | Max.                             | Min.  | Max.             | Min.  | Max.                     | Min.  | Max.                                   | Min.  | Max.                   | Min.  |
| $\frac{1}{32}$ (5)                                        | 0.0312             | 0.0297 | 0.015                                   | ...                                | ...                              | ...                              | ...   | ...              | ...   | ...                      | ...   | ...                                    | ...   | ...                    | ...   |
| $\frac{3}{64}$ (5)                                        | 0.0469             | 0.0454 | 0.031                                   | ...                                | ...                              | ...                              | ...   | ...              | ...   | ...                      | ...   | ...                                    | ...   | ...                    | ...   |
| $\frac{1}{16}$                                            | 0.0625             | 0.0610 | 0.031                                   | 0.005                              | 0.0065                           | 0.088                            | 0.068 | ...              | ...   | ...                      | ...   | ...                                    | ...   | ...                    | ...   |
| $\frac{5}{64}$ (5)                                        | 0.0781             | 0.0766 | 0.031                                   | 0.005                              | 0.0087                           | 0.104                            | 0.084 | ...              | ...   | ...                      | ...   | ...                                    | ...   | ...                    | ...   |
| $\frac{3}{32}$                                            | 0.0938             | 0.0923 | 0.031                                   | 0.005                              | 0.0091                           | 0.135                            | 0.115 | 0.038            | 0.028 | 0.041                    | 0.031 | 0.016                                  | 0.016 | 0.067                  | 0.057 |
| $\frac{7}{64}$ (5)                                        | 0.1094             | 0.1074 | 0.031                                   | 0.005                              | 0.0110                           | 0.150                            | 0.130 | 0.038            | 0.028 | 0.041                    | 0.031 | 0.016                                  | 0.016 | 0.082                  | 0.072 |
| $\frac{1}{8}$                                             | 0.1250             | 0.1230 | 0.031                                   | 0.005                              | 0.0130                           | 0.166                            | 0.146 | 0.069            | 0.059 | 0.041                    | 0.031 | 0.031                                  | 0.031 | 0.088                  | 0.078 |
| $\frac{5}{32}$                                            | 0.1563             | 0.1543 | 0.062                                   | 0.005                              | 0.0170                           | 0.198                            | 0.178 | 0.069            | 0.059 | 0.057                    | 0.047 | 0.031                                  | 0.031 | 0.109                  | 0.099 |
| $\frac{3}{16}$                                            | 0.1875             | 0.1855 | 0.062                                   | 0.016                              | 0.0180                           | 0.260                            | 0.240 | 0.069            | 0.059 | 0.057                    | 0.047 | 0.031                                  | 0.031 | 0.130                  | 0.120 |
| $\frac{7}{32}$                                            | 0.2188             | 0.2168 | 0.062                                   | 0.016                              | 0.0220                           | 0.291                            | 0.271 | 0.101            | 0.091 | 0.072                    | 0.062 | 0.047                                  | 0.047 | 0.151                  | 0.141 |

Table 8.2.1-1 Dimensions of Grooved Pins (Cont'd)

| Nominal Size or Basic Pin Diameter<br>[Note (3)] | Pin Diameter, <i>A</i> |        | Refer-<br>ence<br>Pilot<br>Length,<br><i>C</i> | Minimum<br>Chamfer<br>Length,<br><i>D</i><br>[Note (4)] | Nominal<br>Crown<br>Height,<br><i>E</i><br>[Note (4)] | Crown<br>Radius, <i>F</i><br>[Note (4)] |       | Neck Width,<br><i>G</i> |       | Shoulder<br>Length,<br><i>H</i> |       | Refer-<br>ence<br>Neck<br>Radius,<br><i>J</i> | Neck<br>Diameter,<br><i>K</i> |       |
|--------------------------------------------------|------------------------|--------|------------------------------------------------|---------------------------------------------------------|-------------------------------------------------------|-----------------------------------------|-------|-------------------------|-------|---------------------------------|-------|-----------------------------------------------|-------------------------------|-------|
|                                                  | Max.                   | Min.   |                                                |                                                         |                                                       | Max.                                    | Min.  | Max.                    | Min.  | Max.                            | Min.  |                                               | Max.                          | Min.  |
| $\frac{1}{4}$                                    | 0.2500                 | 0.2500 | 0.2480                                         | 0.062                                                   | 0.016                                                 | 0.322                                   | 0.302 | 0.101                   | 0.091 | 0.072                           | 0.062 | 0.047                                         | 0.172                         | 0.162 |
| $\frac{5}{16}$                                   | 0.3125                 | 0.3125 | 0.3105                                         | 0.094                                                   | 0.031                                                 | 0.385                                   | 0.365 | 0.132                   | 0.122 | 0.104                           | 0.094 | 0.062                                         | 0.214                         | 0.204 |
| $\frac{3}{8}$                                    | 0.3750                 | 0.3750 | 0.3730                                         | 0.094                                                   | 0.031                                                 | 0.479                                   | 0.459 | 0.132                   | 0.122 | 0.135                           | 0.125 | 0.062                                         | 0.255                         | 0.245 |
| $\frac{7}{16}$                                   | 0.4375                 | 0.4375 | 0.4355                                         | 0.094                                                   | 0.031                                                 | 0.541                                   | 0.521 | 0.195                   | 0.185 | 0.135                           | 0.125 | 0.094                                         | 0.298                         | 0.288 |
| $\frac{1}{2}$                                    | 0.5000                 | 0.5000 | 0.4980                                         | 0.094                                                   | 0.031                                                 | 0.635                                   | 0.615 | 0.195                   | 0.185 | 0.135                           | 0.125 | 0.094                                         | 0.317                         | 0.307 |


## GENERAL NOTES:

- (a) For expanded diameters applicable to pins made from corrosion resistant steel or Monel, see Table 8.2.2-2; and for pins made from other materials, see Table 8.2.2-1.  
 (b) For additional requirements and recommended hole sizes, see section 8.

## NOTES:

- (1) Type F replaces Type C as previously used in ANSI B18.8.2-1978 (see Nonmandatory Appendix C).  
 (2) Type H replaces Types B and D as previously used in ANSI B18.8.2-1978 (see Nonmandatory Appendix C).  
 (3) Where specifying nominal size in decimals, zeros preceding decimal and in the fourth decimal place shall be omitted.  
 (4) Pins in  $\frac{1}{32}$  in. and  $\frac{3}{64}$  in. sizes of any length and all sizes  $\frac{1}{4}$  in. nominal length, or shorter, are not crowned or chamfered. See para. 8.4 of General Data. Alloy steel pins of all types shall have chamfered ends conforming with Type F pins, included within the pin length.  
 (5) Nonstock items — not recommended for new design.

Table 8.2.1-2 Dimensions of Round-Head Grooved Drive Studs

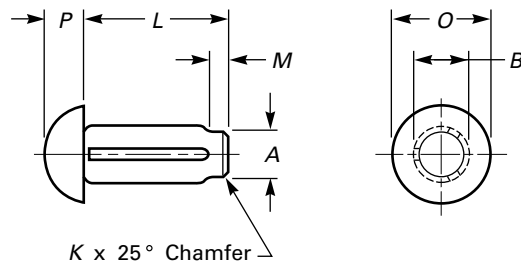


| Stud Size<br>No. and<br>Basic<br>Shank Dia.<br>[Note (1)] | Shank Dia.,<br><i>A</i> |       | Head Dia.,<br><i>O</i> |       | Head Height,<br><i>P</i> |       | Expanded Pin Diameter, <i>B</i> (±0.002), for Nominal Stud Length<br>[Note (2)] |       |       |       |       |       |       |       |       |       | Min.<br>Chamfer,<br><i>K</i> |
|-----------------------------------------------------------|-------------------------|-------|------------------------|-------|--------------------------|-------|---------------------------------------------------------------------------------|-------|-------|-------|-------|-------|-------|-------|-------|-------|------------------------------|
|                                                           | Max.                    | Min.  | Max.                   | Min.  | Max.                     | Min.  | 1/8                                                                             | 3/16  | 1/4   | 5/16  | 3/8   | 1/2   | 5/8   | 3/4   |       |       |                              |
| 0                                                         | 0.067                   | 0.067 | 0.065                  | 0.130 | 0.120                    | 0.050 | 0.040                                                                           | 0.074 | 0.074 | 0.074 | ...   | ...   | ...   | ...   | ...   | 0.005 |                              |
| 2                                                         | 0.086                   | 0.086 | 0.084                  | 0.162 | 0.146                    | 0.070 | 0.059                                                                           | 0.096 | 0.096 | 0.095 | ...   | ...   | ...   | ...   | ...   | 0.005 |                              |
| 4                                                         | 0.104                   | 0.104 | 0.102                  | 0.211 | 0.193                    | 0.086 | 0.075                                                                           | ...   | 0.115 | 0.113 | 0.113 | ...   | ...   | ...   | ...   | 0.005 |                              |
| 6                                                         | 0.120                   | 0.120 | 0.118                  | 0.260 | 0.240                    | 0.103 | 0.091                                                                           | ...   | ...   | 0.132 | 0.130 | 0.130 | ...   | ...   | ...   | 0.005 |                              |
| 7                                                         | 0.136                   | 0.136 | 0.134                  | 0.309 | 0.287                    | 0.119 | 0.107                                                                           | ...   | ...   | ...   | 0.147 | 0.147 | 0.144 | ...   | ...   | 0.005 |                              |
| 8                                                         | 0.144                   | 0.144 | 0.142                  | 0.309 | 0.287                    | 0.119 | 0.107                                                                           | ...   | ...   | ...   | ...   | 0.155 | 0.153 | 0.153 | ...   | 0.005 |                              |
| 10                                                        | 0.161                   | 0.161 | 0.159                  | 0.359 | 0.334                    | 0.136 | 0.124                                                                           | ...   | ...   | ...   | ...   | 0.173 | 0.171 | 0.171 | ...   | 0.016 |                              |
| 12                                                        | 0.196                   | 0.196 | 0.194                  | 0.408 | 0.382                    | 0.152 | 0.140                                                                           | ...   | ...   | ...   | ...   | ...   | 0.206 | 0.204 | 0.204 | 0.016 |                              |
| 14                                                        | 0.221                   | 0.221 | 0.219                  | 0.457 | 0.429                    | 0.169 | 0.156                                                                           | ...   | ...   | ...   | ...   | ...   | 0.234 | 0.232 | 0.232 | 0.016 |                              |
| 16                                                        | 0.250                   | 0.250 | 0.248                  | 0.472 | 0.443                    | 0.174 | 0.161                                                                           | ...   | ...   | ...   | ...   | ...   | 0.263 | ...   | ...   | 0.016 |                              |

## NOTES:

- (1) Where specifying stud size in decimals, zeros preceding decimal and in the fourth decimal place shall be omitted.
- (2) Sizes and length, for which  $B$  values are tabulated are normally readily available in carbon steel. For other size-length combinations or materials, manufacturers should be consulted.

Table 8.2.1-3 Dimensions of Grooved T-Head Cotter Pins

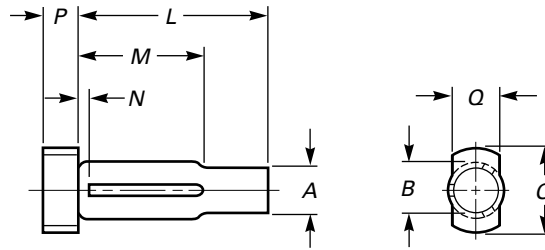

| Nominal Size<br>(or Basic<br>Shank Dia.)<br>[Note (1)] | Shank Dia.<br><i>A</i> |       | Expanded<br>Shank Dia.,<br><i>B</i> |       | Max. Length,<br><i>N</i> |      | Head Dia.,<br><i>O</i> |      | Head Height,<br><i>P</i> |      | Head Width,<br><i>Q</i> |      | Recommended<br>Hole Size |       |
|--------------------------------------------------------|------------------------|-------|-------------------------------------|-------|--------------------------|------|------------------------|------|--------------------------|------|-------------------------|------|--------------------------|-------|
|                                                        | Min.                   | Max.  | Max.                                | Min.  | Max.                     | Min. | Max.                   | Min. | Max.                     | Min. | Max.                    |      |                          |       |
| <sup>5</sup> / <sub>32</sub>                           | 0.156                  | 0.154 | 0.150                               | 0.168 | 0.163                    | 0.08 | 0.26                   | 0.24 | 0.11                     | 0.09 | 0.18                    | 0.15 | 0.161                    | 0.156 |
| <sup>3</sup> / <sub>16</sub>                           | 0.187                  | 0.186 | 0.182                               | 0.201 | 0.195                    | 0.09 | 0.30                   | 0.28 | 0.13                     | 0.11 | 0.22                    | 0.18 | 0.193                    | 0.187 |
| <sup>1</sup> / <sub>4</sub>                            | 0.250                  | 0.248 | 0.244                               | 0.265 | 0.258                    | 0.12 | 0.40                   | 0.38 | 0.17                     | 0.15 | 0.28                    | 0.24 | 0.257                    | 0.250 |
| <sup>5</sup> / <sub>16</sub>                           | 0.312                  | 0.310 | 0.305                               | 0.326 | 0.320                    | 0.16 | 0.51                   | 0.48 | 0.21                     | 0.19 | 0.34                    | 0.30 | 0.319                    | 0.312 |
| <sup>23</sup> / <sub>64</sub>                          | 0.359                  | 0.358 | 0.353                               | 0.375 | 0.369                    | 0.18 | 0.57                   | 0.54 | 0.24                     | 0.22 | 0.38                    | 0.35 | 0.366                    | 0.359 |
| <sup>1</sup> / <sub>2</sub>                            | 0.500                  | 0.498 | 0.493                               | 0.520 | 0.514                    | 0.25 | 0.79                   | 0.76 | 0.32                     | 0.30 | 0.54                    | 0.49 | 0.508                    | 0.500 |

GENERAL NOTE: For groove lengths,  $M$ , which vary with pin length, see Table 8.5.3-3.

NOTE:

(1) Where specifying nominal size in decimals, zeros preceding decimal and in the fourth decimal place shall be omitted.

**Table 8.2.2-1 Expanded Diameters for Grooved Pins Made From Low Carbon or Alloy Steel**

| Groove Length<br>[Note (1)] | Expanded Pin Diameter, <i>B</i> , for Nominal Size |                                            |                              |                                            |                              |                                            |                             |                              |                              |                              |                             |                              |                             |                              |                             |  |
|-----------------------------|----------------------------------------------------|--------------------------------------------|------------------------------|--------------------------------------------|------------------------------|--------------------------------------------|-----------------------------|------------------------------|------------------------------|------------------------------|-----------------------------|------------------------------|-----------------------------|------------------------------|-----------------------------|--|
|                             | ± 0.0015                                           |                                            |                              |                                            |                              | ±0.002                                     |                             | ± 0.0025                     |                              |                              |                             |                              | ± 0.003                     |                              |                             |  |
|                             | <sup>1</sup> / <sub>32</sub><br>[Note (2)]         | <sup>3</sup> / <sub>64</sub><br>[Note (2)] | <sup>1</sup> / <sub>16</sub> | <sup>5</sup> / <sub>64</sub><br>[Note (2)] | <sup>3</sup> / <sub>32</sub> | <sup>7</sup> / <sub>64</sub><br>[Note (2)] | <sup>1</sup> / <sub>8</sub> | <sup>5</sup> / <sub>32</sub> | <sup>3</sup> / <sub>16</sub> | <sup>7</sup> / <sub>32</sub> | <sup>1</sup> / <sub>4</sub> | <sup>5</sup> / <sub>16</sub> | <sup>3</sup> / <sub>8</sub> | <sup>7</sup> / <sub>16</sub> | <sup>1</sup> / <sub>2</sub> |  |
| 0.125                       | 0.035                                              | 0.051                                      | 0.068                        | 0.084                                      | 0.101                        | 0.117                                      | 0.134                       | ...                          | ...                          | ...                          | ...                         | ...                          | ...                         | ...                          | ...                         |  |
| 0.188                       | 0.035                                              | 0.051                                      | 0.068                        | 0.084                                      | 0.101                        | 0.117                                      | 0.134                       | 0.166                        | 0.198                        | ...                          | ...                         | ...                          | ...                         | ...                          | ...                         |  |
| 0.250                       | 0.035                                              | 0.051                                      | 0.068                        | 0.084                                      | 0.101                        | 0.117                                      | 0.134                       | 0.166                        | 0.198                        | 0.230                        | 0.263                       | ...                          | ...                         | ...                          | ...                         |  |
| 0.312                       | 0.035                                              | 0.051                                      | 0.068                        | 0.084                                      | 0.101                        | 0.117                                      | 0.134                       | 0.166                        | 0.198                        | 0.230                        | 0.263                       | 0.329                        | ...                         | ...                          | ...                         |  |
| 0.375                       | 0.035                                              | 0.051                                      | 0.068                        | 0.084                                      | 0.101                        | 0.117                                      | 0.134                       | 0.166                        | 0.198                        | 0.230                        | 0.263                       | 0.329                        | 0.394                       | ...                          | ...                         |  |
| 0.438                       | 0.035                                              | 0.051                                      | 0.068                        | 0.084                                      | 0.101                        | 0.117                                      | 0.134                       | 0.166                        | 0.198                        | 0.230                        | 0.263                       | 0.329                        | 0.394                       | 0.459                        | ...                         |  |
| 0.500                       | 0.035                                              | 0.051                                      | 0.068                        | 0.084                                      | 0.101                        | 0.117                                      | 0.134                       | 0.166                        | 0.198                        | 0.230                        | 0.263                       | 0.329                        | 0.394                       | 0.459                        | 0.525                       |  |
| 0.562                       | ...                                                | 0.051                                      | 0.068                        | 0.084                                      | 0.101                        | 0.117                                      | 0.134                       | 0.166                        | 0.198                        | 0.230                        | 0.263                       | 0.329                        | 0.394                       | 0.459                        | 0.525                       |  |
| 0.625                       | ...                                                | 0.051                                      | 0.068                        | 0.084                                      | 0.101                        | 0.117                                      | 0.134                       | 0.166                        | 0.198                        | 0.230                        | 0.263                       | 0.329                        | 0.394                       | 0.459                        | 0.525                       |  |
| 0.750                       | ...                                                | ...                                        | 0.067                        | 0.083                                      | 0.100                        | 0.116                                      | 0.134                       | 0.166                        | 0.198                        | 0.230                        | 0.263                       | 0.329                        | 0.394                       | 0.459                        | 0.525                       |  |
| 0.875                       | ...                                                | ...                                        | 0.067                        | 0.083                                      | 0.100                        | 0.116                                      | 0.133                       | 0.166                        | 0.198                        | 0.230                        | 0.263                       | 0.329                        | 0.394                       | 0.459                        | 0.525                       |  |
| 1.000                       | ...                                                | ...                                        | 0.067                        | 0.083                                      | 0.100                        | 0.116                                      | 0.133                       | 0.166                        | 0.198                        | 0.230                        | 0.263                       | 0.329                        | 0.394                       | 0.459                        | 0.525                       |  |
| 1.125                       | ...                                                | ...                                        | ...                          | ...                                        | 0.100                        | 0.116                                      | 0.132                       | 0.164                        | 0.197                        | 0.230                        | 0.263                       | 0.329                        | 0.394                       | 0.459                        | 0.525                       |  |
| 1.250                       | ...                                                | ...                                        | ...                          | ...                                        | 0.100                        | 0.116                                      | 0.132                       | 0.164                        | 0.197                        | 0.230                        | 0.263                       | 0.329                        | 0.394                       | 0.459                        | 0.525                       |  |
| 1.375                       | ...                                                | ...                                        | ...                          | ...                                        | ...                          | ...                                        | 0.132                       | 0.164                        | 0.197                        | 0.229                        | 0.262                       | 0.329                        | 0.394                       | 0.459                        | 0.525                       |  |
| 1.500                       | ...                                                | ...                                        | ...                          | ...                                        | ...                          | ...                                        | 0.132                       | 0.164                        | 0.197                        | 0.229                        | 0.262                       | 0.329                        | 0.394                       | 0.459                        | 0.525                       |  |
| 1.625                       | ...                                                | ...                                        | ...                          | ...                                        | ...                          | ...                                        | ...                         | 0.163                        | 0.197                        | 0.229                        | 0.262                       | 0.328                        | 0.393                       | 0.459                        | 0.525                       |  |
| 1.750                       | ...                                                | ...                                        | ...                          | ...                                        | ...                          | ...                                        | ...                         | 0.163                        | 0.197                        | 0.229                        | 0.262                       | 0.328                        | 0.393                       | 0.459                        | 0.525                       |  |
| 1.875                       | ...                                                | ...                                        | ...                          | ...                                        | ...                          | ...                                        | ...                         | 0.163                        | 0.196                        | 0.229                        | 0.262                       | 0.328                        | 0.393                       | 0.458                        | 0.525                       |  |
| 2.000                       | ...                                                | ...                                        | ...                          | ...                                        | ...                          | ...                                        | ...                         | 0.163                        | 0.196                        | 0.229                        | 0.262                       | 0.328                        | 0.393                       | 0.458                        | 0.525                       |  |
| 2.125                       | ...                                                | ...                                        | ...                          | ...                                        | ...                          | ...                                        | ...                         | ...                          | 0.196                        | 0.229                        | 0.262                       | 0.328                        | 0.393                       | 0.458                        | 0.524                       |  |
| 2.250                       | ...                                                | ...                                        | ...                          | ...                                        | ...                          | ...                                        | ...                         | ...                          | 0.196                        | 0.229                        | 0.262                       | 0.328                        | 0.393                       | 0.458                        | 0.524                       |  |
| 2.500                       | ...                                                | ...                                        | ...                          | ...                                        | ...                          | ...                                        | ...                         | ...                          | ...                          | 0.228                        | 0.261                       | 0.327                        | 0.393                       | 0.458                        | 0.524                       |  |
| 2.750                       | ...                                                | ...                                        | ...                          | ...                                        | ...                          | ...                                        | ...                         | ...                          | ...                          | 0.228                        | 0.261                       | 0.327                        | 0.393                       | 0.458                        | 0.524                       |  |
| 3.000                       | ...                                                | ...                                        | ...                          | ...                                        | ...                          | ...                                        | ...                         | ...                          | ...                          | 0.227                        | 0.260                       | 0.327                        | 0.392                       | 0.457                        | 0.523                       |  |
| 3.250                       | ...                                                | ...                                        | ...                          | ...                                        | ...                          | ...                                        | ...                         | ...                          | ...                          | ...                          | 0.260                       | 0.326                        | 0.392                       | 0.457                        | 0.523                       |  |
| 3.500                       | ...                                                | ...                                        | ...                          | ...                                        | ...                          | ...                                        | ...                         | ...                          | ...                          | ...                          | ...                         | 0.326                        | 0.391                       | 0.456                        | 0.522                       |  |
| 3.750                       | ...                                                | ...                                        | ...                          | ...                                        | ...                          | ...                                        | ...                         | ...                          | ...                          | ...                          | ...                         | ...                          | 0.391                       | 0.456                        | 0.522                       |  |
| 4.000                       | ...                                                | ...                                        | ...                          | ...                                        | ...                          | ...                                        | ...                         | ...                          | ...                          | ...                          | ...                         | ...                          | 0.390                       | 0.455                        | 0.521                       |  |
| 4.250                       | ...                                                | ...                                        | ...                          | ...                                        | ...                          | ...                                        | ...                         | ...                          | ...                          | ...                          | ...                         | ...                          | 0.390                       | 0.455                        | 0.521                       |  |
| 4.500                       | ...                                                | ...                                        | ...                          | ...                                        | ...                          | ...                                        | ...                         | ...                          | ...                          | ...                          | ...                         | ...                          | ...                         | 0.454                        | 0.520                       |  |

GENERAL NOTE: For expanded diameters applicable to pins made from corrosion resistant steel or Monel, see [Table 8.2.2-2](#).

## NOTES:

- (1) Groove length shall be considered as being substantially equal to the pin length for Types A, C, and F grooved pins, and equal to one-half of the pin length for Types B, D, E, and G grooved pins. For groove lengths not shown, use expanded diameters given for the next longer tabulated groove length.
- (2) Nonstock items — not recommended for new design.



**Table 8.2.2-2 Expanded Diameters for Grooved Pins Made From Corrosion Resistant Steel and Monel**

| Expanded Pin Diameter, <i>B</i> , for Nominal Size |                                            |                                            |                              |                                            |                              |                                            |                             |                              |                              |                              |                             |                              |                             |                              |                             |     |
|----------------------------------------------------|--------------------------------------------|--------------------------------------------|------------------------------|--------------------------------------------|------------------------------|--------------------------------------------|-----------------------------|------------------------------|------------------------------|------------------------------|-----------------------------|------------------------------|-----------------------------|------------------------------|-----------------------------|-----|
| Groove Length<br>[Note (1)]                        | ± 0.0015                                   |                                            |                              |                                            |                              | ±0.002                                     |                             | ± 0.0025                     |                              |                              |                             |                              | ± 0.003                     |                              |                             |     |
|                                                    | <sup>1</sup> / <sub>32</sub><br>[Note (2)] | <sup>3</sup> / <sub>64</sub><br>[Note (2)] | <sup>1</sup> / <sub>16</sub> | <sup>5</sup> / <sub>64</sub><br>[Note (2)] | <sup>3</sup> / <sub>32</sub> | <sup>7</sup> / <sub>64</sub><br>[Note (2)] | <sup>1</sup> / <sub>8</sub> | <sup>5</sup> / <sub>32</sub> | <sup>3</sup> / <sub>16</sub> | <sup>7</sup> / <sub>32</sub> | <sup>1</sup> / <sub>4</sub> | <sup>5</sup> / <sub>16</sub> | <sup>3</sup> / <sub>8</sub> | <sup>7</sup> / <sub>16</sub> | <sup>1</sup> / <sub>2</sub> |     |
| 0.125                                              | 0.034                                      | 0.050                                      | 0.066                        | 0.082                                      | 0.099                        | 0.115                                      | 0.132                       | ...                          | ...                          | ...                          | ...                         | ...                          | ...                         | ...                          | ...                         | ... |
| 0.188                                              | 0.034                                      | 0.050                                      | 0.066                        | 0.082                                      | 0.099                        | 0.115                                      | 0.132                       | 0.164                        | 0.195                        | ...                          | ...                         | ...                          | ...                         | ...                          | ...                         | ... |
| 0.250                                              | 0.034                                      | 0.050                                      | 0.066                        | 0.082                                      | 0.099                        | 0.115                                      | 0.132                       | 0.164                        | 0.195                        | 0.227                        | 0.260                       | ...                          | ...                         | ...                          | ...                         | ... |
| 0.312                                              | 0.034                                      | 0.050                                      | 0.066                        | 0.082                                      | 0.099                        | 0.115                                      | 0.132                       | 0.164                        | 0.195                        | 0.227                        | 0.260                       | 0.325                        | ...                         | ...                          | ...                         | ... |
| 0.375                                              | 0.034                                      | 0.050                                      | 0.066                        | 0.082                                      | 0.099                        | 0.115                                      | 0.132                       | 0.164                        | 0.195                        | 0.227                        | 0.260                       | 0.325                        | 0.389                       | ...                          | ...                         | ... |
| 0.438                                              | 0.034                                      | 0.050                                      | 0.066                        | 0.082                                      | 0.099                        | 0.115                                      | 0.132                       | 0.164                        | 0.195                        | 0.227                        | 0.260                       | 0.325                        | 0.389                       | 0.453                        | ...                         | ... |
| 0.500                                              | 0.034                                      | 0.050                                      | 0.066                        | 0.082                                      | 0.099                        | 0.115                                      | 0.132                       | 0.164                        | 0.195                        | 0.227                        | 0.260                       | 0.325                        | 0.389                       | 0.453                        | 0.519                       | ... |
| 0.562                                              | ...                                        | 0.050                                      | 0.066                        | 0.082                                      | 0.099                        | 0.115                                      | 0.132                       | 0.164                        | 0.195                        | 0.227                        | 0.260                       | 0.325                        | 0.389                       | 0.453                        | 0.519                       | ... |
| 0.625                                              | ...                                        | 0.050                                      | 0.066                        | 0.082                                      | 0.099                        | 0.115                                      | 0.132                       | 0.164                        | 0.195                        | 0.227                        | 0.260                       | 0.325                        | 0.389                       | 0.453                        | 0.519                       | ... |
| 0.750                                              | ...                                        | ...                                        | 0.065                        | 0.081                                      | 0.098                        | 0.114                                      | 0.132                       | 0.164                        | 0.195                        | 0.227                        | 0.260                       | 0.325                        | 0.389                       | 0.453                        | 0.519                       | ... |
| 0.875                                              | ...                                        | ...                                        | 0.065                        | 0.081                                      | 0.098                        | 0.114                                      | 0.131                       | 0.163                        | 0.195                        | 0.227                        | 0.260                       | 0.325                        | 0.389                       | 0.453                        | 0.519                       | ... |
| 1.000                                              | ...                                        | ...                                        | 0.065                        | 0.081                                      | 0.098                        | 0.113                                      | 0.131                       | 0.163                        | 0.195                        | 0.227                        | 0.260                       | 0.325                        | 0.389                       | 0.453                        | 0.519                       | ... |
| 1.125                                              | ...                                        | ...                                        | ...                          | ...                                        | 0.098                        | 0.113                                      | 0.130                       | 0.162                        | 0.194                        | 0.227                        | 0.260                       | 0.325                        | 0.389                       | 0.453                        | 0.519                       | ... |
| 1.250                                              | ...                                        | ...                                        | ...                          | ...                                        | ...                          | ...                                        | 0.130                       | 0.162                        | 0.194                        | 0.227                        | 0.260                       | 0.325                        | 0.389                       | 0.453                        | 0.519                       | ... |
| 1.375                                              | ...                                        | ...                                        | ...                          | ...                                        | ...                          | ...                                        | 0.130                       | 0.162                        | 0.194                        | 0.226                        | 0.259                       | 0.325                        | 0.389                       | 0.453                        | 0.519                       | ... |
| 1.500                                              | ...                                        | ...                                        | ...                          | ...                                        | ...                          | ...                                        | 0.130                       | 0.162                        | 0.194                        | 0.226                        | 0.259                       | 0.325                        | 0.389                       | 0.453                        | 0.519                       | ... |
| 1.625                                              | ...                                        | ...                                        | ...                          | ...                                        | ...                          | ...                                        | ...                         | 0.161                        | 0.194                        | 0.226                        | 0.259                       | 0.324                        | 0.388                       | 0.453                        | 0.519                       | ... |
| 1.750                                              | ...                                        | ...                                        | ...                          | ...                                        | ...                          | ...                                        | ...                         | 0.161                        | 0.194                        | 0.226                        | 0.259                       | 0.324                        | 0.388                       | 0.453                        | 0.519                       | ... |
| 1.875                                              | ...                                        | ...                                        | ...                          | ...                                        | ...                          | ...                                        | ...                         | 0.161                        | 0.193                        | 0.226                        | 0.259                       | 0.324                        | 0.388                       | 0.452                        | 0.519                       | ... |
| 2.000                                              | ...                                        | ...                                        | ...                          | ...                                        | ...                          | ...                                        | ...                         | 0.161                        | 0.193                        | 0.226                        | 0.259                       | 0.324                        | 0.388                       | 0.452                        | 0.519                       | ... |
| 2.125                                              | ...                                        | ...                                        | ...                          | ...                                        | ...                          | ...                                        | ...                         | ...                          | 0.193                        | 0.226                        | 0.259                       | 0.324                        | 0.388                       | 0.452                        | 0.518                       | ... |
| 2.250                                              | ...                                        | ...                                        | ...                          | ...                                        | ...                          | ...                                        | ...                         | ...                          | 0.193                        | 0.226                        | 0.259                       | 0.324                        | 0.388                       | 0.452                        | 0.518                       | ... |
| 2.500                                              | ...                                        | ...                                        | ...                          | ...                                        | ...                          | ...                                        | ...                         | ...                          | ...                          | 0.225                        | 0.258                       | 0.323                        | 0.388                       | 0.452                        | 0.518                       | ... |
| 2.750                                              | ...                                        | ...                                        | ...                          | ...                                        | ...                          | ...                                        | ...                         | ...                          | ...                          | 0.225                        | 0.258                       | 0.323                        | 0.388                       | 0.452                        | 0.518                       | ... |
| 3.000                                              | ...                                        | ...                                        | ...                          | ...                                        | ...                          | ...                                        | ...                         | ...                          | ...                          | 0.224                        | 0.257                       | 0.323                        | 0.387                       | 0.451                        | 0.517                       | ... |
| 3.250                                              | ...                                        | ...                                        | ...                          | ...                                        | ...                          | ...                                        | ...                         | ...                          | ...                          | ...                          | 0.257                       | 0.322                        | 0.387                       | 0.451                        | 0.517                       | ... |
| 3.500                                              | ...                                        | ...                                        | ...                          | ...                                        | ...                          | ...                                        | ...                         | ...                          | ...                          | ...                          | ...                         | 0.322                        | 0.387                       | 0.450                        | 0.516                       | ... |
| 3.750                                              | ...                                        | ...                                        | ...                          | ...                                        | ...                          | ...                                        | ...                         | ...                          | ...                          | ...                          | ...                         | ...                          | 0.387                       | 0.450                        | 0.516                       | ... |
| 4.000                                              | ...                                        | ...                                        | ...                          | ...                                        | ...                          | ...                                        | ...                         | ...                          | ...                          | ...                          | ...                         | ...                          | 0.386                       | 0.449                        | 0.515                       | ... |
| 4.250                                              | ...                                        | ...                                        | ...                          | ...                                        | ...                          | ...                                        | ...                         | ...                          | ...                          | ...                          | ...                         | ...                          | 0.386                       | 0.449                        | 0.515                       | ... |
| 4.500                                              | ...                                        | ...                                        | ...                          | ...                                        | ...                          | ...                                        | ...                         | ...                          | ...                          | ...                          | ...                         | ...                          | ...                         | 0.448                        | 0.514                       | ... |

GENERAL NOTE: For expanded diameters applicable to pins made from low carbon or alloy steel, see [Table 8.2.2-1](#).

## NOTES:

- (1) Groove length shall be considered as being substantially equal to the pin length for Types A, C, and F grooved pins, and equal to one-half of the pin length for Types B, D, E, and G grooved pins. For groove lengths not shown, use expanded diameters given for the next longer tabulated groove length.
- (2) Nonstock items — not recommended for new design

**8.5.3 Standard Lengths.** The standard sizes and lengths in which grooved pins of all types, grooved drive studs, and T-head cotter pins are normally available are depicted in [Tables 8.2.1-2, 8.5.3-1, 8.5.3-2, and 8.5.3-3](#), respectively. Where other size-length combinations and materials are required, manufacturers should be consulted.

## 8.6 Materials

**8.6.1 Grooved Pins.** Grooved pins are normally made from cold-drawn low carbon steel wire or rod. Where additional performance is required, carbon steel pins may be supplied surface hardened to a hardness consistent with the performance requirements.

Where required for specific applications, pins may also be made from alloy steel, corrosion resistant steel, brass, Monel, and other nonferrous metals having chemical properties as agreed upon between the manufacturer and purchaser.

**8.6.2 Grooved Drive Studs and T-Head Cotter Pins.** Unless otherwise specified, grooved drive studs and T-head cotter pins shall be made from low carbon steel. Where so indicated by the purchaser, they may be made from corrosion resistant steel, brass, and other nonferrous metals as agreed upon between the manufacturer and purchaser.

## 8.7 Performance Requirements

Grooved pins shall be capable of withstanding the minimum double shear loads tabulated in [Table 8.7-1](#) for the respective materials, when tested in accordance with the double shear testing of pins set forth in [Nonmandatory Appendix B](#). The holes in the fixtures for testing grooved pins shall conform with the specified recommended hole size limits.

Grooved pins which have been sheared at loads exceeding the minimums specified shall exhibit a ductile fracture at the shear point with no longitudinal cracks.

## 8.8 Hole Sizes

To obtain optimum product retention under average conditions, it is recommended that holes for installation of grooved pins and grooved drive studs shown in

[Tables 8.8-1 and 8.8-2](#), and those for grooved T-head cotter pins given in [Table 8.2.1-3](#) be held as close as possible to the limits tabulated. The minimum limits given correspond to the drill size which is equivalent to the basic pin or shank diameter. The maximum limits shown are generally suitable for length-to-diameter ratios of not less than 4 to 1 and not greater than 10 to 1. For smaller length-to-diameter ratios, the holes should be held closer to the minimum limits where retention is critical. Conversely, for larger length-to-diameter ratios or where retention requirements are not essential, it may be desirable to increase the hole diameter beyond the maximum limits shown.

In applications where the grooved products are to be installed into materials which are appreciably harder than the product material, it is recommended the edges of the holes be chamfered or otherwise relieved to avoid shearing of the expanded pin or shank section during insertion.

## 8.9 Finishes

**8.9.1 Corrosion Protection.** Unless otherwise specified, low carbon steel pins and drive studs shall have a flash plating of zinc to provide interim corrosion protection and products of other materials shall be furnished with a natural (as processed) finish, unplated or uncoated. Other finishes, where required, shall be subject to agreement between the manufacturer and purchaser.

**8.9.2 Relief from Hydrogen Embrittlement.** Where a corrosion preventative finish applied to hardened carbon or alloy steel pins is such that it might produce hydrogen embrittlement, the pins shall be baked for a suitable time at a temperature that will obviate such embrittlement. Baking shall be accomplished as soon as possible following the plating or coating operation inasmuch as delay is detrimental to achieving the desired result.

## 8.10 Workmanship

Grooved pins, drive studs, and T-head cotter pins shall be free from burrs, seams, loose scale, sharp edges, and any other defects affecting their serviceability.

Table 8.5.3-1 Standard Sizes and Lengths of Grooved Pins

| Nominal Length | Nominal Size   |                |               |                |                |                |               |                |               |                |               |
|----------------|----------------|----------------|---------------|----------------|----------------|----------------|---------------|----------------|---------------|----------------|---------------|
|                | $\frac{1}{16}$ | $\frac{3}{32}$ | $\frac{1}{8}$ | $\frac{5}{32}$ | $\frac{3}{16}$ | $\frac{7}{32}$ | $\frac{1}{4}$ | $\frac{5}{16}$ | $\frac{3}{8}$ | $\frac{7}{16}$ | $\frac{1}{2}$ |
| $\frac{1}{8}$  | Y              | ...            | ...           | ...            | ...            | ...            | ...           | ...            | ...           | ...            | ..            |
| $\frac{1}{4}$  | Y              | Y              | Y             | ...            | ...            | ...            | ...           | ...            | ...           | ...            | ...           |
| $\frac{3}{8}$  | Y              | X              | X             | X              | X              | ...            | ...           | ...            | ...           | ...            | ...           |
| $\frac{1}{2}$  | Y              | X              | X             | X              | X              | X              | X             | ...            | ...           | ...            | ...           |
| $\frac{5}{8}$  | Y              | X              | X             | X              | X              | X              | X             | X              | ...           | ...            | ...           |
| $\frac{3}{4}$  | Y              | X              | X             | X              | X              | X              | X             | X              | X             | ...            | ...           |
| $\frac{7}{8}$  | Y              | X              | X             | X              | X              | X              | X             | X              | X             | X              | ...           |
| 1              | Y              | X              | X             | X              | X              | X              | X             | X              | X             | X              | X             |
| $1\frac{1}{4}$ | ...            | X              | X             | X              | X              | X              | X             | X              | X             | X              | X             |
| $1\frac{1}{2}$ | ...            | ...            | X             | X              | X              | X              | X             | X              | X             | X              | X             |
| $1\frac{3}{4}$ | ...            | ..             | ...           | X              | X              | X              | X             | X              | X             | X              | X             |
| 2              | ...            | ...            | ...           | X              | X              | X              | X             | X              | X             | X              | X             |
| $2\frac{1}{4}$ | ...            | ...            | ...           | ...            | X              | X              | X             | X              | X             | X              | X             |
| $2\frac{1}{2}$ | ...            | ...            | ...           | ...            | ...            | X              | X             | X              | X             | X              | X             |
| $2\frac{3}{4}$ | ...            | ...            | ...           | ...            | ...            | X              | X             | X              | X             | X              | X             |
| 3              | ...            | ...            | ...           | ...            | ...            | X              | X             | X              | X             | X              | X             |
| $3\frac{1}{4}$ | ...            | ...            | ...           | ...            | ...            | ...            | X             | X              | X             | X              | X             |
| $3\frac{1}{2}$ | ...            | ...            | ...           | ...            | ...            | ...            | ...           | X              | X             | X              | X             |
| $3\frac{3}{4}$ | ...            | ...            | ...           | ...            | ...            | ...            | ...           | ...            | X             | X              | X             |
| 4              | ...            | ...            | ...           | ...            | ...            | ...            | ...           | ...            | X             | X              | X             |
| $4\frac{1}{4}$ | ...            | ...            | ...           | ...            | ...            | ...            | ...           | ...            | X             | X              | X             |
| $4\frac{1}{2}$ | ...            | ...            | ...           | ...            | ...            | ...            | ...           | ...            | ...           | X              | X             |

## GENERAL NOTE:

Pins made from carbon steel are normally available as indicated above, where X designates all types of pins and Y designates all types except Type G. For other size-length combinations and materials, manufacturers should be consulted.

Table 8.5.3-2 Pilot Length Dimensions for Round-Head Grooved Drive Studs

| Pilot Length, $M$ , for Nominal Size |       |       |       |       |       |       |       |       |       |       |       |       |       |      |      |      |      |      |      |      |  |
|--------------------------------------|-------|-------|-------|-------|-------|-------|-------|-------|-------|-------|-------|-------|-------|------|------|------|------|------|------|------|--|
| 0                                    |       | 2     |       | 4     |       | 6     |       | 7     |       | 8     |       | 10    |       | 12   |      | 14   |      | 16   |      |      |  |
| Nominal Length                       | Max.  | Min.  | Max.  | Min.  | Max.  | Min.  | Max.  | Min.  | Max.  | Min.  | Max.  | Min.  | Max.  | Min. | Max. | Min. | Max. | Min. | Max. | Min. |  |
| $\frac{1}{8}$                        | 0.051 | 0.031 | 0.051 | 0.031 | ...   | ...   | ...   | ...   | ...   | ...   | ...   | ...   | ...   | ...  | ...  | ...  | ...  | ...  | ...  | ...  |  |
| $\frac{3}{16}$                       | 0.067 | 0.047 | 0.067 | 0.047 | ...   | ...   | ...   | ...   | ...   | ...   | ...   | ...   | ...   | ...  | ...  | ...  | ...  | ...  | ...  | ...  |  |
| $\frac{1}{4}$                        | 0.082 | 0.062 | 0.082 | 0.062 | 0.082 | 0.062 | 0.082 | 0.062 | ...   | ...   | ...   | ...   | ...   | ...  | ...  | ...  | ...  | ...  | ...  | ...  |  |
| $\frac{5}{16}$                       | ...   | ...   | ...   | 0.098 | 0.078 | 0.098 | 0.078 | 0.098 | 0.078 | ...   | ...   | ...   | ...   | ...  | ...  | ...  | ...  | ...  | ...  | ...  |  |
| $\frac{3}{8}$                        | ...   | ...   | ...   | 0.114 | 0.094 | 0.114 | 0.094 | 0.114 | 0.094 | 0.114 | 0.094 | 0.114 | 0.094 | ...  | ...  | ...  | ...  | ...  | ...  | ...  |  |
| $\frac{1}{2}$                        | ...   | ...   | ...   | ...   | ...   | ...   | ...   | 0.14  | 0.12  | 0.14  | 0.12  | 0.14  | 0.12  | 0.14 | 0.12 | 0.14 | 0.12 | 0.14 | 0.12 | 0.12 |  |
| $\frac{5}{8}$                        | ...   | ...   | ...   | ...   | ...   | ...   | ...   | ...   | ...   | 0.18  | 0.16  | 0.18  | 0.16  | 0.18 | 0.16 | 0.18 | 0.16 | 0.18 | 0.16 | ...  |  |
| $\frac{3}{4}$                        | ...   | ...   | ...   | ...   | ...   | ...   | ...   | ...   | ...   | ...   | ...   | ...   | 0.20  | 0.18 | 0.20 | 0.18 | 0.20 | 0.18 | ...  | ...  |  |

GENERAL NOTE: To find total pilot length of lengths, *L*, not shown above, use the next shorter length.

**Table 8.5.3-3 Groove Length Dimensions for Grooved T-Head Cotter Pins**

| Nominal Length | Pilot Length, <i>M</i> , for Nominal Size [Note (1)] |      |                |      |               |      |                |      |               |      |               |      |
|----------------|------------------------------------------------------|------|----------------|------|---------------|------|----------------|------|---------------|------|---------------|------|
|                | $\frac{5}{32}$                                       |      | $\frac{3}{16}$ |      | $\frac{1}{4}$ |      | $\frac{5}{16}$ |      | $\frac{3}{8}$ |      | $\frac{1}{2}$ |      |
|                | Max.                                                 | Min. | Max.           | Min. | Max.          | Min. | Max.           | Min. | Max.          | Min. | Max.          | Min. |
| $\frac{3}{4}$  | 0.50                                                 | 0.48 | 0.50           | 0.48 | ...           | ...  | ...            | ...  | ...           | ...  | ...           | ...  |
| $\frac{7}{8}$  | 0.50                                                 | 0.48 | 0.50           | 0.48 | ...           | ...  | ...            | ...  | ...           | ...  | ...           | ...  |
| 1              | 0.62                                                 | 0.60 | 0.62           | 0.60 | 0.62          | 0.60 | ...            | ...  | ...           | ...  | ...           | ...  |
| $1\frac{1}{8}$ | 0.68                                                 | 0.66 | 0.68           | 0.66 | 0.68          | 0.66 | 0.68           | 0.66 | ...           | ...  | ...           | ...  |
| $1\frac{1}{4}$ | ...                                                  | ...  | 0.75           | 0.73 | 0.75          | 0.73 | 0.75           | 0.73 | 0.75          | 0.73 | ...           | ...  |
| $1\frac{1}{2}$ | ...                                                  | ...  | ...            | ...  | 0.88          | 0.86 | 0.88           | 0.86 | 0.88          | 0.86 | ...           | ...  |
| $1\frac{3}{4}$ | ...                                                  | ...  | ...            | ...  | ...           | ...  | 1.00           | 0.98 | 1.00          | 0.98 | ...           | ...  |
| 2              | ...                                                  | ...  | ...            | ...  | ...           | ...  | 1.25           | 1.23 | 1.25          | 1.23 | 1.25          | 1.23 |
| $2\frac{1}{4}$ | ...                                                  | ...  | ...            | ...  | ...           | ...  | ...            | ...  | ...           | ...  | 1.31          | 1.29 |
| $2\frac{1}{2}$ | ...                                                  | ...  | ...            | ...  | ...           | ...  | ...            | ...  | ...           | ...  | 1.50          | 1.48 |
| $2\frac{3}{4}$ | ...                                                  | ...  | ...            | ...  | ...           | ...  | ...            | ...  | ...           | ...  | 1.62          | 1.60 |
| 3              | ...                                                  | ...  | ...            | ...  | ...           | ...  | ...            | ...  | ...           | ...  | 1.85          | 1.83 |

NOTE:

(1) Sizes and lengths for which *M* values are tabulated are normally readily available. For other size-length combinations, manufacturers should be consulted.

**Table 8.7-1 Minimum Performance Requirements of Grooved Pins**

| Nominal Pin Size Diameter | Minimum Double-Shear Load, lb, by Material Type |                               |                           |        |
|---------------------------|-------------------------------------------------|-------------------------------|---------------------------|--------|
|                           | Low Carbon Steel                                | Alloy Steel (Rockwell C40-48) | Corrosion Resistant Steel | Brass  |
| $\frac{1}{32}$            | 100                                             | 180                           | 140                       | 60     |
| $\frac{3}{64}$            | 220                                             | 400                           | 300                       | 140    |
| $\frac{1}{16}$            | 410                                             | 720                           | 540                       | 250    |
| $\frac{5}{64}$            | 620                                             | 1,120                         | 860                       | 390    |
| $\frac{3}{32}$            | 890                                             | 1,600                         | 1,240                     | 560    |
| $\frac{7}{64}$            | 1,220                                           | 2,180                         | 1,680                     | 760    |
| $\frac{1}{8}$             | 1,600                                           | 2,820                         | 2,200                     | 990    |
| $\frac{5}{32}$            | 2,300                                           | 4,520                         | 3,310                     | 1,540  |
| $\frac{3}{16}$            | 3,310                                           | 6,440                         | 4,760                     | 2,220  |
| $\frac{7}{32}$            | 4,510                                           | 8,770                         | 6,480                     | 3,020  |
| $\frac{1}{4}$             | 5,880                                           | 11,500                        | 8,460                     | 3,950  |
| $\frac{5}{16}$            | 7,660                                           | 17,900                        | 12,700                    | 6,170  |
| $\frac{3}{8}$             | 11,000                                          | 26,000                        | 18,200                    | 9,050  |
| $\frac{7}{16}$            | 15,000                                          | 35,200                        | 24,800                    | 12,100 |
| $\frac{1}{2}$             | 19,600                                          | 46,000                        | 32,400                    | 15,800 |

**Table 8.8-1 Recommended Hole Sizes for Unplated Grooved Pins**

| Recommended Hole Sizes for Unplated Grooved Pins |                |               |        |
|--------------------------------------------------|----------------|---------------|--------|
| Nominal Pin Size                                 | Drill Size     | Hole Diameter |        |
|                                                  |                | Max.          | Min.   |
| $\frac{1}{32}$                                   | $\frac{1}{32}$ | 0.0324        | 0.0312 |
| $\frac{3}{64}$                                   | $\frac{3}{64}$ | 0.0482        | 0.0469 |
| $\frac{1}{16}$                                   | $\frac{1}{16}$ | 0.0640        | 0.0625 |
| $\frac{5}{64}$                                   | $\frac{5}{64}$ | 0.0798        | 0.0781 |
| $\frac{3}{32}$                                   | $\frac{3}{32}$ | 0.0956        | 0.0938 |
| $\frac{7}{64}$                                   | $\frac{7}{64}$ | 0.1113        | 0.1094 |
| $\frac{1}{8}$                                    | $\frac{1}{8}$  | 0.1271        | 0.1250 |
| $\frac{5}{32}$                                   | $\frac{5}{32}$ | 0.1587        | 0.1563 |
| $\frac{3}{16}$                                   | $\frac{3}{16}$ | 0.1903        | 0.1875 |
| $\frac{7}{32}$                                   | $\frac{7}{32}$ | 0.2219        | 0.2188 |
| $\frac{1}{4}$                                    | $\frac{1}{4}$  | 0.2534        | 0.2500 |
| $\frac{5}{16}$                                   | $\frac{5}{16}$ | 0.3166        | 0.3125 |
| $\frac{3}{8}$                                    | $\frac{3}{8}$  | 0.3797        | 0.3750 |
| $\frac{7}{16}$                                   | $\frac{7}{16}$ | 0.4428        | 0.4375 |
| $\frac{1}{2}$                                    | $\frac{1}{2}$  | 0.5060        | 0.5000 |

**Table 8.8-2 Recommended Hole Sizes for Unplated Grooved Drive Studs**

| Recommended Hole Sizes for Unplated Grooved Pins |            |               |        |
|--------------------------------------------------|------------|---------------|--------|
| Nominal Pin Size                                 | Drill Size | Hole Diameter |        |
|                                                  |            | Max.          | Min.   |
| 0                                                | 51         | 0.0686        | 0.0670 |
| 2                                                | 44         | 0.0877        | 0.0860 |
| 4                                                | 37         | 0.1059        | 0.1040 |
| 6                                                | 31         | 0.1220        | 0.1200 |
| 7                                                | 29         | 0.1382        | 0.1360 |
| 8                                                | 27         | 0.1463        | 0.1440 |
| 10                                               | 20         | 0.1636        | 0.1610 |
| 12                                               | 9          | 0.1990        | 0.1960 |
| 14                                               | 2          | 0.2240        | 0.2210 |
| 16                                               | 1/4        | 0.2534        | 0.2500 |

### 8.11 Designation

**8.11.1** Grooved pins, drive studs, and T-head cotter pins shall be designated by the following data, in the sequence shown: product name (noun first), including type designation for pins; nominal size (number, fraction or decimal equivalent); length (fraction or decimal equivalent); material, including specification or heat treatment where necessary; protective finish, if required. See examples below.

EXAMPLES:

- (1) Pin, Type A Grooved,  $\frac{3}{32} \times \frac{3}{4}$ , Steel, Zinc Plated
- (2) Pin, Type F Grooved, 0.250  $\times$  1.500, Corrosion Resistant Steel
- (3) Drive Stud, Round Head Grooved, No. 10  $\times$   $\frac{1}{2}$ , Steel, Zinc Plated
- (4) Pin, Grooved T-Head Cotter,  $\frac{1}{4} \times 1\frac{1}{4}$ , Steel, Zinc Plated

## 9 GENERAL DATA FOR SPRING PINS

### 9.1 Diameter

**9.1.1 Slotted Type.** Due to the manufacturing process, the outer periphery of slotted-type spring pins in the free-state deviates somewhat from true round. Therefore, conformance with the specified maximum diameter limits shall be checked with GO ring gages. The length of the hole in the ring gage shall be 0.125 in. The minimum diameter shall be determined by averaging three measurements taken at successive 45 deg intervals away from the center of slot. These measurements shall be made at approximately the center of pins 1 in. or shorter nominal length, and at a distance of 0.25 in. from the end of pins having longer nominal lengths.

**9.1.2 Coiled Type.** Due to the manufacturing process, the outer periphery of coiled-type spring pins somewhat deviates from true round. Suppliers may use measurement techniques for minimum and maximum diameter

inspection as they deem appropriate. However, for diameter arbitration between the supplier and purchaser, the specified minimum and maximum diameter limits shall be determined with GO and NO GO plain ring gages, respectively. The length of the hole in the ring gage shall be 0.125 in.

### 9.2 Slots

The dimension and end configuration of the circumference of slotted-type pins shall be such that pins, in the free state, will not interlock and that sides of the slot will not touch on  $\frac{9}{64}$  in. (0.141 in.) and larger sizes when the pin is inserted into a minimum hole size within a tolerance of  $\pm 0.0003$  in. All sizes smaller than  $\frac{9}{64}$  in. (0.141 in.) shall assemble satisfactorily into the minimum hole and the sides of the slot may touch. The edges of the slot intersecting the pin diameter shall be broken or rounded.

### 9.3 Ends

Both ends of all spring pins shall be chamfered as depicted in the figures and specified in the dimensional tables. The contour of the chamfer shall be optional.

### 9.4 Length

**9.4.1 Measurement.** The length of spring pins shall be measured overall from end to end, parallel to the pin axis.

**9.4.2 Tolerance on Length.** The tolerance on the length of spring pins shall be as tabulated in Table 9.4.2-1 for the respective types.

**9.4.3 Practical Lengths.** The diameter-length combinations in which spring pins are normally readily available are depicted in Table 9.4.3-1. Manufacturers should be consulted concerning the availability of other size-length combinations in the various types, series, and materials.

**9.4.4 Straightness.** The straightness over the length of spring pins shall be such that pins will pass freely through a ring gage of length as tabulated at the end of this subparagraph for the respective pin lengths. The maximum diameter of the gaging hole shall be equivalent to the maximum pin free diameter for the respective pin types and series, given in Tables 9.4.4-1 and 9.4.4-2, plus the straightness diameter allowance tabulated in the following:

| Nominal Pin Length     | Gauge Length ( $\pm 0.005$ ) | Straightness Diameter Allowance |
|------------------------|------------------------------|---------------------------------|
| Up to 1 in., Incl.     | 1.000                        | 0.007                           |
| Over 1 to 2 in., Incl. | 2.000                        | 0.010                           |
| Over 2 in.             | 3.000                        | 0.013                           |

**Table 9.4.2-1 Tolerance on Length of Spring Pins**

| Nominal<br>Pin Size             | Tolerance on Nominal Pin length |                       |                          |                          |        |
|---------------------------------|---------------------------------|-----------------------|--------------------------|--------------------------|--------|
|                                 | Up to 1,<br>incl.               | Over 1<br>to 2, incl. | Over 2<br>to 3,<br>incl. | Over 3<br>to 4,<br>incl. | Over 4 |
| <b>Slotted-Type Spring</b>      |                                 |                       |                          |                          |        |
| $\frac{1}{16}$ to $\frac{3}{4}$ | ±0.015                          | ±0.020                | ±0.025                   | ±0.030                   | ±0.035 |
| <b>Coiled-Type Spring</b>       |                                 |                       |                          |                          |        |
| $\frac{1}{32}$ to $\frac{3}{8}$ | ±0.010                          | ±0.010                | ±0.015                   | ±0.025                   | ±0.025 |
| $\frac{7}{16}$ to $\frac{3}{4}$ | ±0.025                          | ±0.025                | ±0.025                   | ±0.025                   | ±0.025 |

## 9.5 Materials

Spring pins are normally made from SAE 1070 through SAE 1095 carbon steel, SAE 6150H alloy steel, SAE 51410 through SAE 51420 and SAE 30302 and SAE 30304 corrosion resistant steels, and beryllium copper alloy as designated in the respective dimensional tables; heat treated or cold worked to attain the hardness and performance requirements set forth in this Standard. Where required for specific applications, pins may also be made from other materials having chemical and mechanical properties as agreed upon between the manufacturer and purchaser.

## 9.6 Hardness

The hardness of the various spring pin types and materials shall conform to the requirements tabulated in Table 9.6-1.

It is recommended that the Rockwell hardness tests designated for the respective sizes be used in conducting hardness checks. For slotted-type spring pins the hardness readings shall be taken near the midpoint of a longitudinal flat ground on the pin at 180 deg to the slot. For coiled-type spring pins, the pin shall be ground or cut in half along the longitudinal axis and the hardness readings taken on the inside surface of the outer half coil. The Vickers hardness test specimen must be properly mounted to avoid false readings due to pin flexibility.

## 9.7 Performance Requirements

Spring pins shall be capable of withstanding the minimum double-shear loads specified in the dimensional table (Tables 9.4.4-1 and 9.4.4-2) for the respective pin types, series, sizes, and materials, when tested in accor-

dance with the double-shear testing of pins specified in Nonmandatory Appendix B. While the pins must be capable of passing this test, the test itself is not required on a lot-by-lot basis. The holes in the fixtures for testing spring pins shall conform to the nominal size (tolerance H8) of the pin to be tested. Slotted-type spring pins shall be positioned such that the slot is approximately perpendicular to the plane of application of the shear load.

Spring pins that have been sheared at loads exceeding the minimums specified shall exhibit a ductile fracture at the shear point with no longitudinal cracks.

## 9.8 Corrosion Protection

Unless otherwise specified, spring pins shall be furnished with a natural (as processed) finish, unplated or uncoated. Other finishes, where required, shall be subject to agreement between the manufacturer and purchaser.

**9.8.1 Relief From Hydrogen Embrittlement.** Where a corrosion preventative finish applied to spring pins is such that it might produce hydrogen embrittlement, the pins shall be baked for a suitable time at a temperature that will obviate such embrittlement. Baking shall be accomplished as soon as possible following the plating or coating operation inasmuch as delay is detrimental to achieving the desired result.

## 9.9 Workmanship

Spring pins shall be free from burrs, loose scale, seams, notches, sharp edges and corners, and any other defects affecting their serviceability.

## 9.10 Designation

Spring pins shall be designated by the following data, in the sequence shown: product name (noun first); nominal size (fraction or decimal equivalent); nominal length (fraction or decimal equivalent); series, for coiled-type spring pins; material, including specification where necessary; protective finish, if required. See examples below.

EXAMPLES:

- (1) Pin, Coiled Spring,  $\frac{1}{4} \times 1\frac{1}{4}$ , Standard Duty, Steel, Zinc Plated
- (2) Pin, Slotted Spring,  $0.375 \times 1.875$ , SAE 51420 Corrosion Resistant Steel
- (3) Pin, Slotted Spring,  $\frac{1}{2} \times 3$ , Steel, Phosphate Coated

Table 9.4.3-1 Practical Sizes and Lengths of Coiled- and Slotted-Type Spring Pins


| Nominal Length | Nominal Size |       |      |       |      |      |      |      |     |      |      |      |      |     |      |     |      |     |     |     |
|----------------|--------------|-------|------|-------|------|------|------|------|-----|------|------|------|------|-----|------|-----|------|-----|-----|-----|
|                | 1/32         | 0.039 | 3/64 | 0.052 | 1/16 | 5/64 | 3/32 | 7/64 | 1/8 | 9/64 | 5/32 | 3/16 | 7/32 | 1/4 | 5/16 | 3/8 | 7/16 | 1/2 | 5/8 | 3/4 |
| 1/8            | Y            | Y     | Y    | X     | ...  | ...  | ...  | ...  | ... | ...  | ...  | ...  | ...  | ... | ...  | ... | ...  | ... | ... | ... |
| 3/16           | Y            | Y     | Y    | X     | X    | X    | X    | ...  | ... | ...  | ...  | ...  | ...  | ... | ...  | ... | ...  | ... | ... | ... |
| 1/4            | Y            | Y     | Y    | X     | X    | X    | X    | X    | ... | ...  | ...  | ...  | ...  | ... | ...  | ... | ...  | ... | ... | ... |
| 5/16           | Y            | Y     | Y    | X     | X    | X    | X    | X    | X   | ...  | ...  | ...  | ...  | ... | ...  | ... | ...  | ... | ... | ... |
| 3/8            | Y            | Y     | Y    | X     | X    | X    | X    | X    | X   | X    | ...  | ...  | ...  | ... | ...  | ... | ...  | ... | ... | ... |
| 7/16           | Y            | Y     | Y    | X     | X    | X    | X    | X    | X   | X    | X    | ...  | ...  | ... | ...  | ... | ...  | ... | ... | ... |
| 1/2            | Y            | Y     | Y    | X     | X    | X    | X    | X    | X   | X    | X    | X    | X    | X   | ...  | ... | ...  | ... | ... | ... |
| 9/16           | Y            | Y     | Y    | X     | X    | X    | X    | X    | X   | X    | X    | X    | X    | X   | ...  | ... | ...  | ... | ... | ... |
| 5/8            | Y            | Y     | Y    | X     | X    | X    | X    | X    | X   | X    | X    | X    | X    | X   | ...  | ... | ...  | ... | ... | ... |
| 11/16          | ...          | ...   | ...  | ...   | X    | X    | X    | X    | X   | X    | X    | X    | X    | X   | ...  | ... | ...  | ... | ... | ... |
| 3/4            | ...          | ...   | ...  | ...   | X    | X    | X    | X    | X   | X    | X    | X    | X    | X   | X    | X   | ...  | ... | ... | ... |
| 13/16          | ...          | ...   | ...  | ...   | X    | X    | X    | X    | X   | X    | X    | X    | X    | X   | X    | X   | ...  | ... | ... | ... |
| 7/8            | ...          | ...   | ...  | ...   | X    | X    | X    | X    | X   | X    | X    | X    | X    | X   | X    | X   | X    | ... | ... | ... |
| 15/16          | ...          | ...   | ...  | ...   | X    | X    | X    | X    | X   | X    | X    | X    | X    | X   | X    | X   | ...  | ... | ... | ... |
| 1              | ...          | ...   | ...  | ...   | X    | X    | X    | X    | X   | X    | X    | X    | X    | X   | X    | X   | X    | X   | ... | ... |
| 1 1/8          | ...          | ...   | ...  | ...   | ...  | X    | X    | X    | X   | X    | X    | X    | X    | X   | X    | X   | ...  | ... | ... | ... |
| 1 1/4          | ...          | ...   | ...  | ...   | ...  | X    | X    | X    | X   | X    | X    | X    | X    | X   | X    | X   | X    | X   | X   | ... |
| 1 3/8          | ...          | ...   | ...  | ...   | ...  | X    | X    | X    | X   | X    | X    | X    | X    | X   | X    | ... | ...  | ... | ... | ... |
| 1 1/2          | ...          | ...   | ...  | ...   | ...  | X    | X    | X    | X   | X    | X    | X    | X    | X   | X    | X   | X    | X   | X   | ... |
| 1 5/8          | ...          | ...   | ...  | ...   | ...  | ...  | ...  | X    | X   | X    | X    | X    | X    | X   | X    | X   | ...  | ... | ... | ... |
| 1 3/4          | ...          | ...   | ...  | ...   | ...  | ...  | ...  | X    | X   | X    | X    | X    | X    | X   | X    | X   | X    | X   | X   | ... |
| 1 7/8          | ...          | ...   | ...  | ...   | ...  | ...  | ...  | ...  | X   | X    | X    | X    | X    | X   | X    | ... | ...  | ... | ... | ... |
| 2              | ...          | ...   | ...  | ...   | ...  | ...  | ...  | ...  | X   | X    | X    | X    | X    | X   | X    | X   | X    | X   | X   | X   |
| 2 1/4          | ...          | ...   | ...  | ...   | ...  | ...  | ...  | ...  | ... | ...  | X    | X    | X    | X   | X    | X   | X    | X   | X   | X   |
| 2 1/2          | ...          | ...   | ...  | ...   | ...  | ...  | ...  | ...  | ... | ...  | X    | X    | X    | X   | X    | X   | X    | X   | X   | X   |
| 2 3/4          | ...          | ...   | ...  | ...   | ...  | ...  | ...  | ...  | ... | ...  | ...  | ...  | X    | X   | X    | X   | X    | X   | X   | X   |
| 3              | ...          | ...   | ...  | ...   | ...  | ...  | ...  | ...  | ... | ...  | ...  | ...  | X    | X   | X    | X   | X    | X   | X   | X   |
| 3 1/4          | ...          | ...   | ...  | ...   | ...  | ...  | ...  | ...  | ... | ...  | ...  | ...  | ...  | X   | X    | X   | X    | X   | X   | X   |
| 3 1/2          | ...          | ...   | ...  | ...   | ...  | ...  | ...  | ...  | ... | ...  | ...  | ...  | ...  | X   | X    | X   | X    | X   | X   | X   |
| 3 3/4          | ...          | ...   | ...  | ...   | ...  | ...  | ...  | ...  | ... | ...  | ...  | ...  | ...  | ... | X    | X   | X    | X   | X   | X   |
| 4              | ...          | ...   | ...  | ...   | ...  | ...  | ...  | ...  | ... | ...  | ...  | ...  | ...  | ... | X    | X   | X    | X   | X   | X   |
| 4 1/4          | ...          | ...   | ...  | ...   | ...  | ...  | ...  | ...  | ... | ...  | ...  | ...  | ...  | ... | ...  | ... | ...  | ... | X   | X   |
| 4 1/2          | ...          | ...   | ...  | ...   | ...  | ...  | ...  | ...  | ... | ...  | ...  | ...  | ...  | ... | ...  | ... | ...  | ... | X   | X   |
| 4 3/4          | ...          | ...   | ...  | ...   | ...  | ...  | ...  | ...  | ... | ...  | ...  | ...  | ...  | ... | ...  | ... | ...  | ... | X   | X   |
| 5              | ...          | ...   | ...  | ...   | ...  | ...  | ...  | ...  | ... | ...  | ...  | ...  | ...  | ... | ...  | ... | ...  | ... | X   | X   |
| 5 1/4          | ...          | ...   | ...  | ...   | ...  | ...  | ...  | ...  | ... | ...  | ...  | ...  | ...  | ... | ...  | ... | ...  | ... | X   | X   |
| 5 1/2          | ...          | ...   | ...  | ...   | ...  | ...  | ...  | ...  | ... | ...  | ...  | ...  | ...  | ... | ...  | ... | ...  | ... | X   | X   |
| 5 3/4          | ...          | ...   | ...  | ...   | ...  | ...  | ...  | ...  | ... | ...  | ...  | ...  | ...  | ... | ...  | ... | ...  | ... | X   | X   |
| 6              | ...          | ...   | ...  | ...   | ...  | ...  | ...  | ...  | ... | ...  | ...  | ...  | ...  | ... | ...  | ... | ...  | ... | X   | X   |

## GENERAL NOTES:

- (a) X indicates availability of both coiled- and slotted-type spring pins.  
 (b) Y indicates availability of standard duty coiled pins only.  
 (c) Suppliers should be consulted regarding availability of other sizes, lengths, or materials.



Table 9.4.4-1 Dimensions of Slotted-Type Spring Pins

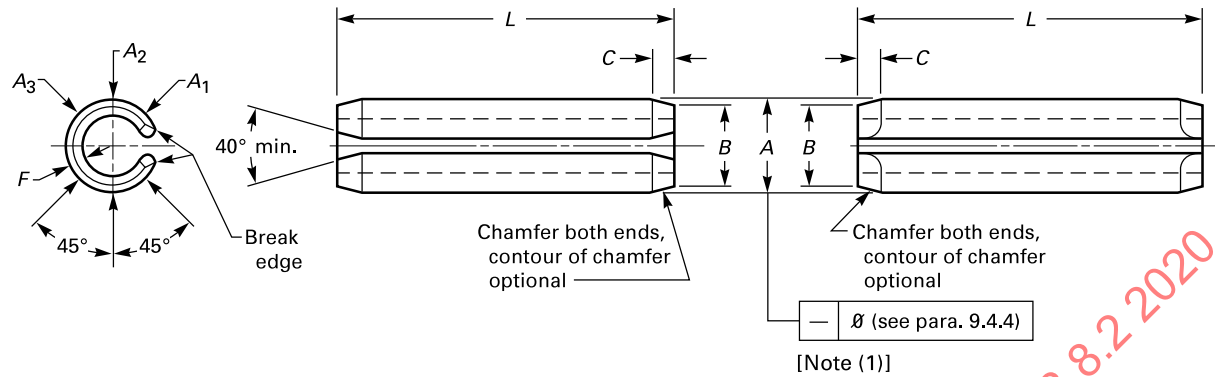


| Nominal Size or Basic Pin Diameter<br>[Note (2)] | Pin Diameter, A |                 | Maximum Chamfer Diameter, B | Chamfer Length, C |       | Basic Stock Thickness, F | Recommended Hole Size |       | Minimum Double-Shear Load, lb, for Material Type |                     |                  |        |
|--------------------------------------------------|-----------------|-----------------|-----------------------------|-------------------|-------|--------------------------|-----------------------|-------|--------------------------------------------------|---------------------|------------------|--------|
|                                                  | Max. [Note (3)] | Min. [Note (4)] |                             | Max.              | Min.  |                          | Max.                  | Min.  | SAE 1070-1095 and SAE 51420 [Note (5)]           | SAE 30302 and 30304 | Beryllium Copper |        |
| $\frac{1}{16}$                                   | 0.062           | 0.069           | 0.066                       | 0.059             | 0.028 | 0.007                    | 0.012                 | 0.065 | 0.062                                            | 430                 | 250              | 270    |
| $\frac{5}{64}$                                   | 0.078           | 0.086           | 0.083                       | 0.075             | 0.032 | 0.008                    | 0.018                 | 0.081 | 0.078                                            | 800                 | 460              | 500    |
| $\frac{3}{32}$                                   | 0.094           | 0.103           | 0.099                       | 0.091             | 0.038 | 0.008                    | 0.022                 | 0.097 | 0.094                                            | 1,150               | 670              | 710    |
| $\frac{1}{8}$                                    | 0.125           | 0.135           | 0.131                       | 0.122             | 0.044 | 0.008                    | 0.028                 | 0.129 | 0.125                                            | 1,875               | 1,090            | 1,170  |
| $\frac{9}{64}$                                   | 0.141           | 0.149           | 0.145                       | 0.137             | 0.044 | 0.008                    | 0.028                 | 0.144 | 0.140                                            | 2,175               | 1,260            | 1,350  |
| $\frac{5}{32}$                                   | 0.156           | 0.167           | 0.162                       | 0.151             | 0.048 | 0.010                    | 0.032                 | 0.160 | 0.156                                            | 2,750               | 1,600            | 1,725  |
| $\frac{3}{16}$                                   | 0.188           | 0.199           | 0.194                       | 0.182             | 0.055 | 0.011                    | 0.040                 | 0.192 | 0.187                                            | 4,150               | 2,425            | 2,600  |
| $\frac{7}{32}$                                   | 0.219           | 0.232           | 0.226                       | 0.214             | 0.065 | 0.011                    | 0.048                 | 0.224 | 0.219                                            | 5,850               | 3,400            | 3,650  |
| $\frac{1}{4}$                                    | 0.250           | 0.264           | 0.258                       | 0.245             | 0.065 | 0.012                    | 0.048                 | 0.256 | 0.250                                            | 7,050               | 4,100            | 4,400  |
| $\frac{5}{16}$                                   | 0.312           | 0.330           | 0.321                       | 0.306             | 0.080 | 0.014                    | 0.062                 | 0.318 | 0.312                                            | 10,800              | 6,300            | 6,750  |
| $\frac{3}{8}$                                    | 0.375           | 0.395           | 0.385                       | 0.368             | 0.095 | 0.016                    | 0.077                 | 0.382 | 0.375                                            | 16,300              | 9,500            | 10,200 |
| $\frac{7}{16}$                                   | 0.438           | 0.459           | 0.448                       | 0.430             | 0.095 | 0.017                    | 0.077                 | 0.445 | 0.437                                            | 19,800              | 11,500           | 12,300 |
| $\frac{1}{2}$                                    | 0.500           | 0.524           | 0.513                       | 0.485             | 0.110 | 0.025                    | 0.094                 | 0.510 | 0.500                                            | 27,100              | 15,800           | 17,000 |
| $\frac{5}{8}$                                    | 0.625           | 0.653           | 0.640                       | 0.608             | 0.125 | 0.030                    | 0.125                 | 0.636 | 0.625                                            | 46,000              | 18,800           | ...    |
| $\frac{3}{4}$                                    | 0.750           | 0.784           | 0.769                       | 0.730             | 0.150 | 0.030                    | 0.150                 | 0.764 | 0.750                                            | 66,000              | 23,200           | ...    |

## NOTES:

- (1) — = straightness;  $\varnothing$  = diameter
- (2) Where specifying nominal size in decimals, zeros preceding the decimal shall be omitted.
- (3) Maximum diameter shall be checked by GO ring gage.
- (4) Minimum diameter shall be average of three diameters measured at points illustrated A min. =  $(A_1 + A_2 + A_3)/3$ .
- (5) Sizes  $\frac{5}{8}$  in. (0.625 mm) and larger are produced from SAE 6150H alloy steel, not SAE 1070-1095.

Technical drawing of a shaft with a break. The drawing shows a cross-section of the shaft with a break indicated by a jagged line. The dimension  $A$  is shown as the distance from the centerline to the break edge. The break edge is labeled "Break edge".

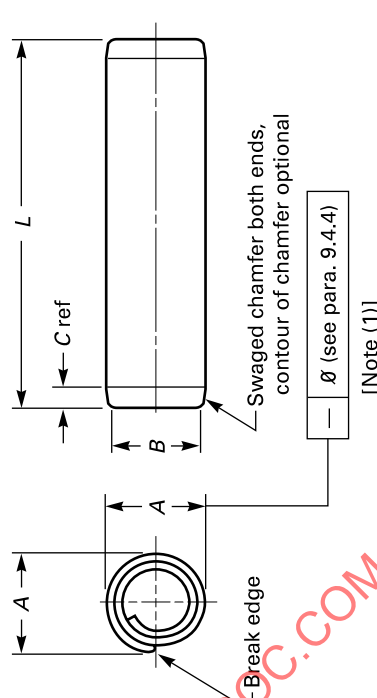

Technical drawing showing a circular feature (likely a hole or a flange) with a break edge. The dimension  $A$  is indicated for the width of the feature. The text "Break edge" points to the break line.