

# INTERNATIONAL STANDARD



**Specifications for particular types of winding wires –  
Part 0-9: General requirements – Enamelled rectangular aluminium wire**

IECNORM.COM : Click to view the full PDF of IEC 60317-0-9:2015+AMD1:2024 CSV





**THIS PUBLICATION IS COPYRIGHT PROTECTED**  
**Copyright © 2024 IEC, Geneva, Switzerland**

All rights reserved. Unless otherwise specified, no part of this publication may be reproduced or utilized in any form or by any means, electronic or mechanical, including photocopying and microfilm, without permission in writing from either IEC or IEC's member National Committee in the country of the requester. If you have any questions about IEC copyright or have an enquiry about obtaining additional rights to this publication, please contact the address below or your local IEC member National Committee for further information.

IEC Secretariat  
3, rue de Varembe  
CH-1211 Geneva 20  
Switzerland

Tel.: +41 22 919 02 11  
[info@iec.ch](mailto:info@iec.ch)  
[www.iec.ch](http://www.iec.ch)

**About the IEC**

The International Electrotechnical Commission (IEC) is the leading global organization that prepares and publishes International Standards for all electrical, electronic and related technologies.

**About IEC publications**

The technical content of IEC publications is kept under constant review by the IEC. Please make sure that you have the latest edition, a corrigendum or an amendment might have been published.

**IEC publications search - [webstore.iec.ch/advsearchform](http://webstore.iec.ch/advsearchform)**

The advanced search enables to find IEC publications by a variety of criteria (reference number, text, technical committee, ...). It also gives information on projects, replaced and withdrawn publications.

**IEC Just Published - [webstore.iec.ch/justpublished](http://webstore.iec.ch/justpublished)**

Stay up to date on all new IEC publications. Just Published details all new publications released. Available online and once a month by email.

**IEC Customer Service Centre - [webstore.iec.ch/csc](http://webstore.iec.ch/csc)**

If you wish to give us your feedback on this publication or need further assistance, please contact the Customer Service Centre: [sales@iec.ch](mailto:sales@iec.ch).

**IEC Products & Services Portal - [products.iec.ch](http://products.iec.ch)**

Discover our powerful search engine and read freely all the publications previews, graphical symbols and the glossary. With a subscription you will always have access to up to date content tailored to your needs.

**Electropedia - [www.electropedia.org](http://www.electropedia.org)**

The world's leading online dictionary on electrotechnology, containing more than 22 500 terminological entries in English and French, with equivalent terms in 25 additional languages. Also known as the International Electrotechnical Vocabulary (IEV) online.

IECNORM.COM : Click to view the full PDF of IEC 60710-15-AMD1:2024 CSV



IEC 60317-0-9

Edition 1.1 2024-06  
CONSOLIDATED VERSION

# INTERNATIONAL STANDARD



Specifications for particular types of winding wires –  
Part 0-9: General requirements – Enamelled rectangular aluminium wire

INTERNATIONAL  
ELECTROTECHNICAL  
COMMISSION

ICS 29.060.10

ISBN 978-2-8322-9187-0

**Warning! Make sure that you obtained this publication from an authorized distributor.**

## CONTENTS

FOREWORD.....	4
INTRODUCTION.....	6
1 Scope.....	7
2 Normative references .....	7
3 Terms, definitions, general notes and appearance.....	7
3.1 Terms and definitions.....	7
3.2 General notes .....	8
3.2.1 Methods of test.....	8
3.2.2 Winding wire.....	8
3.3 Appearance .....	8
4 Dimensions.....	8
4.1 Conductor dimensions .....	8
4.2 Tolerance on conductor dimensions.....	9
4.3 Rounding of corners.....	9
4.4 Increase in dimensions due to the insulation.....	11
4.5 Overall dimensions .....	11
4.5.1 Nominal overall dimensions .....	11
4.5.2 Minimum overall dimensions.....	11
4.5.3 Maximum overall dimensions .....	11
5 Electrical resistance .....	11
6 Elongation .....	12
7 Springiness .....	12
8 Flexibility and adherence.....	12
8.1 Mandrel winding test.....	12
8.2 Adherence test.....	12
9 Heat shock .....	12
10 Cut-through .....	12
11 Resistance to abrasion.....	13
12 Resistance to solvents.....	13
13 Breakdown voltage .....	13
14 Continuity of insulation .....	13
15 Temperature index .....	13
16 Resistance to refrigerants.....	13
17 Solderability .....	14
18 Heat or solvent bonding.....	14
19 Dielectric dissipation factor.....	14
20 Resistance to transformer oil .....	14
21 Loss of mass .....	14
23 Pin hole test .....	14
30 Packaging .....	14
Annex A (informative) Nominal cross-sectional areas for preferred and intermediate sizes.....	15
Annex B (informative) Special tolerances.....	24
Bibliography.....	25

Table 1– Conductor tolerances .....	9
Table 2 – Nominal cross-sectional areas of preferred sizes.....	10
Table 3 – Corner radii .....	11
Table 4 – Increases in dimensions .....	11
Table 5 – Mandrel winding .....	12
Table 6 – Breakdown voltage.....	13
Table A.1 – Nominal cross-sectional areas (1 of 9) .....	15
Table B.1 – Overall dimensional tolerances for grade 2 .....	24

IECNORM.COM : Click to view the full PDF of IEC 60317-0-9:2015+AMD1:2024 CSV

## INTERNATIONAL ELECTROTECHNICAL COMMISSION

**SPECIFICATIONS FOR PARTICULAR TYPES OF WINDING WIRES –****Part 0-9: General requirements – Enamelled rectangular aluminium wire**

## FOREWORD

- 1) The International Electrotechnical Commission (IEC) is a worldwide organization for standardization comprising all national electrotechnical committees (IEC National Committees). The object of IEC is to promote international co-operation on all questions concerning standardization in the electrical and electronic fields. To this end and in addition to other activities, IEC publishes International Standards, Technical Specifications, Technical Reports, Publicly Available Specifications (PAS) and Guides (hereafter referred to as "IEC Publication(s)"). Their preparation is entrusted to technical committees; any IEC National Committee interested in the subject dealt with may participate in this preparatory work. International, governmental and non-governmental organizations liaising with the IEC also participate in this preparation. IEC collaborates closely with the International Organization for Standardization (ISO) in accordance with conditions determined by agreement between the two organizations.
- 2) The formal decisions or agreements of IEC on technical matters express, as nearly as possible, an international consensus of opinion on the relevant subjects since each technical committee has representation from all interested IEC National Committees.
- 3) IEC Publications have the form of recommendations for international use and are accepted by IEC National Committees in that sense. While all reasonable efforts are made to ensure that the technical content of IEC Publications is accurate, IEC cannot be held responsible for the way in which they are used or for any misinterpretation by any end user.
- 4) In order to promote international uniformity, IEC National Committees undertake to apply IEC Publications transparently to the maximum extent possible in their national and regional publications. Any divergence between any IEC Publication and the corresponding national or regional publication shall be clearly indicated in the latter.
- 5) IEC itself does not provide any attestation of conformity. Independent certification bodies provide conformity assessment services and, in some areas, access to IEC marks of conformity. IEC is not responsible for any services carried out by independent certification bodies.
- 6) All users should ensure that they have the latest edition of this publication.
- 7) No liability shall attach to IEC or its directors, employees, servants or agents including individual experts and members of its technical committees and IEC National Committees for any personal injury, property damage or other damage of any nature whatsoever, whether direct or indirect, or for costs (including legal fees) and expenses arising out of the publication, use of, or reliance upon, this IEC Publication or any other IEC Publications.
- 8) Attention is drawn to the Normative references cited in this publication. Use of the referenced publications is indispensable for the correct application of this publication.
- 9) IEC draws attention to the possibility that the implementation of this document may involve the use of (a) patent(s). IEC takes no position concerning the evidence, validity or applicability of any claimed patent rights in respect thereof. As of the date of publication of this document, IEC had not received notice of (a) patent(s), which may be required to implement this document. However, implementers are cautioned that this may not represent the latest information, which may be obtained from the patent database available at <https://patents.iec.ch>. IEC shall not be held responsible for identifying any or all such patent rights.

**This consolidated version of the official IEC Standard and its amendment has been prepared for user convenience.**

**IEC 60317-0-9 edition 1.1 contains the first edition (2015-05) [documents 55/1519/FDIS and 55/1525/RVD] and its amendment 1 (2024-06) [documents 55/1978/CDV and 55/2014/RVC].**

**In this Redline version, a vertical line in the margin shows where the technical content is modified by amendment 1. Additions are in green text, deletions are in strikethrough red text. A separate Final version with all changes accepted is available in this publication.**

International Standard IEC 60317-0-9 has been prepared by IEC technical committee 55: Winding wires.

This publication has been drafted in accordance with the ISO/IEC Directives, Part 2.

The numbering of clauses in this standard is not continuous from Clauses 21 through 30 in order to reserve space for possible future wire requirements prior to those for wire packaging.

A list of all parts in the IEC 60317 series, published under the general title *Specifications for particular types of winding wires*, can be found on the IEC website.

The committee has decided that the contents of this document and its amendment will remain unchanged until the stability date indicated on the IEC website under [webstore.iec.ch](http://webstore.iec.ch) in the data related to the specific document. At this date, the document will be

- reconfirmed,
- withdrawn, or
- revised.

**IMPORTANT – The 'colour inside' logo on the cover page of this publication indicates that it contains colours which are considered to be useful for the correct understanding of its contents. Users should therefore print this document using a colour printer.**

IECNORM.COM : Click to view the full PDF of IEC 60317-0-9:2015+AMD1:2024 CSV

## INTRODUCTION

This part of IEC 60317 is one of a series which deals with insulated wires used for windings in electrical equipment. The series has three groups describing:

- 1) Winding wires – Test methods (IEC 60851 series);
- 2) Specifications for particular types of winding wires (IEC 60317 series);
- 3) Packaging of winding wires (IEC 60264 series).

IECNORM.COM : Click to view the full PDF of IEC 60317-0-9:2015+AMD1:2024 CSV

## SPECIFICATIONS FOR PARTICULAR TYPES OF WINDING WIRES –

### Part 0-9: General requirements – Enamelled rectangular aluminium wire

#### 1 Scope

This part of IEC 60317 specifies the general requirements of enamelled rectangular aluminium winding wires.

The range of nominal conductor dimensions is given in the relevant specification sheet.

When reference is made to a winding wire according to a standard of the IEC 60317 series mentioned under Clause 2, the following information is given in the description:

- reference to IEC specification;
- nominal conductor dimensions in millimetres (width × thickness);
- grade.

EXAMPLE IEC 60317-16 – 4,00 x 1,00 Grade 1

#### 2 Normative references

The following documents, in whole or in part, are normatively referenced in this document and are indispensable for its application. For dated references, only the edition cited applies. For undated references, the latest edition of the referenced document (including any amendments) applies.

IEC 60172<sup>1</sup>, *Test procedure for the determination of the temperature index of enamelled and tape wrapped winding wires*

IEC 60317-0-1, *Specifications for particular types of winding wires – Part 0-1: General requirements – Enamelled round copper wire*

IEC 60851 (all parts), *Winding wires – Test methods*

ISO 3, *Preferred numbers – Series of preferred numbers*

EN 1715-2, *Aluminium and aluminium alloys – Drawing stock – Part 2: Specific requirements for electrical applications*

ASTM B233-97, *Standard Specification for Aluminum 1350 Drawing Stock for Electrical Purposes*

#### 3 Terms, definitions, general notes and appearance

##### 3.1 Terms and definitions

For the purposes of this document, the terms and definitions given in IEC 60317-0-1 apply.

<sup>1</sup> Fourth edition to be published.

## 3.2 General notes

### 3.2.1 Methods of test

All methods of test to be used for this standard are given in IEC 60851.

The clause numbers used in this standard are identical to the corresponding test numbers in the IEC 60851 series of standards.

In case of inconsistencies between the publication on methods of test and this standard, IEC 60317-0-9 shall prevail.

Where no specific range of nominal conductor dimensions is given for a test, the test applies to all nominal conductor dimensions covered by the specification sheet.

Unless otherwise specified, all tests shall be carried out at a temperature from 15 °C to ~~35~~ 40 °C and a relative humidity from ~~45~~ 25 % to 75 %. Before measurements are made, the specimens shall be preconditioned under these atmospheric conditions for a time sufficient to allow the specimens to reach stability.

The wire to be tested shall be removed from the packaging in such a way that the wire will not be subjected to tension or unnecessary bends. Before each test, sufficient wire should be discarded to ensure that any damaged wire is not included in the test specimens.

### 3.2.2 Winding wire

When reference is made to a winding wire according to a standard of the IEC 60317 series mentioned under Clause 2, the following information is given in the description:

- reference to IEC specification;
- nominal conductor dimensions in millimetres (width × thickness);
- grade.

EXAMPLE IEC 60317-18 – 4,00 × 1,00 Grade 1

## 3.3 Appearance

The film coating shall be smooth and continuous, free from streaks, blisters and foreign material when examined with normal vision, as wound on the original spool or reel.

## 4 Dimensions

### 4.1 Conductor dimensions

The dimensions for widths and thickness of conductors of winding wires with rectangular cross-section recommended in this standard are taken from the R 20 and R 40 series according to ISO 3.

Preferred sizes are combinations of width and thickness both according to the R 20 series.

Intermediate sizes are combinations of width or thickness according to the R 20 series with the other dimension according to the R 40 series.

This standard covers:

- widths from 2,00 mm up to and including 16,00 mm;
- thicknesses from 0,80 mm up to and including 5,60 mm.

For thicknesses over 5,600 mm up to and including 10 mm and for widths over 16 mm up to and including 25 mm where, for technical reasons, additional sizes may be needed, the R 40 series shall be used. The ratio width/thickness shall be within the specified limits and combinations of R 40 by R 40 are not allowed in the case of additional sizes.

The ratio width/thickness shall be greater than or equal to 1,4:1 and shall not exceed 8:1.

The actual values of dimensions are given in Table 2.

The nominal cross-sectional areas for preferred sizes are given in Table 2, and the nominal cross-sectional areas for intermediate sizes are given in Table A.1.

#### 4.2 Tolerance on conductor dimensions

The conductor dimensions shall not differ from the nominal values by more than the tolerance given in Table 1.

**Table 1– Conductor tolerances**

Nominal width or thickness of the conductor		Tolerance
mm		
Over	Up to and including	± mm
–	3,15	0,030
3,15	6,30	0,050
6,30	12,50	0,070
12,50	16,00	0,100

#### 4.3 Rounding of corners


The arc shall merge smoothly into the flat surfaces of the conductor and the strip shall be free from sharp, rough and projecting edges. The conductor shall have radiused corners complying with Table 3. The specified radii shall be maintained within ±25 %.

IECNORM.COM : Click to view the full PDF of IEC 60317-0-9:2015+AMD1:2024 CSV

**Table 2 – Nominal cross-sectional areas of preferred sizes**

Width	Thickness																		
	0,80	0,90	1,00	1,12	1,25	1,40	1,60	1,80	2,00	2,24	2,50	2,80	3,15	3,55	4,00	4,50	5,00	5,60	
	Corner radius (0,5 mm*)																		
2,00	1,463	1,626	1,785	2,025	2,285	2,585													
2,24	1,655	1,842	2,205	2,294	2,582	2,921	3,369												
2,50	1,863	2,076	2,285	2,585	2,910	3,285	3,785	4,137											
2,80	2,103	2,346	2,585	2,921	3,285	3,705	4,265	4,677	5,237										
3,15	2,383	2,661	2,935	3,313	3,723	4,195	4,825	5,307	5,937	6,693									
3,55	2,703	3,021	3,335	3,761	4,223	4,755	5,465	6,027	6,737	7,589	8,326								
4,00	3,063	3,426	3,785	4,265	4,785	5,385	6,185	6,831	7,637	8,597	9,451	10,65							
4,50	3,463	3,876	4,285	4,825	5,410	6,085	6,85	7,737	8,631	9,717	10,70	12,05	13,63						
5,00	3,863	4,326	4,785	5,385	6,035	6,785	7,785	8,637	9,637	10,84	12,18	13,45	15,20	17,20					
5,60	4,363	4,866	5,385	6,057	6,785	7,625	8,745	9,717	10,84	12,18	13,45	15,13	17,09	19,33	21,54				
6,30	4,903	5,496	6,085	6,841	7,660	8,605	9,865	10,98	12,24	13,75	15,20	17,09	19,30	21,82	24,34	27,49			
7,10		6,216	6,885	7,737	8,660	9,725	11,15	12,42	13,84	15,54	17,20	19,33	21,82	24,66	27,54	31,09	34,64		
8,00			7,785	8,745	9,785	10,99	12,59	14,04	15,64	17,56	19,45	21,85	24,65	27,85	31,14	35,14	39,14	43,94	
9,00				9,865	11,04	12,39	14,19	15,84	17,64	19,80	21,95	24,65	27,80	31,40	35,14	39,64	44,14	49,54	
10,0					12,29	13,79	15,79	17,64	19,64	22,04	24,45	27,45	30,95	34,95	39,14	44,14	49,14	55,14	
11,2						15,47	17,47	19,80	22,04	24,79	27,46	30,81	34,73	39,21	43,94	49,54	55,14	61,86	
12,5							19,79	22,14	24,64	27,64	30,70	34,45	38,83	43,83	49,14	55,39	61,64	69,14	
14,0								24,84	27,64	31,00	34,45	38,65	43,55	49,15	55,14	62,14	69,14	77,54	
16,0									31,64	35,48	39,45	44,25	49,85	56,25	63,14	71,14	79,14	88,74	

\* Nominal thickness

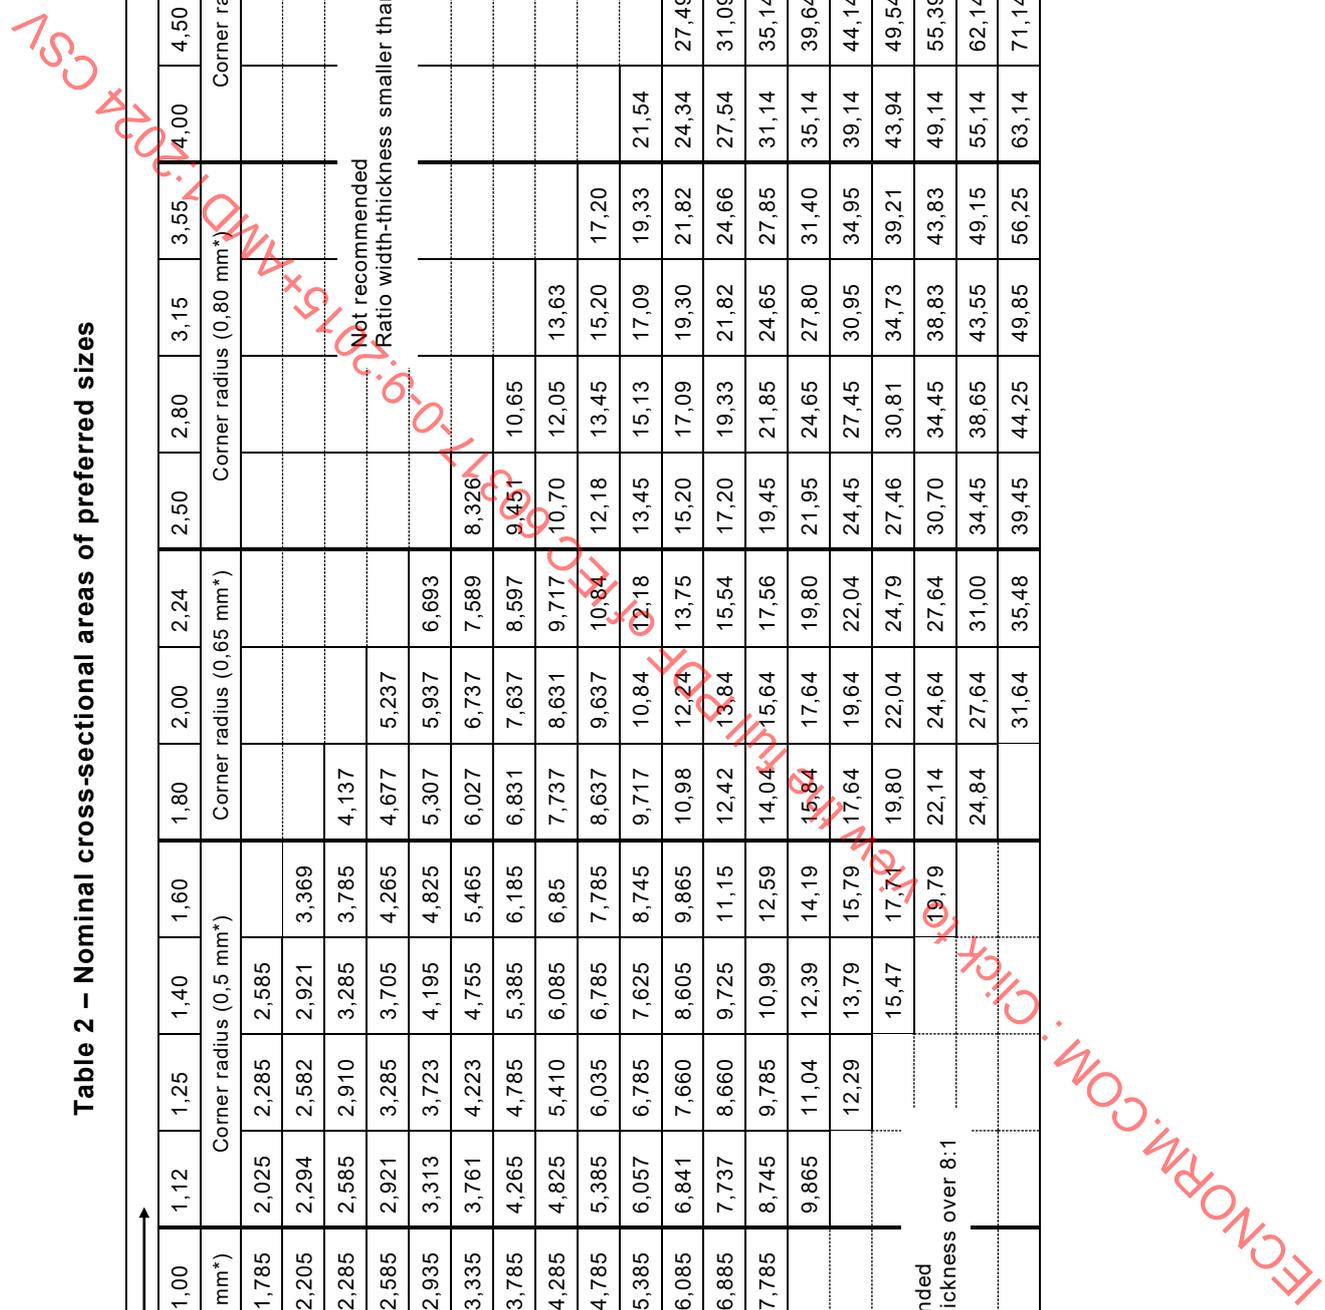

**Table 3 – Corner radii**

Nominal thickness of conductor mm		Corner radius ± mm
Over	Up to and including	
–	1,00	0,50 nominal thickness
1,00	1,60	0,50*
1,60	2,24	0,65**
2,24	3,55	0,80
3,55	5,60	1,00

NOTE If agreed between purchaser and supplier, the corner radii for wires with a width greater than 4,8 mm may be:

\* 0,50 nominal thickness

\*\* 0,80 mm

#### 4.4 Increase in dimensions due to the insulation

The increase in width or thickness due to the insulation shall be as given in Table 4.

**Table 4 – Increases in dimensions**

Grade	Increase in dimensions mm		
	Minimum	Nominal	Maximum
1	0,06	0,085	0,11
2	0,12	0,145	0,17

#### 4.5 Overall dimensions

##### 4.5.1 Nominal overall dimensions

The nominal overall dimensions shall be calculated as the sum of the nominal bare conductor and the nominal increase in dimension due to the insulation.

##### 4.5.2 Minimum overall dimensions

The minimum overall dimensions shall be calculated as the sum of the minimum bare conductor and the minimum increase in dimension due to the insulation. See also note under 4.5.3.

##### 4.5.3 Maximum overall dimensions

The maximum overall dimensions shall be calculated as the sum of the maximum bare conductor and the maximum increase in dimension due to the insulation.

NOTE When agreed between purchaser and supplier, special tolerances for grade 2 as given in Annex B have been established to calculate special maximum and minimum dimensions.

## 5 Electrical resistance

The aluminium rod being used shall comply with EN 1715-2 and ASTM B233-97.

The resistance of the wire shall be expressed as the d.c. resistance at 20 °C. The method used shall provide an accuracy of 0,5 %.

The maximum value of resistance shall be not greater than the value calculated for the minimum tolerated cross-sectional area of the conductor resulting from the minimum dimensions in thickness and width and the maximum for the corner radius, and with a resistivity of 1/35,85 (0,027 894)  $\Omega \cdot \text{mm}^2 \cdot \text{m}^{-1}$ .

One measurement shall be made.

## 6 Elongation

The minimum elongation at fracture shall be 15 %.

## 7 Springiness

~~Test appropriate but no requirements specified.~~

Test inappropriate.

## 8 Flexibility and adherence

### 8.1 Mandrel winding test

The coating shall show no crack after the wire has been bent flatwise and edgewise on a mandrel with a diameter as specified in Table 5.

**Table 5 – Mandrel winding**

Wire bent on		Mandrel diameter
Width	Sizes up to and including 10 mm	4width
	Sizes over 10 mm	5 × width
Thickness	All sizes	4 × thickness

### 8.2 Adherence test

The wire shall be stretched by 15 %. The distance of loss of adhesion shall be less than one time the width.

## 9 Heat shock

The coating shall show no crack after the wire has been bent flatwise on a mandrel with a diameter of six times the thickness.

The minimum heat shock temperature is given in the relevant specification sheet.

## 10 Cut-through

Test inappropriate.

## 11 Resistance to abrasion

Test inappropriate.

## 12 Resistance to solvents

Following immersion in standard solvent, the coating shall not be removed using a pencil of hardness "H".

## 13 Breakdown voltage

When tested at room temperature at least four of the five specimens tested shall not break down at a voltage less than or equal to that given in Table 6, and the fifth shall not break down at less than 50 % of the values specified.

When required by the purchaser, the wire shall be tested at elevated temperature.

The elevated temperature is given in the relevant specification sheet.

**Table 6 – Breakdown voltage**

Grade	Minimum breakdown voltage (r.m.s.) V	
	Room temperature	Elevated temperature
1	1 000	750
2	2 000	1 500

## 14 Continuity of insulation

Test inappropriate.

## 15 Temperature index

The test shall be carried out on a rectangular wire according to IEC 60172, unless otherwise agreed between purchaser and supplier.

When required by a purchaser, the supplier of the enamelled wire shall supply evidence that the wire meets the requirements for the temperature index.

NOTE 1 The temperature index requirement based on an extrapolated life of 20 000 h relates to enamelled wires tested unvarnished and not as part of an insulation system.

NOTE 2 Temperature in degrees Celsius corresponding to the temperature index is not necessarily that at which it is recommended that the wire be operated and this will depend on many factors, including the type of equipment involved.

## 16 Resistance to refrigerants

Test inappropriate.

## 17 Solderability

Test inappropriate.

## 18 Heat or solvent bonding

Test inappropriate.

## 19 Dielectric dissipation factor

For requirements, see the relevant specification sheet.

## 20 Resistance to transformer oil

For requirements, see the relevant specification sheet.

## 21 Loss of mass

Test inappropriate.

## 23 Pin hole test

Test inappropriate.

## 30 Packaging

The kind of packaging may influence certain properties of the wire, for example springback. Therefore the kind of packaging for example, the type of spool, shall be agreed between purchaser and supplier.

The wire shall be evenly and compactly wound on spools or placed in containers. No spool or container shall contain more than one length of wire unless agreed to by purchaser and supplier. Marking of the label when there is more than one length and/or identification of the separate lengths in the package shall be agreed to by purchaser and supplier.

Where wires are delivered in coils, the dimensions and the maximum weights of such coils shall be agreed between purchaser and supplier. Any additional protection for coils shall also be agreed between purchaser and supplier.

Labels shall be attached to each packaging unit as agreed between supplier and user and shall include the following information:

- a) manufacturer name and/or trade mark;
- b) type of wire and insulation, for instance trade name and/or IEC specification number;
- c) net mass of wire;
- d) nominal dimension(s) of wire and grade of insulation;
- e) date of manufacture.

**Annex A**  
 (informative)

**Nominal cross-sectional areas for preferred and intermediate sizes**

Table A.1 provides nominal cross-sectional areas for preferred and intermediate sizes of rectangular aluminium bare conductors, from which the user may select intermediate sizes only for technical reasons.

**Table A.1 – Nominal cross-sectional areas (1 of 9)**

Nominal width	Nominal thickness	Radius on corners	Nominal cross-section area	Nominal width	Nominal thickness	Radius on corners	Nominal cross-section area	
mm	mm	mm	mm <sup>2</sup>	mm	mm	mm	mm <sup>2</sup>	
2,00	0,80	*	1,463	2,50	1,25	0,5	2,910	
	0,85	*	1,545		1,32	0,5	3,085	
	0,90	*	1,626		1,40	0,5	3,285	
	0,95	*	1,706		1,50	0,5	3,535	
	1,00	*	1,785		1,60	0,5	3,785	
	1,06	0,5	1,905		1,70	0,65	3,887	
	1,12	0,5	2,025		1,80	0,65	4,137	
	1,18	0,5	2,145	2,65	0,80	*	1,983	
	1,25	0,5	2,285		0,90	*	2,211	
	1,32	0,5	2,425		1,00	*	2,435	
	1,40	0,5	2,585		1,12	0,5	2,753	
	2,12	0,80	*		1,559	1,25	0,5	3,098
		0,90	*		1,734	1,40	0,5	3,495
		1,00	*		1,905	1,60	0,5	4,025
1,12		0,5	2,160	1,80	0,65	4,407		
1,25		0,5	2,435	2,80	0,80	*	2,103	
1,40		0,5	2,753		0,85	*	2,225	
2,24		0,80	*		1,655	0,90	*	2,346
	0,85	*	1,749		0,95	*	2,466	
	0,90	*	1,842		1,00	*	2,585	
	0,95	*	1,934		1,06	0,5	2,753	
	1,00	*	2,025		1,12	0,5	2,921	
	1,06	0,5	2,160	1,18	0,5	3,089		
	1,12	0,5	2,294	1,25	0,5	3,285		
	1,18	0,5	2,429	1,32	0,5	3,481		
	1,25	0,5	2,585	1,40	0,5	3,705		
	1,32	0,5	2,742	1,50	0,5	3,985		
	1,40	0,5	2,921	1,60	0,5	4,265		
	1,50	0,5	3,145	1,70	0,65	4,397		
	1,60	0,5	3,369	1,80	0,65	4,677		
	2,36	0,80	*	1,751				

Table A.1 (2 of 9)

Nominal width	Nominal thickness	Radius on corners	Nominal cross-section area	Nominal width	Nominal thickness	Radius on corners	Nominal cross-section area	
mm	mm	mm	mm <sup>2</sup>	mm	mm	mm	mm <sup>2</sup>	
2,50	0,90	*	1,950	3,00	1,90	0,65	4,957	
	1,00	*	2,145		2,00	0,65	5,237	
	1,12	0,5	2,429		0,80	*	2,263	
	1,25	0,5	2,735		0,90	*	2,526	
	1,40	0,5	3,089		1,00	*	2,785	
	1,60	0,5	3,561		1,12	0,5	3,145	
	0,80	*	1,863		1,25	0,5	3,535	
	0,85	*	1,970		1,40	0,5	3,985	
	0,90	*	2,076		1,60	0,5	4,585	
	0,95	*	2,181		1,80	0,65	5,037	
	1,00	*	2,285		2,00	0,65	5,637	
	1,06	0,5	2,435		3,15	0,80	*	2,383
	1,12	0,5	2,585			0,85	*	2,522
	1,18	0,5	2,736		3,75	0,80	*	2,863
3,15	0,90	*	2,661	0,90		*	3,201	
	0,95	*	2,799	1,00		*	3,535	
	1,00	*	2,935	1,12		0,5	3,985	
	1,06	0,5	3,124	1,25		0,5	4,473	
	1,12	0,5	3,313	1,40		0,5	5,035	
	1,18	0,5	3,502	1,60		0,5	5,785	
	1,25	0,5	3,723	1,80		0,65	6,387	
	1,32	0,5	3,943	2,00		0,65	7,137	
	1,40	0,5	4,195	2,24		0,65	8,037	
	1,50	0,5	4,510	4,00		2,50	0,8	8,826
	1,60	0,5	4,825			0,80	*	3,063
	1,70	0,65	4,992			0,85	*	3,245
	1,80	0,65	5,307			0,90	*	3,426
	1,90	0,65	5,622		0,95	*	3,606	
2,00	0,65	5,937	1,00		*	3,785		
2,12	0,65	6,315	1,06		0,5	4,025		
2,24	0,65	6,693	1,12		0,5	4,265		
3,35	0,80	*	2,543	1,18	0,5	4,505		
	0,90	*	2,841	1,25	0,5	4,785		
	1,00	*	3,135	1,32	0,5	5,065		
	1,12	0,5	3,537	1,40	0,5	5,385		
	1,25	0,5	3,973	1,50	0,5	5,785		
	1,40	0,5	4,475	1,60	0,5	6,185		
	1,60	0,5	5,145					
	1,80	0,65	5,667					

Table A.1 (3 of 9)

Nominal width	Nominal thickness	Radius on corners	Nominal cross-section area	Nominal width	Nominal thickness	Radius on corners	Nominal cross-section area
mm	mm	mm	mm <sup>2</sup>	mm	mm	mm	mm <sup>2</sup>
3,55	2,00	0,65	6,337	4,25	1,70	0,65	6,437
	2,24	0,65	7,141		1,80	0,65	6,837
	0,80	*	2,703		1,90	0,65	7,237
	0,85	*	2,862		2,00	0,65	7,637
	0,90	*	3,021		2,12	0,65	8,117
	0,95	*	3,179		2,24	0,65	8,597
	1,00	*	3,335		2,36	0,8	8,891
	1,06	0,5	3,548		2,50	0,8	9,451
	1,12	0,5	3,761		2,65	0,8	10,05
	1,18	0,5	3,974		2,80	0,8	10,65
	1,25	0,5	4,223		0,80	*	3,263
	1,32	0,5	4,471		0,90	*	3,651
	1,40	0,5	4,755		1,00	*	4,035
	1,50	0,5	5,110		1,12	0,5	4,545
	1,60	0,5	5,465		1,25	0,5	5,098
	1,70	0,65	5,672		1,40	0,5	5,735
	1,80	0,65	6,027		1,60	0,5	6,585
	1,90	0,65	6,382		1,80	0,65	7,287
	2,00	0,65	6,737		2,00	0,65	8,137
	2,12	0,65	7,163		2,24	0,65	9,157
2,24	0,65	7,589	2,50	0,8	10,08		
2,36	0,8	7,829	2,80	0,8	11,35		
2,50	0,8	8,326	5,00	1,70	0,65	8,137	
0,80	*	3,463		1,80	0,65	8,637	
0,85	*	3,670		1,90	0,65	9,137	
0,90	*	3,876		2,00	0,65	9,637	
0,95	*	4,081		2,12	0,65	10,24	
1,00	*	4,285		2,24	0,65	10,84	
1,06	0,5	4,555		2,36	0,8	11,25	
1,12	0,5	4,825		2,50	0,8	11,95	
1,18	0,5	5,095		2,65	0,8	12,70	
1,25	0,5	5,410		2,80	0,8	13,45	
1,32	0,5	5,725		3,00	0,8	14,45	
1,40	0,5	6,085		3,15	0,8	15,20	
1,50	0,5	6,535		3,35	0,8	16,20	
1,60	0,5	6,985		3,55	0,8	17,20	
1,70	0,65	7,287		5,30	0,80	*	4,103
1,80	0,65	7,737			0,90	*	4,596
1,90	0,65	8,187	1,00		*	5,085	
2,00	0,65	8,637					
2,12	0,65	9,177					

IECNORM.COM · Click to view the full PDF of IEC 60317-0-9:2015+AMD1:2024 CSV

Table A.1 (4 of 9)

Nominal width	Nominal thickness	Radius on corners	Nominal cross-section area	Nominal width	Nominal thickness	Radius on corners	Nominal cross-section area	
mm	mm	mm	mm <sup>2</sup>	mm	mm	mm	mm <sup>2</sup>	
4,75	2,24	0,65	9,717	5,60	1,12	0,5	5,721	
	2,36	0,8	10,07		1,25	0,5	6,410	
	2,50	0,8	10,70		1,40	0,5	7,205	
	2,65	0,8	11,38		1,60	0,5	8,265	
	2,80	0,8	12,05		1,80	0,65	9,177	
	3,00	0,8	12,95		2,00	0,65	10,24	
	3,15	0,8	13,63		2,24	0,65	11,51	
	0,80	*	3,663		2,50	0,8	12,70	
	0,90	*	4,101		2,80	0,8	14,29	
	1,00	*	4,535		3,15	0,8	16,15	
	1,12	0,5	5,105		3,55	0,8	18,27	
	1,25	0,5	5,723		0,80	*	4,343	
	1,40	0,5	6,435		0,85	*	4,605	
	1,60	0,5	7,385		0,90	*	4,866	
	1,80	0,65	8,188		0,95	*	5,126	
	2,00	0,65	9,137		1,00	*	5,385	
2,24	0,65	10,28	1,06	0,5	5,721			
2,50	0,8	11,33	1,12	0,5	6,057			
2,80	0,8	12,75	1,18	0,5	6,393			
3,15	0,8	14,41	1,25	0,5	6,785			
5,00	0,80	*	3,863	1,32	0,5	7,177		
	0,85	*	4,095	1,40	0,5	7,625		
	0,90	*	4,326	1,50	0,5	8,185		
	0,95	*	4,556	1,60	0,5	8,745		
	1,00	*	4,785	1,70	0,65	9,157		
	1,06	0,5	5,085	1,80	0,65	9,717		
	1,12	0,5	5,385	1,90	0,65	10,28		
	1,18	0,5	5,685	2,00	0,65	10,84		
	1,25	0,5	6,035	2,12	0,65	11,51		
	1,32	0,5	6,385	2,24	0,65	12,18		
	1,40	0,5	6,785	2,36	0,8	12,67		
	1,50	0,5	7,285	2,50	0,8	13,45		
	1,60	0,5	7,785	2,65	0,8	14,29		
	5,60	3,00	0,8	16,25	2,80	0,8	15,13	
		3,15	0,8	17,09	6,30	3,75	1,0	22,77
		3,35	0,8	18,21		4,00	1,0	24,34
3,55		0,8	19,33	4,25		1,0	25,92	
				4,50		1,0	27,49	
3,75		1,0	20,14	6,70	0,90	*	5,856	
4,00		1,0	21,54		1,00	*	6,485	

Table A.1 (5 of 9)

Nominal width	Nominal thickness	Radius on corners	Nominal cross-section area	Nominal width	Nominal thickness	Radius on corners	Nominal cross-section area
mm	mm	mm	mm <sup>2</sup>	mm	mm	mm	mm <sup>2</sup>
6,00	0,80	*	4,663	7,10	1,12	0,5	7,289
	0,90	*	5,226		1,25	0,5	8,160
	1,00	*	5,785		1,40	0,5	9,165
					1,60	0,5	10,51
	1,12	0,5	6,505				
	1,25	0,5	7,285		1,80	0,65	11,70
	1,40	0,5	8,185		2,00	0,65	13,04
	1,60	0,5	9,385		2,24	0,65	14,65
	1,80	0,65	10,44		2,50	0,8	16,20
	2,00	0,65	11,64		2,80	0,8	28,21
	2,24	0,65	13,08		3,15	0,8	20,56
					3,55	0,8	23,24
	2,50	0,8	14,45				
	2,80	0,8	16,25		4,00	1,0	25,94
	3,15	0,8	18,35		4,50	1,0	29,29
	3,55	0,8	20,75				
	4,00	1,0	23,14				
	6,30	0,80	*		4,903	0,90	*
0,85		*	5,200	0,95	*	6,551	
0,90		*	5,496	1,00	*	6,885	
0,95		*	5,791				
1,00		*	6,085	1,06	0,5	7,311	
				1,12	0,5	7,737	
1,06		0,5	6,463	1,18	0,5	8,163	
1,12		0,5	6,841	1,25	0,5	8,660	
1,18		0,5	7,219	1,32	0,5	9,157	
1,25		0,5	7,660	1,40	0,5	9,725	
1,32		0,5	8,101	1,50	0,5	10,44	
1,40		0,5	8,605	1,60	0,5	11,15	
1,50		0,5	9,235				
1,60		0,5	9,865	1,70	0,65	11,71	
				1,80	0,65	12,42	
1,70		0,65	10,35	1,90	0,65	13,13	
1,80		0,65	10,98	2,00	0,65	13,84	
1,90		0,65	11,61	2,12	0,65	14,69	
2,00		0,65	12,24	2,24	0,65	15,54	
2,12		0,65	12,99				
2,24		0,65	13,75	2,36	0,8	16,21	
				2,50	0,8	17,20	
2,36		0,8	14,32	2,65	0,8	18,27	
2,50		0,8	15,20	2,80	0,8	19,33	
2,65		0,8	16,15	3,00	0,8	20,75	
2,80		0,8	17,09	3,15	0,8	21,82	
3,00		0,8	18,35	3,35	0,8	23,24	
			3,55	0,8	24,66		
			3,75	1,0	25,77		

Table A.1 (6 of 9)

Nominal width	Nominal thickness	Radius on corners	Nominal cross-section area	Nominal width	Nominal thickness	Radius on corners	Nominal cross-section area
mm	mm	mm	mm <sup>2</sup>	mm	mm	mm	mm <sup>2</sup>
	3,15	0,8	19,30		4,00	1,0	27,54
	3,35	0,8	20,56		4,25	1,0	29,32
	3,55	0,8	21,82				
7,10	4,50	1,0	31,09	8,50	1,12	0,5	9,305
	4,75	1,0	32,87		1,25	0,5	10,41
	5,00	1,0	34,64		1,40	0,5	11,69
			1,60		0,5	13,39	
7,50	1,00	*	7,285	1,80	0,65	14,94	
	1,12	0,5	8,185	2,00	0,65	16,64	
	1,25	0,5	9,160	2,24	0,65	18,68	
	1,40	0,5	10,29	2,50	0,8	20,70	
	1,60	0,5	11,79	2,80	0,8	23,25	
	1,80	0,65	13,14	3,15	0,8	26,23	
	2,00	0,65	14,64	3,55	0,8	29,63	
	2,24	0,65	16,44	4,00	1,0	33,14	
	2,50	0,8	18,20	4,50	1,0	37,39	
	2,80	0,8	20,45	5,00	1,0	41,64	
	3,15	0,8	23,08	5,60	1,0	46,74	
	3,55	0,8	26,08	9,00	1,12	0,5	9,865
	4,00	1,0	29,14		1,18	0,5	10,41
	4,50	1,0	32,89		1,25	0,5	11,04
	5,00	1,0	36,64		1,32	0,5	11,67
	8,00	1,00	*		7,785	1,40	0,5
1,06		0,5	8,265		1,50	0,5	13,29
1,12		0,5	8,745		1,60	0,5	14,19
1,18		0,5	9,225		1,70	0,65	14,94
1,25		0,5	9,785		1,80	0,65	15,84
1,32		0,5	10,35		1,90	0,65	16,74
1,40		0,5	10,99		2,00	0,65	17,64
1,50		0,5	11,79		2,12	0,65	18,72
1,60		0,5	12,59		2,24	0,65	19,80
1,70		0,65	13,24		2,36	0,8	20,69
1,80		0,65	14,04		2,50	0,8	21,95
1,90		0,65	14,84		2,65	0,8	23,30
2,00		0,65	15,64	2,80	0,8	24,65	
2,12		0,65	16,60	3,00	0,8	26,45	
2,24		0,65	17,56	3,15	0,8	27,80	
2,36		0,8	18,33	3,35	0,8	29,60	
2,50	0,8	19,45	3,55	0,8	31,40		
			3,75	1,0	32,89		

IECNORM.COM - Click to view the full PDF of IEC 60317-0-9:2015+AMD1:2024 CSV



Table A.1 (8 of 9)

Nominal width	Nominal thickness	Radius on corners	Nominal cross-section area	Nominal width	Nominal thickness	Radius on corners	Nominal cross-section area
mm	mm	mm	mm <sup>2</sup>	mm	mm	mm	mm <sup>2</sup>
10,60	4,00	1,0	39,14	12,50	3,15	0,8	36,62
	4,25	1,0	41,64		3,55	0,8	41,34
	4,50	1,0	44,14		4,00	1,0	46,34
	4,75	1,0	46,64		4,50	1,0	52,24
	5,00	1,0	49,14		5,00	1,0	58,14
	5,30	1,0	52,14		5,60	1,0	65,22
	5,60	1,0	55,14		1,60	0,5	19,79
	1,40	0,5	14,63		1,70	0,65	20,89
	1,60	0,5	16,75		1,80	0,65	22,14
	1,80	0,65	18,72		1,90	0,65	23,39
	2,00	0,65	20,84		2,00	0,65	24,64
	2,24	0,65	23,38		2,12	0,65	26,14
	2,50	0,8	25,95		2,24	0,65	27,64
	2,80	0,8	29,13		2,36	0,8	28,95
	3,15	0,8	32,84		2,50	0,8	30,70
	3,55	0,8	37,08		2,65	0,8	32,58
4,00	1,0	41,54	2,80	0,8	34,45		
4,50	1,0	46,84	3,00	0,8	36,95		
5,00	1,0	52,14	3,15	0,8	38,83		
5,60	1,0	58,50	3,35	0,8	41,33		
11,20	1,40	0,5	15,47	3,55	0,8	43,83	
	1,50	0,5	16,59	3,75	1,0	46,02	
	1,60	0,5	17,71	4,00	1,0	49,14	
12,50	4,50	1,0	55,39	4,25	1,0	52,27	
	4,75	1,0	58,52	4,75	1,0	65,64	
	5,00	1,0	61,64	5,00	1,0	69,14	
	5,30	1,0	65,39	5,30	1,0	73,34	
	5,60	1,0	69,14	5,60	1,0	77,54	
13,20	1,80	0,65	23,40	14,00	2,00	0,65	29,64
	2,00	0,65	26,04		2,24	0,65	33,24
	2,24	0,65	29,21	2,50	0,8	36,95	
	2,50	0,8	32,45	2,80	0,8	41,45	
	2,80	0,8	36,41	3,15	0,8	46,70	
	3,15	0,8	41,03	3,55	0,8	52,70	
	3,55	0,8	46,31	4,00	1,0	59,14	
	4,00	1,0	51,94	4,50	1,0	66,64	
	4,50	1,0	58,54	5,00	1,0	74,14	
	5,00	1,0	65,14	5,60	1,0	83,14	

**Table A.1** (9 of 9)

Nominal width	Nominal thickness	Radius on corners	Nominal cross-section area	Nominal width	Nominal thickness	Radius on corners	Nominal cross-section area			
mm	mm	mm	mm <sup>2</sup>	mm	mm	mm	mm <sup>2</sup>			
14,00	5,60	1,0	73,06	16,00	2,00	0,65	31,64			
	1,80	0,65	24,84		2,12	0,65	33,56			
		1,90	0,65		26,24	2,24	0,65	35,48		
		2,00	0,65		27,64	2,36	0,8	37,21		
		2,12	0,65		29,32		2,50	0,8	39,45	
		2,24	0,65		31,00		2,65	0,8	41,85	
		2,36	0,8		32,49		2,80	0,8	44,25	
			2,50		0,8		34,45	3,00	0,8	47,45
			2,65		0,8		36,55	3,15	0,8	49,85
			2,80		0,8		38,65	3,35	0,8	53,05
			3,00		0,8		41,45	3,55	0,8	56,25
	3,15		0,8		43,55		3,75	1,0	59,14	
	3,35		0,8		46,35			4,00	1,0	63,14
	3,55		0,8		49,15	4,25		1,0	67,14	
	3,75	1,0	51,64		4,50	1,0		71,14		
		4,00	1,0		55,14	4,75		1,0	75,14	
		4,25	1,0		58,64	5,00		1,0	79,14	
		4,50	1,0		62,14	5,30		1,0	83,94	
						5,60		1,0	88,74	

\* 0,5 mm nominal thickness.

IECNORM.COM : Click to view the full PDF of IEC 60317-0-9:2015+AMD1:2024 CSV

## Annex B (informative)

### Special tolerances

Table B.1 gives the special tolerances used for measuring overall dimensions of grade 2 rectangular aluminium winding wire.

**Table B.1 – Overall dimensional tolerances for grade 2**

Nominal width or thickness of the conductor  mm		Tolerances on nominal overall dimensions for grade 2  ± mm	
Over	Up to and including	Width	Thickness
–	2,00	–	0,03
2,00	3,15	0,06	0,03
3,15	5,60	0,06	0,05
5,60	6,30	0,06	–
6,30	12,50	0,08	–
12,50	16,00	0,10	–

IECNORM.COM : Click to view the full PDF of IEC 60317-0-9:2015+AMD1:2024 CSV

## Bibliography

IEC 60264 (all parts), *Packaging of winding wires*

IEC 60317 (all parts), *Specifications for particular types of winding wires*

---

IECNORM.COM : Click to view the full PDF of IEC 60317-0-9:2015+AMD1:2024 CSV

## CONTENTS

FOREWORD.....	4
INTRODUCTION.....	6
1 Scope.....	7
2 Normative references .....	7
3 Terms, definitions, general notes and appearance.....	7
3.1 Terms and definitions.....	7
3.2 General notes .....	8
3.2.1 Methods of test.....	8
3.2.2 Winding wire.....	8
3.3 Appearance .....	8
4 Dimensions.....	8
4.1 Conductor dimensions .....	8
4.2 Tolerance on conductor dimensions.....	9
4.3 Rounding of corners.....	9
4.4 Increase in dimensions due to the insulation.....	11
4.5 Overall dimensions .....	11
4.5.1 Nominal overall dimensions .....	11
4.5.2 Minimum overall dimensions.....	11
4.5.3 Maximum overall dimensions .....	11
5 Electrical resistance .....	11
6 Elongation .....	12
7 Springiness .....	12
8 Flexibility and adherence.....	12
8.1 Mandrel winding test.....	12
8.2 Adherence test.....	12
9 Heat shock .....	12
10 Cut-through .....	12
11 Resistance to abrasion.....	12
12 Resistance to solvents.....	13
13 Breakdown voltage .....	13
14 Continuity of insulation .....	13
15 Temperature index .....	13
16 Resistance to refrigerants.....	13
17 Solderability .....	13
18 Heat or solvent bonding.....	14
19 Dielectric dissipation factor.....	14
20 Resistance to transformer oil .....	14
21 Loss of mass .....	14
23 Pin hole test .....	14
30 Packaging .....	14
Annex A (informative) Nominal cross-sectional areas for preferred and intermediate sizes.....	15
Annex B (informative) Special tolerances.....	24
Bibliography.....	25

Table 1– Conductor tolerances .....	9
Table 2 – Nominal cross-sectional areas of preferred sizes.....	10
Table 3 – Corner radii .....	11
Table 4 – Increases in dimensions .....	11
Table 5 – Mandrel winding .....	12
Table 6 – Breakdown voltage.....	13
Table A.1 – Nominal cross-sectional areas (1 of 9) .....	15
Table B.1 – Overall dimensional tolerances for grade 2 .....	24

IECNORM.COM : Click to view the full PDF of IEC 60317-0-9:2015+AMD1:2024 CSV

## INTERNATIONAL ELECTROTECHNICAL COMMISSION

**SPECIFICATIONS FOR PARTICULAR TYPES OF WINDING WIRES –****Part 0-9: General requirements – Enamelled rectangular aluminium wire**

## FOREWORD

- 1) The International Electrotechnical Commission (IEC) is a worldwide organization for standardization comprising all national electrotechnical committees (IEC National Committees). The object of IEC is to promote international co-operation on all questions concerning standardization in the electrical and electronic fields. To this end and in addition to other activities, IEC publishes International Standards, Technical Specifications, Technical Reports, Publicly Available Specifications (PAS) and Guides (hereafter referred to as "IEC Publication(s)"). Their preparation is entrusted to technical committees; any IEC National Committee interested in the subject dealt with may participate in this preparatory work. International, governmental and non-governmental organizations liaising with the IEC also participate in this preparation. IEC collaborates closely with the International Organization for Standardization (ISO) in accordance with conditions determined by agreement between the two organizations.
- 2) The formal decisions or agreements of IEC on technical matters express, as nearly as possible, an international consensus of opinion on the relevant subjects since each technical committee has representation from all interested IEC National Committees.
- 3) IEC Publications have the form of recommendations for international use and are accepted by IEC National Committees in that sense. While all reasonable efforts are made to ensure that the technical content of IEC Publications is accurate, IEC cannot be held responsible for the way in which they are used or for any misinterpretation by any end user.
- 4) In order to promote international uniformity, IEC National Committees undertake to apply IEC Publications transparently to the maximum extent possible in their national and regional publications. Any divergence between any IEC Publication and the corresponding national or regional publication shall be clearly indicated in the latter.
- 5) IEC itself does not provide any attestation of conformity. Independent certification bodies provide conformity assessment services and, in some areas, access to IEC marks of conformity. IEC is not responsible for any services carried out by independent certification bodies.
- 6) All users should ensure that they have the latest edition of this publication.
- 7) No liability shall attach to IEC or its directors, employees, servants or agents including individual experts and members of its technical committees and IEC National Committees for any personal injury, property damage or other damage of any nature whatsoever, whether direct or indirect, or for costs (including legal fees) and expenses arising out of the publication, use of, or reliance upon, this IEC Publication or any other IEC Publications.
- 8) Attention is drawn to the Normative references cited in this publication. Use of the referenced publications is indispensable for the correct application of this publication.
- 9) IEC draws attention to the possibility that the implementation of this document may involve the use of (a) patent(s). IEC takes no position concerning the evidence, validity or applicability of any claimed patent rights in respect thereof. As of the date of publication of this document, IEC had not received notice of (a) patent(s), which may be required to implement this document. However, implementers are cautioned that this may not represent the latest information, which may be obtained from the patent database available at <https://patents.iec.ch>. IEC shall not be held responsible for identifying any or all such patent rights.

**This consolidated version of the official IEC Standard and its amendment has been prepared for user convenience.**

**IEC 60317-0-9 edition 1.1 contains the first edition (2015-05) [documents 55/1519/FDIS and 55/1525/RVD] and its amendment 1 (2024-06) [documents 55/1978/CDV and 55/2014/RVC].**

**This Final version does not show where the technical content is modified by amendment 1. A separate Redline version with all changes highlighted is available in this publication.**

International Standard IEC 60317-0-9 has been prepared by IEC technical committee 55: Winding wires.

This publication has been drafted in accordance with the ISO/IEC Directives, Part 2.

The numbering of clauses in this standard is not continuous from Clauses 21 through 30 in order to reserve space for possible future wire requirements prior to those for wire packaging.

A list of all parts in the IEC 60317 series, published under the general title *Specifications for particular types of winding wires*, can be found on the IEC website.

The committee has decided that the contents of this document and its amendment will remain unchanged until the stability date indicated on the IEC website under [webstore.iec.ch](http://webstore.iec.ch) in the data related to the specific document. At this date, the document will be

- reconfirmed,
- withdrawn, or
- revised.

IECNORM.COM : Click to view the full PDF of IEC 60317-0-9:2015+AMD1:2024 CSV

## INTRODUCTION

This part of IEC 60317 is one of a series which deals with insulated wires used for windings in electrical equipment. The series has three groups describing:

- 1) Winding wires – Test methods (IEC 60851 series);
- 2) Specifications for particular types of winding wires (IEC 60317 series);
- 3) Packaging of winding wires (IEC 60264 series).

IECNORM.COM : Click to view the full PDF of IEC 60317-0-9:2015+AMD1:2024 CSV

## SPECIFICATIONS FOR PARTICULAR TYPES OF WINDING WIRES –

### Part 0-9: General requirements – Enamelled rectangular aluminium wire

#### 1 Scope

This part of IEC 60317 specifies the general requirements of enamelled rectangular aluminium winding wires.

The range of nominal conductor dimensions is given in the relevant specification sheet.

When reference is made to a winding wire according to a standard of the IEC 60317 series mentioned under Clause 2, the following information is given in the description:

- reference to IEC specification;
- nominal conductor dimensions in millimetres (width × thickness);
- grade.

EXAMPLE IEC 60317-16 – 4,00 x 1,00 Grade 1

#### 2 Normative references

The following documents, in whole or in part, are normatively referenced in this document and are indispensable for its application. For dated references, only the edition cited applies. For undated references, the latest edition of the referenced document (including any amendments) applies.

IEC 60172<sup>1</sup>, *Test procedure for the determination of the temperature index of enamelled and tape wrapped winding wires*

IEC 60317-0-1, *Specifications for particular types of winding wires – Part 0-1: General requirements – Enamelled round copper wire*

IEC 60851 (all parts), *Winding wires – Test methods*

ISO 3, *Preferred numbers – Series of preferred numbers*

EN 1715-2, *Aluminium and aluminium alloys – Drawing stock – Part 2: Specific requirements for electrical applications*

ASTM B233-97, *Standard Specification for Aluminum 1350 Drawing Stock for Electrical Purposes*

#### 3 Terms, definitions, general notes and appearance

##### 3.1 Terms and definitions

For the purposes of this document, the terms and definitions given in IEC 60317-0-1 apply.

<sup>1</sup> Fourth edition to be published.

## 3.2 General notes

### 3.2.1 Methods of test

All methods of test to be used for this standard are given in IEC 60851.

The clause numbers used in this standard are identical to the corresponding test numbers in the IEC 60851 series of standards.

In case of inconsistencies between the publication on methods of test and this standard, IEC 60317-0-9 shall prevail.

Where no specific range of nominal conductor dimensions is given for a test, the test applies to all nominal conductor dimensions covered by the specification sheet.

Unless otherwise specified, all tests shall be carried out at a temperature from 15 °C to 40 °C and a relative humidity from 25 % to 75 %. Before measurements are made, the specimens shall be preconditioned under these atmospheric conditions for a time sufficient to allow the specimens to reach stability.

The wire to be tested shall be removed from the packaging in such a way that the wire will not be subjected to tension or unnecessary bends. Before each test, sufficient wire should be discarded to ensure that any damaged wire is not included in the test specimens.

### 3.2.2 Winding wire

When reference is made to a winding wire according to a standard of the IEC 60317 series mentioned under Clause 2, the following information is given in the description:

- reference to IEC specification;
- nominal conductor dimensions in millimetres (width × thickness);
- grade.

EXAMPLE IEC 60317-18 – 4,00 × 1,00 Grade 1

## 3.3 Appearance

The film coating shall be smooth and continuous, free from streaks, blisters and foreign material when examined with normal vision, as wound on the original spool or reel.

## 4 Dimensions

### 4.1 Conductor dimensions

The dimensions for widths and thickness of conductors of winding wires with rectangular cross-section recommended in this standard are taken from the R 20 and R 40 series according to ISO 3.

Preferred sizes are combinations of width and thickness both according to the R 20 series.

Intermediate sizes are combinations of width or thickness according to the R 20 series with the other dimension according to the R 40 series.

This standard covers:

- widths from 2,00 mm up to and including 16,00 mm;
- thicknesses from 0,80 mm up to and including 5,60 mm.

For thicknesses over 5,600 mm up to and including 10 mm and for widths over 16 mm up to and including 25 mm where, for technical reasons, additional sizes may be needed, the R 40 series shall be used. The ratio width/thickness shall be within the specified limits and combinations of R 40 by R 40 are not allowed in the case of additional sizes.

The ratio width/thickness shall be greater than or equal to 1,4:1 and shall not exceed 8:1.

The actual values of dimensions are given in Table 2.

The nominal cross-sectional areas for preferred sizes are given in Table 2, and the nominal cross-sectional areas for intermediate sizes are given in Table A.1.

#### 4.2 Tolerance on conductor dimensions

The conductor dimensions shall not differ from the nominal values by more than the tolerance given in Table 1.

**Table 1– Conductor tolerances**

Nominal width or thickness of the conductor		Tolerance
mm		
Over	Up to and including	± mm
–	3,15	0,030
3,15	6,30	0,050
6,30	12,50	0,070
12,50	16,00	0,100

#### 4.3 Rounding of corners

The arc shall merge smoothly into the flat surfaces of the conductor and the strip shall be free from sharp, rough and projecting edges. The conductor shall have radiused corners complying with Table 3. The specified radii shall be maintained within ±25 %.


IECNORM.COM : Click to view the full PDF of IEC 60317-0-9:2015+AMD1:2024 CSV

**Table 2 – Nominal cross-sectional areas of preferred sizes**

Width	Thickness																		
	0,80	0,90	1,00	1,12	1,25	1,40	1,60	1,80	2,00	2,24	2,50	2,80	3,15	3,55	4,00	4,50	5,00	5,60	
	Corner radius (0,5 mm*)																		
2,00	1,463	1,626	1,785	2,025	2,285	2,585													
2,24	1,655	1,842	2,205	2,294	2,582	2,921	3,369												
2,50	1,863	2,076	2,285	2,585	2,910	3,285	3,785	4,137											
2,80	2,103	2,346	2,585	2,921	3,285	3,705	4,265	4,677	5,237										
3,15	2,383	2,661	2,935	3,313	3,723	4,195	4,825	5,307	5,937	6,693									
3,55	2,703	3,021	3,335	3,761	4,223	4,755	5,465	6,027	6,737	7,589	8,326								
4,00	3,063	3,426	3,785	4,265	4,785	5,385	6,185	6,831	7,637	8,597	9,451	10,65							
4,50	3,463	3,876	4,285	4,825	5,410	6,085	6,85	7,737	8,631	9,717	10,70	12,05	13,63						
5,00	3,863	4,326	4,785	5,385	6,035	6,785	7,785	8,637	9,637	10,84	12,18	13,45	15,20	17,20					
5,60	4,363	4,866	5,385	6,057	6,785	7,625	8,745	9,717	10,84	12,18	13,45	15,13	17,09	19,33	21,54				
6,30	4,903	5,496	6,085	6,841	7,660	8,605	9,865	10,98	12,24	13,75	15,20	17,09	19,30	21,82	24,34	27,49			
7,10		6,216	6,885	7,737	8,660	9,725	11,15	12,42	13,84	15,54	17,20	19,33	21,82	24,66	27,54	31,09	34,64		
8,00			7,785	8,745	9,785	10,99	12,59	14,04	15,64	17,56	19,45	21,85	24,65	27,85	31,14	35,14	39,14	43,94	
9,00				9,865	11,04	12,39	14,19	15,84	17,64	19,80	21,95	24,65	27,80	31,40	35,14	39,64	44,14	49,54	
10,0					12,29	13,79	15,79	17,64	19,64	22,04	24,45	27,45	30,95	34,95	39,14	44,14	49,14	55,14	
11,2						15,47	17,41	19,80	22,04	24,79	27,46	30,81	34,73	39,21	43,94	49,54	55,14	61,86	
12,5							19,79	22,14	24,64	27,64	30,70	34,45	38,83	43,83	49,14	55,39	61,64	69,14	
14,0								24,84	27,64	31,00	34,45	38,65	43,55	49,15	55,14	62,14	69,14	77,54	
16,0									31,64	35,48	39,45	44,25	49,85	56,25	63,14	71,14	79,14	88,74	

Not recommended  
Ratio width-thickness smaller than 1,4:1

\* Nominal thickness

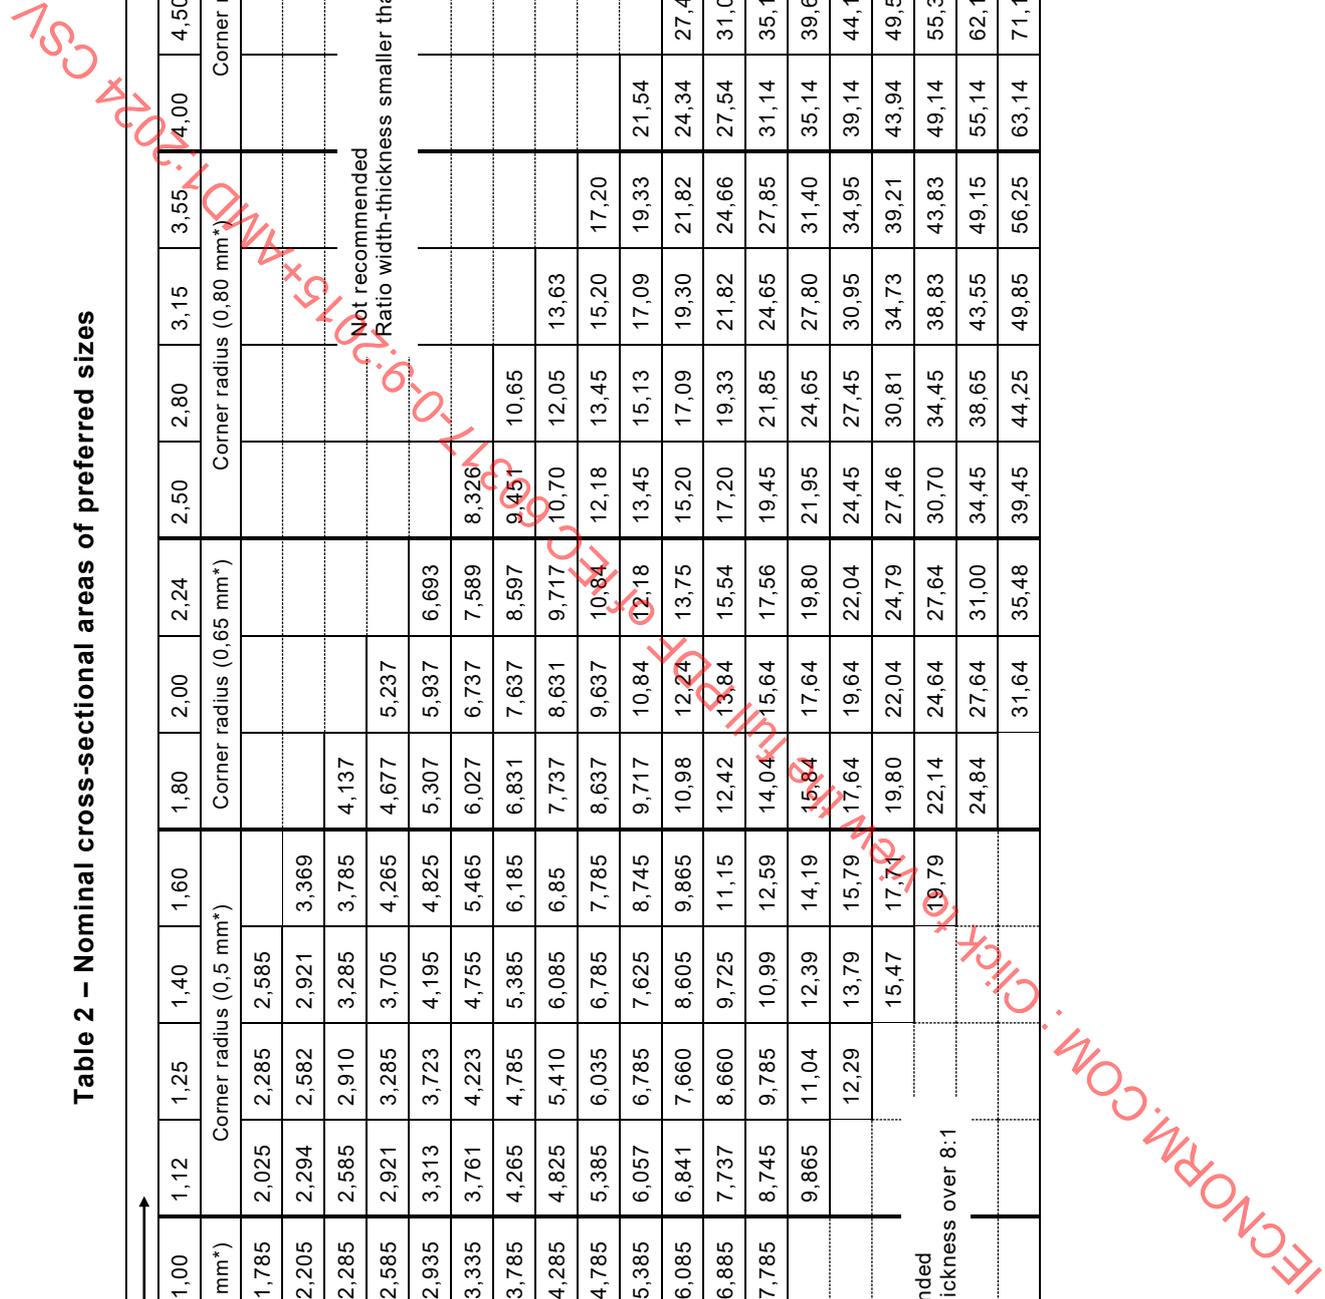

**Table 3 – Corner radii**

Nominal thickness of conductor mm		Corner radius ± mm
Over	Up to and including	
–	1,00	0,50 nominal thickness
1,00	1,60	0,50*
1,60	2,24	0,65**
2,24	3,55	0,80
3,55	5,60	1,00

NOTE If agreed between purchaser and supplier, the corner radii for wires with a width greater than 4,8 mm may be:

\* 0,50 nominal thickness

\*\* 0,80 mm

#### 4.4 Increase in dimensions due to the insulation

The increase in width or thickness due to the insulation shall be as given in Table 4.

**Table 4 – Increases in dimensions**

Grade	Increase in dimensions mm		
	Minimum	Nominal	Maximum
1	0,06	0,085	0,11
2	0,12	0,145	0,17

#### 4.5 Overall dimensions

##### 4.5.1 Nominal overall dimensions

The nominal overall dimensions shall be calculated as the sum of the nominal bare conductor and the nominal increase in dimension due to the insulation.

##### 4.5.2 Minimum overall dimensions

The minimum overall dimensions shall be calculated as the sum of the minimum bare conductor and the minimum increase in dimension due to the insulation. See also note under 4.5.3.

##### 4.5.3 Maximum overall dimensions

The maximum overall dimensions shall be calculated as the sum of the maximum bare conductor and the maximum increase in dimension due to the insulation.

NOTE When agreed between purchaser and supplier, special tolerances for grade 2 as given in Annex B have been established to calculate special maximum and minimum dimensions.

## 5 Electrical resistance

The aluminium rod being used shall comply with EN 1715-2 and ASTM B233-97.

The resistance of the wire shall be expressed as the d.c. resistance at 20 °C. The method used shall provide an accuracy of 0,5 %.

The maximum value of resistance shall be not greater than the value calculated for the minimum tolerated cross-sectional area of the conductor resulting from the minimum dimensions in thickness and width and the maximum for the corner radius, and with a resistivity of 1/35,85 (0,027 894)  $\Omega \cdot \text{mm}^2 \cdot \text{m}^{-1}$ .

One measurement shall be made.

## 6 Elongation

The minimum elongation at fracture shall be 15 %.

## 7 Springiness

Test inappropriate.

## 8 Flexibility and adherence

### 8.1 Mandrel winding test

The coating shall show no crack after the wire has been bent flatwise and edgewise on a mandrel with a diameter as specified in Table 5.

**Table 5 – Mandrel winding**

Wire bent on		Mandrel diameter
Width	Sizes up to and including 10 mm	4width
	Sizes over 10 mm	5 × width
Thickness	All sizes	4 × thickness

### 8.2 Adherence test

The wire shall be stretched by 15 %. The distance of loss of adhesion shall be less than one time the width.

## 9 Heat shock

The coating shall show no crack after the wire has been bent flatwise on a mandrel with a diameter of six times the thickness.

The minimum heat shock temperature is given in the relevant specification sheet.

## 10 Cut-through

Test inappropriate.

## 11 Resistance to abrasion

Test inappropriate.

## 12 Resistance to solvents

Following immersion in standard solvent, the coating shall not be removed using a pencil of hardness "H".

## 13 Breakdown voltage

When tested at room temperature at least four of the five specimens tested shall not break down at a voltage less than or equal to that given in Table 6, and the fifth shall not break down at less than 50 % of the values specified.

When required by the purchaser, the wire shall be tested at elevated temperature.

The elevated temperature is given in the relevant specification sheet.

**Table 6 – Breakdown voltage**

Grade	Minimum breakdown voltage (r.m.s.)	
	V	
	Room temperature	Elevated temperature
1	1 000	750
2	2 000	1 500

## 14 Continuity of insulation

Test inappropriate.

## 15 Temperature index

The test shall be carried out on a rectangular wire according to IEC 60172, unless otherwise agreed between purchaser and supplier.

When required by a purchaser, the supplier of the enamelled wire shall supply evidence that the wire meets the requirements for the temperature index.

NOTE 1 The temperature index requirement based on an extrapolated life of 20 000 h relates to enamelled wires tested unvarnished and not as part of an insulation system.

NOTE 2 Temperature in degrees Celsius corresponding to the temperature index is not necessarily that at which it is recommended that the wire be operated and this will depend on many factors, including the type of equipment involved.

## 16 Resistance to refrigerants

Test inappropriate.

## 17 Solderability

Test inappropriate.

## 18 Heat or solvent bonding

Test inappropriate.

## 19 Dielectric dissipation factor

For requirements, see the relevant specification sheet.

## 20 Resistance to transformer oil

For requirements, see the relevant specification sheet.

## 21 Loss of mass

Test inappropriate.

## 23 Pin hole test

Test inappropriate.

## 30 Packaging

The kind of packaging may influence certain properties of the wire, for example springback. Therefore the kind of packaging for example, the type of spool, shall be agreed between purchaser and supplier.

The wire shall be evenly and compactly wound on spools or placed in containers. No spool or container shall contain more than one length of wire unless agreed to by purchaser and supplier. Marking of the label when there is more than one length and/or identification of the separate lengths in the package shall be agreed to by purchaser and supplier.

Where wires are delivered in coils, the dimensions and the maximum weights of such coils shall be agreed between purchaser and supplier. Any additional protection for coils shall also be agreed between purchaser and supplier.

Labels shall be attached to each packaging unit as agreed between supplier and user and shall include the following information:

- a) manufacturer name and/or trade mark;
- b) type of wire and insulation, for instance trade name and/or IEC specification number;
- c) net mass of wire;
- d) nominal dimension(s) of wire and grade of insulation;
- e) date of manufacture.

**Annex A**  
 (informative)

**Nominal cross-sectional areas for preferred and intermediate sizes**

Table A.1 provides nominal cross-sectional areas for preferred and intermediate sizes of rectangular aluminium bare conductors, from which the user may select intermediate sizes only for technical reasons.

**Table A.1 – Nominal cross-sectional areas (1 of 9)**

Nominal width	Nominal thickness	Radius on corners	Nominal cross-section area	Nominal width	Nominal thickness	Radius on corners	Nominal cross-section area		
mm	mm	mm	mm <sup>2</sup>	mm	mm	mm	mm <sup>2</sup>		
2,00	0,80	*	1,463	2,50	1,25	0,5	2,910		
	0,85	*	1,545		1,32	0,5	3,085		
	0,90	*	1,626		1,40	0,5	3,285		
	0,95	*	1,706		1,50	0,5	3,535		
	1,00	*	1,785		1,60	0,5	3,785		
	1,06	0,5	1,905		1,70	0,65	3,887		
	1,12	0,5	2,025		1,80	0,65	4,137		
	1,18	0,5	2,145		2,65	0,80	*	1,983	
	1,25	0,5	2,285			0,90	*	2,211	
	1,32	0,5	2,425			1,00	*	2,435	
	1,40	0,5	2,585			1,12	0,5	2,753	
	2,12	0,80	*			1,559	1,25	0,5	3,098
		0,90	*			1,734	1,40	0,5	3,495
		1,00	*		1,905	1,60	0,5	4,025	
1,12		0,5	2,160	1,80	0,65	4,407			
1,25		0,5	2,435	2,80	0,80	*	2,103		
1,40		0,5	2,753		0,85	*	2,225		
2,24		0,80	*		1,655	0,90	*	2,346	
	0,85	*	1,749		0,95	*	2,466		
	0,90	*	1,842		1,00	*	2,585		
	0,95	*	1,934		1,06	0,5	2,753		
	1,00	*	2,025		1,12	0,5	2,921		
	1,06	0,5	2,160	1,18	0,5	3,089			
	1,12	0,5	2,294	1,25	0,5	3,285			
	1,18	0,5	2,429	1,32	0,5	3,481			
	1,25	0,5	2,585	1,40	0,5	3,705			
	1,32	0,5	2,742	1,50	0,5	3,985			
	1,40	0,5	2,921	1,60	0,5	4,265			
	1,50	0,5	3,145	1,70	0,65	4,397			
	1,60	0,5	3,369	1,80	0,65	4,677			
	2,36	0,80	*	1,751					

Table A.1 (2 of 9)

Nominal width	Nominal thickness	Radius on corners	Nominal cross-section area	Nominal width	Nominal thickness	Radius on corners	Nominal cross-section area	
mm	mm	mm	mm <sup>2</sup>	mm	mm	mm	mm <sup>2</sup>	
2,50	0,90	*	1,950	3,00	1,90	0,65	4,957	
	1,00	*	2,145		2,00	0,65	5,237	
	1,12	0,5	2,429		0,80	*	2,263	
	1,25	0,5	2,735		0,90	*	2,526	
	1,40	0,5	3,089		1,00	*	2,785	
	1,60	0,5	3,561		1,12	0,5	3,145	
	0,80	*	1,863		1,25	0,5	3,535	
	0,85	*	1,970		1,40	0,5	3,985	
	0,90	*	2,076		1,60	0,5	4,585	
	0,95	*	2,181		1,80	0,65	5,037	
	1,00	*	2,285		2,00	0,65	5,637	
	1,06	0,5	2,435		3,15	0,80	*	2,383
	1,12	0,5	2,585			0,85	*	2,522
	1,18	0,5	2,736		3,75	0,80	*	2,863
3,15	0,90	*	2,661	0,90		*	3,201	
	0,95	*	2,799	1,00		*	3,535	
	1,00	*	2,935	1,12		0,5	3,985	
	1,06	0,5	3,124	1,25		0,5	4,473	
	1,12	0,5	3,313	1,40		0,5	5,035	
	1,18	0,5	3,502	1,60		0,5	5,785	
	1,25	0,5	3,723	1,80		0,65	6,387	
	1,32	0,5	3,943	2,00		0,65	7,137	
	1,40	0,5	4,195	2,24		0,65	8,037	
	1,50	0,5	4,510	4,00		2,50	0,8	8,826
	1,60	0,5	4,825			0,80	*	3,063
	1,70	0,65	4,992			0,85	*	3,245
	1,80	0,65	5,307			0,90	*	3,426
	1,90	0,65	5,622		0,95	*	3,606	
2,00	0,65	5,937	1,00		*	3,785		
2,12	0,65	6,315	1,06		0,5	4,025		
2,24	0,65	6,693	1,12		0,5	4,265		
3,35	0,80	*	2,543		1,18	0,5	4,505	
	0,90	*	2,841		1,25	0,5	4,785	
	1,00	*	3,135		1,32	0,5	5,065	
	1,12	0,5	3,537		1,40	0,5	5,385	
	1,25	0,5	3,973		1,50	0,5	5,785	
	1,40	0,5	4,475		1,60	0,5	6,185	
	1,60	0,5	5,145					
	1,80	0,65	5,667					

Table A.1 (3 of 9)

Nominal width	Nominal thickness	Radius on corners	Nominal cross-section area	Nominal width	Nominal thickness	Radius on corners	Nominal cross-section area
mm	mm	mm	mm <sup>2</sup>	mm	mm	mm	mm <sup>2</sup>
3,55	2,00	0,65	6,337	4,25	1,70	0,65	6,437
	2,24	0,65	7,141		1,80	0,65	6,837
	0,80	*	2,703		1,90	0,65	7,237
	0,85	*	2,862		2,00	0,65	7,637
	0,90	*	3,021		2,12	0,65	8,117
	0,95	*	3,179		2,24	0,65	8,597
	1,00	*	3,335		2,36	0,8	8,891
	1,06	0,5	3,548		2,50	0,8	9,451
	1,12	0,5	3,761		2,65	0,8	10,05
	1,18	0,5	3,974		2,80	0,8	10,65
	1,25	0,5	4,223		0,80	*	3,263
	1,32	0,5	4,471		0,90	*	3,651
	1,40	0,5	4,755		1,00	*	4,035
	1,50	0,5	5,110		1,12	0,5	4,545
	1,60	0,5	5,465		1,25	0,5	5,098
	1,70	0,65	5,672		1,40	0,5	5,735
	1,80	0,65	6,027		1,60	0,5	6,585
	1,90	0,65	6,382		1,80	0,65	7,287
	2,00	0,65	6,737		2,00	0,65	8,137
	2,12	0,65	7,163		2,24	0,65	9,157
2,24	0,65	7,589	2,50	0,8	10,08		
2,36	0,8	7,829	2,80	0,8	11,35		
2,50	0,8	8,326	5,00	1,70	0,65	8,137	
0,80	*	3,463		1,80	0,65	8,637	
0,85	*	3,670		1,90	0,65	9,137	
0,90	*	3,876		2,00	0,65	9,637	
0,95	*	4,081		2,12	0,65	10,24	
1,00	*	4,285		2,24	0,65	10,84	
1,06	0,5	4,555		2,36	0,8	11,25	
1,12	0,5	4,825		2,50	0,8	11,95	
1,18	0,5	5,095		2,65	0,8	12,70	
1,25	0,5	5,410		2,80	0,8	13,45	
1,32	0,5	5,725		3,00	0,8	14,45	
1,40	0,5	6,085		3,15	0,8	15,20	
1,50	0,5	6,535		3,35	0,8	16,20	
1,60	0,5	6,985		3,55	0,8	17,20	
1,70	0,65	7,287		5,30	0,80	*	4,103
1,80	0,65	7,737			0,90	*	4,596
1,90	0,65	8,187	1,00		*	5,085	
2,00	0,65	8,637					
2,12	0,65	9,177					