

INTERNATIONAL STANDARD



**Coaxial communication cables –
Part 1-212: Environmental test methods – UV stability**

IECNORM.COM : Click to view the full PDF of IEC 61196-1-212:2021



THIS PUBLICATION IS COPYRIGHT PROTECTED
Copyright © 2021 IEC, Geneva, Switzerland

All rights reserved. Unless otherwise specified, no part of this publication may be reproduced or utilized in any form or by any means, electronic or mechanical, including photocopying and microfilm, without permission in writing from either IEC or IEC's member National Committee in the country of the requester. If you have any questions about IEC copyright or have an enquiry about obtaining additional rights to this publication, please contact the address below or your local IEC member National Committee for further information.

IEC Central Office
3, rue de Varembe
CH-1211 Geneva 20
Switzerland

Tel.: +41 22 919 02 11
info@iec.ch
www.iec.ch

About the IEC

The International Electrotechnical Commission (IEC) is the leading global organization that prepares and publishes International Standards for all electrical, electronic and related technologies.

About IEC publications

The technical content of IEC publications is kept under constant review by the IEC. Please make sure that you have the latest edition, a corrigendum or an amendment might have been published.

IEC publications search - webstore.iec.ch/advsearchform

The advanced search enables to find IEC publications by a variety of criteria (reference number, text, technical committee, ...). It also gives information on projects, replaced and withdrawn publications.

IEC Just Published - webstore.iec.ch/justpublished

Stay up to date on all new IEC publications. Just Published details all new publications released. Available online and once a month by email.

IEC Customer Service Centre - webstore.iec.ch/csc

If you wish to give us your feedback on this publication or need further assistance, please contact the Customer Service Centre: sales@iec.ch.

IEC online collection - oc.iec.ch

Discover our powerful search engine and read freely all the publications previews. With a subscription you will always have access to up to date content tailored to your needs.

Electropedia - www.electropedia.org

The world's leading online dictionary on electrotechnology, containing more than 22 000 terminological entries in English and French, with equivalent terms in 18 additional languages. Also known as the International Electrotechnical Vocabulary (IEV) online.

IECNORM.COM : Click to view the full PDF of IEC 61856-1-212:2021

INTERNATIONAL STANDARD



**Coaxial communication cables –
Part 1-212: Environmental test methods – UV stability**

INTERNATIONAL
ELECTROTECHNICAL
COMMISSION

ICS 33.120.10

ISBN 978-2-8322-9984-5

Warning! Make sure that you obtained this publication from an authorized distributor.

CONTENTS

FOREWORD.....	3
INTRODUCTION.....	5
1 Scope.....	6
2 Normative references	6
3 Terms and definitions	7
4 Test methods.....	7
4.1 Test methods for outdoor application	7
4.1.1 Method A: xenon arc source	7
4.1.2 Method B: fluorescent UV lamp.....	8
4.1.3 Method C: mercury vapour lamp	10
4.2 Test methods for indoor application	11
4.2.1 Method A: xenon arc source	11
4.2.2 Method B: fluorescent UV lamp.....	11
4.2.3 Method C: mercury vapour lamp	11
5 Measurements.....	12
5.1 Loss in mechanical properties.....	12
5.1.1 General	12
5.1.2 Defined test duration	12
5.1.3 Defined loss in property	12
5.2 Change in appearance.....	12
5.3 Change in colour.....	12
6 Evaluation of results	12
7 Test report.....	13
Annex A (informative) Example of UV test apparatus with mercury vapour lamp source	14
Annex B (informative) Guidelines to the interpretation and use	16
Bibliography.....	19
Figure A.1 – Vapour mercury test apparatus	14
Figure A.2 – Vapour mercury test apparatus – Details of construction.....	15
Table B.1 – Excerpt from MICE table	17
Table B.2 – Measurement units and conversion ^a	17

INTERNATIONAL ELECTROTECHNICAL COMMISSION

COAXIAL COMMUNICATION CABLES –

Part 1-212: Environmental test methods – UV stability

FOREWORD

- 1) The International Electrotechnical Commission (IEC) is a worldwide organization for standardization comprising all national electrotechnical committees (IEC National Committees). The object of IEC is to promote international co-operation on all questions concerning standardization in the electrical and electronic fields. To this end and in addition to other activities, IEC publishes International Standards, Technical Specifications, Technical Reports, Publicly Available Specifications (PAS) and Guides (hereafter referred to as “IEC Publication(s)”). Their preparation is entrusted to technical committees; any IEC National Committee interested in the subject dealt with may participate in this preparatory work. International, governmental and non-governmental organizations liaising with the IEC also participate in this preparation. IEC collaborates closely with the International Organization for Standardization (ISO) in accordance with conditions determined by agreement between the two organizations.
- 2) The formal decisions or agreements of IEC on technical matters express, as nearly as possible, an international consensus of opinion on the relevant subjects since each technical committee has representation from all interested IEC National Committees.
- 3) IEC Publications have the form of recommendations for international use and are accepted by IEC National Committees in that sense. While all reasonable efforts are made to ensure that the technical content of IEC Publications is accurate, IEC cannot be held responsible for the way in which they are used or for any misinterpretation by any end user.
- 4) In order to promote international uniformity, IEC National Committees undertake to apply IEC Publications transparently to the maximum extent possible in their national and regional publications. Any divergence between any IEC Publication and the corresponding national or regional publication shall be clearly indicated in the latter.
- 5) IEC itself does not provide any attestation of conformity. Independent certification bodies provide conformity assessment services and, in some areas, access to IEC marks of conformity. IEC is not responsible for any services carried out by independent certification bodies.
- 6) All users should ensure that they have the latest edition of this publication.
- 7) No liability shall attach to IEC or its directors, employees, servants or agents including individual experts and members of its technical committees and IEC National Committees for any personal injury, property damage or other damage of any nature whatsoever, whether direct or indirect, or for costs (including legal fees) and expenses arising out of the publication, use of, or reliance upon, this IEC Publication or any other IEC Publications.
- 8) Attention is drawn to the Normative references cited in this publication. Use of the referenced publications is indispensable for the correct application of this publication.
- 9) Attention is drawn to the possibility that some of the elements of this IEC Publication may be the subject of patent rights. IEC shall not be held responsible for identifying any or all such patent rights.

IEC 61196-1-212 has been prepared by subcommittee 46A: Coaxial cables, of IEC technical committee 46: Cables, wires, waveguides, RF connectors, RF and microwave passive components and accessories. It is an International Standard.

The text of this International Standard is based on the following documents:

Draft	Report on voting
46A/1452/CDV	46A/1487/RVC

Full information on the voting for its approval can be found in the report on voting indicated in the above table.

The language used for the development of this International Standard is English.

This document was drafted in accordance with ISO/IEC Directives, Part 2, and developed in accordance with ISO/IEC Directives, Part 1 and ISO/IEC Directives, IEC Supplement, available at www.iec.ch/members_experts/refdocs. The main document types developed by IEC are described in greater detail at www.iec.ch/standardsdev/publications.

A list of all parts in the IEC 61196 series, published under the general title *Coaxial communication cables*, can be found on the IEC website.

The committee has decided that the contents of this document will remain unchanged until the stability date indicated on the IEC website under webstore.iec.ch in the data related to the specific document. At this date, the document will be

- reconfirmed,
- withdrawn,
- replaced by a revised edition, or
- amended.

IMPORTANT – The "colour inside" logo on the cover page of this document indicates that it contains colours which are considered to be useful for the correct understanding of its contents. Users should therefore print this document using a colour printer.

IECNORM.COM : Click to view the full PDF of IEC 61196-1-212:2021

INTRODUCTION

UV hazard assessment for synthetic compounds is possible using a number of UV sources. For the purposes of this document, three alternative methods are given.

- 1) Method A uses a xenon arc source to simulate the UV effect on cable sheath. The effect is measured by the variation of mechanical characteristics and/or change in colour after exposure.
- 2) Method B uses a fluorescent lamp to simulate the UV effect on cable sheath. Two different lamps may be used: type I (called UV-A lamps) and type II (called UV-B lamps). The effect is measured, as for method A, by the variation of mechanical characteristics and/or change in colour after exposure.
- 3) Method C uses a mercury vapour lamp to simulate the UV effect on cable sheath. As for methods A and B, the effect is determined by the variation of mechanical characteristics and/or change in colour after exposure. This test has been typically used for telecommunication cables.

For outdoor cable application only, the test specimens are periodically subjected to water attack, for methods A and B. A recent modification of method C now allows for a water immersion cycle.

For method C, the round robin tests made without water (see Annex B) indicate the method may be applicable to outdoor environments.

Other sources and determination methods are capable of detecting and analysing the UV hazard for a cable sheath. Examples of such methods are metal halide lamps or sunshine carbon arc lamps, in combination with proper filters in order to cut off most radiation having wavelengths lower than 290 nm. Contracting parties may agree to use such other methods, but such methods cannot claim conformity to this document. If used, it is recommended that such methods have at least equivalent sensitivity and detection levels as those in this document.

Informative Annex B gives guidelines for the use and interpretation of results.

NOTE It is useful to recall the introduction to ISO 4892-1:2016, which says, "*The relative durability of materials in actual-use exposures can be very different depending on the location of the exposure because of differences in UV radiation, time of wetness, temperature, pollutants and other factors. Therefore, even if results from a specific accelerated laboratory test are found to be useful for comparing the relative durability of materials exposed in a particular outdoor location or in particular actual-use conditions, it cannot be assumed that they will be useful for determining the relative durability of materials exposed in a different outdoor location or in different actual-use conditions.*"

COAXIAL COMMUNICATION CABLES –

Part 1-212: Environmental test methods – UV stability

1 Scope

This part of IEC 61196 describes three methods to determine the UV resistance of sheath materials for electric and optical fibre cables. These tests apply for outdoor and indoor cable applications according to the product standard. The samples of sheath are taken from the finished cables.

Although this test method is written principally for communication cables, it can be used for energy cables if called up by the relevant product standard.

Where a sheath is of cross-linked (thermosetting) material, it is recalled that the preparation of moulded plaques is made before crosslinking.

Methods differ by the nature of the UV source.

Due to the excessive time to failure, the methods described are inappropriate to products where UV resistance is conferred by $\geq 2,0$ % carbon black content meeting the requirements defined in IEC 60708.

2 Normative references

The following documents are referred to in the text in such a way that some or all of their content constitutes requirements of this document. For dated references, only the edition cited applies. For undated references, the latest edition of the referenced document (including any amendments) applies.

IEC 60708, *Low-frequency cables with polyolefin insulation and moisture barrier polyolefin sheath*

IEC 60811-202, *Electric and optical fibre cables – Test methods for non-metallic materials – Part 202: General tests – Measurement of thickness of non-metallic sheath*

IEC 60811-501, *Electric and optical fibre cables – Test methods for non-metallic materials – Part 501: Mechanical tests – Tests for determining the mechanical properties of insulating and sheathing compounds*

ISO 4892-1:2016, *Plastics – Methods of exposure to laboratory light sources – Part 1: General guidance*

ISO 4892-2, *Plastics – Methods of exposure to laboratory light sources – Part 2: Xenon-arc lamps*

ISO 9370, *Plastics – Instrumental determination of radiant exposure in weathering tests – General guidance and basic test method*

EN 16472, *Plastics – Method for artificial accelerated photoageing using medium pressure mercury vapour lamps*

3 Terms and definitions

For the purposes of this document, the following terms and definitions apply.

ISO and IEC maintain terminological databases for use in standardization at the following addresses:

- IEC Electropedia: available at <http://www.electropedia.org/>
- ISO Online browsing platform: available at <http://www.iso.org/obp>

3.1

median value

when several test results have been obtained and ordered in an increasing (or decreasing) succession, middle value if the number of available values is odd, and mean of the two middle values if the number is even

[SOURCE: IEC 60811-100:2012, 3.1]

4 Test methods

4.1 Test methods for outdoor application

4.1.1 Method A: xenon arc source

4.1.1.1 General

According to ISO 4892-1:2016, Clause C.2, the xenon arc lamp, when appropriately filtered, produces radiations with a spectral power distribution that is a good simulation of average daylight throughout the UV and visible region.

The exposure apparatus is typically constituted by a rotating specimen holder drum, which rotates around the light source, as per ISO 4892-1:2016, Figure A.1.

Apparatus having a fixed specimen holder is also permitted. In this case, it is important that air can circulate around the sample to allow a homogeneous repartition of temperature.

4.1.1.2 Apparatus

The testing apparatus is equipped with the following lamps and filters and is set with the parameters prescribed below:

- a ray source consisting of a xenon arc lamp ("long arc" type) equipped with borosilicate filters so that the typical irradiance should be 43 W/m^2 ($1 \pm 15 \%$) with a spectrum between 300 nm and 400 nm;
- a means to provide automatic control of temperature, humidity and cycles;
- a generator of deionised water with a conductivity not greater than $5 \mu\text{S/cm}$ (the pH should be recorded); the water shall leave no observable stains or deposits and should therefore contain less than 1 ppm of solids; the rate of flow should be sufficient to guarantee that all the test specimens can be washed;
- a means to control the irradiance to produce $(43,0 \pm 0,2) \text{ W/m}^2$ at 340 nm (if the apparatus is not equipped with irradiance control, follow the device manufacturer's recommendations to produce this irradiance).

More details are given in ISO 4892-2.

4.1.1.3 Sample and test specimen preparation

A sample, at least 600 mm long, shall be taken of the finished cable or of the outer sheath removed from the finished cable. It shall be used to prepare 12 test specimens. Test specimens shall be prepared according to IEC 60811-202.

In case, for geometrical reasons, it is not possible to use the above samples (finished cable or outer sheath), test specimens shall be cut from a finished cable, a moulded plaque prepared from pieces of the cable sheath or a moulded plaque produced from granules of the same material and colour of the cable sheath. The thickness of the test pieces shall be $(1,0 \pm 0,1)$ mm.

4.1.1.4 Procedure

Six test specimens shall be suspended vertically so that the external surface is uniformly exposed to the action of the actinic rays. During the test, the temperature indicated by the black-panel or the black-standard thermometer shall remain in the range (60 ± 3) °C and the relative humidity shall remain in the range of (50 ± 5) % (only in the dry period in the case of a test for outdoor application). The rotating drum carrying the test specimens shall turn at a speed of $(1 \pm 0,1)$ r/min. If a flat specimen plane is used, the minimum irradiance in any point of the specimen exposure area shall be at least 90 % of maximum irradiance.

Test specimens are cycled through periods of UV exposure, followed by periods of no radiation during which temperature changes occur.

The periods of each cycle, total time of 120 min, are the following:

- 102 min of dry UV exposure at a temperature of (60 ± 3) °C¹, followed by
- 18 min of deionised water exposure, without radiation, at a temperature of (50 ± 5) °C.

The overall duration of the test shall be as defined in the relevant product standard. In the absence of such a definition, guidance is given in Annex B.

After the exposure, the exposed test specimens shall be removed from the equipment and conditioned at ambient temperature for at least 16 h.

The six other test specimens shall be kept at ambient temperature and protected from any light source during the UV treatment; they shall be tested at the same time as the exposed test specimens.

4.1.2 Method B: fluorescent UV lamp

4.1.2.1 General

According to ISO 4892-3:2016 [6]², 4.1.1, there are different types of fluorescent UV lamps that may be used as laboratory light sources:

- type I lamps (commonly called UV-A lamps), with the preferred option of the UV-A 340 lamp, having a spectral radiation that peaks at 340 nm;
- type II lamps (commonly called UV-B lamps), having a spectral radiation that peaks near the 313 nm mercury line; these type II fluorescent UV lamps emit significant amount of radiation below 300 nm, the nominal cut off wavelength for solar radiation, which may result in ageing processes not completely equal to those occurring outdoors. The method using UV-B lamps is however frequently used by agreement between the parties.

¹ Temperature indicated by the black-panel or the black-standard thermometer.

² Numbers in square brackets refer to the Bibliography.

The exposure apparatus is typically constituted by a device where specimens are positioned in a flat plane in front of an array of light sources, as per ISO 4892-1:2016, Figure A.2.

4.1.2.2 Apparatus

The testing apparatus is equipped as follows:

- a ray source consisting of type I or type II fluorescent UV lamps, having a typical irradiance peak of at least $0,68 \text{ W/m}^2$ at 340 nm for the UV-A 340 lamp, and at 313 nm for the UV-B 313 lamp;
- an exposure chamber constructed from inert material, such as to provide uniform irradiance, with a means for controlling temperature and cycles and a means for providing the formation of water condensate on the exposed face of the specimens;
- a means to control the specified value of irradiance or, if the apparatus is not equipped with irradiance control, follow the device manufacturer's recommendations on the procedure necessary to maintain the required irradiance.

4.1.2.3 Sample and test specimen preparation

See 4.1.1.3.

4.1.2.4 Procedure

Six test specimens shall be mounted so that the exposed face is uniformly exposed to the action of the actinic rays.

Depending on the apparatus, lamp replacement, lamp rotation and test specimens, re-arrangement may be required to obtain uniform exposure of all specimens to UV radiation and temperature. In such a case, follow the manufacturer's recommendations for lamp replacement/rotation or for the re-arrangement of the test specimens.

Test specimens are cycled through periods of UV exposure, followed by periods of no radiation during which temperature changes occur and condensation forms on the specimens.

The periods of each cycle, total time of 720 min, are the following:

- 600 min of dry UV exposure at a temperature of $(60 \pm 3) \text{ }^\circ\text{C}^3$, followed by
- 120 min of condensation exposure, without radiation, at a temperature of $(50 \pm 3) \text{ }^\circ\text{C}^3$.

For coloured compounds, a black-standard temperature of $(60 \pm 3) \text{ }^\circ\text{C}$ shall be used.

The overall duration of the test shall be as defined in the relevant product standard. In the absence of such a definition, guidance is given in Annex B.

After the exposure, the exposed test specimens shall be removed from the equipment and conditioned at ambient temperature for at least 16 h.

The six other test specimens shall be kept at ambient temperature and protected from direct sunlight during the UV treatment; they shall be tested at the same time as the exposed test specimens.

3 Temperature indicated by the black-panel or the black-standard thermometer.

4.1.3 Method C: mercury vapour lamp

4.1.3.1 General

EN 16472 specifies a method for carrying out artificial accelerated photoageing of test specimens by exposing them to medium pressure filtered mercury vapour lamp as light source, under controlled temperature conditions. An example of a test chamber is shown in Annex A.

4.1.3.2 Apparatus

The apparatus shall consist of a test chamber as described in EN 16472.

The UV irradiance, between 300 nm to 400 nm, is typically controlled in the range $(90 \pm 10) \text{ W/m}^2$ by mean of an additional radiometer, according to ISO 9370.

The drum carrying the test specimens shall rotate at a minimal speed of 0,5 r/min.

4.1.3.3 Sample and test specimen preparation

Twelve test specimens shall be cut from a moulded plaque of the same material as the cable sheath to be tested. The material used for the test specimens shall have the same composition as the relevant cable sheath, and be of the same colour.

Test specimens shall be prepared according to IEC 60811-202; the thickness shall be $(1,0 \pm 0,1) \text{ mm}$.

In case, for geometrical reasons, it is not possible to use the above samples (finished cable or outer sheath), test specimens shall be cut from a finished cable, a moulded plaque prepared from pieces of the cable sheath or a moulded plaque produced from granules of the same material and colour of the cable sheath. The thickness of the test pieces shall be $(1,0 \pm 0,1) \text{ mm}$.

4.1.3.4 Procedure

Six test specimens shall be suspended vertically so that the surface is exposed to the action of the UV lamp. During the test, the temperature of the temperature sensor shall remain in the range of $(60 \pm 2) \text{ }^\circ\text{C}$.

The overall duration of the test shall be as defined in the relevant product standard. In the absence of such a definition, guidance is given in Annex B.

After the exposure, the exposed test specimens shall be removed from the equipment and conditioned at ambient temperature for at least 16 h.

The six other test specimens shall be kept at ambient temperature and protected from direct sunlight during the UV treatment; they shall be tested at the same time as the exposed test specimens.

If an immersion cycle is used, the kind of aqueous solution, the frequency, temperature and duration of the immersion shall be reported.

If dark periods are introduced in the cycle, their frequency, temperature and duration shall be reported.

Cycles shall be agreed upon by the interested parties.

4.2 Test methods for indoor application

4.2.1 Method A: xenon arc source

4.2.1.1 General

See 4.1.1.1.

4.2.1.2 Apparatus

The testing apparatus is equipped with the following lamps and filters and is set with the parameters prescribed below:

- a ray source consisting of a xenon arc lamp ("long arc" type) equipped with borosilicate filters so that the typical irradiance should be $(43,0 \pm 0,2)$ W/m² at 340 nm;
- a means to provide automatic control of temperature and cycles;
- a means to control the irradiance to produce $(43,0 \pm 0,2)$ W/m² at 340 nm (if the apparatus is not equipped with irradiance control, follow the device manufacturer's recommendations to produce this irradiance).

4.2.1.3 Sample and test specimen preparation

See 4.1.1.3.

4.2.1.4 Procedure

Six test specimens shall be suspended vertically so that the external surface is uniformly exposed to the action of the actinic rays. During the test, the temperature indicated by the black-panel or the black-standard thermometer shall remain in the range (60 ± 3) °C.

The rotating drum carrying the test specimens shall turn at a speed of $(1 \pm 0,1)$ r/min. If a flat specimen plane is used, the minimum irradiance in any point of the specimen exposure area shall be at least 90 % of maximum irradiance.

Test specimens are cycled through periods of UV exposure, followed by periods of no radiation during which no temperature changes occur.

The periods of each cycle, total time of 120 min, are the following:

- 102 min of dry UV exposure at a black-standard temperature of (60 ± 3) °C, followed by
- 18 min without radiation, at a black-standard temperature of (60 ± 3) °C.

The overall duration of the test shall be as defined in the relevant product standard. In the absence of such a definition, guidance is given in Annex B.

After the exposure, the exposed test specimens shall be removed from the equipment and conditioned at ambient temperature for at least 16 h.

The six other test specimens shall be kept at ambient temperature and protected from direct sunlight during the UV treatment; they shall be tested at the same time as the exposed test specimens.

4.2.2 Method B: fluorescent UV lamp

See 4.1.2.

4.2.3 Method C: mercury vapour lamp

See 4.1.3.

An additional standard window glass filter (3 mm of thickness) shall be placed between the exposed test specimen and the source (not too close to the test specimen exposed surface to prevent any abnormal heating).

5 Measurements

5.1 Loss in mechanical properties

5.1.1 General

After the appropriate procedure of Clause 4, the mechanical properties of the exposed and the unexposed test pieces shall be measured in accordance with IEC 60811-501. The performance requirements for a particular type or class of cable should preferably be given in the relevant cable standard. In the absence of specific requirements, either of the following options may be applied.

5.1.2 Defined test duration

After exposure for the specified duration, the variation of tensile strength and elongation at break shall be less than $\pm 30\%$ compared to a reference sample tested at the same time.

5.1.3 Defined loss in property

Samples should be periodically removed from the test chamber and tested for their tensile strength and elongation at break. The results should be plotted with time as the x-axis. By interpolation, the time at which the sample has lost 50 % of their initial tensile strength or elongation may be estimated. Normally it is found that the loss of elongation is the parameter most sensitive to UV degradation. This approach requires far more samples to be exposed (e.g. 6 samples per exposure time). To minimize equipment loading, it may be found helpful to use some other technique (such as oxidative induction time (ISO 11357-6) [5]) to monitor the depletion in stabilizer.

5.2 Change in appearance

In the absence of a specific requirement in the product standard or specification, any change of appearance (specifically cracking or other textural change) should be recorded and added to the test report.

5.3 Change in colour

In the absence of a specific requirement in the product standard or specification, any change of colour should be recorded and added to the test report.

For further study.

6 Evaluation of results

Calculate the tensile strength and the elongation at break, according to the definitions given in IEC 60811-501.

The values found for the exposed test specimens shall be calculated as a variation compared to the unexposed test specimens and according to the following formulae:

$$V_T = \frac{T_E - T_U}{T_U} 100 \quad (1)$$

$$V_E = \frac{E_E - E_U}{E_U} 100 \quad (2)$$

where

V_T is the variation of the tensile strength in percent;

T_E is the tensile strength of the aged test specimen;

T_U is the tensile strength of the untreated test specimen;

V_E is the variation of the elongation at break in percent;

E_E is the elongation at break of the aged test specimen in percent;

E_U is the elongation at break of the untreated test specimen in percent.

The value and the variation between the median value obtained of the test specimens exposed and the median value of the values obtained for the unexposed test specimens (see IEC 60811-501), expressed as a percentage of the latter, shall not exceed the percentage specified in the standard for the material in the relevant standard for the type of cable.

7 Test report


The test report shall include:

- type and model of exposure device;
- method, light source and wattage;
- type and age of filters;
- spectral irradiance at sample location, W/m²;
- irradiation, kJ/m²;
- elapsed exposure time, h;
- light, dark, water, or humidity programme employed (not applicable for indoor test);
- type of thermometer (black-panel or black standard) to indicate the temperature;
- operating temperature;
- operating relative humidity (if any);
- type of water spray (if any);
- conductivity (or pH) of water used for specimens spray (if any, not applicable for a test for indoor application);
- type of spray nozzle (if any, not applicable for a test for indoor application);
- test pieces relocation procedure;
- type of specimens – pieces of cable, mouldings from pieces of cable or mouldings from granules;
- variation of tensile strength, in percent;
- results of the visual inspection (possible cracks or their absence);
- variation of elongation at break, in percent;
- determination of colour (if specified).

Annex A (informative)

Example of UV test apparatus with mercury vapour lamp source

An example of the test chamber is shown in Figure A.1. A vapour mercury test apparatus is shown in Figure A.2.

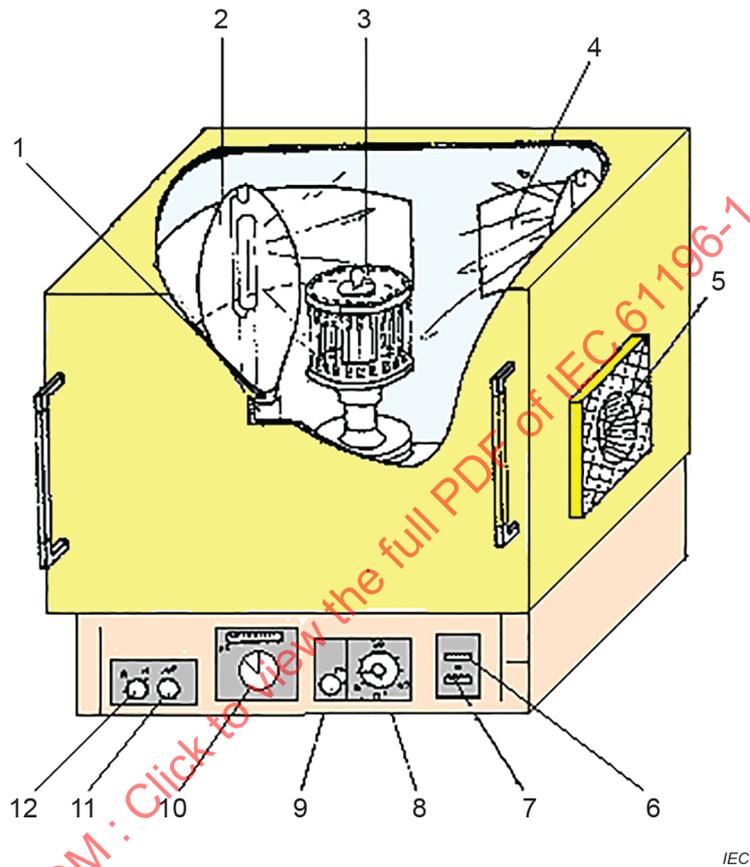

IEC

Key

- | | | | |
|---|-------------------------|----|--------------------------------|
| 1 | checking device | 7 | hour indicator checking device |
| 2 | UV lamp | 8 | timing device |
| 3 | test specimens holder | 9 | selection for timing |
| 4 | light reflecting device | 10 | temperature regulation device |
| 5 | fan | 11 | feed |
| 6 | general hour indicator | 12 | interrupter |

Figure A.1 – Vapour mercury test apparatus – Test chamber

Annex B (informative)

Guidelines to the interpretation and use

This document describes methodologies to perform artificial accelerated UV ageing. The three test methods described in this document have each different advantages and disadvantages. It is a matter for the product standard and/or the user to choose which of the three methods is applicable in each case. Some guidance on this is given below.

- "Artificial" means that the light is artificially produced with equivalence to a greater or lesser extent to the natural light spectrum. For the consideration of oxidative degradation, it is important that the lamp wavelength be above 295 nm to 300 nm, which corresponds to the lowest wavelength of natural light. Exposure below these wavelengths could lead to a poor correlation with outdoor weathering.
- "Accelerated" means that the degradation is faster in comparison to natural exposure. As the specimen undergoes photo-oxidation, acceleration is due to the severe light exposure (high irradiance) and also to the increase of the temperature (often around 60 °C) in the test cell. Thus, simple irradiance comparisons could lead to erroneous data because of the temperature factor.
- The acceleration factor (used for lifetime prediction) which could be calculated to quantify the acceleration produced between artificial and natural ageing depends on several parameters:
 - the compound (i.e. the polymer type, the formulation - amount and type of additives, anti-oxidant etc.);
 - the test device (i.e. type of lamp, the irradiance, the temperature, the type of cycle etc.);
 - the climatic conditions at the outdoor destination.

Thus, generalities and empirical factors that are not confirmed by experiments could lead to erroneous lifetime estimation. To aid the interpretation of data, the use of standardised test conditions is strongly recommended.

- Due to the excessive time to failure, the methods described are inappropriate to products where UV resistance is conferred by $\geq 2,0$ % carbon black content meeting the requirements⁴ defined in IEC 60708. Such products should be deemed to satisfy MICE C1, C2 and C3 (see Table B.1).

In 2005 to 2007, a round robin comparing the methods specified in the European Standard EN 50289-4-17 was completed [7]. One of the targets of the work is to see if there is any correlation between the methods. The approach taken is to attempt to define by inspection, limits which would give the same pass/fail result for each method.

- For unstabilized LLDPE, the xenon (wet) exposure was < 504 h, the xenon (dry) exposure 720 h to 1 500 h, the UVA < 720 h, the UVB 504 h to 720 h and the Hg lamp < 350 h. The results suggest that the xenon (wet), the UVA and UVB give deterioration in the same order of magnitude. The xenon (dry) is less severe and the Hg lamp is significantly more severe. For UV stabilized LLDPE, none of the methods caused a significant deterioration.
- For EPR, the xenon (dry) and Hg lamp need the same order of exposure duration and for the QUVB just 10 % of the xenon duration. The consistency of results across the three test methods is remarkable.
- For TPU/C, the Hg lamp needs 50 % of the xenon duration, the QUVA is similar to the xenon and the QUVB again just 2 % of the xenon duration.

⁴ In some jurisdictions, the carbon black dispersion is specified by an absorption coefficient greater than 400 per millimetre.

It is clear that the sensitivity is polymer dependent.

Performance level for a number of mechanical, ingress, climatic and electromagnetic (MICE) parameters including UV ageing [14], [9] were defined. These parameters are to be applied to cables. Three classes are identified (1-3), where class 3 represents the most demanding requirement. In MICE Table 9 [9] summarizing details of environmental class, the following values relating to weathering/UV resistance of materials are defined.

Table B.1 – Excerpt from MICE table

	C1	C2	C3
Solar radiation (wavelength ffs)	700 W/m ²	1 120 W/m ²	1 120 W/m ²
UV exposure	500 h	3 000 h	6 000 h

The value for irradiance of 1 120 W/m² corresponds to full spectrum (Table B.1). The value 700 W/m² is not specifically mentioned in IEC 60068-2-5 [17] but it presumably corresponds to the UV and visible spectrum. In a report 10 concerning the development of a blank detail specification in support of ISO/IEC 24702 [4], the source of solar radiation levels is described as follows: "The three climatic environments of the MICE concept use two limits (700 W/m² or 1 120 W/m²). These values are taken from IEC 60068-2-5 which defines a power spectrum across a wavelength range. Solar radiation may influence both mechanical and cosmetic (colour change) properties. We look forward to receiving your input for pass/fail criteria."

Some measurement units and conversion factors are shown in Table B.2. The unit Langley is sometimes used to measure radiant exposure when subjecting materials to natural weathering, and corresponds to 1 calorie per square centimetre of irradiated surface. As the term implies all wavelengths of the solar spectrum, it cannot be directly related to artificial light sources.

Table B.2 – Measurement units and conversion ^a

1 kilo-Langley (1 kLy)	41,84 MJ/m ²
Xenon lamp: $E = 0,35 \text{ W/m}^2 \text{ nm}$ ($\lambda = 340 \text{ nm}$); $E = 30 \text{ W/m}^2$ ($\lambda = 300 \text{ nm to } 385 \text{ nm}$)	
1 h WOM ($30 \text{ W/m}^2 \times 3 600 \text{ s}$)	0,108 MJ/m ²
1 year WOM	946 MJ/m ²
1 year Basel (global $\lambda = 295 \text{ nm to } 3 000 \text{ nm}$)	4 200 MJ/m ² = 100 kLy
1 year Florida (global $\lambda = 295 \text{ nm to } 3 000 \text{ nm}$)	6 000 MJ/m ² = 144 kLy
1 year Basel (UV irradiation $\lambda = 295 \text{ nm to } 385 \text{ nm}$)	165 MJ/m ²
1 year Florida (UV irradiation $\lambda = 295 \text{ nm to } 385 \text{ nm}$)	285 MJ/m ²
^a See [1], [2] and [12].	

EXAMPLE 1 Assuming that the UV part of the spectrum is the most important part of light for degradation of a polymeric material, the relation between natural weathering in Florida and laboratory weathering in a Weather-Ometer (WOM) can be estimated. The UV radiant exposure per year in Florida is 285 MJ/m². The same level is