

# INTERNATIONAL STANDARD

**IEC**  
**61965**

Second edition  
2003-07

---

---

## **Mechanical safety of cathode ray tubes**

*Sécurité mécanique des tubes cathodiques*

IECNORM.COM : Click to view the full PDF of IEC 61965:2003



Reference number  
IEC 61965:2003(E)

## Publication numbering

As from 1 January 1997 all IEC publications are issued with a designation in the 60000 series. For example, IEC 34-1 is now referred to as IEC 60034-1.

## Consolidated editions

The IEC is now publishing consolidated versions of its publications. For example, edition numbers 1.0, 1.1 and 1.2 refer, respectively, to the base publication, the base publication incorporating amendment 1 and the base publication incorporating amendments 1 and 2.

## Further information on IEC publications

The technical content of IEC publications is kept under constant review by the IEC, thus ensuring that the content reflects current technology. Information relating to this publication, including its validity, is available in the IEC Catalogue of publications (see below) in addition to new editions, amendments and corrigenda. Information on the subjects under consideration and work in progress undertaken by the technical committee which has prepared this publication, as well as the list of publications issued, is also available from the following:

- **IEC Web Site** ([www.iec.ch](http://www.iec.ch))

- **Catalogue of IEC publications**

The on-line catalogue on the IEC web site ([www.iec.ch/searchpub](http://www.iec.ch/searchpub)) enables you to search by a variety of criteria including text searches, technical committees and date of publication. On-line information is also available on recently issued publications, withdrawn and replaced publications, as well as corrigenda.

- **IEC Just Published**

This summary of recently issued publications ([www.iec.ch/online\\_news/justpub](http://www.iec.ch/online_news/justpub)) is also available by email. Please contact the Customer Service Centre (see below) for further information.

- **Customer Service Centre**

If you have any questions regarding this publication or need further assistance, please contact the Customer Service Centre:

Email: [custserv@iec.ch](mailto:custserv@iec.ch)  
Tel: +41 22 919 02 11  
Fax: +41 22 919 03 00

# INTERNATIONAL STANDARD

# IEC 61965

Second edition  
2003-07

---

---

## Mechanical safety of cathode ray tubes

*Sécurité mécanique des tubes cathodiques*

IECNORM.COM : Click to view the full PDF of IEC 61965:2003

© IEC 2003 — Copyright - all rights reserved

No part of this publication may be reproduced or utilized in any form or by any means, electronic or mechanical, including photocopying and microfilm, without permission in writing from the publisher.

International Electrotechnical Commission, 3, rue de Varembé, PO Box 131, CH-1211 Geneva 20, Switzerland  
Telephone: +41 22 919 02 11 Telefax: +41 22 919 03 00 E-mail: inmail@iec.ch Web: www.iec.ch



Commission Electrotechnique Internationale  
International Electrotechnical Commission  
Международная Электротехническая Комиссия

PRICE CODE

**XA**

*For price, see current catalogue*

## CONTENTS

FOREWORD .....	5
INTRODUCTION .....	6
1 Scope .....	7
2 Normative references.....	7
3 Definitions .....	8
4 General requirements .....	9
4.1 Corrosion protection .....	9
4.2 Mechanical damage.....	9
4.3 Handling .....	9
4.4 Film-coated CRTs.....	9
5 Environmental conditioning .....	10
5.1 Standard atmospheric conditions for testing.....	10
5.2 Preconditioning.....	10
5.3 Thermal conditioning .....	10
6 Sampling .....	10
6.1 Sampling plans .....	10
6.2 Sample numbers.....	10
6.3 Compliance .....	10
7 Test preparation and set-up .....	10
7.1 Scratch patterns .....	10
7.2 Barriers .....	11
7.3 Mounting .....	11
7.4 Mounting position .....	11
8 Testing of large CRTs.....	11
8.1 Mechanical strength (ball impact test).....	11
8.2 Implosion test (missile).....	12
8.3 Implosion test (thermal shock).....	13
8.4 High-energy impact test.....	13
9 Testing of small CRTs.....	14
9.1 Mechanical strength (ball impact test).....	14
9.2 Implosion test (high ball).....	15
9.3 Implosion test (thermal shock) .....	15
9.4 High-energy impact test.....	15
10 Testing of prestressed banded CRTs with protective film .....	16
10.1 General .....	16
10.2 Film scoring pattern for CRTs with protective film .....	16
10.3 Peel test.....	17
10.4 Immersion test.....	17
11 Marking .....	17
12 Application notes for pre-stressed banded CRTs with protective film.....	18
13 Normative requirements for the use of Tables 1 and 2 (prestressed banded CRTs) .....	18
13.1 Sampling plan I: New construction .....	18
13.2 Sampling plan II: New construction with known resin or tape .....	19
13.3 Sampling plan III: Tension band and alternative tension band.....	19
13.4 Sampling plan IV: Alternative construction .....	20

14	Normative requirements for the use of Tables 3 and 4 (prestressed banded with protective film).....	21
14.1	Sampling plan I: New construction.....	21
14.2	Sampling plan II: New construction with known resin, tape, film or adhesive.....	22
14.3	Sampling plan III: Alternative tension band.....	22
14.4	Sampling plan IV: Alternative construction.....	23
15	Alternative thermal conditioning for use with Tables 3 and 4 (prestressed banded with protective film).....	24
15.1	Additional peel force requirements where alternative thermal conditioning is to be performed.....	24
15.2	Tensile strength test where alternative thermal conditioning is to be performed.....	24
16	Normative requirements for the use of Tables 6 and 7 (bonded frame CRTs).....	25
16.1	Sampling plan I: New construction.....	25
16.2	Sampling plan II: Alternative construction.....	26
17	Normative requirements for the use of Tables 8 and 9 (laminated CRTs).....	26
17.1	Sampling plan I: New construction.....	26
17.2	Sampling plan II: Alternative construction.....	26
	Annex A (informative) Background to the development of this standard.....	46
A.1	Mechanical strength test.....	47
A.2	Implosion test.....	47
A.3	Small CRTs (76 mm to 160 mm diagonal).....	47
A.4	Evaluation time.....	47
	Annex B (informative) Velocity and potential force of glass particles expelled from a CRT subjected to a ball impact – Ballistic and statistical calculations.....	48
B.1	Introduction.....	48
B.2	Analysis without friction.....	48
B.3	Analysis with friction.....	54
B.4	Potential threat.....	57
B.5	Conclusions.....	57
	Figure 1 – Example of a test cabinet.....	35
	Figure 2 – Example of a ball impact test.....	36
	Figure 3 – Example of a 2,3 kg steel missile.....	37
	Figure 4 – Missile impact area on a typical CRT.....	38
	Figure 5 – Example of a missile impact test.....	39
	Figure 6 – Options for scratch patterns for implosions by the thermal shock method.....	40
	Figure 7 – Film scoring tool.....	41
	Figure 8 – Example of high-energy impact test set-up.....	42
	Figure 9 – Steel pins used in high-energy impact test.....	43
	Figure 10 –Weights used in high-energy impact test.....	44
	Figure 11 – Example of 1,4 kg steel missile.....	45
	Figure B.1 – Height of the barriers and distances from the CRT face.....	48

Figure B.2 – Example of the parabolic trajectory of a glass particle and the definition of the distances.....	49
Figure B.3 – Definition of the initial angle and initial velocity and the forces acting on a particle.....	50
Figure B.4 – Initial velocity required to pass over barriers at $x = l_1$ (solid line) or $x = l_2$ (dashed line) as a function of the initial angle $\beta$ .....	52
Figure B.5 – Trajectories for a glass particle for different initial angles and an initial velocity of 4 m/s .....	52
Figure B.6 – Definition of the forces acting on a particle.....	54
Figure B.7 – Measurements of a typical glass particle .....	55
Figure B.8 – Trajectory of a glass particle with an initial velocity of 2 m/s and an initial angle of 45° without friction (dashed line) and with friction (solid line) .....	56
Figure B.9 – Trajectories of a glass particle with an initial velocity of 2 m/s and an initial angle of 45° for different values of the cross-sectional area .....	57
Table 1 – Sampling and test programme for prestressed banded CRTs exceeding 160 mm diagonal.....	27
Table 2 – Sampling and test programme for prestressed banded CRTs from 76 mm to 160 mm diagonal.....	28
Table 3 – Sampling and test programme for prestressed banded CRTs with protective film exceeding 160 mm diagonal .....	29
Table 4 – Sampling and test programme for prestressed banded CRTs with protective film from 76 mm to 160 mm diagonal.....	30
Table 5 – Sampling and test programme for adhesion of film used in CRTs with protective film (tested according to Tables 3 and 4) .....	31
Table 6 – Sampling and test programme for bonded frame CRTs exceeding 160 mm diagonal.....	32
Table 7 – Sampling and test programme for bonded frame CRTs from 76 mm to 160 mm diagonal.....	32
Table 8 – Sampling and test programme for laminated CRTs exceeding 160 mm diagonal.....	33
Table 9 – Sampling and test programme for laminated CRTs from 76 mm to 160 mm diagonal.....	33
Table 10 – CRT size and deflection angle ranges.....	34
Table B.1 – Values of the distances .....	49
Table B.2 – Upper and lower boundary values of the initial angle.....	51

## INTERNATIONAL ELECTROTECHNICAL COMMISSION

**MECHANICAL SAFETY OF CATHODE RAY TUBES**

## FOREWORD

- 1) The International Electrotechnical Commission (IEC) is a worldwide organization for standardization comprising all national electrotechnical committees (IEC National Committees). The object of IEC is to promote international co-operation on all questions concerning standardization in the electrical and electronic fields. To this end and in addition to other activities, IEC publishes International Standards, Technical Specifications, Technical Reports, and Guides (hereafter referred to as "IEC Publication(s)"). Their preparation is entrusted to technical committees; any IEC National Committee interested in the subject dealt with may participate in this preparatory work. International, governmental and non-governmental organizations liaising with the IEC also participate in this preparation. IEC collaborates closely with the International Organization for Standardization (ISO) in accordance with conditions determined by agreement between the two organizations.
- 2) The formal decisions or agreements of IEC on technical matters express, as nearly as possible, an international consensus of opinion on the relevant subjects since each technical committee has representation from all interested IEC National Committees.
- 3) IEC Publications have the form of recommendations for international use and are accepted by IEC National Committees in that sense. While all reasonable efforts are made to ensure that the technical content of IEC Publications is accurate, IEC cannot be held responsible for the way in which they are used or for any misinterpretation by any end user.
- 4) In order to promote international uniformity, IEC National Committees undertake to apply IEC Publications transparently to the maximum extent possible in their national and regional publications. Any divergence between any IEC Publication and the corresponding national or regional publication shall be clearly indicated in the latter.
- 5) IEC provides no marking procedure to indicate its approval and cannot be rendered responsible for any equipment declared to be in conformity with an IEC Publication.
- 6) All users should ensure that they have the latest edition of this publication.
- 7) No liability shall attach to IEC or its directors, employees, servants or agents including individual experts and members of its technical committees and IEC National Committees for any personal injury, property damage or other damage of any nature whatsoever, whether direct or indirect, or for costs (including legal fees) and expenses arising out of the publication, use of, or reliance upon, this IEC Publication or any other IEC Publications.
- 8) Attention is drawn to the Normative references cited in this publication. Use of the referenced publications is indispensable for the correct application of this publication.
- 9) Attention is drawn to the possibility that some of the elements of this IEC Publication may be the subject of patent rights. IEC shall not be held responsible for identifying any or all such patent rights.

International Standard IEC 61965 has been prepared by IEC technical committee 39: Electronic tubes.

This second edition cancels and replaces the first edition published in 2000. This second edition constitutes a technical revision.

The main change with respect to the previous edition is the inclusion of the requirements for cathode ray tubes with film attached to the face plate.

The text of this standard is based on the following documents:

FDIS	Report on voting
39/264/FDIS	39/265/RVD

Full information on the voting for the approval of this standard can be found in the report on voting indicated in the above table.

This publication has been drafted in accordance with the ISO/IEC Directives, Part 2.

The committee has decided that the contents of this publication will remain unchanged until 2005. At this date, the publication will be

- reconfirmed;
- withdrawn;
- replaced by a revised edition, or
- amended.

## INTRODUCTION

This International Standard sets forth test methods and limits for cathode ray tubes (CRTs). Originally, the only IEC standard for the mechanical safety of CRTs had been contained within Clause 18 of the equipment standard IEC 60065. Whereas that standard had been accepted and used by many countries, many others were not able to implement its requirements because of differing local needs. IEC 61965 was therefore published in 2000 with the aim of providing the basis for wider acceptance and use and reflecting the current IEC policy of producing separate component standards to which equipment standards can refer.

This 2nd edition covers the requirements for the CRTs with film attached to the faceplate as part of the safety implosion protection system.

Many years of experience had been built up in the use of both the IEC 60065 test and the other commonly used national alternatives. During the development of IEC 61965, extensive test programmes and ballistic and statistical calculations were carried out to verify that the requirements of the standard give protection for users of CRTs when the tubes are mounted in the equipment for which they are intended. This was also done to ensure that IEC 61965 maintains the stringent requirements of both IEC 60065 and the alternative tests in common use. These tests and calculations also confirmed

- a) the acceptability of one standard ball for the mechanical strength test, and
- b) the need for the implosion test where it is not always possible to induce rapid devacuation using the ball impact test.

As the impact tests in this standard are overstress tests, only the effect of rapid devacuation is evaluated and not subsequent relaxation of mechanical stresses in the CRT from the implosion protection system.

IECNORM.COM : Click to view the full PDF of IEC 61965:2003

## MECHANICAL SAFETY OF CATHODE RAY TUBES

### 1 Scope

This International Standard is applicable to cathode ray tubes and cathode ray tube assemblies (hereinafter referred to as CRTs) which are intended for use as components in apparatus and which have integral protection with respect to the effects of implosion.

These requirements apply to CRTs intended for use in apparatus including electrical and electronic measuring and testing equipment, information technology equipment, medical equipment, telephone equipment, television equipment and other similar electronic apparatus.

This standard is intended to apply only to those CRTs in which the face of the CRT forms part of the enclosure for the apparatus. The test methods do not apply to CRTs which are protected by separate safety screens.

A CRT covered by this standard is intended to be installed in an enclosure designed both to protect the rear of the CRT against mechanical or other damage under normal conditions of operation and to protect the user against particles expelled in a backwards direction from the CRT face in the event of implosion.

This standard contains requirements for CRTs of 76 mm diagonal and larger that incorporate implosion protection systems providing protection against the hazards of particles expelled forwards beyond the face. There is no intended protection against particles expelled in other directions.

Compliance is tested by subjecting CRTs to the test procedures and criteria, which are given in Clauses 8 (large CRTs), 9 (small CRTs) and 10 (CRTs with protective film) of this standard. The definitions of large and small CRTs are given in Clause 3.

NOTE This set of requirements replaces the current requirements for the mechanical safety of cathode ray tubes (CRTs) as described in IEC 60065 (Clause 18), which will be modified accordingly.

### 2 Normative references

The following referenced documents are indispensable for the application of this document. For dated references, only the edition cited applies. For undated references, the latest edition of the referenced document (including any amendments) applies.

IEC 60065:2001, *Audio, video and similar electronic apparatus – Safety requirements*

IEC 60068-1:1988, *Environmental testing – Part 1: General and guidance*  
Amendment 1 (1992)

IEC 60216-1:2001, *Electrical insulating materials – Properties of thermal endurance – Part 1: Ageing procedures and evaluation of test results*

ISO 527-1:1993, *Plastics – Determination of tensile properties – Part 1: General principles*

ISO 527-3:1995, *Plastics – Determination of tensile properties – Part 3: Test conditions for films and sheets*

ISO 8510-1:1990, *Adhesives – Peel test for a flexible-bonded-to-rigid test specimen assembly – Part 1: 90 degree peel*

### 3 Definitions

For the purposes of this document the following definitions apply.

#### 3.1

##### **bonded frame**

system employing a preformed metal frame that covers the periphery of the CRT rim area. The space or void between the CRT rim and the metal frame is filled with resin or equivalent

#### 3.2

##### **CRT diagonal**

nominal diagonal of the glass envelope at its maximum dimension (for example, mould-match line) excluding any hardware

#### 3.3

##### **CRT envelope**

structure consisting of a face or faceplate, funnel and neck assembly

#### 3.4

##### **devacuation**

equalization of the pressure in a CRT relative to the ambient pressure

#### 3.5

##### **fracture**

one or more cracks in the faceplate or funnel causing a rapid or slow devacuation of the CRT envelope

#### 3.6

##### **glass particle**

piece of glass that exceeds 0,025 g in weight

#### 3.7

##### **implosion**

devacuation due to the rapid and sudden inward collapse of a CRT envelope, usually accompanied by a loud report

#### 3.8

##### **laminated CRT**

system that provides a separate external safety panel bonded to the face of the CRT

#### 3.9

##### **prestressed banded CRT**

system that employs a metal tension band (located over the CRT rim area) that is tightened by thermal shrinking, or other means, to a tensile load. The system may also include a metal rim band located between the tension band and the CRT rim. The tension band or the rim band or both may have an interlayer of tape, resin or the equivalent placed between the mating parts

#### 3.10

##### **prestressed banded CRTs with protective film**

system employing a prestressed banded construction (see 3.9) that also includes a layer of film adhered to the CRT face as an integral component of the protection system

**3.11****shaling**

condition where the glassware splits into thin layers

**3.12****test cabinet**

enclosure, which is used to accommodate the CRT during tests

**3.13****useful phosphor screen**

a) colour CRT: the visible phosphored area of the CRT as viewed from the front

b) monochrome CRT: specified maximum useful phosphored area of the CRT

**3.14****large CRT**

CRT with diagonal dimension exceeding 160 mm

**3.15****small CRT**

rectangular CRT with a minor face dimension of at least 50 mm, a minimum diagonal dimension of 76 mm and a maximum diagonal dimension of 160 mm; a round CRT of a minimum diameter of 76 mm and a maximum diameter of 160 mm

**3.16****common quality management system**

quality management system described in documentation which is identical with systems used in two or more plants and under one central control and management

**4 General requirements****4.1 Corrosion protection**

If corrosion of a metal part will contribute to a failure to meet the requirements of this standard, then the part shall be adequately protected against corrosion.

**4.2 Mechanical damage**

To improve repeatability and reproducibility of test results, it should be verified that samples submitted for test have no external visible scratching on the surface of the faceplates.

**4.3 Handling**

Safety precautions should be addressed when handling test samples prior to and after testing.

**4.4 Film-coated CRTs**

In the case of CRTs with film, which is not an integral part of the implosion protection system, the product must be tested without film in accordance with Tables 1 and 2 and 6 to 9.

## 5 Environmental conditioning

### 5.1 Standard atmospheric conditions for testing

Unless otherwise specified, all tests and measurements shall be made under standard atmospheric conditions for testing as given in 5.3 of IEC 60068-1:

- temperature: 15 °C to 35 °C;
- relative humidity: 25 % to 75 %;
- air pressure: 86 kPa to 106 kPa

### 5.2 Preconditioning

Before CRTs are subjected to thermal conditioning or to testing they will be allowed to stabilize at standard atmospheric conditions for testing (see 5.1) for a minimum period of 16 h.

### 5.3 Thermal conditioning

Details of thermal conditioning are given in Tables 1 to 9. After thermal conditioning has been completed, the CRTs will be allowed to stabilize at standard atmospheric conditions for testing (see 5.1) for a minimum period of 24 h.

## 6 Sampling

### 6.1 Sampling plans

Details are given in Tables 1 to 9.

### 6.2 Sample numbers

The numbers of CRTs and the test programmes for prestressed banded CRTs are given in Tables 1, 2, 3 and 4, for bonded frame CRTs in Tables 6 and 7 and for laminated CRTs in Tables 8 and 9.

NOTE 1 Additionally, the number of samples for film-adhesion testing are given in Table 5.

NOTE 2 In addition to the quantities specified in the tables, additional samples should be made available for use in case of retest to satisfy the intent of the requirement.

### 6.3 Compliance

All CRTs in a test group shall comply with the test requirements for that group, except that, if only one CRT from all the test groups does not comply with the requirements, acceptability may be determined by subjecting a second test group to the set of tests during which unacceptable results occurred. The construction is acceptable if all CRTs in the second test group comply with the requirements.

## 7 Test preparation and set-up

### 7.1 Scratch patterns

As the form and depth of the scratch patterns may affect the force which is needed to obtain implosion or devacuation of the CRT, it is recommended that the scratches be made using a diamond- or carbide-tipped stylus, a glasscutter with a wheel of hardened steel or other similar tools.

## 7.2 Barriers

Barriers as specified in the test procedures, each made of 10 mm to 20 mm thick material,  $250_{-3}^0$  mm high and  $(2,00 \pm 0,01)$  m long, shall be placed on the floor in front of the test cabinet at the specified locations, measured horizontally from the vertical plane of the centre of the front surface of the CRT to the near surface of the barrier closest to the tube face. The tolerance on the position of the barrier shall be  $\pm 10$  mm, unless otherwise stated. The barriers may be less than 2 m long provided that they extend to the walls of the test room (see Figures 2 and 5). A non-skid surface such as a blanket or rug may be placed on the floor.

NOTE A particle travelling past the plane of the front surface of the barrier shall be considered to have passed the barrier.

## 7.3 Mounting

The CRT shall be mounted in a test cabinet of rigid construction and of suitable dimensions that does not permit a gap or opening wider than 6 mm around the CRT (see Figure 1). The mounting of the CRT in front of, or behind, the front panel of the test cabinet shall be in accordance with the CRT manufacturer's specifications or intended application. When mounting specifications are not available, the preferred mounting method shall be behind the front panel unless design features do not allow this condition.

A hole of suitable area shall be provided at the top of the cabinet to allow access to the funnel. This hole shall be covered during the impact test.

An opening having an area of not less than one-quarter of the area of the face of the CRT or  $0,02 \text{ m}^2$ , whichever is the smaller, shall also be provided in the bottom or rear of the cabinet for air intake in the event of an implosion.

The cabinet shall be firmly supported so as to prevent movement during the test.

## 7.4 Mounting position

The centre of the CRT shall be  $(1,00 \pm 0,05)$  m above the floor.

## 8 Testing of large CRTs

### 8.1 Mechanical strength (ball impact test)

#### 8.1.1 Test procedure

A solid smooth steel ball of  $(40 \pm 1)$  mm diameter and mass of  $(260 \pm 15)$  g, including the hook, and a minimum C scale Rockwell hardness of 60, shall be suspended by suitable means such as a fine wire or chain with a mass not exceeding 10 % of the mass of the ball and the hook. It shall be allowed to fall freely as a pendulum from a calculated height and strike the face of the CRT with an energy of  $(5,5 \pm 0,1)$  J. The CRT shall be placed so that the face is vertical and in the same vertical plane as the point of support of the pendulum. A single impact shall be applied to any point on the CRT face at a distance of 40 mm or greater from the edge of the useful phosphor screen.

NOTE The test laboratory should consider all their test set-up uncertainties to ensure this 40 mm minimum position of the point of impact.

The barrier shall be placed 1,5 m from the plane of the centre of the face of the CRT (see Figure 2).

### 8.1.2 Glass throw criteria

A CRT is in compliance if the expulsion of glass within 5 s of the initial impact meets the following requirements:

- a) there shall be no glass particle (a single piece of glass having a mass greater than 0,025 g) past the 1,5 m barrier;
- b) the total mass of all pieces of glass past the 1,5 m barrier shall not exceed 0,1 g.

## 8.2 Implosion test (missile)

### 8.2.1 Test procedure

The face of the CRT at the top and bottom shall be scratched ( $3 \pm 1$ ) mm from the screen or phosphor edge into the viewing area. The scratches shall be horizontal lines ( $100 \pm 5$ ) mm long.

The impact object shall be a steel missile (see example in Figure 3) with a mass of ( $2,3 \pm 0,1$ ) kg, a minimum C scale Rockwell hardness of 60 and having one end rounded on a radius of ( $25 \pm 0,5$ ) mm.

The CRT shall be subjected to a single impact, intending to cause rapid devacuation using the minimum energy within the range. The impact object shall be swung through an arc of a pendulum to obtain an impact of not less than 7,0 J and not more than 14,0 J to cause rapid devacuation of the samples in the test group.

The impact area shall be the area bounded by two concentric circles where the radius of one circle is one-sixth of the height of the useful phosphor screen and the second circle radius is one-half of the height of the useful phosphor screen less 50 mm (see Figure 4). In Figure 4, if  $R_2$  is less than  $R_1$  then the impact shall be applied to the circle specified in  $R_1$ .

NOTE Previous testing experience on a particular CRT design (obtained from the CRT manufacturer or the test laboratory) should be considered when selecting the energy level within the range and the impact location.

The impact object travel shall be restricted so that the rounded end of the missile penetrates the CRT face equal to, or less than, 25 mm (see Figure 5).

Barriers shall be placed 1,0 m and 1,5 m from the vertical plane of the centre of the face of the CRT (see Figure 5).

If no CRTs devacuate as a result of this test then the alternative implosion test (missile) described in 8.2.3 shall be carried out.

### 8.2.2 Glass throw criteria

A CRT is in compliance if the expulsion of glass within 5 s of the initial impact meets the following requirements:

- a) there shall be no single piece of glass having a mass greater than 15 g between the 1,0 m and 1,5 m barriers;
- b) the total mass of all pieces of glass between the 1,0 m and 1,5 m barriers shall not exceed 45 g;
- c) there shall be no single piece of glass having a mass greater than 1,5 g beyond the 1,5 m barrier.

### 8.2.3 Alternative implosion test (missile)

This alternative test shall be used as an additional test when the test in 8.2.1 has devacuated no CRTs, or may be used as an alternative to the test in 8.2.1 when it can be shown that the 8.2.1 test is unlikely to devacuate at least one CRT of the sample group.

### 8.2.3.1 Test procedure

As in 8.2.1, except that the impact object will be a steel missile (see example in Figure 11) with a mass of  $(1,4 \pm 0,1)$  kg, a minimum C scale Rockwell hardness of 60 and one end rounded on a radius of  $(15 \pm 0,5)$  mm.

### 8.2.3.2 Glass throw criteria

As in 8.2.2. If no CRTs devacuate as a result of the test in 8.2.3.1, then the glass throw requirements of 8.2.2 are deemed to have been satisfied.

## 8.3 Implosion test (thermal shock)

### 8.3.1 Test procedure

The CRT shall be mounted in the test cabinet, which is described in 7.3 and 7.4. The barrier shall be placed at  $(150 \pm 2)$  mm from the vertical plane of the centre of the face of the CRT. An area shall be scratched on the faceplate sidewall or face of the CRT using one of the patterns illustrated in Figure 6.

A thermal shock shall be applied using one of the following methods:

a) Liquid nitrogen

The scratched area shall be cooled using liquid nitrogen until a fracture occurs. A dam of modelling clay or equivalent may be used to contain the liquid nitrogen.

b) Hot rod

The end of an ordinary flint glass rod, of suitable diameter (for example, 10 mm) shall be heated until it is red hot and nearly fluid. The heated end of the rod shall be pressed firmly on the scratched area of the CRT. If devacuation of the CRT does not occur within 10 s then the rod shall be withdrawn and cold water poured slowly on the scratched area. If a devacuation cannot be induced by repeated applications of the hot rod then the test shall be carried out using liquid nitrogen (see 8.3.1a).

### 8.3.2 Glass throw criteria

A CRT is in compliance if, within 5 s of the initial fracture, no glass particle is expelled through the plane of the face beyond the 150 mm barrier.

## 8.4 High-energy impact test

CRTs, which have a laminated implosion protection system, shall be subjected to the following high-energy impact test.

### 8.4.1 Test procedure

A  $(25 \pm 1)$  mm diameter steel pin (see Figure 9) shall be inserted through the hole at the top of the test cabinet and placed on the CRT envelope  $(3 \pm 1)$  mm behind the seal of the faceplate and funnel. If the hardware extends back from the seal more than 3 mm so as to interfere with the placement of the pin, then the pin shall be placed as close as possible to the hardware without touching it. A weight (see Figure 10), having a mass of  $(4,5 \pm 0,1)$  kg, shall be caused to fall from a height so as to impact the pin at the end of its fall.

The height of the test mass shall be adjusted to limit the amount of energy to the minimum required to produce fracturing of the glassware, but not less than 7 J.

If fracturing of the glass does not occur, the impact energy shall be increased in 7 J increments to a maximum of 63 J using a new test sample each time until all the CRTs in the test group have suffered rapid devacuation.

The impact energy shall not be so large as to cause the pin to punch a hole with little or no cracking or shaling of the glassware. If this condition does occur then a lower impact energy shall be selected so as to result in fracturing (7 J steps not necessary).

NOTE Previous testing experience on a particular CRT design (obtained from the CRT manufacturer or the test laboratory) should be considered when selecting the energy level within the range.

The implosion pin shall be restricted so that its travel on impact shall be a maximum of 6 mm. The pin travel restriction assembly shall be positioned so that its impact energy shall not be transferred to the test cabinet. Figures 8, 9 and 10 give examples of equipment that may be used.

Barriers shall be placed 1,0 m and 1,5 m from the plane of the centre of the face of the CRT.

#### 8.4.2 Glass throw criteria

A CRT is in compliance if the expulsion of glass within 5 s of the initial impact meets the following requirements:

- a) there shall be no single piece of glass having a mass greater than 15 g between the 1,0 m and 1,5 m barriers;
- b) the total mass of all pieces of glass between the 1,0 m and 1,5 m barriers shall not exceed 45 g;
- c) there shall be no single piece of glass having a mass greater than 1,5 g beyond the 1,5 m barrier.

### 9 Testing of small CRTs

#### 9.1 Mechanical strength (ball impact test)

##### 9.1.1 Test procedure

A solid smooth steel ball of  $(40 \pm 1)$  mm diameter and mass of  $(260 \pm 15)$  g, including the hook, and a minimum C scale Rockwell hardness of 60, shall be suspended by suitable means such as a fine wire or chain with a mass not exceeding 10 % of the mass of the ball and hook. It shall be allowed to fall freely as a pendulum from a calculated height and strike the face of the CRT with an energy of  $(2,0 \pm 0,1)$  J. The CRT shall be placed so that the face is vertical and in the same vertical plane as the point of support of the pendulum. A single impact shall be applied to any point on the CRT face at a distance of 25 mm or greater from the edge of the useful screen.

NOTE The test laboratory should consider all their test set-up uncertainties to ensure this 25 mm minimum position of the point of impact.

The barrier shall be placed 0,6 m from the plane of the centre of the face of the CRT (see Figure 2).

##### 9.1.2 Glass throw criteria

A CRT is in compliance if the expulsion of glass within 5 s of the initial impact meets the following requirements:

- a) there shall be no glass particle (a single piece of glass having a mass greater than 0,025 g) past the 0,6 m barrier;
- b) the total mass of all pieces of glass past the 0,6 m barrier shall not exceed 0,1 g.

## 9.2 Implosion test (high ball)

If implosion or rapid devacuation does not occur when the CRT is tested as specified in 9.1 then a CRT having other than a laminated implosion protection system shall be subjected to the following test.

### 9.2.1 Test procedure

The face of the CRT shall be scratched at the top and bottom edges ( $3 \pm 1$ ) mm from the screen phosphor edge into the viewing area. The length of the scratches shall be 45 % to 55 % of the longest dimension/width of the face of the CRT.

Using a ( $40 \pm 1$ ) mm diameter steel ball having a mass of ( $260 \pm 15$ ) g and a minimum C scale Rockwell hardness of 60, a CRT having other than a laminated implosion screen shall be subject to additional impact tests during which the impact energy shall be increased in 0,7 J increments until fracturing occurs. A new sample shall be used for each test until all CRTs in the test group have been tested, with implosion or rapid devacuation occurring.

Barriers shall be placed 0,6 m and 1,2 m from the plane of the centre of the face of the CRT (see Figure 2).

### 9.2.2 Glass throw criteria

A CRT is in compliance if the expulsion of glass within 5 s of the initial impact meets the following requirements:

- a) there shall be no single piece of glass having a mass greater than 15 g between the 0,6 m and 1,2 m barriers;
- b) the total mass of all pieces of glass between the 0,6 m and 1,2 m barriers shall not exceed 45 g;
- c) there shall be no single piece of glass having a mass greater than 1,5 g beyond the 1,2 m barrier.

## 9.3 Implosion test (thermal shock)

### 9.3.1 Test procedure

As 8.3.1.

### 9.3.2 Glass throw criteria

As 8.3.2.

## 9.4 High-energy impact test

CRTs, which have a laminated implosion protection system, shall be subjected to the following high-energy impact test.

### 9.4.1 Test procedure

A ( $9,5 \pm 0,5$ ) mm diameter steel pin shall be inserted through the hole in the top of the test cabinet and placed directly on the envelope seal line. A weight (see Figure 10) having a mass of ( $0,45 \pm 0,02$ ) kg shall be caused to fall freely from a height so as to impact the pin at the end of its fall.

The height of the test mass shall be adjusted to limit the amount of energy to the minimum amount required to produce fracturing of the glassware, but not less than 2,7 J.

If fracturing of the glass does not occur, the impact energy shall be increased in 0,7 J increments, using a new test sample each time, until all CRTs in the test group have been tested with rapid devacuation.

The impact energy shall not be so large as to cause the pin to punch a hole with little or no cracking or shaling of the glassware. If this condition does occur then a lower impact energy shall be selected so as to result in fracturing (0,7 J steps not necessary).

NOTE Previous testing experience on a particular CRT design (obtained from the CRT manufacturer or the test laboratory) should be considered when selecting the energy level within the range.

The impact pin shall be restricted so that its travel on impact shall be a maximum of 6 mm. The pin travel restriction assembly shall be positioned so that impact energy shall not be transferred to the test cabinet. Figures 8, 9 and 10 give examples of equipment that may be used.

Barriers shall be placed 0,6 m and 1,2 m from the plane of the centre of the face of the CRT.

#### 9.4.2 Glass throw criteria

A CRT is in compliance if the expulsion of glass within 5 s after the initial impact meets the following requirements:

- a) there shall be no single piece of glass having a mass greater than 15 g between the 0,6 m and 1,2 m barriers;
- b) the total mass of all pieces of glass between the 0,6 m and 1,2 m barriers shall not exceed 45 g;
- c) there shall be no single piece of glass having a mass greater than 1,5 g beyond the 1,2 m barrier.

### 10 Testing of prestressed banded CRTs with protective film

#### 10.1 General

For CRTs that employ a film layer on the CRT face that is an integral part of the implosion protection system, the tests described in Clauses 8 and 9 shall be applied in accordance with Tables 3 or 4. The film on all samples tested with the protective film attached shall first be scored as described in 10.2. Additionally, the tests of 10.3 and 10.4 are required in accordance with Table 5.

NOTE In the case of CRTs with film which is not an integral part of the implosion protection system, this clause does not apply and the product must be tested without film in accordance with Tables 1 and 2 and 6 to 9.

#### 10.2 Film scoring pattern for CRTs with protective film

All samples subjected to the tests in Tables 3 and 4 with the protective film attached shall be scored along both diagonals of the face for a minimum of 80 % of the external glass dimension using one of the following methods, at the CRT manufacturer's option:

- a) scoring shall be done with a tool and stylus as defined in Figure 7 and applied under the following conditions:
  - tool orientation with respect to glass surface:  $(90 \pm 10)^\circ$ ;
  - force:  $(4 \pm 2)$  N;
  - speed: 2 to 10 cm/s;
- b) scoring shall be done with a sharp utility knife with a short blade to cut through the total thickness of the film, but avoiding damage to the glass.

### 10.3 Peel test

#### 10.3.1 Sample preparation

Twenty samples of the film, bonded to glass sections, shall be prepared. The glass sections shall be 35 mm minimum wide and 150 mm minimum length. The attached film test samples shall be  $(25 \pm 0,5)$  mm wide and 250 mm minimum length. Test samples shall be produced using representative manufacturing conditions.

**10.3.1.1** Sample conditioning shall be in accordance with Table 5.

**10.3.1.2** Additionally, all test samples are to be conditioned for at least 24 h at  $(25 \pm 2)$  °C immediately prior to the peel test.

#### 10.3.2 Test procedure

The tests are to be performed in accordance with ISO 8510-1. The film strip is to be pulled from the surface at an angle of 90° at a rate of  $(50 \pm 5)$  mm/min. The average peel force for at least 100 mm detachment is to be recorded and the average peel force per cm of width is to be calculated.

#### 10.3.3 Requirements

The average peel force, for each individual sample, shall be a minimum of 3,5 N per cm of width. The film shall withstand the specified force of 3,5 N without tearing.

### 10.4 Immersion test

#### 10.4.1 Test procedure

Four samples of film bonded to glass sections, prepared as described in 10.3.1, shall be immersed each in one of the following aqueous solutions for 24 h:

- 1)  $(70 \pm 5)$  V/V % denatured ethyl alcohol
- 2)  $(9 \pm 1)$  W/W % aqueous ammonia solution
- 3)  $(5 \pm 1)$  W/W % sodium hypochlorite
- 4)  $(70 \pm 5)$  V/V % isopropyl alcohol.

NOTE All four solutions are to be used. Only one test section is to be subjected to each solution.

The test samples are to be removed from the test solutions, blotted dry and conditioned for 24 h at  $(25 \pm 2)$  °C.

The samples are then to be subjected to the peel test described in 10.3.2.

#### 10.4.2 Requirements

The average peel force, for each individual sample, shall be a minimum of 3,5 N per cm of width. The film shall withstand the specified force of 3,5 N without tearing.

## 11 Marking

Along with the CRT manufacturer's name, trade name or identifying code, and a type number, each CRT which meets the requirements of this standard shall be marked with the following statement, or wording with a similar meaning. The marking shall be of a permanent and legible type and in the appropriate language.

**WARNING** This cathode ray tube employs integral implosion protection. For continued safety it must be replaced with a cathode ray tube of the same or equivalent type number.

## 12 Application notes for pre-stressed banded CRTs with protective film

The CRT manufacturer shall provide application notes with the following statements or wording with a similar meaning, and in the appropriate language:

### SAFETY NOTES

- a) Manufacturers of products incorporating CRTs must ensure that the enclosure front bezel totally covers all edges of the protective film applied to the face of these CRTs.
- b) The end-product manufacturer shall provide a warning statement in the user's instruction manual. This shall state:

**WARNING** The CRT in this product employs a protective film on the face. This film must not be removed as it serves a safety function and removal will increase the risk of serious injury.

## 13 Normative requirements for the use of Tables 1 and 2 (prestressed banded CRTs)

Sampling and testing for new construction (sampling plan I), new construction with known tape or resin (sampling plan II), tension band only (sampling plan III) and alternative construction (sampling plan IV) will be used when any of the following new construction features or variations in construction apply. Unique constructions may require a special investigation.

### 13.1 Sampling plan I: New construction

Applicable to first-time testing for a CRT manufacturer or a change in construction of a previously tested CRT that employs any of the following nominal design changes.

#### 13.1.1 Size

New CRT diagonal size range (see Table 10).

#### 13.1.2 Deflection angle

New deflection angle range for a particular CRT size range (see Table 10).

#### 13.1.3 Glassware shape

Glassware, in a particular CRT size and deflection angle range, having the following shape variations, is considered a new glassware shape:

- a) front panel outside curvature: a change in height measurement from the Z point to the centre of the face panel of more than  $\pm 10\%$  from a previously tested CRT for a manufacturer;
- b) aspect ratio: any change in the height-to-width ratio of the front panel from a previously tested CRT for a manufacturer;
- c) glassware thickness: a change in glassware thickness of more than  $\pm 20\%$  at any point, other than the neck, from a previously tested CRT for a manufacturer;
- d) corner radius: any change in external or internal panel corner radius (plan view) of more than  $\pm 10\%$ .

#### **13.1.4 Glassware supplier**

New glassware supplier not previously used by the CRT manufacturer. Subsidiaries of present glassware suppliers who use the same chemistry, mould designs, processes and quality control arrangements, under a common quality management system, are not considered to be new suppliers.

#### **13.1.5 Resin**

New resin in the prestressed banded system. A resin is considered new if it is of a different generic type, for example, epoxy, polyester or other material.

#### **13.1.6 Tape**

New tape employed in the tension band system. A tape is considered new if one or more of the following circumstances apply:

- a) tape width – the tape width under the tension band is reduced by more than 20 %;
- b) change in generic type of adhesive, for example, acrylic, silicone, natural rubber, etc.;
- c) adhesion – more than 20 % decrease in adhesion strength;
- d) single-sided adhesive – tape that is changed from a double-sided adhesive to a single-sided adhesive;
- e) any combination that differs from that used in previously tested CRTs;
- f) change in backing generic type, for example, polyester cloth, etc.;
- g) change in backing thickness of more than  $\pm 20$  %.

### **13.2 Sampling plan II: New construction with known resin or tape**

Applicable to first-time testing for a CRT manufacturer or a change in construction of a previously tested CRT that employs any of the following nominal design changes:

#### **13.2.1 Tape and resin**

A new CRT construction as defined in 13.1.1 to 13.1.4 with a tape or resin, which has been previously tested and found acceptable for a CRT manufacturer in the same or a larger CRT size.

### **13.3 Sampling plan III: Tension band and alternative tension band**

Applicable to any of the following changes in tension band or hardware:

#### **13.3.1 Tension band only**

CRTs using this construction employ only a tension band. There is no material between the tension band and the CRT envelope. This sampling plan applies to new constructions as well as a construction change where tape or resin is deleted from the system.

#### **13.3.2 Band-end securement**

For tension band only construction, where there are significant changes in the band-end securement method, such as a change from spot weld to crimp type.

#### **13.3.3 Band tension**

A change in nominal band tension or minimum glassware recovery value of greater than  $-5$  % to  $+15$  % from a previously tested CRT, employing a particular size range, deflection angle range and glassware shape.

#### **13.3.4 Band-tension system**

Change in the band-tensioning system such as a change from machine tightened to shrink band, or others.

#### **13.3.5 Hardware**

Change in the hardware system such as addition or deletion of rim bands, reinforcing bars or other structural materials between the tension band and the CRT envelope.

#### **13.3.6 Band width**

Reduction of nominal tension bandwidth by more than 10 %.

#### **13.3.7 Band material**

Change in metallurgical composition.

#### **13.3.8 Band position**

Change in the nominal location of the band (forward or backward) by more than 3 mm from its original position as measured from the front of the band to the Z point on the panel.

#### **13.3.9 Band-surface coating**

Addition or change in the surface coating of the tension band when welding is the method of band-end securement. CRTs need not be tested if the tensile strength of the new welded band is equal to, or greater than, the original.

### **13.4 Sampling plan IV: Alternative construction**

Applicable to any tension band construction such as tension band only, tension band with tape, rim band, etc. Alternative construction consists of variation in construction in any of the following.

#### **13.4.1 Size**

New size within a diagonal size range previously tested for the CRT manufacturer.

#### **13.4.2 Deflection angle**

New deflection angle within a range previously tested for a CRT manufacturer.

#### **13.4.3 Glassware supplier**

Glassware supplier previously used by the CRT manufacturer in another size range.

#### **13.4.4 Glassware thickness**

Glassware whose minimum thickness varies from the glassware originally tested by more than  $\pm 10\%$  and less than, or equal to,  $\pm 20\%$  at any point other than the neck, is considered an alternative construction.

#### **13.4.5 Resin**

Resin used in the prestressed banded system is considered an alternative construction if the tensile strength of the cured resin is less than 80 % of the original resin. Addition of tested resin to a CRT construction previously tested using a tension band only (without resin) will be accepted without testing.

#### 13.4.6 Tape

Addition of tested tape to a CRT construction previously tested using a tension band only (without tape) will be accepted without testing.

### 14 Normative requirements for the use of Tables 3 and 4 (prestressed banded with protective film)

Sampling and testing for new construction (sampling plan I), new construction with known resin, tape, film or adhesive (sampling plan II), alternative tension band (sampling plan III) and alternative construction (sampling plan IV) will be used when any of the following new or variations in construction apply. Unique constructions may require a special investigation.

#### 14.1 Sampling plan I: New construction

Applicable to first-time testing for a CRT manufacturer or a change in construction of a previously tested CRT that employs any of the following nominal design changes.

##### 14.1.1 Size

New CRT diagonal measurement size range (see Table 10).

##### 14.1.2 Deflection angle

New deflection angle range for a particular CRT size range (see Table 10).

##### 14.1.3 Glassware shape

Glassware in a particular CRT size and deflection angle range, having the following shape variations, is considered a new glassware shape.

- a) Front panel outside curvature – a change in height measurement from the Z point of the centre of the face panel of more than  $\pm 10\%$  from a previously tested CRT for a manufacturer;
- b) aspect ratio – any change in the height-to-width ratio of the front panel from a previously tested CRT for a manufacturer;
- c) glassware thickness – a change in glassware thickness of more than  $\pm 20\%$  at any point, other than the neck, from a previously tested CRT for a manufacturer;
- d) corner radius – any change in external or internal panel corner radius (plan view) of more than  $\pm 10\%$ .

##### 14.1.4 Glassware supplier

New glassware supplier not previously used by the CRT manufacturer. Subsidiaries of present glassware suppliers who use the same chemistry, mould designs, processes and quality control arrangements, under a common quality management system, are not considered to be new suppliers.

##### 14.1.5 Resin

New resin in the pre-stressed banded system. A resin is considered new if it is a different generic type, for example, epoxy, polyester or other material.

#### **14.1.6 Tape**

New tape employed in the tension band system. A tape is considered new if

- a) tape width – the tape width under the tension band is reduced by more than 20 %;
- b) change in generic type of adhesive, for example, acrylic, silicone, natural rubber, etc.;
- c) adhesion – more than 20 % decrease in adhesion strength;
- d) single-sided adhesive – tape that is changed from a double-sided adhesive to a single-sided adhesive;
- e) any combination that differs from that used in previously tested CRTs;
- f) change in backing generic type, for example, polyester cloth, etc;
- g) change in backing thickness of more than  $\pm 20$  %.

#### **14.1.7 Adhesive for protective film**

New adhesive used with protective film. An adhesive is considered new if:

- a) change in generic type of adhesive, for example, acrylic, silicone, natural rubber, etc.;
- b) adhesion – more than 20 % decrease in adhesion strength.

#### **14.1.8 Protective film**

New film employed in the protection system. A film is considered new if:

- a) change in film generic type, for example, polyester, etc.;
- b) change in film thickness of more than  $\pm 15$  %.

### **14.2 Sampling plan II: New construction with known resin, tape, film or adhesive**

Applicable to first-time testing for a CRT manufacturer or a change in construction of a previously tested CRT that employs any of the following nominal design changes.

#### **14.2.1 Tape and resin**

A new CRT construction as defined in 14.1.1 to 14.1.4 with a tape or resin, which has been previously tested and found acceptable for a CRT manufacturer in the same or a larger CRT size.

#### **14.2.2 Film and adhesive**

A new CRT construction as defined in 14.1.1 to 14.1.4 with a film and adhesive combination which has been previously tested and found acceptable for a CRT manufacturer in the same or a larger CRT size.

### **14.3 Sampling plan III: Alternative tension band**

Applicable to any of the following changes in tension band or hardware.

#### **14.3.1 General**

This sampling plan applies to construction changes in tension band or hardware as well as a construction change where tape or resin is deleted from the tension band system.

#### **14.3.2 Band-end securement**

A significant change in the band-end securement method, such as a change from spot weld to crimp type.

#### **14.3.3 Band tension**

A change in nominal band tension or minimum glassware recovery value of greater than -5 % to +15 % from a previously tested CRT, employing a particular size range, deflection angle range and glassware shape.

#### **14.3.4 Band-tension system**

Change in the band-tensioning system such as a change from machine tightened to shrink band, or others.

#### **14.3.5 Hardware**

Change in the hardware system such as addition or deletion of rim bands, reinforcing bars or other structural materials between the tension band and the CRT envelope.

#### **14.3.6 Band width**

Reduction of tension bandwidth by more than 10 %.

#### **14.3.7 Band material**

Change in metallurgical composition.

#### **14.3.8 Band position**

Change in the location of the band (forward or backward) by more than 3 mm from its original position as measured from the front of the band to the Z point on the panel.

#### **14.3.9 Band surface coating**

Addition or change in the surface coating of the tension band when welding is the method of band-end securement. CRTs need not be tested if the tensile strength of the new welded band is equal to, or greater than, the original.

### **14.4 Sampling plan IV: Alternative construction**

Applicable to any tension band construction such as tension band only, tension band with tape, rim band, etc. Alternative construction consists of the variation in construction in any of the following:

#### **14.4.1 Size**

New size within a range previously tested for the CRT manufacturer.

#### **14.4.2 Glassware supplier**

Glassware supplier previously used by the CRT manufacturer in another size range.

#### **14.4.3 Glassware thickness**

Glassware whose minimum thickness varies from the glassware originally tested by more than  $\pm 10\%$  and less than, or equal to,  $\pm 20\%$  at any point other than the neck, is considered an alternative construction.

#### 14.4.4 Resin

Resin used in the prestressed banded system is considered an alternative construction if the tensile strength of the cured resin is less than 80 % of the original resin. Addition of resin to a CRT construction previously tested using a tension band only (without resin) will be accepted without testing.

#### 14.4.5 Tape

Addition of tape to a CRT construction previously tested using a tension band only (without tape) will be accepted without testing.

### 15 Alternative thermal conditioning for use with Tables 3 and 4 (prestressed banded with protective film)

This alternative high temperature thermal conditioning can be used where the requirements of 15.1 and 15.2 are satisfied. Samples of the CRT only, without the film, are conditioned at 150 °C for 48 h or other Arrhenius based time/temperature combinations as specified in footnote d of Tables 3 and 4. After removal from the conditioning chamber, the CRT samples are allowed to stabilize for at least 24 h at  $(25 \pm 2)$  °C. The film is then to be affixed to the CRT face, using representative manufacturing conditions and stabilized at standard atmospheric conditions for at least 24 h, prior to impact and implosion testing as defined in Tables 3 and 4.

#### 15.1 Additional peel force requirements where alternative thermal conditioning is to be performed

The five-sample average of the average peel force of the test pieces thermally conditioned according to 10.3.1.2 shall not be less than 90 % of the five-sample average of the average peel force of the as-received test pieces (10.3.1.1). In no case shall the average peel force for any single sample be less than 3,5 N per cm of width.

#### 15.2 Tensile strength test where alternative thermal conditioning is to be performed

##### 15.2.1 Sample preparation

Ten samples of the film shall be prepared according to the requirements of ISO 527-1 and ISO 527-3. Five of these samples in the as-received condition shall be set aside for test. The other five samples shall be thermally conditioned in accordance with 10.3.1.2.

##### 15.2.2 Test procedure

Samples shall be tested in accordance with the test method of ISO 527-1 and ISO 527-3. The rate of separation of the grips of the testing machine shall be the same for both as-received samples and thermally conditioned samples.

The average of the tensile strength ( $\sigma_m$ ) of the film shall be calculated for the as-received samples and, separately, for the thermally conditioned samples.

##### 15.2.3 Requirements

The average tensile strength ( $\sigma_m$ ) for the thermally conditioned samples shall not be less than 90 % of the average  $\sigma_m$  for the as-received samples.

## 16 Normative requirements for the use of Tables 6 and 7 (bonded frame CRTs)

Sampling and testing for new construction (sampling plan I) and alternative construction (sampling plan II) will be used when any of the following new construction features or variations in construction applies. Unique constructions may require a special investigation.

### 16.1 Sampling plan I: New construction

Applicable to first-time testing for a CRT manufacturer or change in construction of a previously tested CRT that employs any of the following nominal design variations:

#### 16.1.1 Size

New CRT diagonal size range (see Table 10).

#### 16.1.2 Deflection angle

New deflection angle range for a particular CRT size range (see Table 10).

#### 16.1.3 Glassware shape

Glassware in a particular CRT size and deflection angle range having the following shape variations is considered a new glassware shape:

- a) front panel curvature and corner radius – a change in height measurement from the Z point to the centre of the face panel of more than  $\pm 10\%$  from a previously tested CRT for a CRT manufacturer;
- b) aspect ratio – any change in the nominal height-to-width ratio of the front panel from a previously tested CRT for a CRT manufacturer;
- c) glassware thickness – a change in glassware thickness of more than  $\pm 20\%$  at any point, other than the neck, from a previously tested CRT for a CRT manufacturer.

#### 16.1.4 Glassware supplier

New glassware supplier not previously used by the CRT manufacturer. Subsidiaries of present glassware suppliers who use the same chemistry, mould designs, processes and quality control arrangements, under a common quality management system, are not considered to be new suppliers.

#### 16.1.5 Resin

New resin used in a CRT employing a particular size range, deflection angle range and glassware shape.

#### 16.1.6 Resin thickness

A change in the resin thickness of more than  $\pm 25\%$ .

#### 16.1.7 Frame thickness

A change in the thickness of the material used to form the frame of more than  $\pm 10\%$ .

## **16.2 Sampling plan II: Alternative construction**

Consists of variation in construction in any of the following nominal design changes.

### **16.2.1 Size**

New size within a diagonal size range previously tested for a CRT manufacturer.

### **16.2.2 Deflection angle**

New deflection angle within a range previously tested for a CRT manufacturer.

### **16.2.3 Glassware supplier**

Glassware supplier previously used by the CRT manufacturer in another size range.

### **16.2.4 Glassware thickness**

Glassware whose thickness varies from the glassware originally tested by more than  $\pm 10\%$  and less than, or equal to,  $\pm 20\%$  at any point other than the neck, is considered an alternative construction.

### **16.2.5 Resin**

New resin for a size within a size range previously tested for that particular resin.

### **16.2.6 Resin thickness**

A change in resin thickness of more than  $\pm 10\%$  but less than, or equal to,  $\pm 25\%$ .

## **17 Normative requirements for the use of Tables 8 and 9 (laminated CRTs)**

Sampling and testing for new construction (sampling plan I) and alternative construction (sampling plan II) will be used when any of the following new construction features or variations in construction applies. Unique constructions may require a special investigation.

### **17.1 Sampling plan I: New construction**

Applicable to first-time testing for a CRT manufacturer or a change in construction of a previously tested CRT that employs any of the following nominal design variations.

#### **17.1.1 Bonding material**

New bonding material used or proportion of resin to hardener changed by more than  $\pm 20\%$ .

#### **17.1.2 Bonding material thickness**

A change in bonding material thickness of more than  $\pm 25\%$ .

#### **17.1.3 Front panel thickness**

A decrease in front panel glass thickness of more than  $25\%$ .

### **17.2 Sampling plan II: Alternative construction**

Applicable to a variation in construction in any of the following nominal design changes.

**17.2.1 Bonding material**

Bonding material previously tested for a CRT manufacturer but used in a different size range (see Table 10).

**17.2.2 Bonding material thickness**

A change in bonding material thickness of more than  $\pm 10\%$  and less than, or equal to,  $\pm 25\%$ .

**17.2.3 Front panel thickness**

A decrease in front panel glass thickness in the range of 10 % to 25 %.

**Table 1 – Sampling and test programme for prestressed banded CRTs exceeding 160 mm diagonal**

Sampling plan	CRT design <sup>a</sup>	Thermal conditioning				Impact and implosion test groups		
		Number of CRTs	Circulating air chamber			Number of CRTs to be tested as described in		
			Temp °C <sup>b</sup>	RH %	Time h	8.1 (ball) <sup>c</sup>	8.3 (thermal)	8.2 (missile)
I	New construction	5	–	–	–	Group A	Group B	Group C
		4	150 <sup>d</sup>	–	48 <sup>d</sup>	2	1	1
		4	50	90 – 95	48	2	1	1
		4	<sup>e</sup>	–	<sup>e</sup>	2	1	1
II	New construction with previously tested tape or resin	12	–	–	–	6	2	4
III	Tension band only and alternative tension band	9	–	–	–	4	2	3
IV	Alternative construction	6	–	–	–	3	1	2

<sup>a</sup> See Clause 13 for details of the requirements regarding changes in design features.

<sup>b</sup> The tolerance of the oven temperature shall be  $\pm 2\text{ }^{\circ}\text{C}$ .

<sup>c</sup> CRTs not visibly damaged in this test may also be subjected to the tests described in 8.2 and 8.3. If a CRT yields unacceptable results in either of these tests, the results shall be considered inconclusive and disregarded. A new CRT shall be tested in its place, as previous testing might have weakened the CRT.

<sup>d</sup> Other Arrhenius based time/temperature combinations (according to the principles of IEC 60216-1) may be used (for example, 140 °C for 96 h, 130 °C for 168 h, 120 °C for 336 h or 110 °C for 672 h).

<sup>e</sup> CRTs shall be thermally cycled between  $-40\text{ }^{\circ}\text{C}$  and  $+70\text{ }^{\circ}\text{C}$  at the rate of two cycles per day for a total of five cycles and held at each temperature extreme for 4 h.

**Table 2 – Sampling and test programme for prestressed banded CRTs from 76 mm to 160 mm diagonal**

Sampling plan	CRT design <sup>a</sup>	Thermal conditioning				Impact and implosion test groups		
		Number of CRTs <sup>f</sup>	Circulating air chamber			Number of CRTs to be tested as described in		
			Temp °C <sup>b</sup>	RH %	Time h	9.1 (ball) <sup>c</sup>	9.3 (thermal)	9.2 (high ball) <sup>f</sup>
I	New construction	5	–	–	–	Group A	Group B	Group C
		4	150 <sup>d</sup>	–	48 <sup>d</sup>	2	1	2
		4	50	90 – 95	48	2	1	1
		4	e	–	e	2	1	1
II	New construction with previously tested tape or resin	12	–	–	–	6	2	4
III	Tension band only and alternative tension band	9	–	–	–	4	2	3
IV	Alternative construction	6	–	–	–	3	1	2

<sup>a</sup> See Clause 13 for details of the requirements regarding changes in design features.

<sup>b</sup> The tolerance of the oven temperature shall be ±2 °C.

<sup>c</sup> CRTs not visibly damaged in this test may also be subjected to the tests described in 9.2 and 9.3. If a CRT yields unacceptable results in either of these tests, the results shall be considered inconclusive and disregarded. A new CRT shall be tested in its place, as previous testing might have weakened the CRT.

<sup>d</sup> Other Arrhenius based time/temperature combinations (according to the principles of IEC 60216-1) may be used (for example, 140 °C for 96 h, 130 °C for 168 h, 120 °C for 336 h or 110 °C for 672 h).

<sup>e</sup> CRTs shall be thermally cycled between –40 °C and +70 °C at the rate of two cycles per day for a total of five cycles and held at each temperature extreme for 4 h.

<sup>f</sup> Test 9.2 is only applied if implosion or rapid devacuation does not occur in ball test 9.1.

IECNORM.COM · Click to view the full PDF of IEC 61965:2003

**Table 3 – Sampling and test programme for prestressed banded CRTs with protective film exceeding 160 mm diagonal**

Sampling plan	CRT design <sup>a</sup>	Thermal conditioning				Impact and implosion test groups		
		Number of CRTs	Circulating air chamber			Number of CRTs to be tested as described in		
			Temp °C <sup>b</sup>	RH %	Time h	8.1 (ball) <sup>c</sup>	8.3 (thermal)	8.2 (missile)
I	New construction	5 <sup>f</sup>	---	---	---	<b>Group A</b>	<b>Group B</b>	<b>Group C</b>
		4 <sup>f</sup> & p	150 <sup>d</sup>	---	48 <sup>d</sup>	2	1 <sup>g</sup>	2 <sup>h</sup>
		4 <sup>f</sup>	50	90 – 95	48	2	1 <sup>g</sup>	1 <sup>h</sup>
		4 <sup>f</sup>	e	---	e	2	1 <sup>g</sup>	1 <sup>h</sup>
		5 <sup>k</sup>	---	---	---	4 <sup>m</sup>	1 <sup>n</sup>	---
II	New construction with previously tested tape or resin and film/ adhesive combination	12 <sup>f</sup>	---	---	---	6	2 <sup>g</sup>	4 <sup>h</sup>
		4 <sup>k</sup>	---	---	---	3 <sup>m</sup>	1 <sup>n</sup>	---
III	Alternative tension band	9 <sup>f</sup>	---	---	---	4	2 <sup>g</sup>	3 <sup>h</sup>
		3 <sup>k</sup>	---	---	---	2 <sup>m</sup>	1 <sup>n</sup>	---
IV	Alternative construction	6 <sup>f</sup>	---	---	---	3	1 <sup>g</sup>	2 <sup>h</sup>
		3 <sup>k</sup>	---	---	---	2 <sup>m</sup>	1 <sup>n</sup>	---

<sup>a</sup> See Clause 14 for details of the requirements regarding changes in design features.

<sup>b</sup> The tolerance of the oven temperature shall be  $\pm 2$  °C.

<sup>c</sup> CRTs not visibly damaged in this test may also be subjected to the tests described in 8.2 and 8.3. If a CRT yields unacceptable results in either of these tests, the results shall be considered inconclusive and disregarded. A new CRT shall be tested in its place, as previous testing might have weakened the CRT.

<sup>d</sup> Other Arrhenius based time/temperature combinations (according to the principles of IEC 60216-1) may be used (for example, 140 °C for 96 h, 130 °C for 168 h, 120 °C for 336 h or 110 °C for 672 h).

<sup>e</sup> CRTs shall be thermally cycled between -40 °C and +70 °C at the rate of 2 cycles per day for a total of 5 cycles and held at each temperature extreme for 4 h.

<sup>f</sup> Film on all samples is scored as detailed in 10.2.

<sup>g</sup> The scratch patterns described in 8.3.1 shall be positioned on the faceplate sidewall.

<sup>h</sup> The film is to be cut in the prescribed scratch pattern of 8.2.1. The glass is then scratched through the same cuts in the film.

<sup>k</sup> Supplied by manufacturer without film.

<sup>m</sup> Glass throw criteria of 8.1.2 modified to "there shall be no glass particle having a mass greater than 10 g past the 1,5 m barrier".

<sup>n</sup> Glass throw criteria of 8.3.2 modified to "there shall be no glass particle having a mass greater than 2 g past a 0,5 m barrier and no glass particle beyond a 2,0 m barrier".

<sup>p</sup> See Clause 15 for alternative thermal conditioning.

**Table 4 – Sampling and test programme for prestressed banded CRTs with protective film from 76 mm to 160 mm diagonal**

Sampling plan	CRT design <sup>a</sup>	Thermal conditioning				Impact and implosion test groups		
		Number of CRTs	Circulating air chamber			Number of CRTs to be tested as described in		
			Temp °C <sup>b</sup>	RH %	Time h	9.1 (ball) <sup>c</sup>	9.3 (thermal)	9.2 (high ball) <sup>j</sup>
I	New construction	5 <sup>f</sup>	---	---	---	<b>Group A</b>	<b>Group B</b>	<b>Group C</b>
		4 <sup>f &amp; p</sup>	150 <sup>d</sup>	---	48 <sup>d</sup>	2	1 <sup>g</sup>	2 <sup>h</sup>
		4 <sup>f</sup>	50	90 – 95	48	2	1 <sup>g</sup>	1 <sup>h</sup>
		4 <sup>f</sup>	e	---	e	2	1 <sup>g</sup>	1 <sup>h</sup>
		5 <sup>k</sup>	---	---	---	4 <sup>m</sup>	1 <sup>n</sup>	---
II	New construction with previously tested tape or resin and film/adhesive combination	12 <sup>f</sup>	---	---	---	6	2 <sup>g</sup>	4 <sup>h</sup>
		4 <sup>k</sup>	---	---	---	3 <sup>m</sup>	1 <sup>n</sup>	---
III	Alternative tension band	9 <sup>f</sup>	---	---	---	4	2 <sup>g</sup>	3 <sup>h</sup>
		3 <sup>k</sup>	---	---	---	2 <sup>m</sup>	1 <sup>n</sup>	---
IV	Alternative construction	6 <sup>f</sup>	---	---	---	3	1 <sup>g</sup>	2 <sup>h</sup>
		3 <sup>k</sup>	---	---	---	2 <sup>m</sup>	1 <sup>n</sup>	---

<sup>a</sup> See Clause 14 for details of the requirements regarding changes in design features.

<sup>b</sup> The tolerance of the oven temperature shall be ±2 °C.

<sup>c</sup> CRTs not visibly damaged in this test may also be subjected to the tests described in 9.2 and 9.3. If a CRT yields unacceptable results in either of these tests, the results shall be considered inconclusive and disregarded. A new CRT shall be tested in its place, as previous testing might have weakened the CRT.

<sup>d</sup> Other Arrhenius based time/temperature combinations (according to the principles of IEC 60216-1) may be used (for example, 140 °C for 96 h, 130 °C for 168 h, 120 °C for 336 h or 110 °C for 672 h).

<sup>e</sup> CRTs shall be thermally cycled between -40 °C and +70 °C at the rate of 2 cycles per day for a total of 5 cycles and held at each temperature extreme for 4 h.

<sup>f</sup> Film on all samples is scored as detailed in 10.2.

<sup>g</sup> The scratch patterns described in 9.3.1 (8.3.1) shall be positioned on the faceplate sidewall, or direct on face in a cut out window of minimal 20 mm × 20 mm.

<sup>h</sup> The film is to be cut in the prescribed scratch pattern of 9.2.1. The glass is then scratched through the same cuts in the film.

<sup>j</sup> Test 9.2 is only applied if implosion or rapid devacuation does not occur in ball test 9.1.

<sup>k</sup> Supplied by manufacturer without film.

<sup>m</sup> Glass throw criteria of 9.1.2 modified to “there shall be no glass particle having a mass greater than 10 g past the 1,5 m barrier”.

<sup>n</sup> Glass throw criteria of 9.3.2 (8.3.2) modified to “there shall be no glass particle having a mass greater than 2 g past a 0,5 m barrier and no glass particle beyond a 2.0 m barrier” .

<sup>p</sup> See Clause 15 for alternative thermal conditioning.

**Table 5 – Sampling and test programme for adhesion of film used in CRTs with protective film (tested according to Tables 3 and 4)**

Sampling plan	CRT design <sup>a</sup>	Thermal conditioning				Test groups	
		Number test samples	Preconditioning			Number of test samples to be tested as described in	
			Temp °C <sup>b</sup>	RH %	Time h	10.3 (peel test)	10.4 (immersion test)
I	New construction	5 <sup>c</sup>	---	---	---	5	---
		5 <sup>c</sup>	100 <sup>d</sup>	---	168 <sup>d</sup>	5	---
		5 <sup>c</sup>	32	80 – 90	168	5	---
		5 <sup>c</sup>	e	---	e	5	---
		4 <sup>f</sup>	---	---	---	---	4

<sup>a</sup> See Clause 14 for details of the requirements regarding changes in design features.  
<sup>b</sup> The tolerance of the oven temperature shall be  $\pm 2$  °C.  
<sup>c</sup> Test samples prepared according to 10.3.1.  
<sup>d</sup> Other time/temperature combinations may be used, as follows: 90 °C for 336 h, 87 °C for 504 h or 82 °C for 1 440 h.  
<sup>e</sup> Test samples shall be thermally cycled between  $(-40 \pm 2)$  °C and  $(+70 \pm 2)$  °C at the rate of 2 cycles per day for a total of 5 cycles and held at each temperature extreme for 4 h.  
<sup>f</sup> Test samples prepared according to 10.4.1.

IECNORM.COM : Click to view the full PDF of IEC 61965:2003

**Table 6 – Sampling and test programme for bonded frame CRTs exceeding 160 mm diagonal**

Sampling plan	CRT design <sup>a</sup>	Thermal conditioning				Impact and implosion test groups		
		Number of CRTs	Circulating air chamber			Number of CRTs to be tested as described in		
			Temp °C <sup>b</sup>	RH %	Time h	8.1 (ball) <sup>c</sup>	8.3 (thermal)	8.2 (missile)
I	New construction	5	–	–	–	Group A	Group B	Group C
		4	150 <sup>d</sup>	–	48 <sup>d</sup>	2	1	1
		4	50	90 – 95	48	2	1	1
		4	e	–	e	2	1	1
II	Alternative construction	6	–	–	–	3	1	2

- <sup>a</sup> See Clause 16 for details of the requirements regarding changes in design features.
- <sup>b</sup> The tolerance of the oven temperature shall be  $\pm 2$  °C.
- <sup>c</sup> CRTs not visibly damaged in this test may also be subjected to the tests described in 8.2 and 8.3. If a CRT yields unacceptable results in either of these tests, the results shall be considered inconclusive and disregarded. A new CRT shall be tested in its place, as previous testing might have weakened the CRT.
- <sup>d</sup> Other Arrhenius based time/temperature combinations (according to the principles of IEC 60216-1) may be used (for example, 140 °C for 96 h, 130 °C for 168 h, 120 °C for 336 h or 110 °C for 672 h).
- <sup>e</sup> CRTs shall be thermally cycled between –40 °C and +70 °C at the rate of two cycles per day for a total of five cycles and held at each temperature extreme for 4 h.

**Table 7 – Sampling and test programme for bonded frame CRTs from 76 mm to 160 mm diagonal**

Sampling plan	CRT design <sup>a</sup>	Thermal conditioning				Impact and implosion test groups		
		Number of CRTs <sup>f</sup>	Circulating air chamber			Number of CRTs to be tested as described in		
			Temp °C <sup>b</sup>	RH %	Time h	9.1 (ball) <sup>c</sup>	9.3 (thermal)	9.2 (high ball) <sup>f</sup>
I	New construction	5	–	–	–	Group A	Group B	Group C
		4	150 <sup>d</sup>	–	48 <sup>d</sup>	2	1	1
		4	50	90 – 95	48	2	1	1
		4	e	–	e	2	1	1
II	Alternative construction	6	–	–	–	3	1	2

- <sup>a</sup> See Clause 16 for details of the requirements regarding changes in design features.
- <sup>b</sup> The tolerance of the oven temperature shall be  $\pm 2$  °C.
- <sup>c</sup> CRTs not visibly damaged in this test may also be subjected to the tests described in 9.2 and 9.3. If a CRT yields unacceptable results in either of these tests, the results shall be considered inconclusive and disregarded. A new CRT shall be tested in its place, as previous testing might have weakened the CRT.
- <sup>d</sup> Other Arrhenius based time/temperature combinations (according to the principles of IEC 60216-1) may be used (for example, 140 °C for 96 h, 130 °C for 168 h, 120 °C for 336 h or 110 °C for 672 h).
- <sup>e</sup> CRTs shall be thermally cycled between –40 °C and +70 °C at the rate of two cycles per day for a total of five cycles and held at each temperature extreme for 4 h.
- <sup>f</sup> Test 9.2 is only applied if implosion or rapid devacuation does not occur in ball test 9.1.

**Table 8 – Sampling and test programme for laminated CRTs exceeding 160 mm diagonal**

Sampling plan	CRT design <sup>a</sup>	Thermal conditioning			Impact and implosion test groups		
		Number of CRTs	Circulating air chamber		Number of CRTs to be tested as described in		
			Temp °C <sup>b</sup>	Time h	8.1 (ball) <sup>c</sup>	8.3 (thermal)	8.4 (high energy)
I	New construction	5	–	–	Group A	Group B	Group C
		5	150 <sup>d</sup>	48 <sup>d</sup>	2	1	2
II	Alternative construction	5	–	–	2	1	2

<sup>a</sup> See Clause 17 for details of the requirements regarding changes in design features.

<sup>b</sup> The tolerance of the oven temperature shall be  $\pm 2$  °C.

<sup>c</sup> CRTs not visibly damaged in this test may also be subjected to the tests described in 8.3 and 8.4. If a CRT yields unacceptable results in either of these tests, the results shall be considered inconclusive and disregarded. A new CRT shall be tested in its place, as previous testing might have weakened the CRT.

<sup>d</sup> Other Arrhenius based time/temperature combinations (according to the principles of IEC 60216-1) may be used (for example, 140 °C for 96 h, 130 °C for 168 h, 120 °C for 336 h or 110 °C for 672 h).

**Table 9 – Sampling and test programme for laminated CRTs from 76 mm to 160 mm diagonal**

Sampling plan	CRT design <sup>a</sup>	Thermal conditioning			Impact and implosion test groups		
		Number of CRTs	Circulating air chamber		Number of CRTs to be tested as described in		
			Temp °C <sup>b</sup>	Time h	9.1 (ball) <sup>c</sup>	9.3 (thermal)	9.4 (high energy)
I	New construction	4	–	–	Group A	Group B	Group C
		4	150 <sup>d</sup>	48 <sup>d</sup>	2	1	1
II	Alternative construction	3	–	–	1	1	1

<sup>a</sup> See Clause 17 for details of the requirements regarding changes in design features.

<sup>b</sup> The tolerance of the oven temperature shall be  $\pm 2$  °C.


<sup>c</sup> CRTs not visibly damaged in this test may also be subjected to the tests described in 9.3 and 9.4. If a CRT yields unacceptable results in either of these tests, the results shall be considered inconclusive and disregarded. A new CRT shall be tested in its place, as previous testing might have weakened the CRT.

<sup>d</sup> Other Arrhenius based time/temperature combinations (according to the principles of IEC 60216-1) may be used (for example, 140 °C for 96 h, 130 °C for 168 h, 120 °C for 336 h or 110 °C for 672 h).

**Table 10 – CRT size and deflection angle ranges**

CRT diagonal size range mm		Diagonal deflection angle degrees	
Laminated construction	Prestressed banded and bonded frame construction	Laminated construction	Prestressed banded and bonded frame construction
76 – 160	76 – 160	40 – up	40 – 69
161 – 320	161 – 255		70 – 99
321 – 520	256 – 350		100 – 112
521 – 690	351 – 460		113 – up
691 – 850	461 – 540		
	541 – 640		
	641 – 740		
	741 – 890		
	891 – 1 200		

IECNORM.COM : Click to view the full PDF of IEC 61965:2003

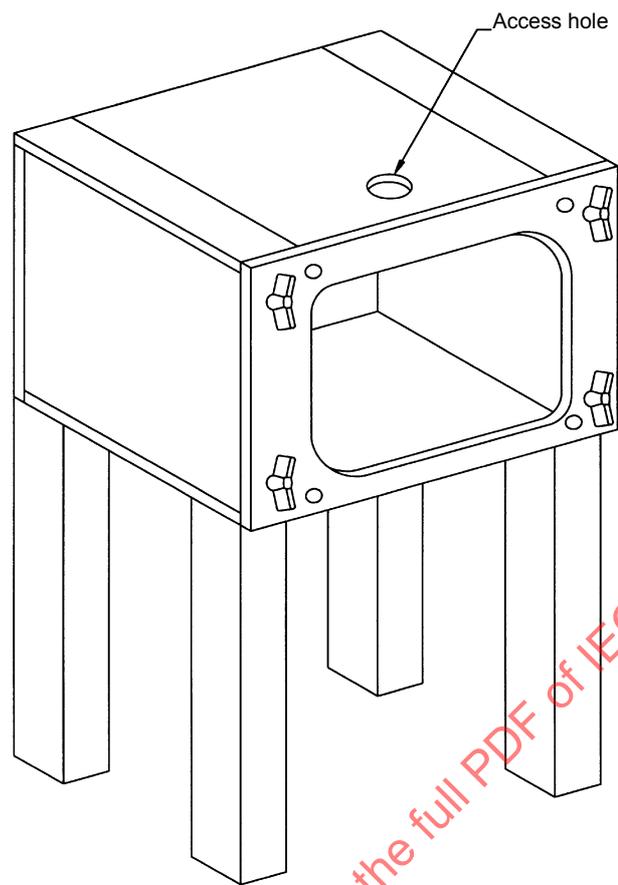


IEC 1643/2000

NOTE 1 A cabinet is typically 20 mm thick and made of plywood or metal of similar strength. The front panel should be made of plywood, typically 20 mm thick.

NOTE 2 An opening having an area of not less than one-quarter of the area of the face of the CRT or 0,02 m<sup>2</sup>, whichever is the smaller, should be provided in the bottom or rear of the cabinet for air intake in the event of an implosion.


**Figure 1 – Example of a test cabinet**

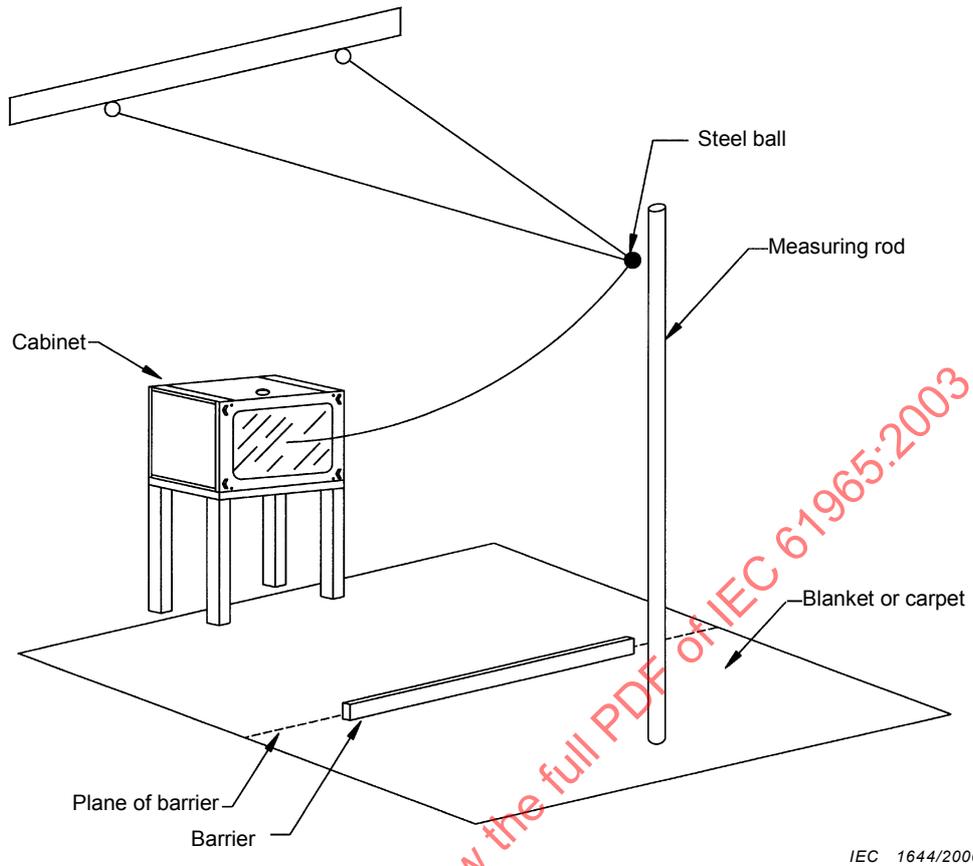

IEC 1644/2000

Figure 2 – Example of a ball impact test


IECNORM.COM : Click to view the full PDF of IEC 61965:2003

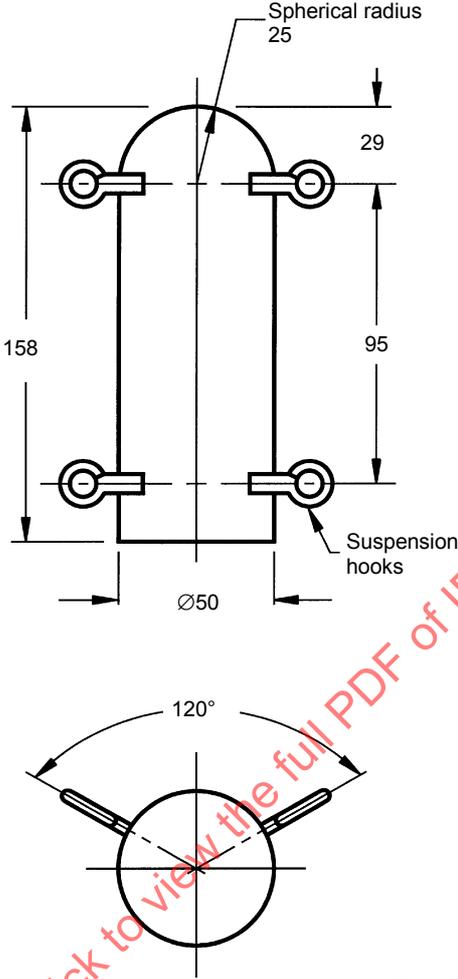

IEC 1645/2000

NOTE All linear dimensions are in millimetres.

Figure 3 – Example of a 2,3 kg steel missile

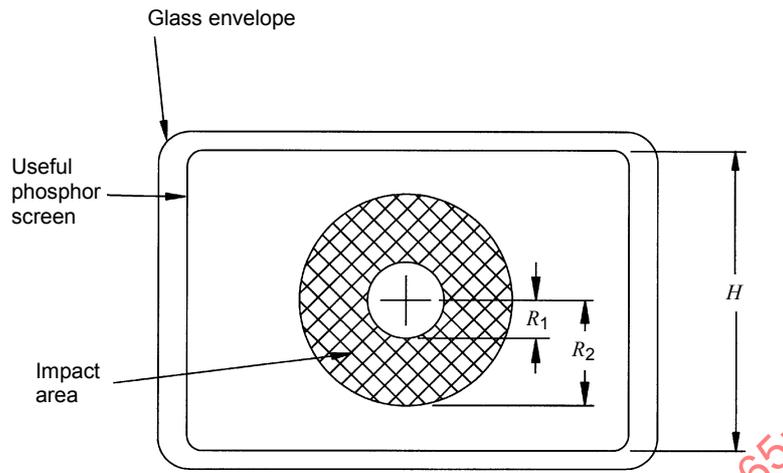

IEC 879/03

**Key**


$H$  height of the useful phosphor screen

$R_1$   $H/6$

$R_2$   $H/2 - 50$  mm

**Figure 4 – Missile impact area on a typical CRT**


IECNORM.COM : Click to view the full PDF of IEC 61965:2003

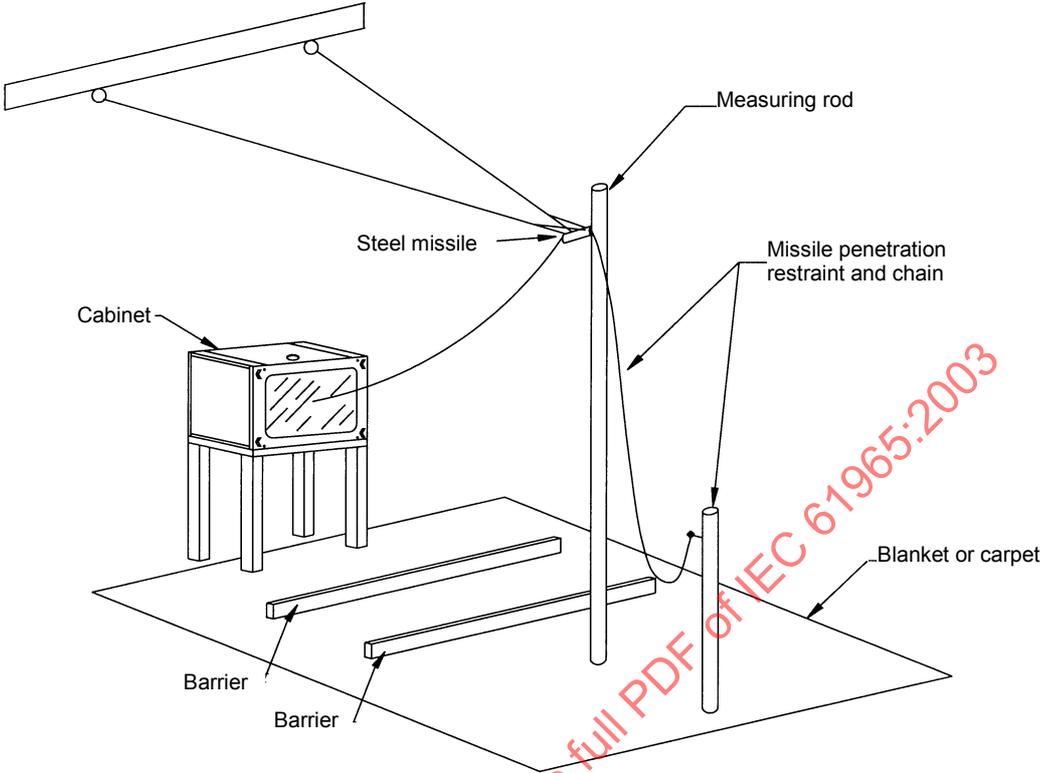

IEC 1647/2000

Figure 5 – Example of a missile impact test

IECNORM.COM : Click to view the full PDF of IEC 61965:2003

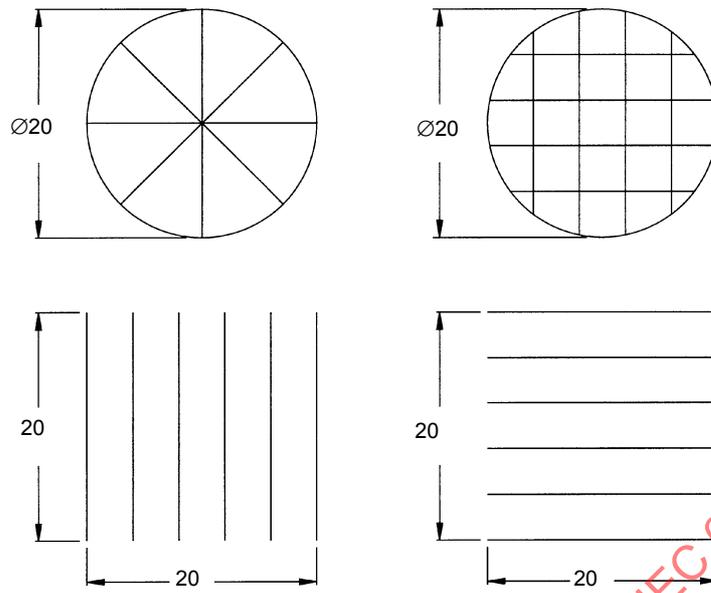


IEC 1648/2000

NOTE All linear dimensions are in millimetres.

**Figure 6 – Options for scratch patterns for implosions by the thermal shock method**


IECNORM.COM : Click to view the full PDF of IEC 61965:2003

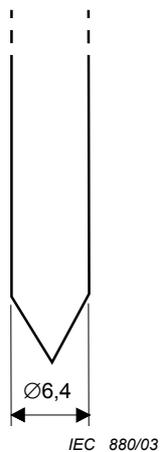

Steel drill rod, hardened to 60-62 on Rockwell C scale and with 60° conical tip and a tip radius of 0,03 mm  $\pm$  30 %

**Figure 7 – Film scoring tool**


IECNORM.COM : Click to view the full PDF of IEC 61965:2003

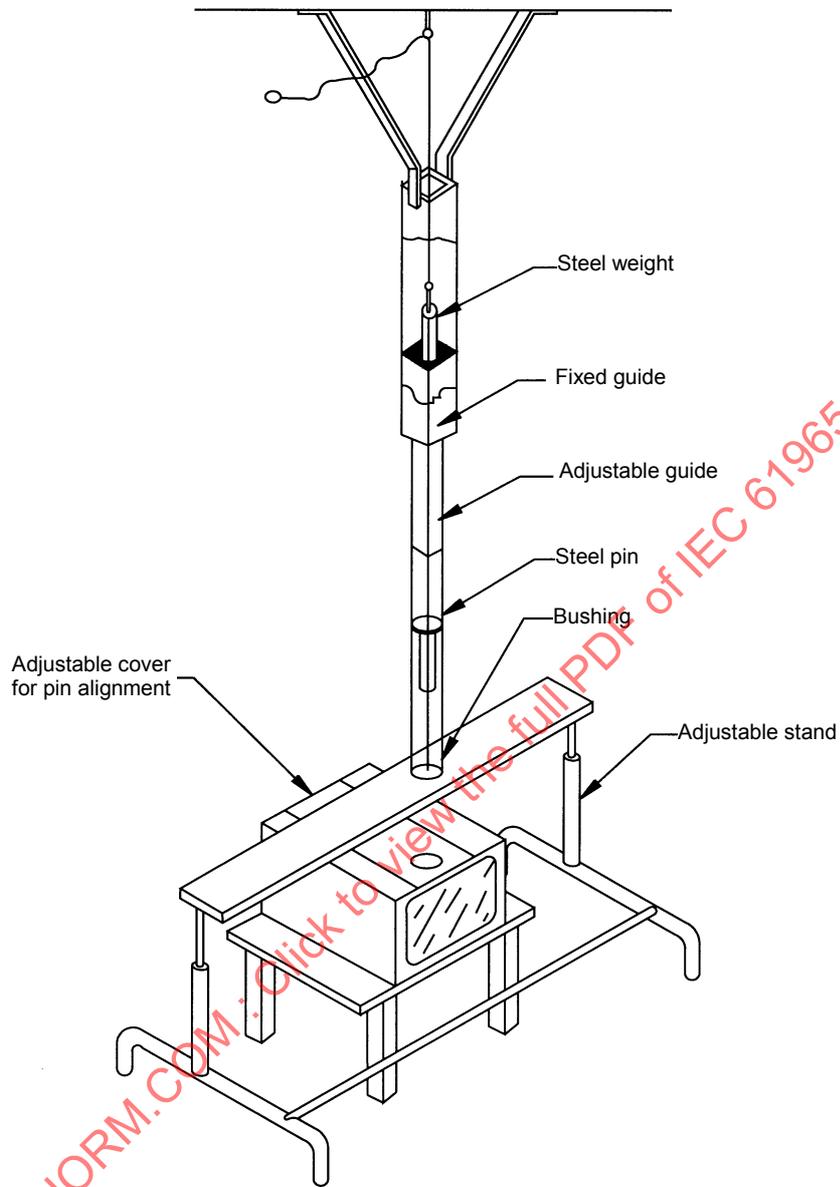

IEC 1649/2000


NOTE Adjust height of adjustable stand in such a way that, when the weight hits the pin, the amount of penetration of the pin into the CRT will be a maximum of 6 mm.

**Figure 8 – Example of high-energy impact test set-up**

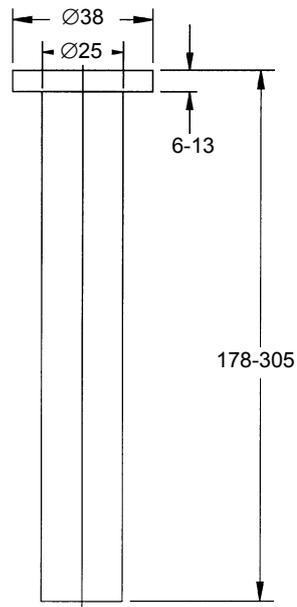

IEC 1650/2000

Example of steel pin for CRTs exceeding 160 mm face diagonal  
used in high-energy impact test

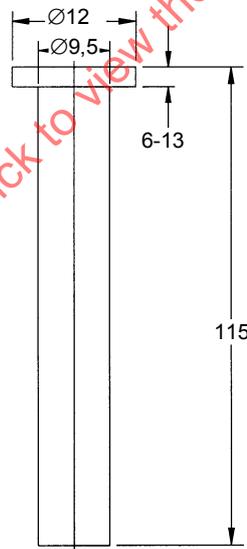


IEC 1651/2000

Example of steel pin for CRTs from 76 mm to 160 mm diagonal  
used in high-energy impact test


NOTE All linear dimensions are in millimetres.

**Figure 9 – Steel pins used in high-energy impact test**

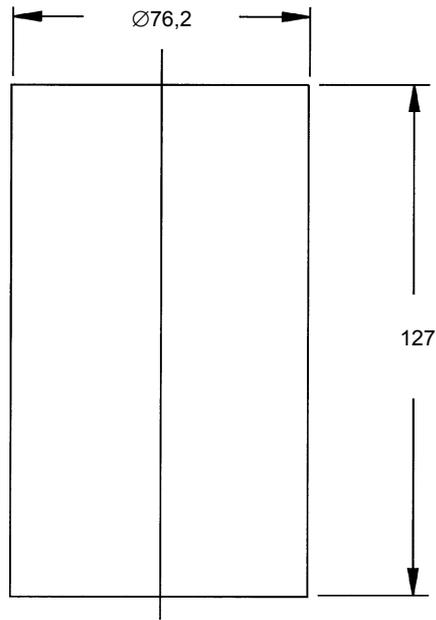

IEC 1652/2000

Example of 4,5 kg weight used in high-energy impact test on CRTs exceeding 160 mm diagonal

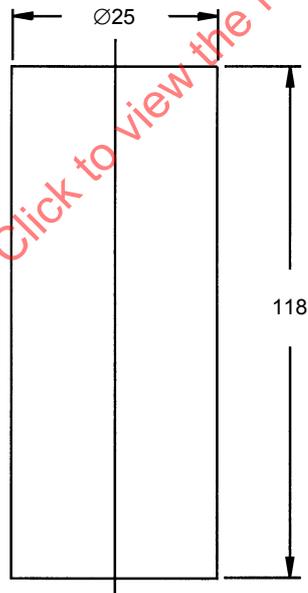


IEC 1653/2000

Example of 0,45 kg weight used in high-energy impact test on CRTs from 76 mm to 160 mm face diagonal

NOTE All linear dimensions are in millimetres.

**Figure 10 – Weights used in high-energy impact test**

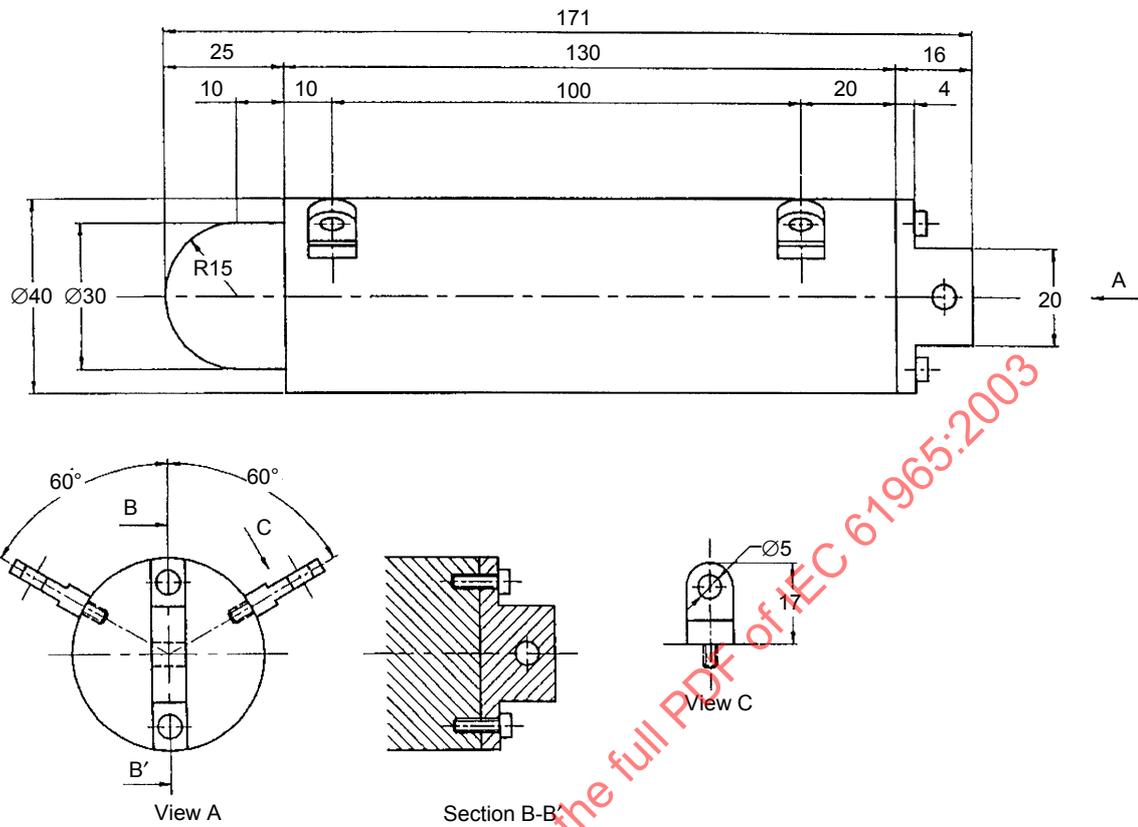

IEC 1654/2000

NOTE 1 All linear dimensions are in millimetres.

NOTE 2 Weight: approx. 1,4 kg.

NOTE 3 Rockwell hardness: >60.

NOTE 4 Surface: chromium coating.

Figure 11 – Example of 1,4 kg steel missile

## **Annex A** (informative)

### **Background to the development of this standard**

At its meeting in Eindhoven on 8-9 November 1994, IEC TC 39 noted that a confusing and costly situation had developed world wide concerning the certification of the mechanical strength of cathode ray tubes (CRTs). The current Clause 18 of IEC 60065 was still being used in most countries and had proved to be satisfactory to them. The binational standard UL 1418/CSA-C22.2 No. 228-92 was also being used for certification, mainly in the North American continent. The committee decided to propose a New Work Item 39/231/NP to develop a new standard which would ultimately replace the existing standards. After the voting stage it was clear that sufficient support existed and Working Group 2 was established comprising experts from Canada, Italy, Japan, Korea, the Netherlands, United Kingdom, United States of America and Germany.

IEC 60065 is an equipment standard under the responsibility of IEC TC 92. TC 39 undertook the task of creating a new standard intended to replace Clause 18 of IEC 60065, in line with the IEC policy that component requirements should be published in component standards, in the development of which due notice should be given to the component user requirements (Administrative Circular No. 71/1988).

At its first meeting, TC 39/WG 2 noted that, in fact, Clause 18 of IEC 60065 and the binational UL/CSA standard were the two documents which required harmonization. The two standards are similar in approach to testing. They both contain conditioning regimes and tests to prove the mechanical strength and the effects to the user of the implosion or rapid devacuation of the CRT. Both standards address only CRTs which have integral implosion protection systems.

Over 30 years' experience has been built up in the use of both standards. In that time, CRT technology has moved forward in the area of implosion protection systems and with the evolution of larger CRTs. Experience has also shown that certain areas of interpretation need to be addressed.

This standard contains the following main clauses:

- environmental conditioning instructions for use prior to testing;
- test methods and requirements which demonstrate that the CRT is mechanically strong enough to withstand impact damage which could be encountered in normal use so that the viewer is adequately protected against injury;
- test methods and requirements which demonstrate that, in the event of an implosion or rapid devacuation of the CRT, the implosion occurs in a controlled manner;
- detailed sampling tables which specify the numbers of CRTs to be tested to certify new designs and changes in design or construction;
- dedicated test methods and requirements for small CRTs (76 mm to 160 mm diagonal) and large CRTs (exceeding 160 mm diagonal).

During the development of the new standard, the TC 39/WG 2 members carried out extensive testing programmes and calculations to demonstrate that the proposed new test methods ensure protection for the users of the CRTs which are covered by the standard, and that the stringent requirements of either of the existing standards are not degraded. The conclusions of these findings are summarized as follows.

### **A.1 Mechanical strength test**

- a) The ball impact test attempts to simulate the situation where the CRT can be struck by any likely domestic object. The shape and energy of such objects will vary enormously and the choice of a single device size and energy for this test is in order to ensure standardization i.e., an easily reproducible and repeatable test with the minimum of variability.
- b) The 40 mm/5,5 J ball test was selected as it was already in use in IEC 60065 and was optional in the binational standard. Testing showed it to be generally equivalent to the use of the 51 mm/7 J ball when combined with the use of a single barrier at 1,5 m.
- c) From ballistic and statistical calculations the kinetic energy of a 0,025 g particle (the maximum size permitted by this standard) is of the order of  $1 \times 10^{-4}$  J and the maximum particle speed is around 4 m/s (9 m.p.h.). This energy level is negligible with respect to its ability to cause flesh damage as human skin exhibits visco-elastic properties (people performing normal activities frequently encounter airborne particles of greater mass and higher velocity than this).

### **A.2 Implosion test**

Due to the introduction of larger CRTs having thicker faceplates and to the use of laminated screens, it is not possible, in some cases, to induce rapid devacuation using the ball impact test. In order to evaluate the effectiveness of the implosion protection system, a test with a larger impact object (missile or high-energy) is used to induce rapid devacuation.

### **A.3 Small CRTs (76 mm to 160 mm diagonal)**

Research has shown that small CRTs may require implosion protection systems. Scaled-down tests have been developed for these sizes.

### **A.4 Evaluation time**

As the impact tests in this standard are overstress tests, evaluation of test results includes only the effect of rapid devacuation and not subsequent relaxation of mechanical stresses in the CRT from the implosion protection system. Five seconds is deemed satisfactory to evaluate the result of rapid devacuation and exclude results of stress relaxation.