

# INTERNATIONAL STANDARD

**IEC**  
**62317-9**

First edition  
2006-04

---

---

## Ferrite cores – Dimensions –

### Part 9: Planar cores

IECNORM.COM: Click to view the full PDF of IEC 62317-9:2006



Reference number  
IEC 62317-9:2006(E)

## Publication numbering

As from 1 January 1997 all IEC publications are issued with a designation in the 60000 series. For example, IEC 34-1 is now referred to as IEC 60034-1.

## Consolidated editions

The IEC is now publishing consolidated versions of its publications. For example, edition numbers 1.0, 1.1 and 1.2 refer, respectively, to the base publication, the base publication incorporating amendment 1 and the base publication incorporating amendments 1 and 2.

## Further information on IEC publications

The technical content of IEC publications is kept under constant review by the IEC, thus ensuring that the content reflects current technology. Information relating to this publication, including its validity, is available in the IEC Catalogue of publications (see below) in addition to new editions, amendments and corrigenda. Information on the subjects under consideration and work in progress undertaken by the technical committee which has prepared this publication, as well as the list of publications issued, is also available from the following:

- **IEC Web Site** ([www.iec.ch](http://www.iec.ch))

- **Catalogue of IEC publications**

The on-line catalogue on the IEC web site ([www.iec.ch/searchsub](http://www.iec.ch/searchsub)) enables you to search by a variety of criteria including text searches, technical committees and date of publication. On-line information is also available on recently issued publications, withdrawn and replaced publications, as well as corrigenda.

- **IEC Just Published**

This summary of recently issued publications ([www.iec.ch/online\\_news/justpub](http://www.iec.ch/online_news/justpub)) is also available by email. Please contact the Customer Service Centre (see below) for further information.

- **Customer Service Centre**

If you have any questions regarding this publication or need further assistance, please contact the Customer Service Centre:

Email: [custserv@iec.ch](mailto:custserv@iec.ch)  
Tel: +41 22 919 02 11  
Fax: +41 22 919 03 00

# INTERNATIONAL STANDARD

# IEC 62317-9

First edition  
2006-04

---

---

## Ferrite cores – Dimensions –

### Part 9: Planar cores

IECNORM.COM: Click to view the full PDF of IEC 62317-9:2006

© IEC 2006 — Copyright - all rights reserved

No part of this publication may be reproduced or utilized in any form or by any means, electronic or mechanical, including photocopying and microfilm, without permission in writing from the publisher.

International Electrotechnical Commission, 3, rue de Varembé, PO Box 131, CH-1211 Geneva 20, Switzerland  
Telephone: +41 22 919 02 11 Telefax: +41 22 919 03 00 E-mail: [inmail@iec.ch](mailto:inmail@iec.ch) Web: [www.iec.ch](http://www.iec.ch)



Commission Electrotechnique Internationale  
International Electrotechnical Commission  
Международная Электротехническая Комиссия


PRICE CODE

Q

*For price, see current catalogue*

## CONTENTS

FOREWORD.....	3
INTRODUCTION.....	5
1 Scope.....	6
2 Normative references .....	6
3 Primary standards .....	6
3.1 Planar shape and dimensions.....	6
3.2 Dimensions of planar core EL and the mating PLT-core.....	7
3.3 Dimensions of low-profile core E-core and the mating PLT-core.....	9
3.4 Dimensions of low-profile core ER-core .....	11
Annex A (normative) Low-profile core design .....	15
Figure 1 – Planar core EL and the mating PLT-core.....	7
Figure 2 – Low-profile E-core and the mating PLT-core.....	9
Figure 3 – Low-profile ER-core .....	11
Table 1 – Dimensions of planar core EL and the mating PLT-core .....	7
Table 2 – Effective parameter values and $A_{\min}$ values.....	8
Table 3 – Dimensions of low-profile E-core and the mating PLT-core.....	9
Table 4 – Effective parameter values and $A_{\min}$ values.....	10
Table 5 – Dimensions of low-profile ER-core.....	12
Table 6 – Effective parameter values and $A_{\min}$ values.....	14
Table A.1 – Sizes and design ratios for ER-core .....	17

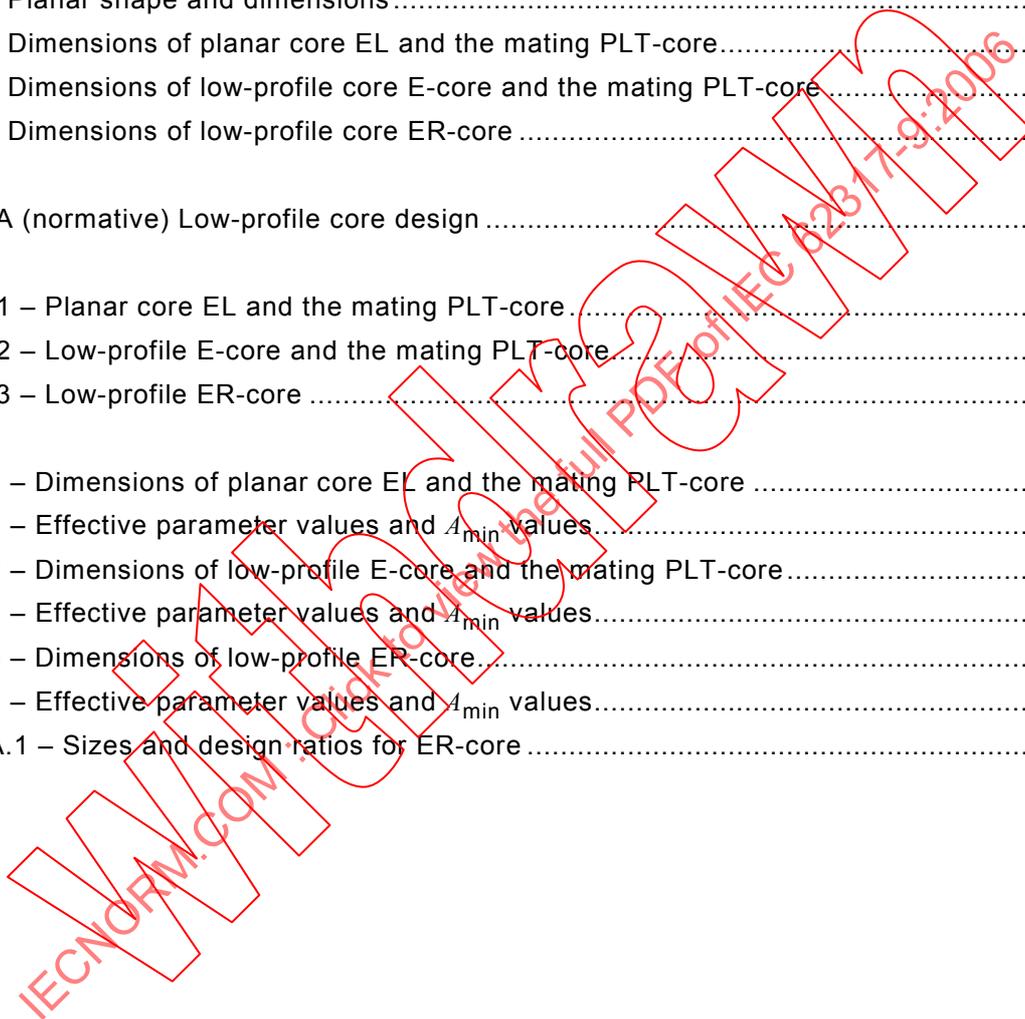

## INTERNATIONAL ELECTROTECHNICAL COMMISSION

**FERRITE CORES – DIMENSIONS –****Part 9: Planar cores**

## FOREWORD

- 1) The International Electrotechnical Commission (IEC) is a worldwide organization for standardization comprising all national electrotechnical committees (IEC National Committees). The object of the IEC is to promote international co-operation on all questions concerning standardization in the electrical and electronic fields. To this end and in addition to other activities, IEC publishes International Standards, Technical Specifications, Technical Reports, Publicly Available Specifications (PAS) and Guides (hereafter referred to as "IEC Publication(s)"). Their preparation is entrusted to technical committees; any IEC National Committee interested in the subject dealt with may participate in this preparatory work. International, governmental and non-governmental organizations liaising with the IEC also participate in this preparation. IEC collaborates closely with the International Organization for Standardization (ISO) in accordance with conditions determined by agreement between the two organizations.
- 2) The formal decisions or agreements of IEC on technical matters express, as nearly as possible, an international consensus of opinion on the relevant subjects since each technical committee has representation from all interested IEC National Committees.
- 3) IEC Publications have the form of recommendations for international use and are accepted by IEC National Committees in that sense. While all reasonable efforts are made to ensure that the technical content of IEC Publications is accurate, IEC cannot be held responsible for the way in which they are used or for any misinterpretation by any end user.
- 4) In order to promote international uniformity, IEC National Committees undertake to apply IEC Publications transparently to the maximum extent possible in their national and regional publications. Any divergence between any IEC Publication and the corresponding national or regional publication shall be clearly indicated in the latter.
- 5) IEC provides no marking procedure to indicate its approval and cannot be rendered responsible for any equipment declared to be in conformity with an IEC Publication.
- 6) All users should ensure that they have the latest edition of this publication.
- 7) No liability shall attach to IEC or its directors, employees, servants or agents including individual experts and members of its technical committees and IEC National Committees for any personal injury, property damage or other damage of any nature whatsoever, whether direct or indirect, or for costs (including legal fees) and expenses arising out of the publication, use of, or reliance upon, this IEC Publication or any other IEC Publications.
- 8) Attention is drawn to the Normative references cited in this publication. Use of the referenced publications is indispensable for the correct application of this publication.
- 9) Attention is drawn to the possibility that some of the elements of this IEC publication may be the subject of patent rights. IEC shall not be held responsible for identifying any or all such patent rights.

International Standard IEC 62317-9 has been prepared IEC technical committee 51: Magnetic components and ferrite materials.

This International Standard cancels and replaces IEC 61860 published in 2000. This edition constitutes a technical revision. This International Standard includes the following significant technical changes and additions with respect to IEC 61860:2000:

- a) addition of the planar EL family of cores;
- b) addition of the low-profile ER family of cores;
- c) the low-profile RM-family defined in IEC 61860:2000 has been moved to IEC 62137-4 for RM-cores and associated parts.

This publication has been drafted in accordance with the ISO/IEC Directives, Part 2.

The text of this standard is based on the following documents:

FDIS	Report on voting
51/849/FDIS	51/858/RVD

Full information on the voting for the approval of this standard can be found in the report on voting indicated in the above table.

IEC 62317 consists of the following parts, under the general title *Ferrite cores – Dimensions*:

- Part 1: General (under consideration)
- Part 2: Pot cores (under consideration, currently available as IEC 60133)
- Part 3: Half pot cores (under consideration, currently available as IEC 62323)
- Part 4: RM-cores and associated parts
- Part 5: EP-cores (under consideration, currently available as IEC 61596)
- Part 6: ETD-cores (under consideration, currently available as IEC 61185)
- Part 7: EER-cores
- Part 8: E-cores
- Part 9: Planar cores
- Part 10: PM-cores (under consideration, currently available as IEC 61247)
- Part 11: EC-cores (under consideration, currently available as IEC 60647)
- Part 12: Uncoated ring cores (under consideration, currently available as IEC 61604)

The committee has decided that the contents of this publication will remain unchanged until the maintenance result date indicated on the IEC web site under "<http://webstore.iec.ch>" in the data related to the specific publication. At this date, the publication will be

- reconfirmed;
- withdrawn;
- replaced by a revised edition, or
- amended.

A bilingual version of this publication may be issued at a later date.

## INTRODUCTION

Nowadays, d.c.-d.c. converter power supplies increasingly employ transformers and chokes the windings of which are made of multi-layer printed circuit board or the windings are constructed in the motherboard, rather than the transformers wound by conventional copper wires. This part of IEC 62317 specifies the optimum shapes and dimensions of cores for SMD (Surface Mounted Device) and of cores for which the windings are constructed in the motherboard. The motherboard has slots cut out to accept the ferrite cores. This is called the total integration in a multi-layer motherboard. The core shape specified in this part of IEC 62317 satisfies the demand for lower profile as well as for smaller floor space.

IECNORM.COM: Click to view the full PDF of IEC 62317-9:2006  
Withdrawn

# FERRITE CORES – DIMENSIONS –

## Part 9: Planar cores

### 1 Scope

This International Standard specifies the shapes and dimensions of ferrite cores for inductive components (transformers and chokes) of which the coil is typically constructed by multi-layer board or the coil is part of the motherboard.

The general consideration upon which the design of this range of cores is based is given in Annex A.

### 2 Normative references

The following referenced documents are indispensable for the application of this document. For dated references, only the edition cited applies. For undated references, the latest edition of the referenced document (including any amendments) applies.

IEC 60205, *Calculation of the effective parameters of magnetic piece parts*

IEC 62317-4:2005, *Ferrite cores – Dimensions – Part 4: RM cores and associated parts*

### 3 Primary standard

#### 3.1 Planar shape and dimensions

The main shapes and dimensions shall be as given in the following figures and tables.

The main shape, dimensions, and parameters for EL core are given in:

Figure 1 – Planar core EL and mating PLT-core;

Table 1 – Dimensions of planar core EL and the mating PLT-core;

Table 2 – Effective parameter values and  $A_{\min}$  values.

The main shape, dimensions, and parameters for low-profile E-cores are given in:

Figure 2 – Low-profile E-core and mating PLT-core;

Table 3 – Dimensions of low-profile E-core and the mating PLT-core;

Table 4 – Effective parameter values and  $A_{\min}$  values.

The main shape, dimensions, and parameters for ER-cores are given in:

Figure 3 – Low-profile ER-core;

Table 5 – Dimensions of low-profile ER-core;

Table 6 – Effective parameter values and  $A_{\min}$  values.

A uniform dimensional nomenclature has been chosen in order to facilitate a comparison of major physical attributes among the different core shapes.

### 3.2 Dimensions of planar core EL and the mating PLT-core

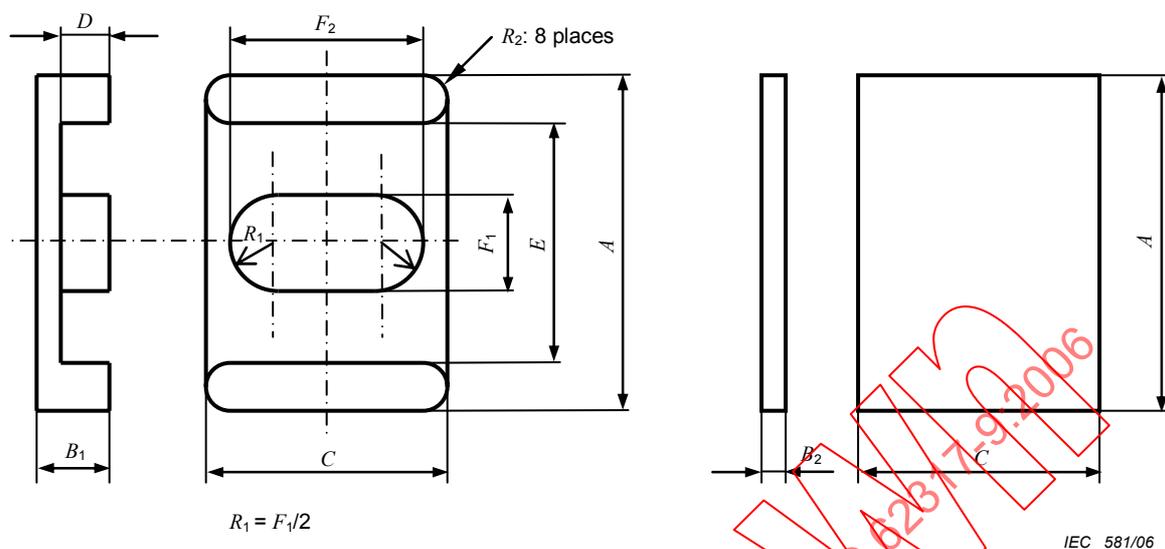


Figure 1 – Planar core EL and the mating PLT-core

Table 1 – Dimensions of planar core EL and the mating PLT-core

*Dimensions in millimetres*

Size		A	B <sub>1</sub>	B <sub>2</sub>	C	D	E	F <sub>1</sub>	F <sub>2</sub>	R <sub>2</sub>
EL11 × 2,0	min.	10,80	1,91		8,60	0,90	8,97	2,68	6,25	0,3
	max.	11,20	2,11		9,00	1,10	9,37	2,88	6,55	
EL11 × 3,0	min.	10,80	2,91		8,60	1,90	8,97	2,68	6,25	0,3
	max.	11,20	3,11		9,00	2,10	9,37	2,88	6,55	
PLT11 × 1,0	min.	10,80		0,96	8,60					
	max.	11,20		1,06	9,00					
EL13 × 2,2	min.	12,75	2,09		10,20	0,90	10,63	3,19	7,41	0,3
	max.	13,25	2,29		10,60	1,10	11,03	3,39	7,71	
EL13 × 3,2	min.	12,75	3,09		10,20	1,90	10,63	3,19	7,41	0,3
	max.	13,25	3,29		10,60	2,10	11,03	3,39	7,71	
PLT13 × 1,2	min.	12,75		1,14	10,20					
	max.	13,25		1,24	10,60					
EL15,5 × 2,9	min.	15,20	2,82		12,15	1,40	12,67	3,82	8,81	0,3
	max.	15,80	3,02		12,65	1,60	13,17	4,02	9,21	
EL15,5 × 4,4	min.	15,20	4,32		12,15	2,90	12,67	3,82	8,81	0,3
	max.	15,80	4,52		12,65	3,10	13,17	4,02	9,21	
PLT15,5 × 1,4	min.	15,20		1,32	12,15					
	max.	15,80		1,52	12,65					
EL18 × 3,7	min.	17,70	3,55		14,15	1,90	14,70	4,45	10,27	0,3
	max.	18,30	3,75		14,65	2,10	15,30	4,65	10,67	
EL18 × 5,7	min.	17,70	5,55		14,15	3,85	14,70	4,45	10,27	0,3
	max.	18,30	5,75		14,65	4,15	15,30	4,65	10,67	

Table 1 (continued)

*Dimensions in millimetres*

Size		A	B <sub>1</sub>	B <sub>2</sub>	C	D	E	F <sub>1</sub>	F <sub>2</sub>	R <sub>2</sub>
PLT18 × 1,7	min.	17,70		1,55	14,15					
	max.	18,30		1,75	14,65					
EL20 × 3,8	min.	19,65	3,73		15,70	1,90	16,37	4,91	11,43	0,5
	max.	20,35	3,93		16,30	2,10	16,97	5,21	11,83	
EL20 × 5,8	min.	19,65	5,68		15,70	3,85	16,37	4,91	11,43	0,5
	max.	20,35	5,98		16,30	4,15	16,97	5,21	11,83	
PLT20 × 1,8	min.	19,65		1,73	15,70					
	max.	20,35		1,93	16,30					
EL22 × 4,0	min.	21,60	3,92		17,30	1,90	17,98	5,41	12,54	0,5
	max.	22,40	4,12		17,90	2,10	18,68	5,71	13,04	
EL22 × 6,0	min.	21,60	5,87		17,30	3,85	17,98	5,41	12,54	0,5
	max.	22,40	6,17		17,90	4,15	18,68	5,71	13,04	
PLT22 × 2,0	min.	21,60		1,92	17,30					
	max.	22,40		2,12	17,90					
EL25 × 4,3	min.	24,55	4,19		19,65	1,90	20,48	6,17	14,29	0,5
	max.	25,45	4,39		20,35	2,10	21,18	6,47	14,79	
EL25 × 6,3	min.	24,55	6,14		19,65	3,85	20,48	6,17	14,29	0,5
	max.	25,45	6,44		20,35	4,15	21,18	6,47	14,79	
PLT25 × 2,3	min.	24,55		2,19	19,65					
	max.	25,45		2,39	20,35					

Table 2 – Effective parameter values and A<sub>min</sub> values


Size	C <sub>1</sub> mm <sup>-1</sup>	C <sub>2</sub> mm <sup>-3</sup>	l <sub>e</sub> mm	A <sub>e</sub> mm <sup>2</sup>	V <sub>e</sub> mm <sup>3</sup>	A <sub>min</sub> <sup>a)</sup> mm <sup>2</sup>	Remarks
EL-EL11 × 4,0	0,826 45	49,923 × 10 <sup>-3</sup>	13,7	16,5	226	15,9	Combination EL-EL refers to two shorter height EL cores for size-designation.
EL-EL13 × 4,4	0,666 66	28,815 × 10 <sup>-3</sup>	15,4	23,1	357	22,4	
EL-EL15,5 × 5,8	0,596 74	18,143 × 10 <sup>-3</sup>	19,6	32,9	646	31,9	
EL-EL18 × 7,3	0,538 30	12,162 × 10 <sup>-3</sup>	23,8	44,3	1 050	43,0	
EL-EL20 × 7,7	0,468 64	8,586 6 × 10 <sup>-3</sup>	25,6	54,6	1 400	52,9	
EL-EL22 × 8,0	0,412 80	6,231 4 × 10 <sup>-3</sup>	27,3	66,2	1 810	64,2	
EL-EL25 × 8,6	0,350 34	4,094 2 × 10 <sup>-3</sup>	30,0	85,6	2 570	83,0	
EL-PLT11 × 4,0	0,826 45	49,943 × 10 <sup>-3</sup>	13,7	16,5	226	15,9	Combination EL-PLT refers to one taller height EL core paired with one PLT core for each size-designation.
EL-PLT13 × 4,4	0,666 66	28,815 × 10 <sup>-3</sup>	15,4	23,1	357	22,4	
EL-PLT15,5 × 5,8	0,569 74	18,143 × 10 <sup>-3</sup>	19,6	32,9	646	31,9	
EL-PLT18 × 7,3	0,538 30	12,162 × 10 <sup>-3</sup>	23,8	44,3	1 050	43,0	
EL-PLT20 × 7,7	0,468 64	8,586 6 × 10 <sup>-3</sup>	25,6	54,6	1 400	52,9	
EL-PLT22 × 8,0	0,412 80	6,231 4 × 10 <sup>-3</sup>	27,3	66,2	1 810	64,2	
EL-PLT25 × 8,6	0,350 34	4,094 2 × 10 <sup>-3</sup>	30,0	85,6	2 570	83,0	

Table 2 (continued)

Size	$C_1$ mm <sup>-1</sup>	$C_2$ mm <sup>-3</sup>	$l_e$ mm	$A_e$ mm <sup>2</sup>	$V_e$ mm <sup>3</sup>	$A_{\min}^{a)}$ mm <sup>2</sup>	Remarks
EL-PLT11 × 3,0	0,701 76	42,170 × 10 <sup>-3</sup>	11,7	16,6	194	15,9	Combination EL-PLT refers to one thinner height EL core paired with one PLT for each size-designation.
EL-PLT13 × 3,4	0,577 71	24,857 × 10 <sup>-3</sup>	13,4	23,2	312	22,4	
EL-PLT15,5 × 4,3	0,502 96	15,212 × 10 <sup>-3</sup>	16,6	33,1	550	31,9	
EL-PLT18 × 5,3	0,445 54	10,011 × 10 <sup>-3</sup>	19,8	44,5	882	43,0	
EL-PLT20 × 5,7	0,392 32	7,167 9 × 10 <sup>-3</sup>	21,6	54,9	1 180	52,9	
EL-PLT22 × 6,0	0,350 61	5,264 5 × 10 <sup>-3</sup>	23,4	66,6	1 560	64,2	
EL-PLT25 × 6,6	0,302 22	3,515 6 × 10 <sup>-3</sup>	26,0	86,0	2 230	83,0	

a) See 2.2 of IEC 60205.

### 3.3 Dimensions of low-profile core E-core and the mating PLT-core

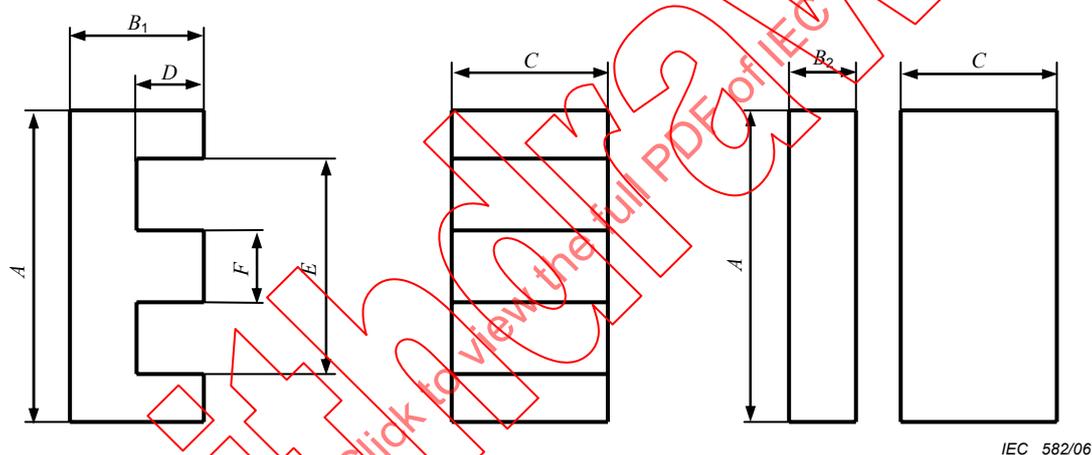

IEC 582/06

Figure 2 – Low-profile E-core and the mating PLT-core

Table 3 – Dimensions of low-profile E-core and the mating PLT-core

Size		Dimensions in millimetres						
		$A$	$B_1$	$B_2$	$C$	$D$	$E$	$F$
E14 × 3,5 × 5	min.	13,70	3,40		4,90	1,90	10,75	2,95
	max.	14,30	3,60		5,10	2,10	11,25	3,05
PLT14 × 1,5 × 5	min.	13,70		1,40	4,90			
	max.	14,30		1,60	5,10			
E18 × 4 × 10	min.	17,65	3,90		9,80	1,90	13,70	3,90
	max.	18,35	4,10		10,20	2,10	14,30	4,10
PLT18 × 2 × 10	min.	17,65		1,90	9,80			
	max.	18,35		2,10	10,20			
E22 × 6 × 16	min.	21,40	5,60		15,50	3,10	16,40	4,90
	max.	22,20	5,80		16,10	3,30	17,20	5,10
PLT22 × 2,5 × 16	min.	21,40		2,40	15,50			
	max.	22,20		2,60	16,10			

**Table 3 (continued)**

*Dimensions in millimetres*

Size		A	B <sub>1</sub>	B <sub>2</sub>	C	D	E	F
E32 × 6 × 20	min.	31,10	6,20		19,90	2,95	24,90	6,20
	max.	32,40	6,50		20,75	3,40	26,10	6,50
PLT32 × 3 × 20	min.	31,10		3,00	19,90			
	max.	32,40		3,35	20,75			
E38 × 8 × 25	min.	37,30	8,10		24,85	4,30	30,20	7,40
	max.	38,90	8,40		25,95	4,60	31,40	7,80
PLT38 × 4 × 25	min.	37,30		3,65	24,85			
	max.	38,90		3,95	25,95			
E43 × 10 × 28	min.	42,30	9,35		27,30	5,25	34,70	7,90
	max.	44,10	9,65		28,50	5,55	36,30	8,30
PLT43 × 4 × 28	min.	42,30		3,95	27,30			
	max.	44,10		4,25	28,50			
E58 × 11 × 38	min.	57,20	10,35		37,30	6,35	50,00	7,90
	max.	59,60	10,75		38,90	6,65	52,20	8,30
PLT58 × 4 × 38	min.	57,20		3,85	37,30			
	max.	59,60		4,25	38,90			
E64 × 10 × 50	min.	62,70	10,05		49,70	4,95	52,50	10,00
	max.	65,30	10,35		51,90	5,25	54,70	10,40
PLT64 × 5 × 50	min.	62,70		4,95	49,70			
	max.	65,30		5,25	51,90			
E102 × 20 × 38	min.	100,0	20,10		36,50	12,90	85,00	13,70
	max.	104,0	20,50		38,50	13,40	88,60	14,30
PLT102 × 7 × 38	min.	100,0		6,95	36,50			
	max.	104,0		7,35	38,50			

**Table 4 – Effective parameter values and A<sub>min</sub> values**

Size	C <sub>1</sub> mm <sup>-1</sup>	C <sub>2</sub> mm <sup>-3</sup>	l <sub>e</sub> mm	A <sub>e</sub> mm <sup>2</sup>	V <sub>e</sub> mm <sup>3</sup>	A <sub>min</sub> <sup>a)</sup> mm <sup>2</sup>	Remarks
E-E14	1,380 8	92,005 × 10 <sup>-3</sup>	20,7	15,0	311	15,0	Combination E-E
E-E18	0,607 08	15,177 × 10 <sup>-3</sup>	24,3	40,0	971	40,0	
E-E22	0,410 81	5,200 1 × 10 <sup>-3</sup>	32,5	79,0	2 560	79,0	
E-E32	0,324 58	2,525 5 × 10 <sup>-3</sup>	41,8	129	5 370	127	
E-E38	0,276 13	1,443 9 × 10 <sup>-3</sup>	52,8	191	10 100	185	
E-E43	0,274 13	1,219 7 × 10 <sup>-3</sup>	61,6	225	13 800	215	
E-E58	0,269 43	0,893 10 × 10 <sup>-3</sup>	81,3	302	24 500	278	
E-E64	0,153 67	0,295 56 × 10 <sup>-3</sup>	79,9	520	41 500	518	
E-E102	0,273 88	0,506 86 × 10 <sup>-3</sup>	148	540	80 000	525	


Table 4 (continued)

Size	$C_1$ mm <sup>-1</sup>	$C_2$ mm <sup>-3</sup>	$l_e$ mm	$A_e$ mm <sup>2</sup>	$V_e$ mm <sup>3</sup>	$A_{\min}^{a)}$ mm <sup>2</sup>	Remarks
E-PLT14	1,114 2	74,277 × 10 <sup>-3</sup>	16,7	15,0	251	15,0	Combina- tion E-PLT
E-PLT18	0,507 08	12,677 × 10 <sup>-3</sup>	20,3	40,0	811	40,0	
E-PLT22	0,329 80	4,174 6 × 10 <sup>-3</sup>	26,1	79,0	2 060	79,0	
E-PLT32	0,275 28	2,138 6 × 10 <sup>-3</sup>	35,4	129	4 560	127	
E-PLT38	0,229 08	1,195 0 × 10 <sup>-3</sup>	43,9	192	8 420	185	
E-PLT43	0,225 10	0,996 95 × 10 <sup>-3</sup>	50,8	226	11 500	214	
E-PLT58	0,225 00	0,740 83 × 10 <sup>-3</sup>	68,3	304	20 800	278	
E-PLT64	0,134 18	0,258 30 × 10 <sup>-3</sup>	70,0	519	36 200	518	
E-PLT102	0,225 70	0,418 68 × 10 <sup>-3</sup>	121	539	65 600	525	

a) See 2.2 of IEC 60205.

NOTE Values ignore the effect of radii. These may have some influence on the outcome of the calculation. They can be incorporated in the formulas as shown in IEC 60205.

### 3.4 Dimensions of low-profile core ER-core

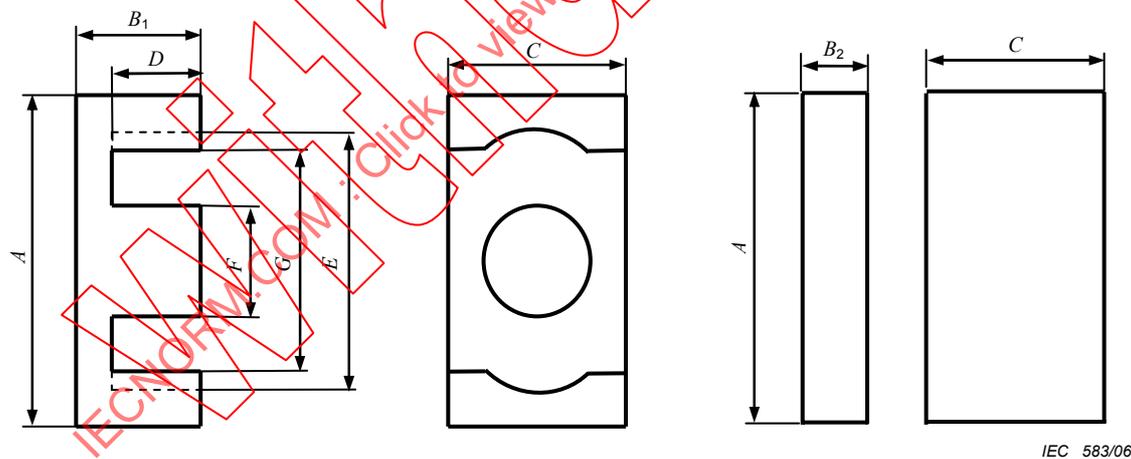

IEC 583/06

Figure 3 – Low-profile ER-core

**Table 5 – Dimensions of low-profile ER-core**

*Dimensions in millimetres*

<b>Size</b>		<i>A</i>	<i>B<sub>1</sub></i>	<i>B<sub>2</sub></i>	<i>C</i>	<i>D</i>	<i>E</i>	<i>F</i>	<i>G</i>
ER9,5 × 2,5 × 5	min.	9,15	2,375		4,80	1,60	7,50	3,25	7,00
	max.	9,55	2,525		5,00	1,75	7,75	3,55	7,40
PLT9,5 × 1 × 5	min.	9,15		0,70	4,80				
	max.	9,55		0,85	5,00				
ER11 × 2,5 × 6	min.	10,65	2,375		5,80	1,50	8,70	4,00	7,90
	max.	11,00	2,525		6,00	1,65	9,00	4,25	8,30
PLT11 × 1 × 6	min.	10,65		0,80	5,80				
	max.	11,00		0,95	6,00				
ER13 × 3 × 9	min.	12,5	2,775		8,45	1,625	10,9	4,85	8,75
	max.	13,1	2,925		8,95	1,875	11,5	5,15	9,35
PLT13 × 1 × 9	min.	12,5		1,00	8,45				
	max.	13,1		1,20	8,95				
ER14,5 × 3 × 7	min.	14,30	2,90		6,60	1,55	11,6	4,60	11,6
	max.	14,70	3,00		6,80	1,75	12,0	4,80	12,0
PLT14,5 × 1 × 7	min.	14,30		1,20	6,60				
	max.	14,70		1,40	6,80				
ER18 × 3 × 10	min.	17,65	3,05		9,5	1,50	15,3	6,05	13,5
	max.	18,35	3,25		9,9	1,70	15,9	6,35	14,1
PLT18 × 1,5 × 10	min.	17,65		1,45	9,5				
	max.	18,35		1,65	9,9				
ER23 × 3,6 × 13	min.	22,75	3,50		12,25	1,50	19,8	7,8	17,5
	max.	23,65	3,70		12,75	1,70	20,6	8,2	18,2
ER23 × 5 × 13	min.	22,75	5,00		12,25	3,00	19,8	7,8	17,5
	max.	23,65	5,20		12,75	3,20	20,6	8,2	18,2
PLT23 × 2 × 13	min.	22,75		1,90	12,25				
	max.	23,65		2,10	12,75				
ER25 × 8 × 18	min.	24,6	7,90		17,7	5,00	21,6	10,8	14,5
	max.	25,4	8,10		18,3	5,30	22,4	11,2	14,9
PLT25 × 3 × 18	min.	24,6		2,75	17,7				
	max.	25,4		2,95	18,3				
ER25 × 6 × 15	min.	24,5	5,40		14,5	3,00	21,3	9,20	18,3
	max.	25,5	5,60		15,1	3,20	22,1	9,60	18,7
PLT25 × 2,4 × 15	min.	24,5		2,30	14,5				
	max.	25,5		2,50	15,1				
ER25 × 6 × 18	min.	24,6	5,55		17,7	3,05	21,6	10,8	14,5
	max.	25,4	5,65		18,3	3,35	22,4	11,2	14,9
PLT25 × 2 × 18	min.	24,6		2,35	17,7				
	max.	25,4		2,45	18,3				
ER30 × 8 × 20	min.	29,6	7,85		19,7	5,10	25,6	10,8	19,05
	max.	30,4	8,15		20,3	5,50	26,4	11,2	19,85

Table 5 (continued)

*Dimensions in millimetres*

Size		<i>A</i>	<i>B</i> <sub>1</sub>	<i>B</i> <sub>2</sub>	<i>C</i>	<i>D</i>	<i>E</i>	<i>F</i>	<i>G</i>
PLT30 × 3 × 20	min.	29,6		2,60	19,7				
	max.	30,4		2,80	20,3				
ER32 × 6 × 25	min.	31,65	5,84		25,0	2,65	26,8	12,15	26,8
	max.	32,75	6,13		25,8	2,91	27,6	12,55	27,6
PLT32 × 3 × 25	min.	31,65		3,14	25,0				
	max.	32,75		3,34	25,8				
ER35 × 10 × 26	min.	34,6	9,90		25,6	5,00	29,6	14,1	26,4
	max.	35,4	10,1		26,4	5,30	30,4	14,7	27,5
PLT35 × 5 × 26	min.	34,6		4,75	25,6				
	max.	35,4		4,95	26,4				
ER40 × 10 × 28	min.	39,6	9,90		27,6	5,00	34,6	14,6	31,5
	max.	40,4	10,1		28,4	5,30	35,4	15,2	32,5
PLT40 × 5 × 28	min.	39,6		4,75	27,6				
	max.	40,4		4,95	28,4				

**Table 6 – Effective parameter values and  $A_{min}$  values**

Size	$C_1$ mm <sup>-1</sup>	$C_2$ mm <sup>-3</sup>	$l_e$ mm	$A_e$ mm <sup>2</sup>	$V_e$ mm <sup>3</sup>	$A_{min}^{a)}$ mm <sup>2</sup>	Remarks
ER9,5 × 2,5 × 5	1,748 1	206,49 × 10 <sup>-3</sup>	14,8	8,47	125	7,60	Combination ER-ER
ER11 × 2,5 × 6	1,309 5	111,14 × 10 <sup>-3</sup>	15,4	11,8	182	10,3	
ER13 × 3 × 9	0,925 25	46,334 × 10 <sup>-3</sup>	18,5	20,0	369	19,1	
ER14,5 × 3 × 7	1,132 7	64,571 × 10 <sup>-3</sup>	19,9	17,5	348	17,3	
ER18 × 3 × 10	0,745 76	24,517 × 10 <sup>-3</sup>	22,7	30,4	690	30,1	
ER23 × 3,6 × 13	0,544 75	10,818 × 10 <sup>-3</sup>	27,4	50,4	1 380	50,0	
ER23 × 5 × 13	0,662 27	13,120 × 10 <sup>-3</sup>	33,4	50,5	1 690	50,0	
ER25 × 6 × 15	0,496 74	7,024 4 × 10 <sup>-3</sup>	35,1	70,7	2 480	69,4	
ER25 × 6 × 18	0,373 73	4,065 8 × 10 <sup>-3</sup>	34,4	91,9	3 160	86,4	
ER30 × 8 × 20	0,400 44	4,090 7 × 10 <sup>-3</sup>	47,4	108	5 110	95,0	
ER32 × 8 × 20	0,300 61	2,097 4 × 10 <sup>-3</sup>	43,1	143	6 180	121	
ER35 × 10 × 27	0,273 90	1,371 5 × 10 <sup>-3</sup>	54,7	200	10 900	163	
ER40 × 10 × 32	0,272 57	1,253 9 × 10 <sup>-3</sup>	59,2	217	12 900	174	
ER9,5 × 2,5 × 5 / PLT9,5 × 1 × 5	1,393 1	169,80 × 10 <sup>-3</sup>	11,5	8,25	94,9	7,60	Combination ER-PLT
ER11 × 2,5 × 6 / PLT11 × 1 × 6	1,081 3	94,593 × 10 <sup>-3</sup>	12,4	11,4	141	10,3	
ER13 × 3 × 9 / PLT13 × 1 × 9	0,759 96	38,478 × 10 <sup>-3</sup>	15,0	19,8	296	19,1	
ER14,5 × 3 × 7 / PLT14,5 × 1 × 7	0,946 33	54,047 × 10 <sup>-3</sup>	16,6	17,5	290	17,1	
ER18 × 3 × 10 / PLT18 × 1,5 × 10	0,642 62	21,190 × 10 <sup>-3</sup>	19,5	30,3	591	30,1	
ER23 × 3,6 × 13 / PLT23 × 2 × 13	0,482 08	9,590 5 × 10 <sup>-3</sup>	24,2	50,3	1 220	50,0	
ER23 × 5 × 13 / PLT23 × 2 × 13	0,540 83	10,742 × 10 <sup>-3</sup>	27,2	50,3	1 370	50,0	
ER25 × 6 × 15 / PLT25 × 2,4 × 15	0,408 79	5,776 4 × 10 <sup>-3</sup>	28,9	70,8	2 050	69,4	
ER25 × 6 × 18 / PLT25 × 2 × 18	0,308 89	3,407 3 × 10 <sup>-3</sup>	28,0	90,6	2 540	86,4	
ER30 × 8 × 20 / PLT30 × 3 × 20	0,344 98	3,206 6 × 10 <sup>-3</sup>	37,1	108	3 990	95,0	
ER32 × 6 × 25 / PLT32 × 3 × 25	0,255 38	1,729 4 × 10 <sup>-3</sup>	37,7	148	5 570	121	
ER35 × 10 × 26 / PLT35 × 5 × 26	0,213 91	1,021 1 × 10 <sup>-3</sup>	44,8	209	9 390	163	
ER40 × 10 × 28 / PLT40 × 5 × 28	0,216 62	0,949 56 × 10 <sup>-3</sup>	49,4	228	11 300	174	

a) See 2.2 of IEC 60205.

NOTE Values ignore the effect of radii. These may have some influence on the outcome of the calculation. They can be incorporated in the formulas as shown in IEC 60205.

## Annex A (normative)

### Low-profile core design

#### A.1 General design

The design of low-profile cores standardized by the IEC is based on the form factors that are defined by the following core proportions:

- a)  $A > 2B$
- b)  $C > B$
- c)  $A > C$

where

$A$  is the overall length of the core back;

$B$  is the outside height of the core;

$C$  is the core width or floor width at wire aperture.

Those cores which exhibit the planar form factor as defined above, and which were initially designed to meet the requirements of designers for low-profile, board-mounted power transformers and chokes are the ones that have been standardized here. Other cores, originally designed for other uses, are frequently modified to achieve the planar form factor in order to have application in board-mounted power. Most frequently, this is achieved by reducing the leg lengths of standard PQ, RM and pot cores. Standardization, if any, for those low-profile sizes is reflected in the relevant IEC standard for the size. (See IEC 62317-4 for RM-cores and associated parts)

#### A.2 EL-core design

The design of the EL standard cores is based on the following considerations:

- a) since the motherboard or multi-layer board must typically have slots cut out to accept the cores, the core shapes are designed to result in cut outs that are simple and economical;
- b) with consideration of the output power of on-board type d.c.-d.c. converter for telecommunication, seven base sizes from 11 mm to 25 mm are standardised;
- c) outer leg dimensions are selected to allow economical production of cores.  $(A - E)/A = 1/6$ ;
- d) with consideration of minimizing leakage inductance, aspect ratio  $C$  is chosen as  $C = 0,8A$ ;
- e) the area of centre leg and outer leg are designed to be equal;
- f) an oval shaped centre leg is selected so that the ratio of average wire length to cross-section of winding is minimized. Copper loss is a function of this ratio and this ratio is minimized when  $F_2/F_1 = 2,3$ ;
- g) the dimension of back wall thickness is designed to be equal to  $1,1(A - E)/2$ , so that its minimum cross section is close to the cross section of the leg;
- h) height of  $B_1$  is designed with consideration of slot spacing for telecommunication equipment.