

INTERNATIONAL STANDARD



Flexible display devices –
Part 6-1: Mechanical **stress** test methods – Deformation tests

IECNORM.COM : Click to view the full PDF of IEC 62715-6-1:2018 RLV



THIS PUBLICATION IS COPYRIGHT PROTECTED

Copyright © 2018 IEC, Geneva, Switzerland

All rights reserved. Unless otherwise specified, no part of this publication may be reproduced or utilized in any form or by any means, electronic or mechanical, including photocopying and microfilm, without permission in writing from either IEC or IEC's member National Committee in the country of the requester. If you have any questions about IEC copyright or have an enquiry about obtaining additional rights to this publication, please contact the address below or your local IEC member National Committee for further information.

IEC Central Office
3, rue de Varembe
CH-1211 Geneva 20
Switzerland

Tel.: +41 22 919 02 11
info@iec.ch
www.iec.ch

About the IEC

The International Electrotechnical Commission (IEC) is the leading global organization that prepares and publishes International Standards for all electrical, electronic and related technologies.

About IEC publications

The technical content of IEC publications is kept under constant review by the IEC. Please make sure that you have the latest edition, a corrigenda or an amendment might have been published.

IEC Catalogue - webstore.iec.ch/catalogue

The stand-alone application for consulting the entire bibliographical information on IEC International Standards, Technical Specifications, Technical Reports and other documents. Available for PC, Mac OS, Android Tablets and iPad.

IEC publications search - webstore.iec.ch/advsearchform

The advanced search enables to find IEC publications by a variety of criteria (reference number, text, technical committee,...). It also gives information on projects, replaced and withdrawn publications.

IEC Just Published - webstore.iec.ch/justpublished

Stay up to date on all new IEC publications. Just Published details all new publications released. Available online and also once a month by email.

Electropedia - www.electropedia.org

The world's leading online dictionary of electronic and electrical terms containing 21 000 terms and definitions in English and French, with equivalent terms in 16 additional languages. Also known as the International Electrotechnical Vocabulary (IEV) online.

IEC Glossary - std.iec.ch/glossary

67 000 electrotechnical terminology entries in English and French extracted from the Terms and Definitions clause of IEC publications issued since 2002. Some entries have been collected from earlier publications of IEC TC 37, 77, 86 and CISPR.

IEC Customer Service Centre - webstore.iec.ch/csc

If you wish to give us your feedback on this publication or need further assistance, please contact the Customer Service Centre: sales@iec.ch.

IECNORM.COM : Click to view the full PDF IEC 62716-1:2018 PLV



IEC 62715-6-1

Edition 2.0 2018-04
REDLINE VERSION

INTERNATIONAL STANDARD



Flexible display devices –
Part 6-1: Mechanical **stress** test methods – Deformation tests

INTERNATIONAL
ELECTROTECHNICAL
COMMISSION

ICS 31.120

ISBN 978-2-8322-5629-9

Warning! Make sure that you obtained this publication from an authorized distributor.

CONTENTS

FOREWORD	4
1 Scope	6
2 Normative references	6
3 Terms and definitions	6
4 Standard atmospheric conditions	6
5 Evaluations—Visual evaluation of panel image quality Specimen preparation	7
5.1 General.....	7
5.2 Sample preparation.....	7
6 Mechanical stress test methods	7
6.1 General.....	7
6.2 Cyclic bending test.....	8
6.2.1 General	8
6.2.2 Purpose	8
6.2.3 Test apparatus	8
6.2.4 Test procedure	9
6.2.5 Testing conditions and reporting	9
6.3 Static bending test	12
6.3.1 General	12
6.3.2 Purpose	12
6.3.3 Test apparatus	12
6.3.4 Test procedure	12
6.3.5 Testing conditions and reporting	13
6.4 Combined bending test	12
6.4.1 General	13
6.4.2 Purpose	13
6.4.3 Test apparatus	13
6.4.4 Test procedure	14
6.4.5 Testing conditions and reporting	15
6.5 Rolling test.....	15
6.5.1 General	15
6.5.2 Purpose.....	16
6.5.3 Test apparatus	16
6.5.4 Test procedure	18
6.5.5 Testing conditions and reporting	18
6.6 Static rolling test.....	18
6.6.1 General	19
6.6.2 Purpose.....	19
6.6.3 Test apparatus	19
6.6.4 Test procedure	19
6.6.5 Testing conditions and reporting	20
6.7 Torsion test.....	20
6.7.1 General	20
6.7.2 Purpose.....	20
6.7.3 Test apparatus	20
6.7.4 Test procedure	20
6.7.5 Testing conditions and reporting	22

6.8	Tension test	20
6.8.1	General	23
6.8.2	Purpose	23
6.8.3	Test apparatus	23
6.8.4	Test procedure	23
6.8.5	Testing conditions and reporting	24
	Bibliography	25
	Figure 1 – Apparatus for diverse cyclic bending tests	11
	Figure 2 – Apparatus for static bending test	12
	Figure 3 – Apparatus for combined bending tests consisting of the cyclic bending test and static bending test	15
	Figure 4 – Apparatus for rolling test	17
	Figure 5 – Apparatus for diverse torsion tests	22
	Figure 6 – Apparatus for tension test	24

IECNORM.COM : Click to view the full PDF of IEC 62715-6-1:2018 RLV

INTERNATIONAL ELECTROTECHNICAL COMMISSION

FLEXIBLE DISPLAY DEVICES –

Part 6-1: Mechanical ~~stress~~ test methods – Deformation tests

FOREWORD

- 1) The International Electrotechnical Commission (IEC) is a worldwide organization for standardization comprising all national electrotechnical committees (IEC National Committees). The object of IEC is to promote international co-operation on all questions concerning standardization in the electrical and electronic fields. To this end and in addition to other activities, IEC publishes International Standards, Technical Specifications, Technical Reports, Publicly Available Specifications (PAS) and Guides (hereafter referred to as “IEC Publication(s)”). Their preparation is entrusted to technical committees; any IEC National Committee interested in the subject dealt with may participate in this preparatory work. International, governmental and non-governmental organizations liaising with the IEC also participate in this preparation. IEC collaborates closely with the International Organization for Standardization (ISO) in accordance with conditions determined by agreement between the two organizations.
- 2) The formal decisions or agreements of IEC on technical matters express, as nearly as possible, an international consensus of opinion on the relevant subjects since each technical committee has representation from all interested IEC National Committees.
- 3) IEC Publications have the form of recommendations for international use and are accepted by IEC National Committees in that sense. While all reasonable efforts are made to ensure that the technical content of IEC Publications is accurate, IEC cannot be held responsible for the way in which they are used or for any misinterpretation by any end user.
- 4) In order to promote international uniformity, IEC National Committees undertake to apply IEC Publications transparently to the maximum extent possible in their national and regional publications. Any divergence between any IEC Publication and the corresponding national or regional publication shall be clearly indicated in the latter.
- 5) IEC itself does not provide any attestation of conformity. Independent certification bodies provide conformity assessment services and, in some areas, access to IEC marks of conformity. IEC is not responsible for any services carried out by independent certification bodies.
- 6) All users should ensure that they have the latest edition of this publication.
- 7) No liability shall attach to IEC or its directors, employees, servants or agents including individual experts and members of its technical committees and IEC National Committees for any personal injury, property damage or other damage of any nature whatsoever, whether direct or indirect, or for costs (including legal fees) and expenses arising out of the publication, use of, or reliance upon, this IEC Publication or any other IEC Publications.
- 8) Attention is drawn to the Normative references cited in this publication. Use of the referenced publications is indispensable for the correct application of this publication.
- 9) Attention is drawn to the possibility that some of the elements of this IEC Publication may be the subject of patent rights. IEC shall not be held responsible for identifying any or all such patent rights.

This redline version of the official IEC Standard allows the user to identify the changes made to the previous edition. A vertical bar appears in the margin wherever a change has been made. Additions are in green text, deletions are in strikethrough red text.

International Standard IEC 62715-6-1 has been prepared by IEC technical committee 110: Electronic display devices.

This second edition cancels and replaces the first edition published in 2014. This edition constitutes a technical revision.

This edition includes the following significant technical changes with respect to the previous edition:

- a) changed the part title to differentiate it from other parts;
- b) added new bending testing methods;
- c) added detailed testing procedures.

The text of this International Standard is based on the following documents:

FDIS	Report on voting
110/951/FDIS	110/974/RVD

Full information on the voting for the approval of this International Standard can be found in the report on voting indicated in the above table.

This document has been drafted in accordance with the ISO/IEC Directives, Part 2.

A list of all the parts in the IEC 62715 series, under the general title *Flexible display devices*, can be found on the IEC website.

The committee has decided that the contents of this document will remain unchanged until the stability date indicated on the IEC website under "<http://webstore.iec.ch>" in the data related to the specific document. At this date, the document will be

- reconfirmed,
- withdrawn,
- replaced by a revised edition, or
- amended.

IMPORTANT – The 'colour inside' logo on the cover page of this publication indicates that it contains colours which are considered to be useful for the correct understanding of its contents. Users should therefore print this document using a colour printer.

FLEXIBLE DISPLAY DEVICES –

Part 6-1: Mechanical ~~stress~~ test methods – Deformation tests

1 Scope

The object of this part of IEC 62715 is to define the standard test methods to evaluate the mechanical stability of flexible display modules, specifically mechanical stability against deformation, such as bending, rolling, twisting, and stretching. Display modules include displays such as LCD, e-paper, and OLED. This document takes into account, wherever possible, the mechanical test methods outlined under mechanical stress.

2 Normative references

The following documents are referred to in the text in such a way that some or all of their content constitutes requirements of this document. For dated references, only the edition cited applies. For undated references, the latest edition of the referenced document (including any amendments) applies.

IEC 62341-5:2009, *Organic light emitting diode (OLED) displays – Part 5: Environmental testing methods*

3 Terms and definitions

No terms and definitions are listed in this document.

ISO and IEC maintain terminological databases for use in standardization at the following addresses:

- IEC Electropedia: available at <http://www.electropedia.org/>
- ISO Online browsing platform: available at <http://www.iso.org/obp>

4 Standard atmospheric conditions

The standard atmospheric conditions in IEC 62341-5:2009, 5.3, shall apply as follows, unless otherwise specifically agreed between customer and supplier. ~~The standard atmospheric conditions shall be a temperature of 25 °C ± 5 °C, relative humidity between 45 % and 75 %, and atmospheric pressure between 86 kPa and 106 kPa.~~

- Temperature: 25 °C ± 3 °C
- Relative humidity: 25 % RH to 85 % RH
- Atmospheric pressure: 86 kPa to 106 kPa

When all the different kinds of tests are carried out, the temperature and humidity condition shall be ~~commented~~ reported because the temperature ~~is~~ and humidity are critical for the bending and rolling stability regarding image quality on the panel.

NOTE Preferably, the specimen and apparatus are kept in a controlled environment for at least 24 h prior to and after assembly, before the start of the mechanical deformation test.

5 ~~Evaluations—Visual evaluation of panel image quality~~ Specimen preparation

5.1 General

The specimen shall be the display module since the final evaluation has to be made based on panel image quality such as luminance, chromaticity, uniformity, line defect, and point defect. The bending stress may cause the deterioration of image quality on a panel, [1] to [9]¹.

5.2 Sample preparation

For the measurements both before and after the mechanical deformation test, the display module being tested shall be aligned on an appropriate support which has to be a flat surface. In addition, the module for the measurement shall be of the appropriate geometry for mechanical stress testing. Specify that the test apparatus should be designed to prevent added strain by stretching test specimens upon folding.

The preferred method of attachment between the display module and the test apparatus is adhesive transfer tape. The display should be bonded on both sides, and the distance between the centre of the test specimen and the point of attachment should be specified. If use scenarios require it, a clamping attachment may be used instead, in which the display is clamped on one side and allowed to slide on the other. The clamping force should be sufficient to ensure that the test specimen is firmly anchored to the test apparatus throughout the entire duration of the test cycle.

If some modules are difficult to clamp due to narrow edge width, the module should be fixed on a bendable support substrate with a suitable adhesive strip or glue. Neither the adhesive strip nor the glue should affect the measurement.

NOTE In some cases, the testing specimen can have a short length or has a very narrow edge to clamp for mechanical stress testing.

Specify that in the event of cross-instrument variability in the form of location (centre or edge)-response bias, one should investigate bend axis misalignment, bowing or uneven mounting plates.

For precise optical measurements, it is very important to define the alignment of the measurement specimen because the flexible display module can be easily deformed by external force. Measurements of the visual characteristics of a flexible module shall be made in an aligned flat state. If flexible modules are aligned in a curved state, it is difficult to make a precise visual evaluation. The measurement module shall be supported or fixed so that it is flat.

The flatness and size of the specimen shall be determined between the supplier and customer.

6 Mechanical stress test methods

6.1 General

Flexible displays have a diversity of shapes in comparison with any other non-flexible electronic displays. Therefore, a wide variety of mechanical stress test methods are available, such as a cyclic bending (folding) or dynamic bending test, a static bending test, a rolling test, a combined mechanical test and more. The selection of the appropriate test methods shall be based on the requirement of the application. For each mechanical stress test, the relevant test method specification shall be stated along with the explanation of the purpose of each unique test. The allowable critical bending radius of a panel depends on the application of the flexible display. Therefore, the required critical bending radius will be changed ~~case by case~~ based on the applications.

¹ Numbers in square brackets refer to the Bibliography.

There are several factors to consider when designing a reliable and repeatable mechanical folding or deformation test method, as follows:

- Motion profiles controlled by a single hinge (or pivot axis) and which wrap around a mandrel can stretch samples, and if not precisely actuated or controlled can create a great deal of variability in the test response.
- Motion profiles controlled by more than one hinge or pivot axis can prevent added stretching on test specimens, and offer better control of the test response.
- Clamping samples can prevent shear between layers of multi-layer test specimens containing adhesive, and greatly impact test response.
- Additional considerations, such as attaching too close to the apex of the bend, and fold axis misalignment or slight distortions in the shape of the mounting plates, can also impact reliability and repeatability of the test response.
- Samples should be pre-conditioned in a controlled environment for at least 24 h prior to testing as material properties for adhesives and polymers can be affected by temperature and water uptake.

6.2 Cyclic bending test

6.2.1 General

This procedure is for conditioning the ~~sample~~ specimen under mechanical stress by repeated bending.

6.2.2 Purpose

The purpose of this test is to provide a standard procedure for evaluating the robustness of a flexible display against a cyclic bending stress which might typically happen in application. The bending properties might cover several typical parameters of the characteristics of a display panel's image quality. The typical parameters of a display panel's image quality might cover the luminance, chromaticity, uniformity, line defect, point defect, pixel shrink, and /or presence or absence of cracks.

6.2.3 Test apparatus

The cyclic bending test equipment includes the clamp to hold a bending test ~~sample~~ specimen, the moving part to shuttle, and the control system which regulates the number of cyclic bendings, the moving distance, and the moving speed while testing. The specimen shall be securely clamped with a gripping part during the test. Several kinds of cyclic bending test equipments ~~are~~ is available and shown in Figure 1, [4][7][10]. It is not necessary that a certain type of bending test equipment be preferred but the constant bending radius (r), equal to the radius of the rod, should be kept during the bending test.

NOTE If the bending radius of the test specimen is kept constant during the bending test, the bending rod can be removed as it would scratch the surface of the test specimen during the cyclic bending test.

For the cyclic bending test, the following apparatus is considered:

- the specimen experiences a bending stress when the specimen is shuttled back and forth (Figure 1a)) or while the specimen is folded and unfolded (Figure 1b)),
- when the specimen is repeatedly multi-bent in the inward or outward direction, a cyclic multi-inward bending equipment (Figure 1c)) or cyclic multi-outward bending equipment (Figure 1d)) can be used,
- when the specimen is repeatedly multi-bent in a Z-shape, a cyclic multi-bending equipment can be used,
- when the specimen is repeatedly bent in both the inward and outward direction, a cyclic inward and outward bending equipment can be used (Figure 1e) and/or f)).

6.2.4 Test procedure

The cyclic bending test shall be performed using a repeated motion to move regularly between two points or two states (folded state and unfolded state) as follows. ~~For each test, the moving speed, the bending radius and the number of cyclic bending should be mentioned, because the characteristics of the image quality displayed on the module might depend on these elements. The direction in which the specimen faces shall be stated, such as face up or face down. For example, the conditions shall be selected as below:~~

~~r (bending radius): 20 mm, 10 mm, 5 mm, 3 mm, 2 mm, 1 mm, 0,5 mm, 0,2 mm, 0,1 mm~~

~~t (time for one bend and interval): 0,5 s, 1 s, 2 s, 3 s, 5 s, 10 s~~

- a) Prepare the required number of specimens according to 5.2.
- b) Perform the initial performance, visual characteristics, test for the prepared specimens and record the result.
- c) One edge of the specimen is fixed by the clamp, or fixed with an adhesive, and the other edge is supported properly as stated in 5.2.
- d) Bend the specimen properly with defined conditions such as the rotation angle of the clamp roll and the bending angular velocity.
- e) Bring the specimen back to the initial state before the bending.
- f) If required, bend the specimen in another direction with defined conditions such as the rotation angle of the clamp roll and the bending angular velocity.
- g) Bring the specimen back to the initial state before the bending with the same angular velocity and reversed direction.
- h) Repeat d) to g) for a defined number of cycles.
- i) After the test, the specimen is removed from the apparatus.
- j) Repeat the tests with (an)other specimen(s) following c) to j).
- k) The stressed performance, visual characteristics of the mechanically stressed specimen(s) with the required number of testings are measured and the results are recorded. The initial and stressed performances are compared, and the degree of change due to the bend is determined.
- l) The test and performance measurement for individual specimens are conducted and recorded in the test report.

6.2.5 Testing conditions and reporting

The testing conditions are specified as follows:

NOTE 1 The numerical values of the test conditions are examples.

- a) bending radius

r (bending radius): 20 mm, 10 mm, 5 mm, 3 mm, 2 mm, 1 mm, 0,5 mm, 0,2 mm

- b) bending angle and angular velocity, procedure for one cycle

t (time for one bend and interval): 0,5 s, 1 s, 2 s, 3 s, 5 s, 10 s

- c) load

- d) number of repeating cycles

- e) criteria for acceptance

- f) number of specimens

- g) the bending inner surface is the top surface (face up) or the back side surface (face down)


- h) way of holding specimens and detailed method of holding, such as pressure

- i) surface condition (such as treatment) of both specimen and apparatus


- j) testing of environmental conditions, such as temperature and humidity.

NOTE 2 The criteria for acceptance include the visual performance and specimen geometry both before and after the stressing.

All conditions shall be reported if the test uses conditions other than those mentioned above.

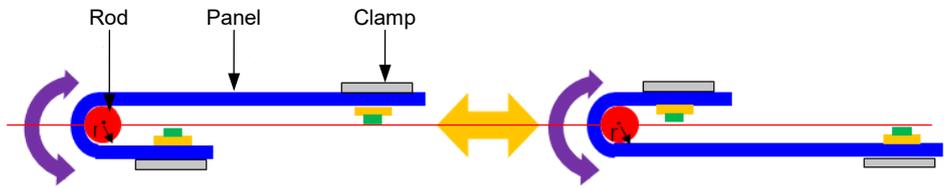

a)

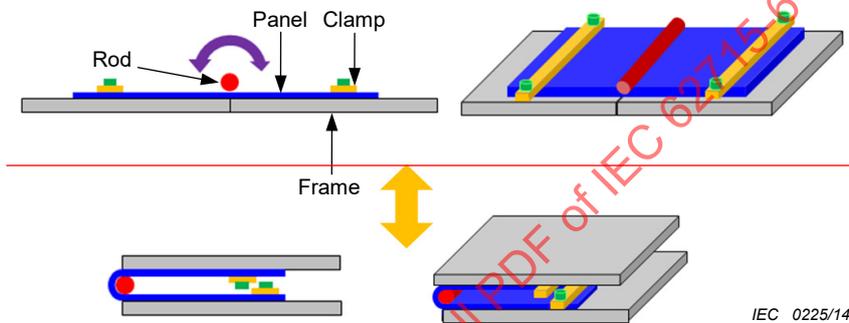

b)

IECNORM.COM : Click to view the full PDF of IEC 62715-6-1:2018 RLV

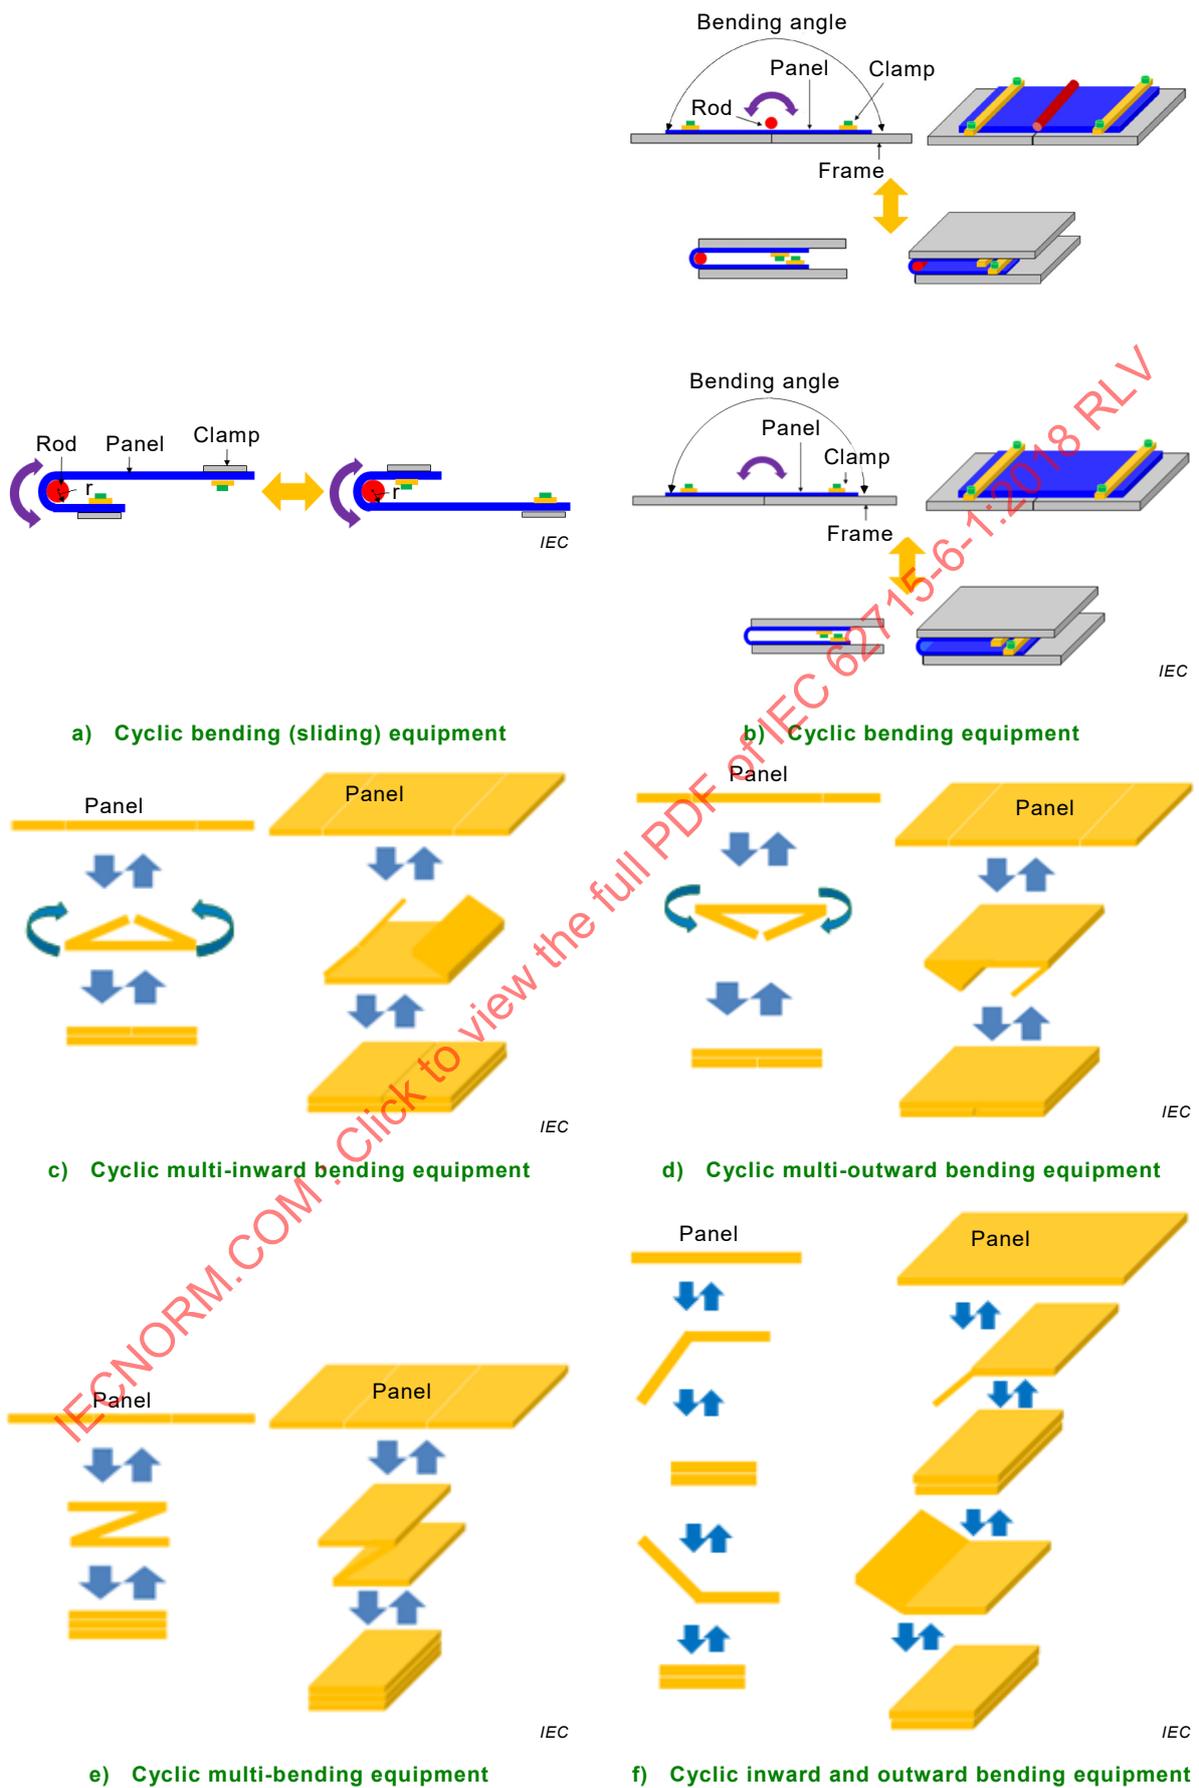


Figure 1 – Apparatus for diverse cyclic bending tests

6.3 Static bending test

6.3.1 General

This test is especially applicable for evaluating the static bending properties of a flexible display device by measuring its performance after it remains bent for a certain period of time. Each specimen is bent at a fixed bending radius for any length of time.

6.3.2 Purpose

This test is to provide a standard procedure for evaluating the static bending properties of a flexible display device under constant stress for a certain period of time. Each specimen is bent at a fixed bending radius for a controlled length of time.

6.3.3 Test apparatus

The body of the display panel shall firmly adhere to the surface of the test equipment during the test, where the test equipment should have a round shape with a certain radius as in Figure 2. The specimen shall be bent at a fixed bending radius for a period of time.

If the bending radius of the test specimen is kept constant during the bending test, the bending rod can be removed as it may scratch the surface of the test specimen during the static bending test. During the test, the flexible printed circuit (FPC) and the driver should be carefully handled ~~in order not to cause~~ so that they are not subject to bending damage ~~on them~~. The chip-on-film (COF) method is preferable in order to avoid the occurrence of bending damage on the driver's integrated circuit (IC) during the bending test.

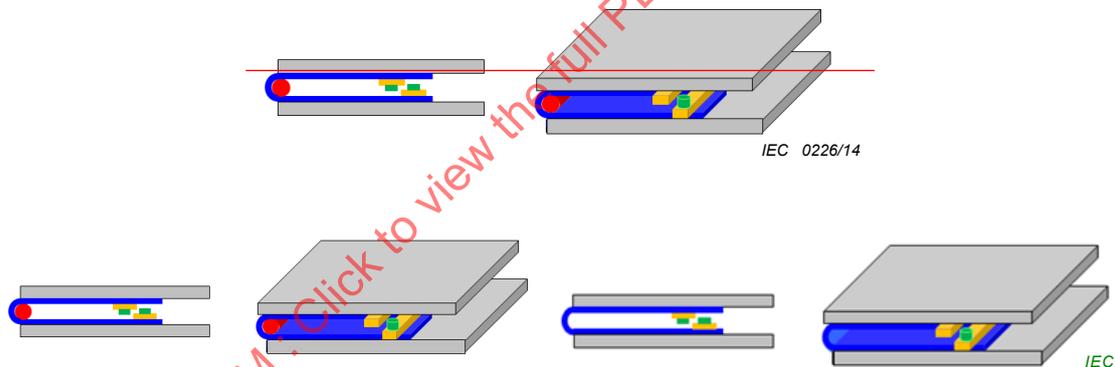


Figure 2 – Apparatus for static bending test

6.3.4 Test procedure

The static ~~time~~ bending test shall be carried out with a fixed bending radius for a certain period of time, as follows. ~~For each test, the bending radius and the period of time shall be mentioned because the static bending properties of the characteristics of the display panel image quality might depend on the bending radius and the period of time.~~

- a) Prepare the required number of specimens according to 5.2.
- b) Perform the initial performance, visual characteristics, test for the prepared specimens and record the result.
- c) One edge of the specimen is fixed by the clamp and the other edge is supported properly.
- d) Bend the specimen properly with defined conditions such as the rotation angle of the clamp roll and the bending angular velocity.
- e) Keep the specimen bent for certain period of time.
- f) Bring the specimen back to the initial state before the bending.
- g) Repeat d) to f) for a defined number of tests.

- h) After the bending, the specimen is removed from the apparatus.
- i) Repeat the tests with (an)other specimen(s) following c) to g).
- j) The stressed performance and visual characteristics of mechanically stressed specimen(s) with the required number of testings are measured, and the results are recorded. The initial and stressed performances are compared, and the degree of change due to bending is determined.
- k) The test and performance measurement for individual specimens are conducted and recorded in the test report.

6.3.5 Testing conditions and reporting

The testing conditions are specified as follows:

NOTE 1 The numerical values of the test conditions are examples.

- a) bending radius
 r (bending radius): 20 mm, 10 mm, 5 mm, 3 mm, 2 mm, 1 mm, 0,5 mm, 0,2 mm
- b) bending angle
- c) holding duration
- d) load
- e) criteria for acceptance
- f) number of specimens
- g) the bending inner surface is the top surface (face-up) or backside surface (face-down)
- h) way of holding specimens and detailed method of holding, such as pressure
- i) surface condition (such as treatment) of both specimen and apparatus
- j) testing of environmental conditions, such as temperature and humidity

NOTE 2 The criteria for acceptance include visual performance and specimen geometry both before and after the stressing.

All conditions shall be reported if the test uses conditions other than those mentioned above.

6.4 Combined bending test

6.4.1 General

This test is especially applicable for evaluating two kinds of ~~combined~~ bending properties (cyclic bending properties and static bending properties (see Figure 3)) of the flexible display device, after the flexible display remains in the curved shape for a certain period of time and goes through the cyclic bending condition for a certain period of time in real-~~usage~~ use environment.

6.4.2 Purpose

The objective of this test is to provide a standard procedure for evaluating the combined bending properties of cyclic bending and duration time bending. This test aims to take the real product-~~usage~~ use environment into consideration, where the real product keeps the panel in a curved, folded, or rolled shape for a long time when it is used or before it is rolled out.

6.4.3 Test apparatus

The combined bending test utilizes the same apparatus as the cyclic bending test as shown in Figure 3. The instrument controller shall be capable of stopping the mechanism while the ~~sample~~ specimen is in a bent state during each iteration of the cycle.

6.4.4 Test procedure

The cyclic bending test procedure is modified to include a ~~pause~~ 'hold' of adjustable duration between each iteration of the cycle where the specimen remains in a fully bent state [4] as follows. ~~The entire test sequence and all of the test conditions of the cyclic bending test part and the static bending test part shall be reported to ensure reproducibility.~~

- a) Prepare the required number of specimens according to 5.2.
 - b) Perform the initial performance, visual characteristics, test for the prepared specimens and record the result.
 - c) One edge of the specimen is fixed by the clamp and the other edge is supported properly.
 - d) Bend the specimen properly with defined conditions such as the rotation angle of the clamp roll and the bending angular velocity.
 - e) Bring the specimen back to the initial state before the bending.
 - f) After performing a certain number of times the bending test in d) and e), bring the specimen in a fully bent state, then hold.
 - g) After certain a period of time on hold, bring the specimen back to the initial state.
 - h) If required, bend the specimen in another direction with defined conditions such as the rotation angle of the clamp roll and the bending angular velocity.
- NOTE If required, the specimen and apparatus are set in a proper setting, such as rotation of the rod, etc.
- i) The bent module is returned to the initial state before the bending with the same angular velocity and reversed direction.
 - j) After performing a certain number of times the bending test in h) and i), bring the specimen in the fully bent state, and then hold.
 - k) After the test, bring the specimen back to the initial state.
 - l) Repeat d) to k) for a defined number of cycles.
 - m) Bring the specimen back to the initial state.
 - n) Repeat the test with (an)other specimen(s) following c) to m).
 - o) The stressed performance and visual characteristics of the mechanically stressed specimen(s) with the required number of testings are measured, and the results are recorded. The initial and stressed performances are compared, and the degree of change due to the bend is determined.
 - p) The test and performance measurement for individual specimens are conducted and recorded in the test report.

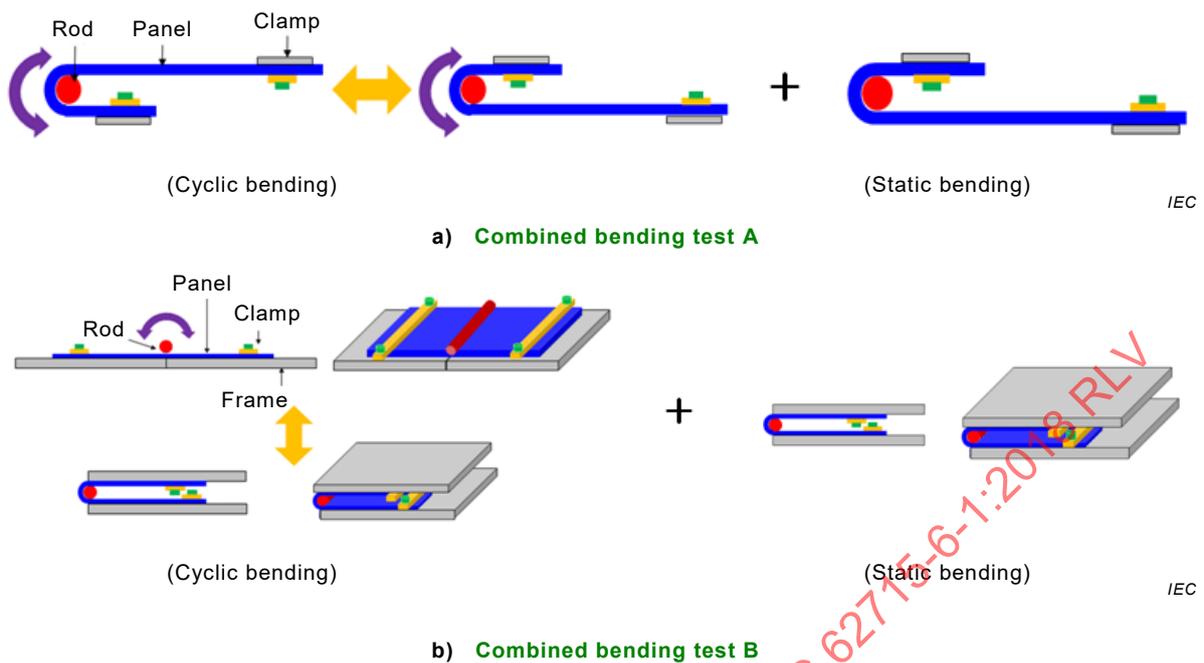


Figure 3 – Apparatus for combined bending tests consisting of the cyclic bending test and static bending test

6.4.5 Testing conditions and reporting

The testing conditions are specified as follows:

NOTE 1 The numerical values of the test conditions are examples.

a) bending radius

r (bending radius): 20 mm, 10 mm, 5 mm, 3 mm, 2 mm, 1 mm, 0,5 mm, 0,2 mm

b) bending angle and angular velocity, procedure for one cycle

t (time for one bend and interval): 0,5 s, 1 s, 2 s, 3 s, 5 s, 10 s

c) duration of 'hold' state

d) load

e) number of repeating cycles

f) criteria for acceptance

g) number of specimens

h) the bending inner surface is the top surface (face up) or backside surface (face down)

i) way of holding specimens and detailed method of holding, such as pressure

j) surface condition (such as treatment) of both specimen and apparatus

k) testing of environmental conditions, such as temperature and humidity

NOTE 2 The criteria for acceptance include the visual performance and specimen geometry both before and after the stressing.

All conditions shall be reported if the test uses conditions other than those mentioned above.

6.5 Rolling test

6.5.1 General

This test is especially applicable for evaluating the rolling properties of a flexible display module after a flexible display is rolled out, rolled in, or remains in the shape of a roll.

6.5.2 Purpose

The objective of this test is to provide a standard procedure for evaluating the robustness of the rolling properties of the flexible display panel.

6.5.3 Test apparatus

The specimen shall be firmly clamped with a gripping part on the roller side and on the stationary side. The roller shall be ~~reciprocated~~ moved forward and backward alternately at a fixed distance, speed, and rolling number as in Figure 4. The roller side has a slot where the edge of the specimen is inserted and clamped. The roller repeatedly shuttles along the roller shaft and the specimen does not touch the plate of the equipment during the rolling test as shown in Figure 4.

During the test, the FPC and the driver ~~shall~~ should be carefully handled ~~in order not to cause so that they are not subjected to twist damage on them~~. The COF method is preferable in order to ~~avoid~~ prevent the occurrence of twist damage on the driver's IC during the bending test.

IECNORM.COM : Click to view the full PDF of IEC 62715-6-1:2018 RLV

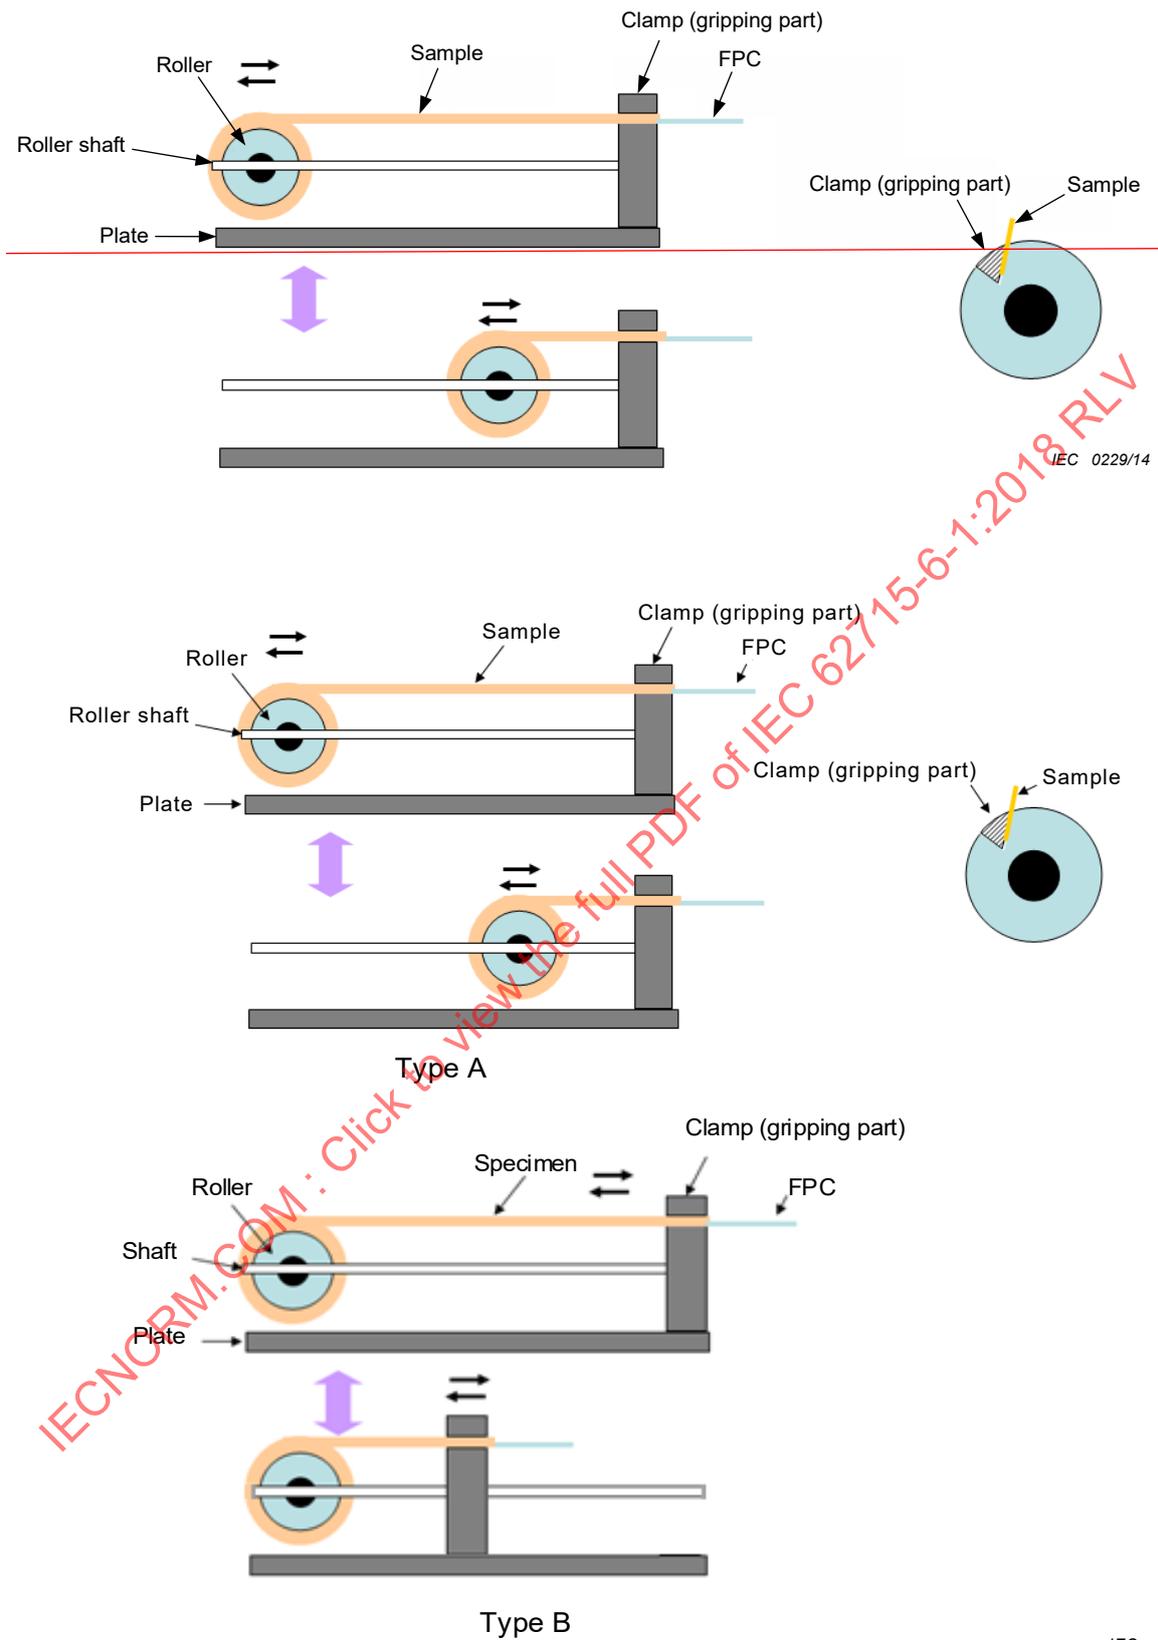


Figure 4 – Apparatus for rolling test

6.5.4 Test procedure

~~A fixed area of the specimen shall be cyclically wounded and unwounded around the roller. The winding rate and the cycle count will be controlled. The test conditions and settings shall be reported to ensure reproducibility.~~

The rolling test shall be performed as follows:

- a) Prepare the required number of specimens according to 5.2.
- b) Perform the initial performance, visual characteristics, and test for the prepared specimens and record result.
- c) Each specimen size is measured and recorded.
- d) One edge of the specimen is fixed on the roll as shown in Figure 4 and the other edge clamp is supported with an individually defined load. Align the specimen with the top surface on the inner or the outer side of the roller.
- e) Roll the specimen with defined conditions such as rolling radius, rolling distance, rolling angular velocity and load.
- f) Bring the specimen back to the initial state before the rolling, with the same angular velocity and reversed rotation direction.
- g) Repeat d) to e) for a defined number of cycles. It is optional to test the other surface side at the same conditions, this being done by agreement between supplier and customer. In this case, follow d) to g) with the reversed surface side.
- h) After the test, remove the specimen from the apparatus.
- i) Repeat the test with (an)other specimen(s) following c) to h).
- j) The stressed performance, electrical and optical characteristics of the mechanically stressed module(s) with the required number of testings are measured, and the results are recorded. The initial and stressed performances are compared, and the degree of change due to the rolling test is determined.
- k) The test and performance measurement for individual specimens are conducted and recorded in the test report.

6.5.5 Testing conditions and reporting

The testing conditions are specified as follows:

- a) roll radius
- b) angular velocity, procedure for one cycle
- c) holding duration
- d) load
- e) number of repeating cycles
- f) criteria for acceptance
- g) number of specimens
- h) rolling inner surface (top surface or back surface)
- i) way of holding specimens and detailed method of holding, such as pressure
- j) surface condition (such as treatment) of both specimen and apparatus
- k) testing of environmental conditions, such as temperature and humidity.

NOTE The criteria for acceptance include the visual performance and specimen geometry both before and after the stressing.

All conditions shall be reported if the test uses conditions other than those mentioned above.

6.6 Static rolling test

6.6.1 General

This test is especially applicable for evaluating the static rolling properties of a flexible display module after a flexible display is rolled out, rolled in, or remains in the shape of a roll.

6.6.2 Purpose

The objective of this test is to provide a standard procedure for evaluating the robustness of the static rolling properties of the flexible display panel.

6.6.3 Test apparatus

The specimen shall be firmly clamped with a gripping part on the roller side and on the stationary side. The roller shall be moved forward and backward alternately at a fixed distance, speed, and rolling number as in Figure 4. The roller side has a slot where the edge of the specimen is inserted and clamped. The roller repeatedly shuttles along the roller shaft and the specimen does not touch the plate of the equipment during the rolling test as shown in Figure 4.

During the test, the FPC and the driver should be carefully handled so that they are not subjected to twist damage. The COF method is preferable in order to prevent the occurrence of twist damage on the driver IC during the bending test.

6.6.4 Test procedure

The rolling test shall be performed as follows:

- a) Prepare the required number of specimens according to 5.2.
- b) Perform the initial performance, visual characteristics, test for the prepared specimens and record the result.
- c) Each specimen size is measured and recorded.
- d) One edge of the specimen is fixed on the roll as shown in Figure 4 and the other edge clamp is supported with an individually defined load. Align the specimen with the top surface on the inner or the outer side of the roller.
- e) Roll the specimen with defined conditions such as rolling radius, rolling distance, rolling angular velocity and load.
- f) Hold the specimen in a rolled shape for a certain period.
- g) Bring the specimen back to the initial state before the rolling with the same angular velocity and reversed rotation direction.
- h) Hold the specimen in a rolled shape for a certain period, if required.
- i) Repeat e) to h) for a defined number of cycles.
- j) It is optional to test the other surface side at the same conditions, this being done by agreement between supplier and customer. In this case, follow d) to i) with the reversed surface side.
- k) After the test, remove the specimen from the apparatus.
- l) Repeat the test with (an)other specimen(s) following c) to k).
- m) The stressed performance, electrical and optical characteristics of mechanically stressed module(s) with the required number of testing are measured, and the results are recorded. The initial and stressed performances are compared, and the degree of change due to the rolling test is determined.
- n) The test and performance measurement for individual specimens are conducted and recorded in the test report.

6.6.5 Testing conditions and reporting

Testing conditions are specified as follows:

- a) roll radius
- b) angular velocity, procedure for one cycle
- c) hold duration
- d) load
- e) number of repeating cycles
- f) criteria for acceptance
- g) number of specimens
- h) rolling inner surface (top surface or back surface)
- i) way of holding specimens and detailed method of holding, such as pressure
- j) surface condition (such as treatment) of both specimen and apparatus
- k) testing of environmental conditions, such as temperature and humidity

NOTE The criteria for acceptance include the visual performance and specimen geometry both before and after the stressing.

All conditions shall be reported if the test uses conditions other than those mentioned above.

6.7 Torsion test

6.7.1 General

This test is applicable for evaluating the torsion properties of a flexible display module after being subjected to torsion during a certain period of time. For flexible displays, torsion is likely to happen easily during ~~usage~~ use.

6.7.2 Purpose

The objective of this test is to provide a standard procedure for evaluating the robustness of a flexible display device against cyclic torsion stress which might typically happen in the application.

6.7.3 Test apparatus

The specimen shall be firmly clamped and twisted at a certain degree of torsion angle, as shown in Figure 5, during the test. The specimen shall be securely clamped with an appropriate gripping part. During the test, the FPC and the driver shall be carefully handled ~~in order not to cause so that they are not subjected to twist damage on them~~. The edge of the ~~sample specimen~~ with the FPC and the driver's IC in the stationary side shall be fixed in order to ~~avoid prevent~~ the occurrence of twist damage during the bending test. When the ~~sample specimen~~ is twisted, the extra tension is applied on the side of the ~~sample specimen~~ in addition to the twist tension. Therefore, the moving part ~~in on~~ the stationary side shall move forward and backward during the test because the extra and unnecessary tension applied on the ~~sample specimen~~ should be removed as shown in Figure 5a) and b).

6.7.4 Test procedure

~~The specimen shall repeatedly be twisted counter clockwise and clockwise at a fixed degree of twisting, a certain speed, and a certain number of twists. The test conditions of the torsion test such as twist speed and number of twists should be mentioned because the characteristics of the display panel image quality might depend on the test conditions mentioned in Clause 4.~~

The torsion test shall be performed as follows:

- a) Prepare the required number of the display modules according to 5.2.
- b) Perform the initial performance, visual characteristics, test for the prepared modules and record result.
- c) Each specimen size is measured, visually inspected and recorded.
- d) Both edges of the testing module(s) are fixed on the gripping parts as shown in Figure 5.
- e) Apply torsion with defined conditions such as clockwise angle and oscillation velocity.
- f) Bring the specimen back to the initial state before the testing with the same angular velocity and reversed rotation direction.
- g) Apply torsion with defined conditions such as counter clockwise angle and oscillation velocity.
- h) Bring the specimen back to the initial state before the testing with the same angular velocity and reversed rotation direction.
- i) Repeat e) to h) for a defined number of cycles.
- j) It is optional to test the other surface side at the same conditions, this being done by agreement between supplier and customer. In this case, follow d) to i) with the reversed surface side.
- k) After the test, remove the specimen from the apparatus.
- l) Repeat the test with (an)other specimen(s) following c) to k).
- m) The stressed performance, electrical and optical characteristics of the mechanically stressed module(s) with the required number of testings are measured and the results are recorded. The initial and stressed performances are compared, and the degree of change due to the torsion test is determined.
- n) The test and performance measurement for individual specimens are conducted and recorded in the test report.

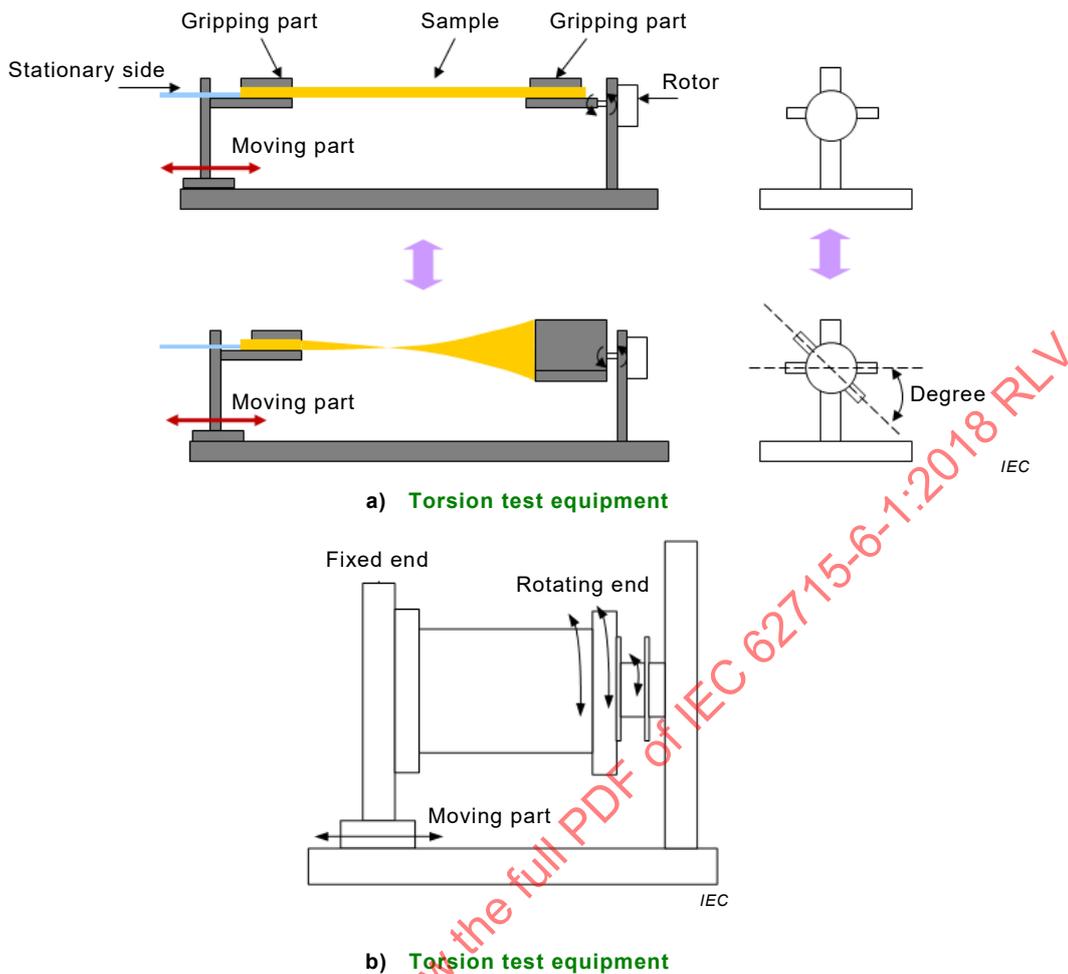


Figure 5 – Apparatus for diverse torsion tests

6.7.5 Testing conditions and reporting

The testing conditions are specified as follows:

- number of specimens
- performance range for initial and stressed electrical and optical performance
- torsion angle and rotation angular velocity
- applied tensile stress
- number of cycles
- criteria for acceptance
- way of holding specimens and detailed method of holding, such as pressure
- surface condition (such as treatment) of both specimen and apparatus
- testing of environmental conditions, such as temperature and humidity

NOTE The criteria for acceptance include the visual performance and specimen geometry both before and after the stressing.

All conditions shall be reported if the test uses conditions other than those mentioned above.

6.8 Tension test

6.8.1 General

This test is applicable for the evaluation of the tension properties of a flexible display module after being subjected to a constant tension at the moment of change between folding and unfolding and between roll-in and roll-out (see Figure 6).

6.8.2 Purpose

The objective of this test is to provide a standard procedure for evaluating the robustness of a flexible display device against cyclic tension stress which might typically happen in the application.

6.8.3 Test apparatus

The apparatus consists of a fixed and movable clamp in which the ~~sample specimen~~ will be secured for the test. The movable clamp shuttles forward and backward linearly at a set rate as shown in Figure 6. The instrument repeatedly applies and relieves the tension in the ~~sample specimen~~ for a set number of cycles. During the test, the FPC and the driver shall be carefully handled ~~in order not to cause so that they are not subjected to tension damage on them~~. The edge of the ~~sample specimen~~ with the FPC and driver's IC in the stationary side shall be fixed in order to avoid the occurrence of twist damage during the bending test.

6.8.4 Test procedure

~~The panel is secured and the movable clamp shuttles back and forth, applying and relieving tensile stress for a predetermined number of cycles. The rate of the movable clamp, tensile stress, tensile strain and cycle number shall be reported as well as the environmental conditions. The panel should be firmly clamped and only the panel is under repeated tension by shuttling the panel from the initial position under no tension to the given position under tension. The speed and tension strength should be mentioned because these factors might influence the tension properties of the device.~~

The tension test shall be performed as follows:

- a) Prepare the required number of display modules according to 5.2.
- b) Each specimen size is measured, visually inspected and recorded.
- c) Perform the initial performance, visual characteristics, test for the prepared modules and record the result.
- d) Both edges of the testing module(s) are fixed by the gripping part as shown in Figure 6.
- e) Apply tension with defined conditions such as tension force or strain distance.
- f) Bring the specimen back to the initial state before applying tension.
- g) Apply tension with the same force losing speed and in the reversed direction.
- h) Repeat e) to g) for a defined number of cycle.
- i) After the test, the testing module(s) is(are) removed from the apparatus.
- j) The stressed performance, electrical and optical characteristics of the mechanically stressed module(s) with the required number of testing are measured and the results are recorded. The initial and stressed performances are compared, and the degree of change due to the tension test is determined.
- k) The test and performance measurement for individual specimens are conducted and recorded in the test report.

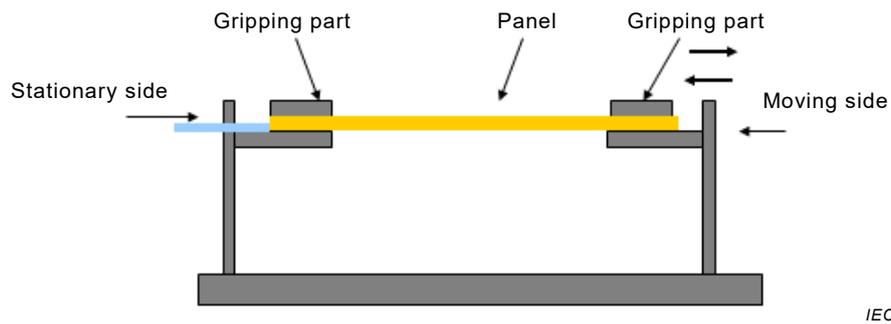


Figure 6 – Apparatus for tension test

IEC

6.8.5 Testing conditions and reporting

The testing conditions are specified as follows:

- maximum tension force or maximum deformation distance applied to the specimen
- tension application procedure such as time-dependent tension force, duration time between tension application
- number of cycles
- criteria for acceptance
- number of specimens
- way of holding specimens and detailed method of holding, such as pressure
- surface condition (such as treatment) of both specimen and apparatus
- testing of environmental conditions, such as temperature and humidity

NOTE The criteria for acceptance include visual performance and specimen geometry both before and after the stressing

All conditions shall be reported if the test uses conditions other than those mentioned above.

IECNORM.COM : Click to view the full PDF of IEC 62715-6-1:2018 RLV

Bibliography

- [1] Suo, Z. et al. Mechanics of rollable and foldable film-on-foil electronics. *Appl. Phys. Lett.* 1999, **74**(8), 1177-1179
 - [2] Gleskova, H., Wagner. S. and Suo. Z. Failure resistance of amorphous silicon transistors under extreme in-plane strain. *Appl. Phys. Lett.* 1999, **75**(19), 3011-3013
 - [3] Gleskova, H. et al. Electrical response of amorphous silicon thin-film transistors under mechanical strain. *J. Appl. Phys.* 2002, **92**, 6224-6229
 - [4] Grego, S. et al. A method to evaluate mechanical performance of thin transparent films for flexible displays. *Thin Solid Films.* 2007, **515**, 4745–4752
 - [5] Menard, E., Nuzzo. R. G. AND Rogers. J. A. Bendable single crystal silicon thin film transistors formed by printing on plastic substrates. *Appl. Phys. Lett.* 2005, **86**(9), 093507
 - [6] Chen. Z. et al. A Mechanical Assessment of Flexible Opto-electronic Devices. *Thin Solid Films.* 2001, **394**, 202-206
 - [7] Servati, P. and Nathan. A. Functional Pixel Circuits for Elastic AMOLED Displays. *Proceedings of the IEEE.* 2005, **93**(7), 1257-1264
 - [8] Rolland, A. et al. Electrical Properties of Amorphous Silicon Transistors and MIS-Devices: Comparative Study of Top Nitride and Bottom Nitride Configurations. *J. Electrochem. Soc.* 1993, **140**(2), 3679-3683
 - [9] Shur, M. S. et al. SPICE Models for Amorphous Silicon and Polysilicon Thin Film Transistors. *J. Electrochem. Soc.* 1997, **144**(8), 2833-2839
 - [10] Cairns. D.R. and Crawford. G.P. Electromechanical Properties of Transparent Conducting Substrates for Flexible Electronic Displays. *Proceedings of the IEEE.* 2005, **93**(8), 1451-1458
-

[IECNORM.COM](https://www.iecnorm.com) : Click to view the full PDF of IEC 62715-6-1:2018 RLV

INTERNATIONAL STANDARD



**Flexible display devices –
Part 6-1: Mechanical test methods – Deformation tests**

IECNORM.COM : Click to view the full PDF of IEC 62715-6-1:2018 RLV

CONTENTS

FOREWORD.....	4
1 Scope.....	6
2 Normative references	6
3 Terms and definitions	6
4 Standard atmospheric conditions	6
5 Specimen preparation.....	7
5.1 General.....	7
5.2 Sample preparation.....	7
6 Mechanical stress test methods.....	7
6.1 General.....	7
6.2 Cyclic bending test.....	8
6.2.1 General	8
6.2.2 Purpose.....	8
6.2.3 Test apparatus	8
6.2.4 Test procedure	9
6.2.5 Testing conditions and reporting.....	9
6.3 Static bending test	11
6.3.1 General	11
6.3.2 Purpose.....	11
6.3.3 Test apparatus	11
6.3.4 Test procedure	11
6.3.5 Testing conditions and reporting.....	12
6.4 Combined bending test	12
6.4.1 General	12
6.4.2 Purpose.....	12
6.4.3 Test apparatus	12
6.4.4 Test procedure	12
6.4.5 Testing conditions and reporting.....	13
6.5 Rolling test.....	14
6.5.1 General	14
6.5.2 Purpose.....	14
6.5.3 Test apparatus	14
6.5.4 Test procedure	15
6.5.5 Testing conditions and reporting.....	16
6.6 Static rolling test.....	16
6.6.1 General	16
6.6.2 Purpose.....	16
6.6.3 Test apparatus	16
6.6.4 Test procedure	17
6.6.5 Testing conditions and reporting.....	17
6.7 Torsion test.....	18
6.7.1 General	18
6.7.2 Purpose.....	18
6.7.3 Test apparatus	18
6.7.4 Test procedure	18
6.7.5 Testing conditions and reporting.....	19

6.8	Tension test	20
6.8.1	General	20
6.8.2	Purpose	20
6.8.3	Test apparatus	20
6.8.4	Test procedure	20
6.8.5	Testing conditions and reporting	21
	Bibliography	22
	Figure 1 – Apparatus for diverse cyclic bending tests	10
	Figure 2 – Apparatus for static bending test	11
	Figure 3 – Apparatus for combined bending tests consisting of the cyclic bending test and static bending test	13
	Figure 4 – Apparatus for rolling test	15
	Figure 5 – Apparatus for diverse torsion tests	19
	Figure 6 – Apparatus for tension test	21

IECNORM.COM : Click to view the full PDF of IEC 62715-6-1:2018 RLV

INTERNATIONAL ELECTROTECHNICAL COMMISSION

FLEXIBLE DISPLAY DEVICES –

Part 6-1: Mechanical test methods – Deformation tests

FOREWORD

- 1) The International Electrotechnical Commission (IEC) is a worldwide organization for standardization comprising all national electrotechnical committees (IEC National Committees). The object of IEC is to promote international co-operation on all questions concerning standardization in the electrical and electronic fields. To this end and in addition to other activities, IEC publishes International Standards, Technical Specifications, Technical Reports, Publicly Available Specifications (PAS) and Guides (hereafter referred to as “IEC Publication(s)”). Their preparation is entrusted to technical committees; any IEC National Committee interested in the subject dealt with may participate in this preparatory work. International, governmental and non-governmental organizations liaising with the IEC also participate in this preparation. IEC collaborates closely with the International Organization for Standardization (ISO) in accordance with conditions determined by agreement between the two organizations.
- 2) The formal decisions or agreements of IEC on technical matters express, as nearly as possible, an international consensus of opinion on the relevant subjects since each technical committee has representation from all interested IEC National Committees.
- 3) IEC Publications have the form of recommendations for international use and are accepted by IEC National Committees in that sense. While all reasonable efforts are made to ensure that the technical content of IEC Publications is accurate, IEC cannot be held responsible for the way in which they are used or for any misinterpretation by any end user.
- 4) In order to promote international uniformity, IEC National Committees undertake to apply IEC Publications transparently to the maximum extent possible in their national and regional publications. Any divergence between any IEC Publication and the corresponding national or regional publication shall be clearly indicated in the latter.
- 5) IEC itself does not provide any attestation of conformity. Independent certification bodies provide conformity assessment services and, in some areas, access to IEC marks of conformity. IEC is not responsible for any services carried out by independent certification bodies.
- 6) All users should ensure that they have the latest edition of this publication.
- 7) No liability shall attach to IEC or its directors, employees, servants or agents including individual experts and members of its technical committees and IEC National Committees for any personal injury, property damage or other damage of any nature whatsoever, whether direct or indirect, or for costs (including legal fees) and expenses arising out of the publication, use of, or reliance upon, this IEC Publication or any other IEC Publications.
- 8) Attention is drawn to the Normative references cited in this publication. Use of the referenced publications is indispensable for the correct application of this publication.
- 9) Attention is drawn to the possibility that some of the elements of this IEC Publication may be the subject of patent rights. IEC shall not be held responsible for identifying any or all such patent rights.

International Standard IEC 62715-6-1 has been prepared by IEC technical committee 110: Electronic display devices.

This second edition cancels and replaces the first edition published in 2014. This edition constitutes a technical revision.

This edition includes the following significant technical changes with respect to the previous edition:

- a) changed the part title to differentiate it from other parts;
- b) added new bending testing methods;
- c) added detailed testing procedures.

The text of this International Standard is based on the following documents:

FDIS	Report on voting
110/951/FDIS	110/974/RVD

Full information on the voting for the approval of this International Standard can be found in the report on voting indicated in the above table.

This document has been drafted in accordance with the ISO/IEC Directives, Part 2.

A list of all the parts in the IEC 62715 series, under the general title *Flexible display devices*, can be found on the IEC website.

The committee has decided that the contents of this document will remain unchanged until the stability date indicated on the IEC website under "<http://webstore.iec.ch>" in the data related to the specific document. At this date, the document will be

- reconfirmed,
- withdrawn,
- replaced by a revised edition, or
- amended.

A bilingual version of this publication may be issued at a later date.

IMPORTANT – The 'colour inside' logo on the cover page of this publication indicates that it contains colours which are considered to be useful for the correct understanding of its contents. Users should therefore print this document using a colour printer.

FLEXIBLE DISPLAY DEVICES –

Part 6-1: Mechanical test methods – Deformation tests

1 Scope

The object of this part of IEC 62715 is to define the standard test methods to evaluate the mechanical stability of flexible display modules, specifically mechanical stability against deformation, such as bending, rolling, twisting, and stretching. Display modules include displays such as LCD, e-paper, and OLED. This document takes into account, wherever possible, the mechanical test methods outlined under mechanical stress.

2 Normative references

The following documents are referred to in the text in such a way that some or all of their content constitutes requirements of this document. For dated references, only the edition cited applies. For undated references, the latest edition of the referenced document (including any amendments) applies.

IEC 62341-5:2009, *Organic light emitting diode (OLED) displays – Part 5: Environmental testing methods*

3 Terms and definitions

No terms and definitions are listed in this document.

ISO and IEC maintain terminological databases for use in standardization at the following addresses:

- IEC Electropedia: available at <http://www.electropedia.org/>
- ISO Online browsing platform: available at <http://www.iso.org/obp>

4 Standard atmospheric conditions

The standard atmospheric conditions in IEC 62341-5:2009, 5.3, shall apply as follows, unless otherwise specifically agreed between customer and supplier.

- Temperature: 25 °C ± 3 °C
- Relative humidity: 25 % RH to 85 % RH
- Atmospheric pressure: 86 kPa to 106 kPa

When all the different kinds of tests are carried out, the temperature and humidity condition shall be reported because the temperature and humidity are critical for the bending and rolling stability regarding image quality on the panel.

NOTE Preferably, the specimen and apparatus are kept in a controlled environment for at least 24 h prior to and after assembly, before the start of the mechanical deformation test.

5 Specimen preparation

5.1 General

The specimen shall be the display module since the final evaluation has to be made based on panel image quality such as luminance, chromaticity, uniformity, line defect, and point defect. The bending stress may cause the deterioration of image quality on a panel, [1] to [9]¹.

5.2 Sample preparation

For the measurements both before and after the mechanical deformation test, the display module being tested shall be aligned on an appropriate support which has to be a flat surface. In addition, the module for the measurement shall be of the appropriate geometry for mechanical stress testing. Specify that the test apparatus should be designed to prevent added strain by stretching test specimens upon folding.

The preferred method of attachment between the display module and the test apparatus is adhesive transfer tape. The display should be bonded on both sides, and the distance between the centre of the test specimen and the point of attachment should be specified. If use scenarios require it, a clamping attachment may be used instead, in which the display is clamped on one side and allowed to slide on the other. The clamping force should be sufficient to ensure that the test specimen is firmly anchored to the test apparatus throughout the entire duration of the test cycle.

If some modules are difficult to clamp due to narrow edge width, the module should be fixed on a bendable support substrate with a suitable adhesive strip or glue. Neither the adhesive strip nor the glue should affect the measurement.

NOTE In some cases, the testing specimen can have a short length or has a very narrow edge to clamp for mechanical stress testing.

Specify that in the event of cross-instrument variability in the form of location (centre or edge)-response bias, one should investigate bend axis misalignment, bowing or uneven mounting plates.

For precise optical measurements, it is very important to define the alignment of the measurement specimen because the flexible display module can be easily deformed by external force. Measurements of the visual characteristics of a flexible module shall be made in an aligned flat state. If flexible modules are aligned in a curved state, it is difficult to make a precise visual evaluation. The measurement module shall be supported or fixed so that it is flat.

The flatness and size of the specimen shall be determined between the supplier and customer.

6 Mechanical stress test methods

6.1 General

Flexible displays have a diversity of shapes in comparison with any other non-flexible electronic displays. Therefore, a wide variety of mechanical stress test methods are available, such as a cyclic bending (folding) or dynamic bending test, a static bending test, a rolling test, a combined mechanical test and more. The selection of the appropriate test methods shall be based on the requirement of the application. For each mechanical stress test, the relevant test method specification shall be stated along with the explanation of the purpose of each unique test. The allowable critical bending radius of a panel depends on the application of the flexible display. Therefore, the required critical bending radius will be changed based on the applications.

¹ Numbers in square brackets refer to the Bibliography.

There are several factors to consider when designing a reliable and repeatable mechanical folding or deformation test method, as follows:

- Motion profiles controlled by a single hinge (or pivot axis) and which wrap around a mandrel can stretch samples, and if not precisely actuated or controlled can create a great deal of variability in the test response.
- Motion profiles controlled by more than one hinge or pivot axis can prevent added stretching on test specimens, and offer better control of the test response.
- Clamping samples can prevent shear between layers of multi-layer test specimens containing adhesive, and greatly impact test response.
- Additional considerations, such as attaching too close to the apex of the bend, and fold axis misalignment or slight distortions in the shape of the mounting plates, can also impact reliability and repeatability of the test response.
- Samples should be pre-conditioned in a controlled environment for at least 24 h prior to testing as material properties for adhesives and polymers can be affected by temperature and water uptake.

6.2 Cyclic bending test

6.2.1 General

This procedure is for conditioning the specimen under mechanical stress by repeated bending.

6.2.2 Purpose

The purpose of this test is to provide a standard procedure for evaluating the robustness of a flexible display against a cyclic bending stress which might typically happen in application. The bending properties might cover several typical parameters of the characteristics of a display panel's image quality. The typical parameters of a display panel's image quality might cover the luminance, chromaticity, uniformity, line defect, point defect, pixel shrink, and/or presence or absence of cracks.

6.2.3 Test apparatus

The cyclic bending test equipment includes the clamp to hold a bending test specimen, the moving part to shuttle, and the control system which regulates the number of cyclic bendings, the moving distance, and the moving speed while testing. The specimen shall be securely clamped with a gripping part during the test. Several kinds of cyclic bending test equipment is available and shown in Figure 1, [4][7][10]. It is not necessary that a certain type of bending test equipment be preferred but the constant bending radius (r), equal to the radius of the rod, should be kept during the bending test.

NOTE If the bending radius of the test specimen is kept constant during the bending test, the bending rod can be removed as it would scratch the surface of the test specimen during the cyclic bending test.

For the cyclic bending test, the following apparatus is considered:

- the specimen experiences a bending stress when the specimen is shuttled back and forth (Figure 1a)) or while the specimen is folded and unfolded (Figure 1b)),
- when the specimen is repeatedly multi-bent in the inward or outward direction, a cyclic multi-inward bending equipment (Figure 1c)) or cyclic multi-outward bending equipment (Figure 1d)) can be used,
- when the specimen is repeatedly multi-bent in a Z-shape, a cyclic multi-bending equipment can be used,
- when the specimen is repeatedly bent in both the inward and outward direction, a cyclic inward and outward bending equipment can be used (Figure 1e) and/or f)).

6.2.4 Test procedure

The cyclic bending test shall be performed using a repeated motion to move regularly between two points or two states (folded state and unfolded state) as follows:

- a) Prepare the required number of specimens according to 5.2.
- b) Perform the initial performance, visual characteristics, test for the prepared specimens and record the result.
- c) One edge of the specimen is fixed by the clamp, or fixed with an adhesive, and the other edge is supported properly as stated in 5.2.
- d) Bend the specimen properly with defined conditions such as the rotation angle of the clamp roll and the bending angular velocity.
- e) Bring the specimen back to the initial state before the bending.
- f) If required, bend the specimen in another direction with defined conditions such as the rotation angle of the clamp roll and the bending angular velocity.
- g) Bring the specimen back to the initial state before the bending with the same angular velocity and reversed direction.
- h) Repeat d) to g) for a defined number of cycles.
- i) After the test, the specimen is removed from the apparatus.
- j) Repeat the tests with (an)other specimen(s) following c) to j).
- k) The stressed performance, visual characteristics of the mechanically stressed specimen(s) with the required number of testings are measured and the results are recorded. The initial and stressed performances are compared, and the degree of change due to the bend is determined.
- l) The test and performance measurement for individual specimens are conducted and recorded in the test report.

6.2.5 Testing conditions and reporting

The testing conditions are specified as follows:

NOTE 1 The numerical values of the test conditions are examples.

- a) bending radius
 r (bending radius): 20 mm, 10 mm, 5 mm, 3 mm, 2 mm, 1 mm, 0,5 mm, 0,2 mm
- b) bending angle and angular velocity, procedure for one cycle
 t (time for one bend and interval): 0,5 s, 1 s, 2 s, 3 s, 5 s, 10 s
- c) load
- d) number of repeating cycles
- e) criteria for acceptance
- f) number of specimens
- g) the bending inner surface is the top surface (face up) or the back side surface (face down)
- h) way of holding specimens and detailed method of holding, such as pressure
- i) surface condition (such as treatment) of both specimen and apparatus
- j) testing of environmental conditions, such as temperature and humidity.

NOTE 2 The criteria for acceptance include the visual performance and specimen geometry both before and after the stressing.

All conditions shall be reported if the test uses conditions other than those mentioned above.

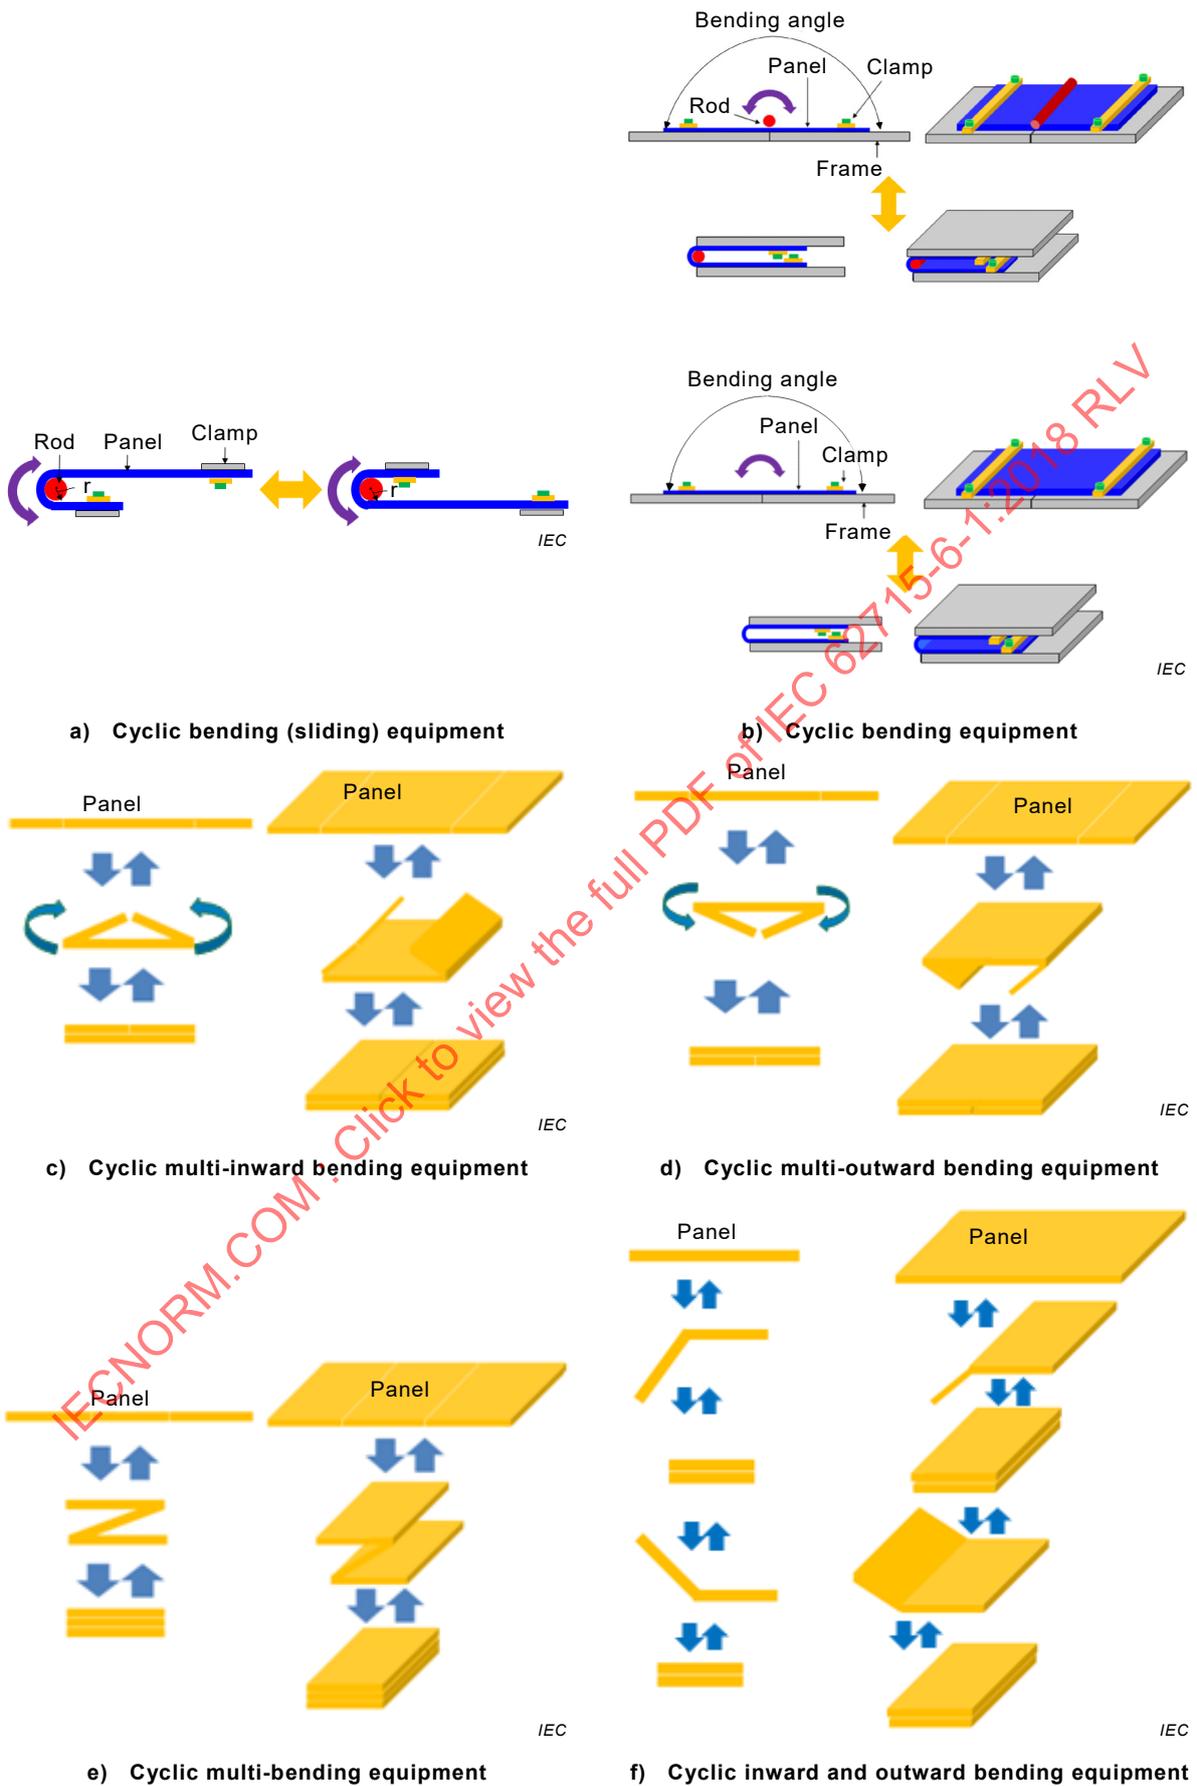


Figure 1 – Apparatus for diverse cyclic bending tests

6.3 Static bending test

6.3.1 General

This test is especially applicable for evaluating the static bending properties of a flexible display device by measuring its performance after it remains bent for a certain period of time. Each specimen is bent at a fixed bending radius for any length of time.

6.3.2 Purpose

This test is to provide a standard procedure for evaluating the static bending properties of a flexible display device under constant stress for a certain period of time. Each specimen is bent at a fixed bending radius for a controlled length of time.

6.3.3 Test apparatus

The body of the display panel shall firmly adhere to the surface of the test equipment during the test, where the test equipment should have a round shape with a certain radius as in Figure 2. The specimen shall be bent at a fixed bending radius for a period of time.

If the bending radius of the test specimen is kept constant during the bending test, the bending rod can be removed as it may scratch the surface of the test specimen during the static bending test. During the test, the flexible printed circuit (FPC) and the driver should be carefully handled so that they are not subject to bending damage. The chip-on-film (COF) method is preferable in order to avoid the occurrence of bending damage on the driver's integrated circuit (IC) during the bending test.

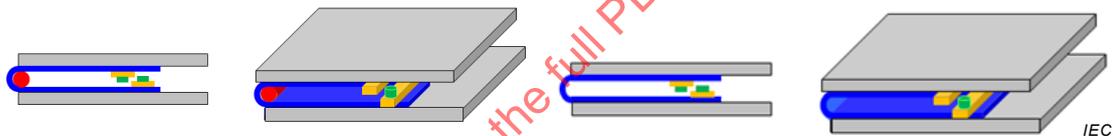


Figure 2 – Apparatus for static bending test

6.3.4 Test procedure

The static bending test shall be carried out with a fixed bending radius for a certain period of time, as follows:

- a) Prepare the required number of specimens according to 5.2.
- b) Perform the initial performance, visual characteristics, test for the prepared specimens and record the result.
- c) One edge of the specimen is fixed by the clamp and the other edge is supported properly.
- d) Bend the specimen properly with defined conditions such as the rotation angle of the clamp roll and the bending angular velocity.
- e) Keep the specimen bent for certain period of time.
- f) Bring the specimen back to the initial state before the bending.
- g) Repeat d) to f) for a defined number of tests.
- h) After the bending, the specimen is removed from the apparatus.
- i) Repeat the tests with (an)other specimen(s) following c) to g).
- j) The stressed performance and visual characteristics of mechanically stressed specimen(s) with the required number of testings are measured, and the results are recorded. The initial and stressed performances are compared, and the degree of change due to bending is determined.
- k) The test and performance measurement for individual specimens are conducted and recorded in the test report.

6.3.5 Testing conditions and reporting

The testing conditions are specified as follows:

NOTE 1 The numerical values of the test conditions are examples.

- a) bending radius
 r (bending radius): 20 mm, 10 mm, 5 mm, 3 mm, 2 mm, 1 mm, 0,5 mm, 0,2 mm
- b) bending angle
- c) holding duration
- d) load
- e) criteria for acceptance
- f) number of specimens
- g) the bending inner surface is the top surface (face-up) or backside surface (face-down)
- h) way of holding specimens and detailed method of holding, such as pressure
- i) surface condition (such as treatment) of both specimen and apparatus
- j) testing of environmental conditions, such as temperature and humidity

NOTE 2 The criteria for acceptance include visual performance and specimen geometry both before and after the stressing.

All conditions shall be reported if the test uses conditions other than those mentioned above.

6.4 Combined bending test

6.4.1 General

This test is especially applicable for evaluating two kinds of bending properties (cyclic bending properties and static bending properties (see Figure 3)) of the flexible display device, after the flexible display remains in the curved shape for a certain period of time and goes through the cyclic bending condition for a certain period of time in real use environment.

6.4.2 Purpose

The objective of this test is to provide a standard procedure for evaluating the combined bending properties of cyclic bending and duration time bending. This test aims to take the real product use environment into consideration, where the real product keeps the panel in a curved, folded, or rolled shape for a long time when it is used or before it is rolled out.

6.4.3 Test apparatus

The combined bending test utilizes the same apparatus as the cyclic bending test as shown in Figure 3. The instrument controller shall be capable of stopping the mechanism while the specimen is in a bent state during each iteration of the cycle.

6.4.4 Test procedure

The cyclic bending test procedure is modified to include a 'hold' of adjustable duration between each iteration of the cycle where the specimen remains in a fully bent state [4] as follows:

- a) Prepare the required number of specimens according to 5.2.
- b) Perform the initial performance, visual characteristics, test for the prepared specimens and record the result.
- c) One edge of the specimen is fixed by the clamp and the other edge is supported properly.
- d) Bend the specimen properly with defined conditions such as the rotation angle of the clamp roll and the bending angular velocity.

- e) Bring the specimen back to the initial state before the bending.
- f) After performing a certain number of times the bending test in d) and e), bring the specimen in a fully bent state, then hold.
- g) After certain a period of time on hold, bring the specimen back to the initial state.
- h) If required, bend the specimen in another direction with defined conditions such as the rotation angle of the clamp roll and the bending angular velocity.

NOTE If required, the specimen and apparatus are set in a proper setting, such as rotation of the rod, etc.

- i) The bent module is returned to the initial state before the bending with the same angular velocity and reversed direction.
- j) After performing a certain number of times the bending test in h) and i), bring the specimen in the fully bent state, and then hold.
- k) After the test, bring the specimen back to the initial state.
- l) Repeat d) to k) for a defined number of cycles.
- m) Bring the specimen back to the initial state.
- n) Repeat the test with (an)other specimen(s) following c) to m).
- o) The stressed performance and visual characteristics of the mechanically stressed specimen(s) with the required number of testings are measured, and the results are recorded. The initial and stressed performances are compared, and the degree of change due to the bend is determined.
- p) The test and performance measurement for individual specimens are conducted and recorded in the test report.

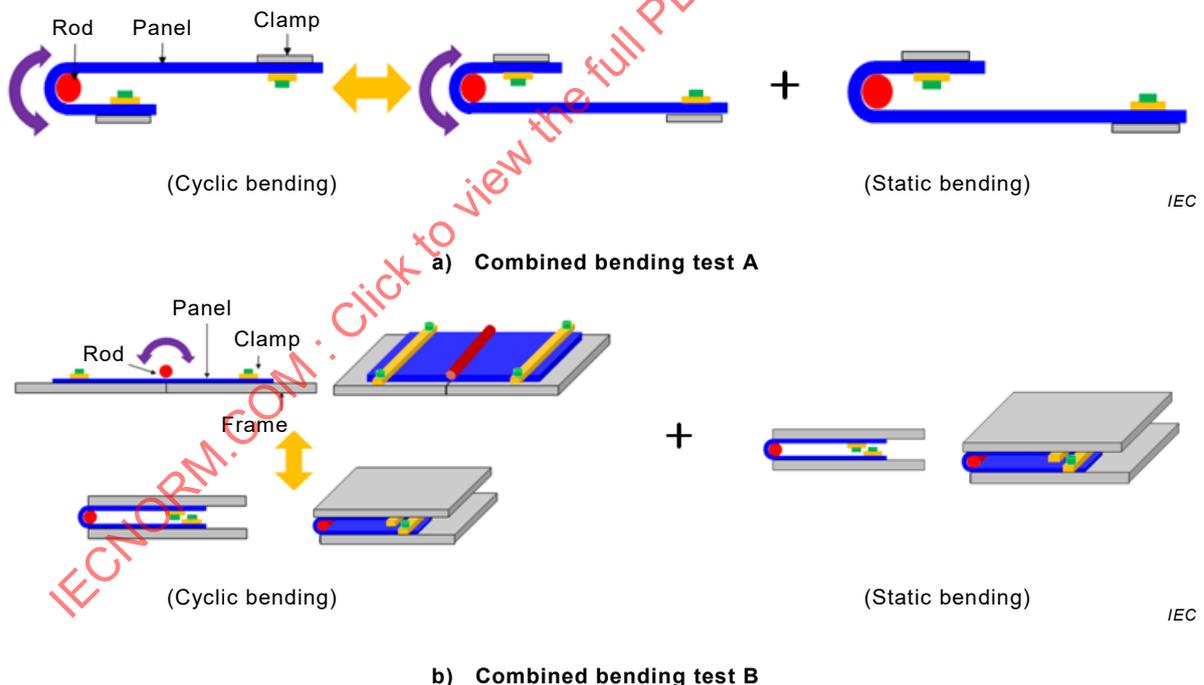


Figure 3 – Apparatus for combined bending tests consisting of the cyclic bending test and static bending test

6.4.5 Testing conditions and reporting

The testing conditions are specified as follows:

NOTE 1 The numerical values of the test conditions are examples.

a) bending radius

r (bending radius): 20 mm, 10 mm, 5 mm, 3 mm, 2 mm, 1 mm, 0,5 mm, 0,2 mm