
**Passenger car tyres — Verifying tyre
capabilities — Laboratory test methods**

*Pneumatiques pour voitures particulières — Vérification de l'aptitude
des pneumatiques — Méthodes d'essai en laboratoire*

STANDARDSISO.COM : Click to view the full PDF of ISO 10191:2010



PDF disclaimer

This PDF file may contain embedded typefaces. In accordance with Adobe's licensing policy, this file may be printed or viewed but shall not be edited unless the typefaces which are embedded are licensed to and installed on the computer performing the editing. In downloading this file, parties accept therein the responsibility of not infringing Adobe's licensing policy. The ISO Central Secretariat accepts no liability in this area.

Adobe is a trademark of Adobe Systems Incorporated.

Details of the software products used to create this PDF file can be found in the General Info relative to the file; the PDF-creation parameters were optimized for printing. Every care has been taken to ensure that the file is suitable for use by ISO member bodies. In the unlikely event that a problem relating to it is found, please inform the Central Secretariat at the address given below.

STANDARDSISO.COM : Click to view the full PDF of ISO 10191:2010



COPYRIGHT PROTECTED DOCUMENT

© ISO 2010

All rights reserved. Unless otherwise specified, no part of this publication may be reproduced or utilized in any form or by any means, electronic or mechanical, including photocopying and microfilm, without permission in writing from either ISO at the address below or ISO's member body in the country of the requester.

ISO copyright office
Case postale 56 • CH-1211 Geneva 20
Tel. + 41 22 749 01 11
Fax + 41 22 749 09 47
E-mail copyright@iso.org
Web www.iso.org

Published in Switzerland

Contents

Page

Foreword	iv
1 Scope	1
2 Normative references	1
3 Terms and definitions	1
4 Test equipment	2
5 Testing	3
5.1 Strength test	3
5.2 Bead unseating test	5
5.3 Endurance test	7
5.4 High speed test	7
6 Requirements	9
6.1 Test sample	9
6.2 Strength test	9
6.3 Bead unseating resistance (tubeless tyres)	10
6.4 Endurance test	11
6.5 High-speed test	11
Annex A (informative) High-speed test — Test conditions for tyres without service description marking	12
Bibliography	14

Foreword

ISO (the International Organization for Standardization) is a worldwide federation of national standards bodies (ISO member bodies). The work of preparing International Standards is normally carried out through ISO technical committees. Each member body interested in a subject for which a technical committee has been established has the right to be represented on that committee. International organizations, governmental and non-governmental, in liaison with ISO, also take part in the work. ISO collaborates closely with the International Electrotechnical Commission (IEC) on all matters of electrotechnical standardization.

International Standards are drafted in accordance with the rules given in the ISO/IEC Directives, Part 2.

The main task of technical committees is to prepare International Standards. Draft International Standards adopted by the technical committees are circulated to the member bodies for voting. Publication as an International Standard requires approval by at least 75 % of the member bodies casting a vote.

Attention is drawn to the possibility that some of the elements of this document may be the subject of patent rights. ISO shall not be held responsible for identifying any or all such patent rights.

ISO 10191 was prepared by Technical Committee ISO/TC 31, *Tyres, rims and valves*, Subcommittee SC 3, *Passenger car tyres and rims*.

This third edition cancels and replaces the second edition (ISO 10191:1995 and also ISO 10191:1995/Amd.1:1998), of which it constitutes a minor revision.

STANDARDSISO.COM : Click to view the full PDF of ISO 10191:2010

Passenger car tyres — Verifying tyre capabilities — Laboratory test methods

1 Scope

This International Standard specifies test methods for verifying the capabilities of tyres for passenger cars. Of the test methods presented, it is possible that only some will be required depending on the type of tyre to be tested. The tests are carried out in a laboratory under controlled conditions.

This International Standard includes a strength test for assessing the capability of the tyre structure, with respect to braking energy, in the tread area.

A second test, the bead unseating test, assesses the resistance of the tyre to bead unseating. It applies to tubeless tyres only.

A third test, the endurance test, assesses the resistance of the tyre with respect to service at full load and moderate speed over long distances.

The fourth test, the high speed test, assesses the capability of the tyre according to its speed category.

The test methods presented in this International Standard are not intended for gradation of tyre performance or quality levels. This International Standard applies to all passenger car tyres.

2 Normative references

The following referenced documents are indispensable for the application of this document. For dated references, only the edition cited applies. For undated references, the latest edition of the referenced document (including any amendments) applies.

ISO 4223-1:2002, *Definitions of some terms used in the tyre industry — Part 1: Pneumatic tyres*

3 Terms and definitions

For the purposes of this document, the terms and definitions given in ISO 4223-1 and the following apply.

3.1

bead separation

breakdown of bond between components in the bead area

3.2

belt separation

parting of rubber compound between belt layers or between belts and plies

3.3

chunking

breaking away of pieces of the tread

- 3.4 cord separation**
cord parting from adjacent rubber compounds
- 3.5 cracking**
any parting within the tread, or innerliner of the tyre extending to cord material
- 3.6 innerliner separation**
parting of innerliner from cord material in the carcass
- 3.7 open splice**
any parting at any junction of tread, or innerliner that extends to cord material
- 3.8 ply separation**
separation of rubber compound between adjacent plies
- 3.9 separation**
parting of the rubber compound from the cord material in the sidewall
- 3.10 tread separation**
pulling away of the tread from the tyre carcass
- 3.11 test rim**
any rim on which the tyre may be fitted which conforms to the dimensions of the recommended rims for the particular tyre designation and type
- 3.12 test drum speed**
peripheral speed of the steel test drum
- 3.13 maximum load rating**
maximum load that the tyre is rated to carry according to its speed category

4 Test equipment

- 4.1 Test drum**, cylindrical driven flywheel (drum) having a diameter of 1,7 m $^{+2}_0$ % or 2 m $^{+2}_0$ %.

The surface of the drum shall be smooth steel. The width of the test surface shall be equal to or exceed the overall width of the test tyre.

For the test drum, the loading device shall have a capacity of at least 1 000 kg and the accuracy shall be within ± 1 % of the full scale. The speed capability of the equipment shall be adequate for the requirements of the test methods. The accuracy of the test drum speed shall be within $^{+2}_0$ km/h.

- 4.2 Plunger**, in cylindrical steel and of sufficient length with a hemispherical end and a diameter of $(19 \pm 1,6)$ mm.

For the plunger equipment, the loading device shall permit gradual application of the force. Indicators of displacement and force provided shall be accurate to within $\pm 1\%$ of full scale. The displacement speed shall be controlled with an accuracy within $\pm 3\%$ of the full scale.

4.3 Bead unseating block, of one of the two types shown in Figure 1.

The bead unseating block loading device shall permit progressive application of the force. Indicators of displacement and force provided shall be accurate to within $\pm 1\%$ of full scale.

The displacement speed of the head unseating block shall be controlled with an accuracy within $\pm 3\%$ of the full scale.

4.4 Inflation pressure gauges, with a maximum scale value of at least 500 kPa and an accuracy within ± 5 kPa.

5 Testing

5.1 Strength test

5.1.1 Preparation of tyre

5.1.1.1 Mount the tyre on a test rim and inflate it to the pressure specified in Table 1.

5.1.1.2 Maintain the assembly at test room for at least 3 h.

Table 1 — Inflation pressures for resistance test

Tyre type	Pressure kPa
Standard	180
Reinforced/extra load	220
T type (temporary use)	360
NOTE In case of other tyre types, the tyre manufacturer shall send a request to ISO for insertion in this table of a different test pressure, with reasons.	

Dimensions in millimetres
 Material: Al-Si2 Mg Ti or Al-Si7 Mg0,3 (see reference [2])
 Condition: TF (see reference [1])
 Surface roughness: Ra 1,25 µm

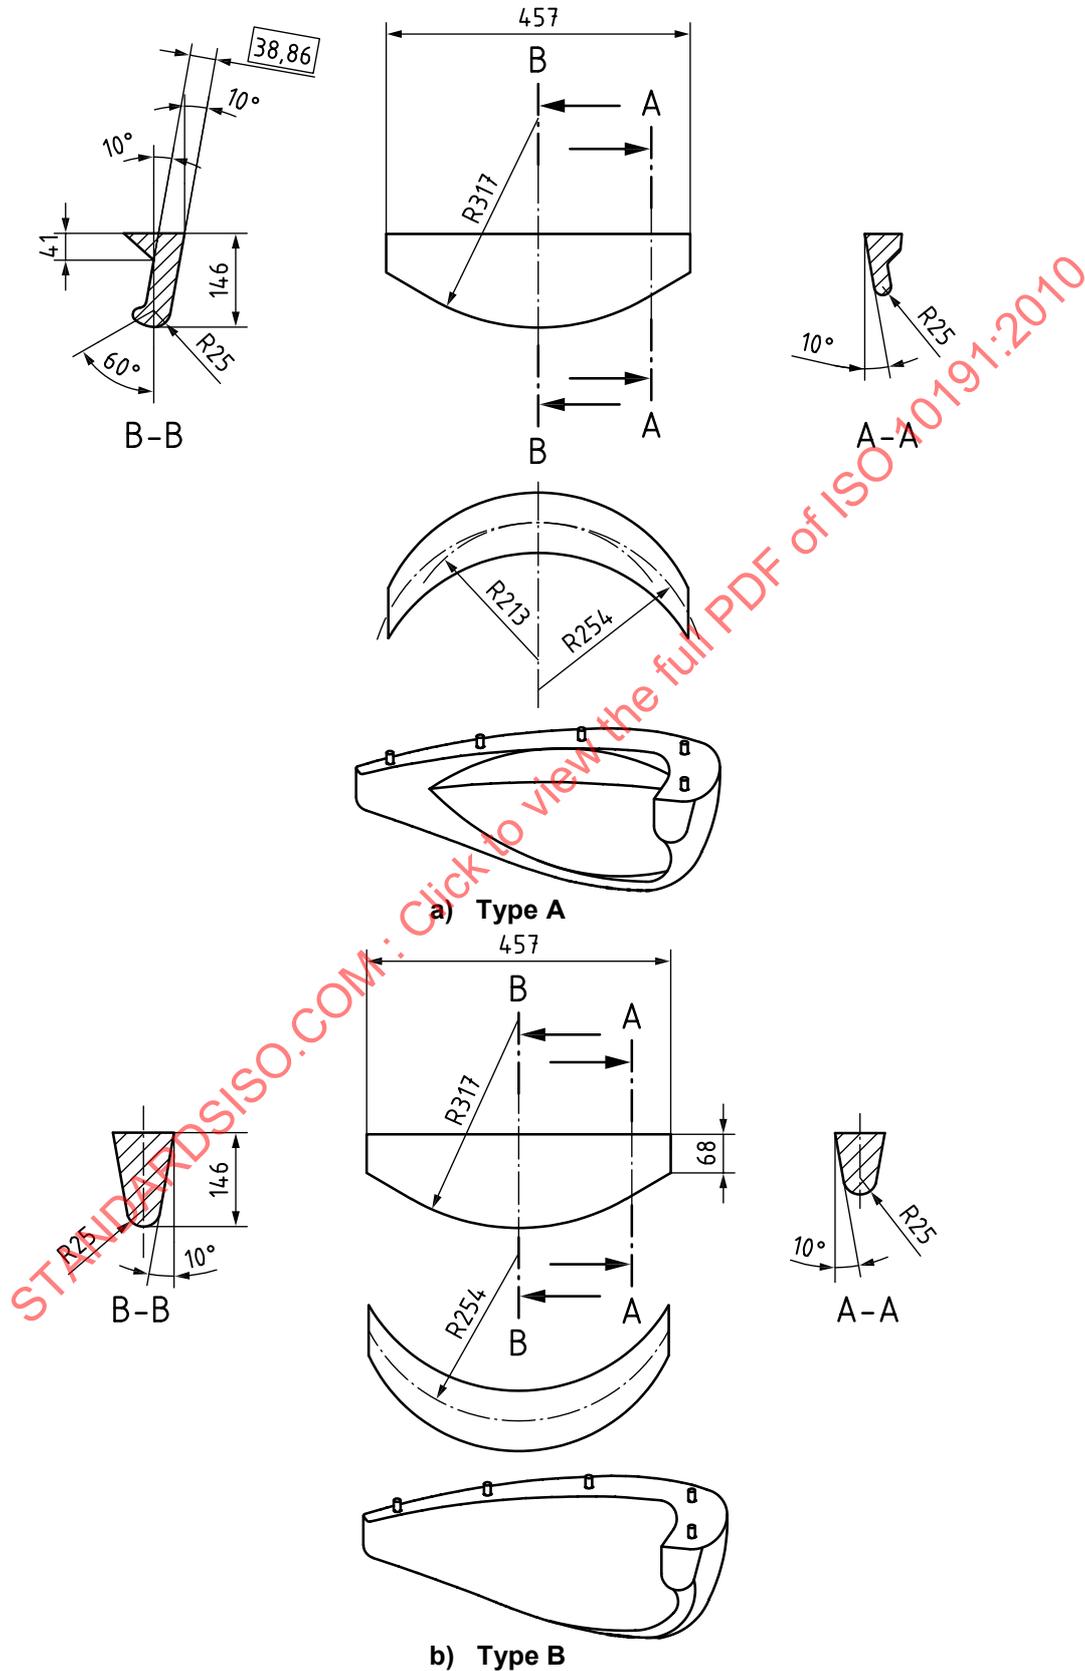


Figure 1 — Diagrams of bead unseating blocks

5.1.2 Test procedure

5.1.2.1 Readjust the tyre pressure to that specified in 5.1.1.1 and mount the assembly on a fixture.

5.1.2.2 Position the plunger as near to the line as possible, avoiding penetration into the tread grooves, and force the plunger perpendicularly into the tread at a rate of $(50 \pm 2,5)$ mm/min.

5.1.2.3 Record the force and penetration at the moment of breaking (see also 5.1.2.7) at each of five test points approximately equally spaced around the tyre circumference. Check the pressure before moving to the next test point.

5.1.2.4 If the tyre fails to break before the plunger is stopped on reaching the rim, then the tyre is deemed to have passed the test at that point.

5.1.2.5 Compute the breaking energy, W , in joules for each test point, except those considered by means of the following formula:

$$W = \frac{F \times P}{2\,000}$$

where

F is the force, in newtons;

P is the penetration, in millimetres.

5.1.2.6 Determine the breaking energy value for the tyre by computing the average of the values obtained.

5.1.2.7 When an appropriate device is available, which automatically evaluates the value of the energy W , the penetration can be stopped shortly after having achieved the prescribed value.

5.1.2.8 In the case of tubeless tyres, means may be provided to ensure the retention of the inflation pressure for the duration of the test.

5.2 Bead unseating test

5.2.1 General

This test applies to tubeless tyres only.

5.2.2 Preparation of tyre


5.2.2.1 Wash the tyre, dry it at the beads, and mount it without lubrication or adhesive on a clean, painted test rim. The rim contour shall be one of those specified for the fitment of the test tyre.

5.2.2.2 Mount the tyre on a test rim and inflate it to the pressure specified in Table 1.

5.2.3 Test procedure

5.2.3.1 Mount the tyre and rim assembly on a fixture as shown in Figure 2.

Dimensions in millimetres

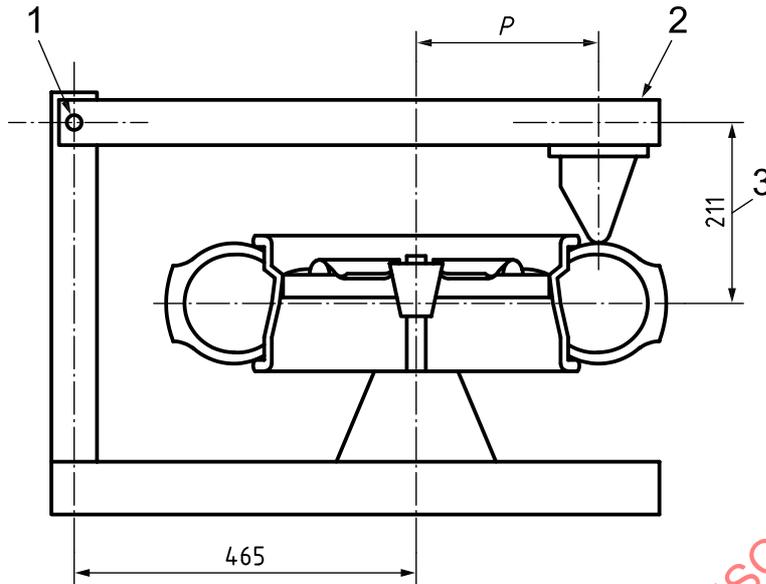

Key

- 1 pivot on centreline of beam
- 2 horizontal beam
- 3 to bottom of anvil

Figure 2 — Bead unseating fixture

- 5.2.3.2** Position the bead unseating block (4.3) against the tyre at a horizontal distance, P , as shown in Table 2.
- 5.2.3.3** Apply a force through the block to the tyre outer at a rate of $(50 \pm 2,5)$ mm/min.
- 5.2.3.4** Increase the force until the bead block seats or until the prescribed value is reached.
- 5.2.3.5** Repeat the test at least four times at places approximately equally spaced around the tyre circumference.

Table 2 — Distance P from bead unseating block (see Figure 2)

Dimensions in millimetres

Nominal rim diameter code	Dimension P	
	T type temporary use spare tyres	All other tyres
10		216
12		241
13		254
14		267
15		279
16		292
17		305
18		318
19		330
290		229
315		241
340		254
365		267
390		279
415		292

5.3 Endurance test

5.3.1 Preparation of tyre

5.3.1.1 Mount the tyre on a test rim and inflate it to the pressure specified in Table 1.

5.3.1.2 Maintain the tyre and rim assembly at an ambient temperature of not less than 35 °C for at least 3 h.

5.3.2 Test procedure

5.3.2.1 Readjust the tyre pressure to the value specified in Table 1 immediately before testing.

5.3.2.2 Mount the tyre and rim assembly on a test axle so that the tyre may be pressed radially against the outer face of test drum.

5.3.2.3 During the test the ambient temperature, at a distance of not less than 150 mm and not more than 1 m from the tyre, shall be at least 35 °C. No provision shall be made for cooling the tyre during the test.

5.3.2.4 Conduct the test, without interruptions, at not less than 80 km/h test speed with loads and test periods not less than those shown in Table 3.

5.3.2.5 Throughout the test, the inflation pressure shall not be corrected and the test loads shall be kept constant at the value corresponding to each test period.

Table 3 — Test parameters for endurance

Test period	Duration	Load
	min.	as a percentage of tyre maximum load rating min.
1	4 h	85 %
2	6 h	90 %
3	24 h	100 %

5.4 High speed test

5.4.1 General

For those tyres not marked with a service description, note should be taken of the additional test conditions given in Annex A.

5.4.2 Preparation of tyre

5.4.2.1 Mount the tyre on a test rim, inflate it to a pressure related to its speed symbol, tyre version and load type, as shown in Table 4.

The tyre manufacturer may request, giving reasons, the use of a different test inflation pressure. In such a case, the tyre shall be inflated to that pressure.

5.4.2.2 Maintain the tyre and rim assembly at test room temperature for at least 3 h.

Table 4 — Inflation pressures for high speed test

Speed symbol	Inflation pressure				
	kPa				
	Diagonal			Radial and bias-belted	
	4PR	6PR	8PR	Normal (standard)	Reinforced (extra load)
L, M, N	230	270	300	240	280
P, Q, R, S	260	300	330	260	300
T, U, H	280	320	350	280	320
V	300	340	370	300	340
W, Y	—	—	—	320	360

NOTE In case of high pressure “temporary use spare” tyres, identified by a prefix T in the size designation, the tyre shall be inflated to 420 kPa.

5.4.3 Test method

5.4.3.1 Before or after mounting the tyre and rim assembly on a test axle, re-adjust the tyre pressure to that specified in 5.4.2.

5.4.3.2 Press the tyre and rim assembly against the outer face of the test drum.

5.4.3.3 Apply a load to the test axle, equal to 80 % of the maximum load rating of the tyre.

For tyres of speed symbol V, the test load shall be equal to 73 % of the load corresponding to their load index, i.e. 80 % of the maximum load allowed at 240 km/h.

For tyres of speed symbols W and Y, the test load shall be equal to 68 % of the load corresponding to their load index, i.e. 80 % of the maximum load allowed at 270 km/h and 300 km/h, respectively.

5.4.3.4 Throughout the test, the inflation pressure shall not be corrected and the test load shall be kept constant.

5.4.3.5 During the test, the temperature in the test room shall be maintained at between 20 °C and 30 °C, or at a higher temperature if the tyre manufacturer agrees.

5.4.3.6 Carry the test through without interruptions as follows, in relation to the tyre speed symbol and the test drum diameter.

a) For tyres of speed symbols L to W

The initial test speed is equal to the tyre's speed category:

- less than 40 km/h on a 1,7 m drum or
 - less than 30 km/h on a 2 m drum.
- 1) Accelerate the equipment at a constant rate such that the initial test speed is reached at the end of 10 min from start-up.
 - 2) Operate the equipment with the test drum speed at the initial test speed for 10 min;
 - then, at the initial test speed plus 10 km/h for at least 10 min;
 - then, at the initial test speed plus 20 km/h for at least 10 min;

- then, at the initial test speed plus 30 km/h for at least 10 min;
- and finally, for a further 10 min, at the initial test speed plus
30 km/h on one or other of the drums or
40 km/h on the 1,7 m drum only.

b) For tyres of speed symbol Y

The test conditions on a 2 m drum are the following.

- 1) Accelerate the equipment at a constant rate such that a speed of 270 km/h is reached at the end of 10 min from start-up.
- 2) Operate the equipment at 270 km/h for 20 min;
 - then, at 280 km/h for 10 min,
 - then, at 290 km/h for 10 min,
 - and finally, at 300 km/h for 10 min.
- 3) When a 1,7 m drum is used, reduce the above speeds by 10 km/h.

6 Requirements

6.1 Test sample

Three tyres with identical characteristics, e.g. size designation and service description or maximum load rating and speed capability, shall comprise a test sample:

- a) one tyre shall be used for the measurement of bead unseating and then of strength;
- b) a second tyre shall be used for the endurance test;
- c) a third tyre shall be used for the high-speed performance test.

The pressures, loads, speeds and durations shall be as specified for each test method.

Each test sample shall conform to the requirements specified in 6.2 to 6.5.

6.2 Strength test

6.2.1 Each test sample shall meet at least the requirements for minimum breaking energy specified when tested in accordance with 5.1. See Table 5.

6.2.2 For tyres with nominal section width less than 160 mm, the required energy value shall be reduced by 25 %.

Table 5 — Minimum breaking energy

Tyre version	Breaking energy
	min. J
Standard	295
Reinforced/extra load	585

NOTE In the case of other tyre versions or when pressures differ from those recommended for tyre measurements in Table 1, the value of the minimum breaking load, E_{min} , in joules, is calculated using the equation:

$$E_{min} = 7,35 (p_1 - 140)$$

where p_1 is the inflation pressure, in kilopascals, specified for the test.

6.2.3 For high pressure “temporary use spare” tyres, identified by a prefix T in the size designation, the energy required shall be:

- a) 295 J for tyres with a maximum load rating of 400 kg and above;
- b) 220 J for tyres with a maximum load rating below 400 kg.

6.3 Bead unseating resistance (tubeless tyres)

6.3.1 When tested in accordance with 5.2, the applied force required to unseat the tyre bead at the point of contact shall not be less, in relation to the nominal section width of the tyre, than that shown in Table 6.

Table 6 — Bead unseating

Nominal section, S mm	Force N
$S < 160$	6 670
$160 \leq S < 205$	8 890
$S \geq 205$	11 120

6.3.2 For high pressure “temporary use spare” tyres, identified by a prefix T in the size designation, the force required to unseat the tyre bead shall not be less, in relation to the tyre load index, than that shown in Table 7.

Table 7 — Bead unseating for temporary use spare tyres

Load index	Force N
≤ 75	6 670
from 76 to 92	8 890
≥ 93	11 120

6.4 Endurance test

6.4.1 When the tyre has been subjected to the laboratory endurance test specified in 5.3, using a test rim and a valve which undergo no permanent deformation and allow no loss of air, there shall be no visual evidence of tread, sidewall, ply, cord, innerliner, belt or bead separation, chunking, open splices, cracking or broken cords.

6.4.2 The tyre pressure measured immediately after the test shall not be less than the initial pressure specified in 5.3.1.1.

6.5 High-speed test

6.5.1 After completion of the laboratory high-speed test specified in 5.4 using a test rim and a valve which undergo no permanent deformation and allow no loss of air, there shall be no visual evidence of tread, sidewall, ply, cord, innerliner, belt or bead separation, chunking, open splices, cracking or broken cords.

6.5.2 The tyre pressure measured immediately after the test shall not be less than the initial pressure specified in 5.4.2.1.

STANDARDSISO.COM : Click to view the full PDF of ISO 10191:2010

Annex A
(informative)

High-speed test — Test conditions for tyres without service description marking

A.1 General

This annex provides additional information on test conditions for those tyres which are not marked with a service description.

The following additional conditions apply.

A.2 Test conditions

A.2.1 Inflation pressure

The inflation pressures (see 5.4.2.1) in Table A.1 shall be used.

Table A.1 — Reference pressures

Tyre type	Inflation pressure
	kPa
VR	300
ZR	320
Radial	280
Diagonal or bias-belted:	
4PR or B	230
6PR or C	270
8PR or D	300

A.2.2 Maximum load rating/speed category

A.2.2.1 The maximum load rating (see 5.4.3.3) is that specified by the tyre manufacturer (or moulded on the tyre), with reference to the speed categories shown in Table A.2.

A.2.2.2 The test load (see 5.4.3.3) shall be 80 % of the maximum load rating (see A.2.2.1).