
**Fibre-reinforced polymer (FRP)
reinforcement of concrete — Test
methods —**

**Part 3:
CFRP strips**

STANDARDSISO.COM : Click to view the full PDF of ISO 10406-3:2019



STANDARDSISO.COM : Click to view the full PDF of ISO 10406-3:2019



COPYRIGHT PROTECTED DOCUMENT

© ISO 2019

All rights reserved. Unless otherwise specified, or required in the context of its implementation, no part of this publication may be reproduced or utilized otherwise in any form or by any means, electronic or mechanical, including photocopying, or posting on the internet or an intranet, without prior written permission. Permission can be requested from either ISO at the address below or ISO's member body in the country of the requester.

ISO copyright office
CP 401 • Ch. de Blandonnet 8
CH-1214 Vernier, Geneva
Phone: +41 22 749 01 11
Fax: +41 22 749 09 47
Email: copyright@iso.org
Website: www.iso.org

Published in Switzerland

Contents

	Page
Foreword	iv
1 Scope	1
2 Normative references	1
3 Terms and definitions	1
4 Symbols	2
5 Test method for determining tensile properties	3
5.1 Test pieces.....	3
5.1.1 Dimensions.....	3
5.1.2 Preparation.....	3
5.1.3 Cutting equipment.....	4
5.1.4 Cutting accuracy for width of test piece.....	4
5.1.5 Number of test pieces.....	4
5.2 Testing machine and measuring devices.....	5
5.2.1 Testing machine.....	5
5.2.2 Strain gauges/extensometers.....	5
5.3 Test method.....	5
5.3.1 Dimensions of test pieces.....	5
5.3.2 Mounting of strain gauges/extensometers.....	5
5.3.3 Mounting of test piece.....	5
5.3.4 Loading rate.....	5
5.3.5 Test temperature.....	5
5.3.6 Range of test.....	5
5.4 Calculation and expression of test results.....	5
5.4.1 General.....	5
5.4.2 Load-strain curve.....	6
5.4.3 Tensile strength.....	6
5.4.4 Young's modulus.....	7
5.5 Test report.....	8
6 Test method for exposure to laboratory light sources	8
6.1 Test pieces.....	8
6.1.1 Test plate for accelerated artificial exposure test.....	8
6.1.2 Number of test plates.....	8
6.1.3 Preparation.....	8
6.1.4 Number of test pieces.....	8
6.2 Testing machine and measuring devices.....	8
6.3 Test method.....	9
6.3.1 Test period.....	9
6.3.2 Tensile strength test.....	9
6.4 Calculation and expression of test results.....	9
6.4.1 Visual inspection.....	9
6.4.2 Handling data.....	9
6.4.3 Tensile strength retention rate.....	9
6.5 Test report.....	9
Bibliography	11

Foreword

ISO (the International Organization for Standardization) is a worldwide federation of national standards bodies (ISO member bodies). The work of preparing International Standards is normally carried out through ISO technical committees. Each member body interested in a subject for which a technical committee has been established has the right to be represented on that committee. International organizations, governmental and non-governmental, in liaison with ISO, also take part in the work. ISO collaborates closely with the International Electrotechnical Commission (IEC) on all matters of electrotechnical standardization.

The procedures used to develop this document and those intended for its further maintenance are described in the ISO/IEC Directives, Part 1. In particular, the different approval criteria needed for the different types of ISO documents should be noted. This document was drafted in accordance with the editorial rules of the ISO/IEC Directives, Part 2 (see www.iso.org/directives).

Attention is drawn to the possibility that some of the elements of this document may be the subject of patent rights. ISO shall not be held responsible for identifying any or all such patent rights. Details of any patent rights identified during the development of the document will be in the Introduction and/or on the ISO list of patent declarations received (see www.iso.org/patents).

Any trade name used in this document is information given for the convenience of users and does not constitute an endorsement.

For an explanation of the voluntary nature of standards, the meaning of ISO specific terms and expressions related to conformity assessment, as well as information about ISO's adherence to the World Trade Organization (WTO) principles in the Technical Barriers to Trade (TBT) see www.iso.org/iso/foreword.html.

This document was prepared by Technical Committee ISO/TC 71, *Concrete, reinforced concrete and pre-stressed concrete*, Subcommittee SC 6, *Non-traditional reinforcing materials for concrete structures*.

Any feedback or questions on this document should be directed to the user's national standards body. A complete listing of these bodies can be found at www.iso.org/members.html.

A list of all parts in the ISO 10406 series can be found on the ISO website.

Fibre-reinforced polymer (FRP) reinforcement of concrete — Test methods —

Part 3: CFRP strips

1 Scope

This document specifies test methods applicable to unidirectional carbon fibre-reinforced polymer (CFRP) strips as external-bonded reinforcements on the concrete substrate.

This document is applicable for the CFRP strips that:

- consist of carbon fibre and thermoset resin;
- are manufactured by pultrusion method;
- have a higher carbon fibre fraction such as over 60 %; and
- have a thickness within 3 mm.

Also, the test pieces for determining tensile properties are cut down from CFRP strips along the CFRP strips axis, and have bonded anchorage block at the both ends.

2 Normative references

The following documents are referred to in the text in such a way that some or all of their content constitutes requirements of this document. For dated references, only the edition cited applies. For undated references, the latest edition of the referenced document (including any amendments) applies.

ISO 7500-1, *Metallic materials — Calibration and verification of static uniaxial testing machines — Part 1: Tension/compression testing machines — Calibration and verification of the force-measuring system*

ISO 10406-2:2015, *Fibre-reinforced polymer (FRP) reinforcement of concrete — Test methods — Part 2: FRP sheets*

3 Terms and definitions

For the purposes of this document, the following terms and definitions apply.

ISO and IEC maintain terminological databases for use in standardization at the following addresses:

- ISO Online browsing platform: available at <https://www.iso.org/obp>
- IEC Electropedia: available at <http://www.electropedia.org/>

3.1

accelerated artificial exposure testing machine

machine that creates reproducible standard test conditions to accelerate weathering artificially

3.2

anchorage block

tab (3.6) corresponding to the test block to prevent bond failure of the CFRP strips

3.3 anchorage portion

end parts of a test piece fitted with anchoring devices to transmit loads from the testing machine to the test portion

3.4 Young's modulus

E_f
elastic modulus in the direction of the fibres

3.5 strip

flat board which has thin thickness compared to width, a flatness-formed rectangular section and stretches in the longitudinal direction

3.6 tab

plate made of fibre-reinforced polymer, aluminium, or any other suitable material bonded to the test piece to transmit loads from the testing machine to the test portion

3.7 tensile capacity

F_u
maximum tensile load which the test piece bears during the tensile test

3.8 tensile strength retention rate

R_{ett}
ratio of the tensile strength after accelerated artificial exposure compared with tensile strength before accelerated artificial exposure

4 Symbols

For the purposes of this document, the symbols presented in [Table 1](#) apply.

Table 1 — Symbols

Symbol	Unit	Description	Reference
A	mm ²	Cross-sectional area	5.4.3 , 5.4.4
D_{tab}	°	Tab bevel angle	5.1.1
E_f	N/mm ²	Young's modulus	5.4.4
f_{fu}	N/mm ²	Tensile strength	5.4.3
f_{fu0}	N/mm ²	Average value for tensile strength before accelerated artificial exposure	6.4.3
f_{fu1}	N/mm ²	Average value for tensile strength after accelerated artificial exposure	6.4.3
F_u	N	Tensile capacity	5.4.3
L_{A1}	mm	Anchorage length	5.1.1
t_A	mm	Anchorage thickness	5.1.1
L_{A2}	mm	Anchorage portion length	5.1.1
b_{test}	mm	Width at the range of the test length	5.1.1
L_{test}	mm	Test length	5.1.1
t_{test}	mm	Thickness	5.1.1
L_{tot}	mm	Total length	5.1.1
R_{ett}	%	Tensile strength retention rate	6.4.3
ΔF	N	Difference between loads at 2 points at 20 % to 50 % tensile capacity	5.4.4

Table 1 (continued)

Symbol	Unit	Description	Reference
$\Delta\varepsilon$	—	Difference between strains at 2 points at 20 % and 50 % tensile capacity	5.4.4

5 Test method for determining tensile properties

5.1 Test pieces

5.1.1 Dimensions

The shape and dimensions of test pieces are given in Figure 1 and Table 2. Test pieces shall be prepared in accordance with the method described in 5.1.2. In case the width of the CFRP strips is 10 mm or less, the width of the test piece shall be equal to the width of the CFRP strips.

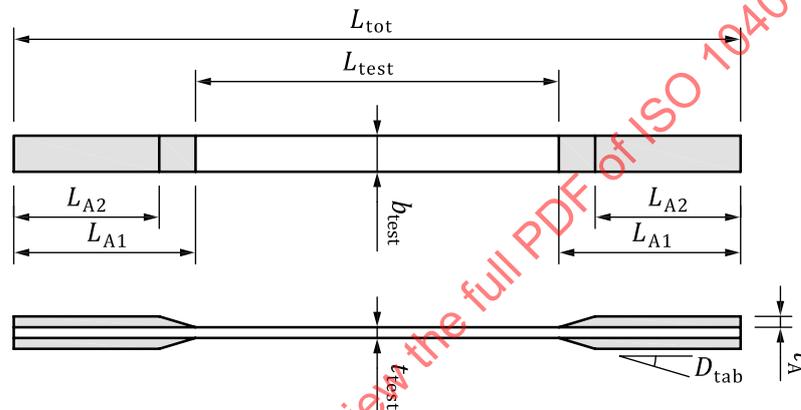


Figure 1 — Shape of the test piece

Table 2 — Dimensions of the test piece

Symbol	Dimensions of test piece	mm
L_{tot}	Total length	≥ 200
b_{test}	Width at the range of the test length ¹⁾	10 to 15
t_{test}	Thickness	≤ 3
L_{test}	Test length	≥ 100
L_{A1}	Anchorage length	≥ 50
t_A	Anchorage thickness	0,5 to 2
L_{A2}	Anchorage portion length	≥ 50
D_{tab}	Tab bevel angle ²⁾	5 to 90°

¹⁾ The width of the test piece can be selected to evaluate material characteristics stably and properly, using a test machine with a capacity of 100 kN or less.


²⁾ Tab bevel angle is recommended to apply 90°.

5.1.2 Preparation

Test pieces shall be prepared using the following method.

- Prepare plate cut to a predetermined length from the CFRP strips for tensile test.

- b) Grind the substrate of anchorage portions of CFRP strips and anchorage block by sandpaper, sand blaster or equivalent.
- c) Paste adhesive on the substrate of anchorage portions of CFRP strips and anchorage block. Also, adhesive shall have sufficient tensile shear bonding strength to keep tensile load during tensile test.
- d) Bond and set up the anchorage to the anchorage portions to form the test pieces, and cure until adhesive hardens.
- e) Draw a marking line along the CFRP strips axis at the position which is approximately 5 mm from edge of CFRP strips and marking lines on both ends of test pieces as shown in [Figure 2](#).
- f) Cut off along the markings.
- g) Cut out test pieces in accordance with cutting accuracy described in [5.1.4](#).
- h) Also, in case of using aluminium tab, tab shall be bonded after cutting out test pieces.

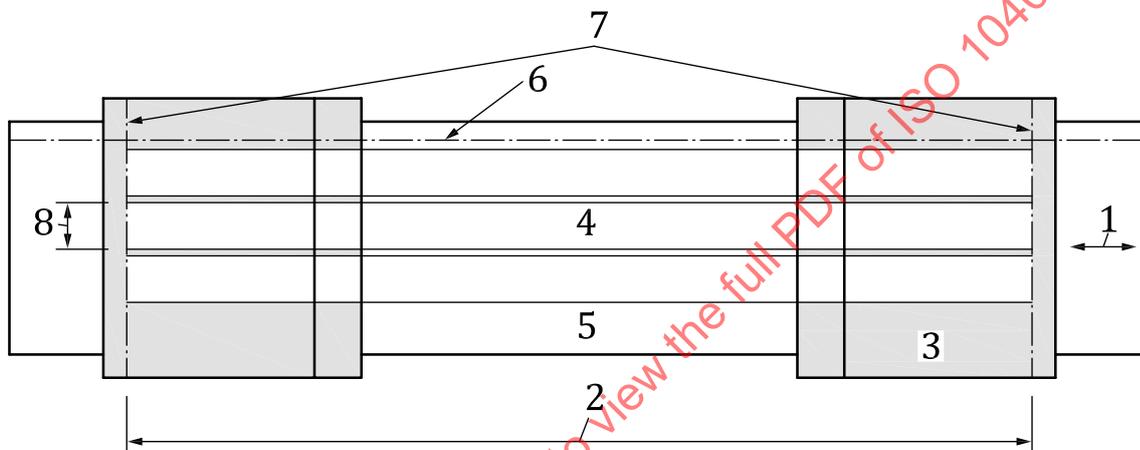

Key

- 1 direction of fibre axis
- 2 section used to prepare test piece: ≥ 200 mm
- 3 tab
- 4 test piece portion
- 5 CFRP strip
- 6 marking line along to CFRP strips axis
- 7 marking lines of both ends of test pieces
- 8 width of test piece

Figure 2 — Dimensions of plate used to prepare test pieces

5.1.3 Cutting equipment

Diamond blades or other equipment blades shall be used for cutting the test pieces.

5.1.4 Cutting accuracy for width of test piece

The cutting accuracy of the width of test pieces shall be within ± 1 mm per 100 mm in axial direction.

5.1.5 Number of test pieces

Determine the number of test pieces suitable for the objective of the test. It shall be no fewer than five.

5.2 Testing machine and measuring devices

5.2.1 Testing machine

The testing machine shall conform to ISO 7500-1. The testing machine shall have a loading capacity in excess of the tensile capacity of the test piece and shall be capable of applying loading at the required loading rate.

5.2.2 Strain gauges/extensometers

- a) Strain gauges/extensometers used to measure the elongation of the test piece under loading should be capable of recording all variations in the test length or elongation during testing with a strain measurement accuracy of at least 10×10^{-6} .
- b) When sanding is used to mount strain gauges on the surface of the test pieces, it shall be ensured that this does not damage the test pieces.

5.3 Test method

5.3.1 Dimensions of test pieces

Measure the width and thickness of the test portion of the test pieces. The width and thickness of the test piece shall be determined as the minimum value of at least three readings taking from different locations at the range of the test length on the test piece. Measurements shall be taken to an accuracy of 0,01 mm.

5.3.2 Mounting of strain gauges/extensometers

Mount the strain gauges/extensometers at the centre of the test portion of the test piece to determine the Young's modulus.

5.3.3 Mounting of test piece

Mount the test piece in such a way that the long axis of the test piece coincides with the centreline between the two chucks.

5.3.4 Loading rate

The standard loading rate shall be a constant strain rate equivalent to 1 %/min to 3 %/min strain with reference to the test length.

5.3.5 Test temperature

In principle, conduct the test in the same atmosphere used for conditioning the test piece, unless otherwise agreed by the interested parties (e.g. for testing at elevated or low temperature).

5.3.6 Range of test

Perform the loading test until tensile failure and record the measurement of loads and strain continuously or at regular intervals at least up to two third of tensile capacity.

5.4 Calculation and expression of test results

5.4.1 General

Results obtained from the test pieces fractured by explosive failure or splitting failure (see [Table 3](#)) can be used. The test results from test pieces that show tensile failure or slippage at the anchorage portion

shall be omitted and additional tests shall be carried out using test pieces from the same lot until the number of test pieces is not less than the prescribed number.

Table 3 — Typical failure mode

Failure mode	Explanation
Explosive (applicable)	<p>This shows failure like blooming in the test portion. CFRP strip of high strength type tends to show the explosive failure.</p> 
Splitting (applicable)	<p>This shows failure like bamboo breaking in the test portion. CFRP strip of high modulus type tends to show the splitting failure.</p> 
Slippage in the anchorage portion (not applicable)	<p>This shows CFRP slipping at anchorage portion. Tensile strength tends to be smaller than that of above failures.</p> 
Partial breaking (not applicable)	<p>This shows partial breaking of CFRP due to partial de-bonding at anchorage portion. Tensile strength tends to be smaller than that of above failures.</p> 

5.4.2 Load-strain curve

When strain gauges/extensometers are mounted, plot a load-strain curve depicting the relationship between the measured load and strain.

5.4.3 Tensile strength

Calculate the tensile strength, f_{fu} , expressed in newtons per square millimetres and rounded off to three significant digits in accordance with ISO 80000-1, using [Formula \(1\)](#):

$$f_{fu} = \frac{F_u}{A} \tag{1}$$

where

F_u is the tensile capacity, expressed in newtons;

A is the cross-sectional area of the test piece, expressed in square millimetres.

5.4.4 Young's modulus

Calculate Young's modulus, E_f , using [Formula \(2\)](#), expressed in newtons per square millimetres, and rounded off to three significant digits in accordance with ISO 5725 (all parts).


$$E_f = \frac{\Delta F}{A} \times \frac{1}{\Delta \varepsilon} \quad (2)$$

where

ΔF is the difference between loads at 2 points at 20 % and 50 % tensile capacity (F_{20} and F_{50} in [Figure 3](#)), expressed in newtons;

$\Delta \varepsilon$ is difference between strains at two points above (ε_{20} and ε_{50} in [Figure 3](#));

A is the cross-sectional area of the test piece, expressed in square millimetres.

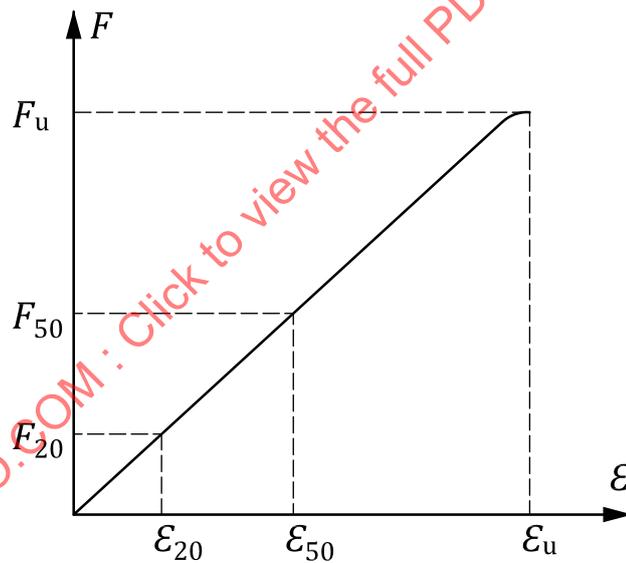

Key

F tensile load

F_u tensile capacity

F_{20} 20 % tensile capacity

F_{50} 50 % tensile capacity

ε strain

ε_u strain at tensile capacity

ε_{20} strain at 20 % tensile capacity

ε_{50} strain at 50 % tensile capacity

Figure 3 — Load-strain curve

5.5 Test report

The test report shall include the following items.

- a) name of CFRP strips and name of product;
- b) type of CFRP strips;
- c) date of manufacture, lot number of production run;
- d) name of manufacturer and symbol of manufacturer;
- e) test date, test temperature, and loading rate;
- f) dimensions of each test piece and calculated cross-sectional area;
- g) tensile strength of each test piece and average and, if required, the standard deviation for these values;
- h) Young's modulus of each test piece and average and, if required, the standard deviation for these values.

6 Test method for exposure to laboratory light sources

6.1 Test pieces

6.1.1 Test plate for accelerated artificial exposure test

Test plate for accelerated artificial exposure test shall be prepared by cutting to a length that can be mounted in the accelerated artificial exposure test sample holder.

6.1.2 Number of test plates

Subject no fewer than two test plates to accelerated artificial exposure tests simultaneously, unless otherwise agreed by the interested parties.

6.1.3 Preparation

Cut the test pieces from the test plate that has undergone accelerated artificial exposure and prepare the test pieces as specified in 5.1. Making test pieces, avoid the edge of the test plate.

6.1.4 Number of test pieces

Determine the number of test pieces suitable for the objective of the test. It shall be no fewer than five.

6.2 Testing machine and measuring devices

6.2.1 Accelerated artificial exposure testing machine specified in ISO 10406-2:2015, 10.2, shall be used.

6.2.2 Two types of accelerated artificial exposure testing machine are available:

- type WV, using an ultraviolet carbon-arc lamp; and
- type WS, using a sunshine carbon-arc lamp.

6.2.3 The configuration of the light source, filter, and testing machine specified in ISO 4892 (all parts) is recommended.