
**Resistance welding — Peel and chisel
testing of resistance spot and projection
welds**

*Soudage par résistance — Essais de pelage et de déboutonnage au
burin appliqués aux soudures par résistance par points et par bossages*

STANDARDSISO.COM : Click to view the full PDF of ISO 10447:2006



PDF disclaimer

This PDF file may contain embedded typefaces. In accordance with Adobe's licensing policy, this file may be printed or viewed but shall not be edited unless the typefaces which are embedded are licensed to and installed on the computer performing the editing. In downloading this file, parties accept therein the responsibility of not infringing Adobe's licensing policy. The ISO Central Secretariat accepts no liability in this area.

Adobe is a trademark of Adobe Systems Incorporated.

Details of the software products used to create this PDF file can be found in the General Info relative to the file; the PDF-creation parameters were optimized for printing. Every care has been taken to ensure that the file is suitable for use by ISO member bodies. In the unlikely event that a problem relating to it is found, please inform the Central Secretariat at the address given below.

STANDARDSISO.COM : Click to view the full PDF of ISO 10447:2006

© ISO 2006

All rights reserved. Unless otherwise specified, no part of this publication may be reproduced or utilized in any form or by any means, electronic or mechanical, including photocopying and microfilm, without permission in writing from either ISO at the address below or ISO's member body in the country of the requester.

ISO copyright office
Case postale 56 • CH-1211 Geneva 20
Tel. + 41 22 749 01 11
Fax + 41 22 749 09 47
E-mail copyright@iso.org
Web www.iso.org

Published in Switzerland

Foreword

ISO (the International Organization for Standardization) is a worldwide federation of national standards bodies (ISO member bodies). The work of preparing International Standards is normally carried out through ISO technical committees. Each member body interested in a subject for which a technical committee has been established has the right to be represented on that committee. International organizations, governmental and non-governmental, in liaison with ISO, also take part in the work. ISO collaborates closely with the International Electrotechnical Commission (IEC) on all matters of electrotechnical standardization.

International Standards are drafted in accordance with the rules given in the ISO/IEC Directives, Part 2.

The main task of technical committees is to prepare International Standards. Draft International Standards adopted by the technical committees are circulated to the member bodies for voting. Publication as an International Standard requires approval by at least 75 % of the member bodies casting a vote.

Attention is drawn to the possibility that some of the elements of this document may be the subject of patent rights. ISO shall not be held responsible for identifying any or all such patent rights.

ISO 10447 was prepared by Technical Committee ISO/TC 117, *International Institute of Welding*, recognized as an international standardizing body in the field of welding in accordance with Council Resolution 42/1999.

This second edition cancels and replaces the first edition (ISO 10447:1991), which has been technically revised.

Requests for official interpretations of any aspect of this International Standard should be directed to the ISO Central Secretariat, who will forward them to the IIW Secretariat for an official response.

Resistance welding — Peel and chisel testing of resistance spot and projection welds

1 Scope

This International Standard specifies the procedure and recommended tooling to be used for testing resistance spot and projection welds by means of peel and chisel tests. It applies to welds made in two or more sheets in the thickness range of 0,5 mm to 3,0 mm.

The aim of these tests is to determine:

- weld size and failure type when the tests are used as destructive tests, and
- verification of welds when the tests are used as non-destructive tests.

NOTE In the previous edition of this International Standard, seam welds were included. The preferred method of peel testing seam welds (mechanized peel testing) is now covered in ISO 14270.

2 Normative references

The following referenced documents are indispensable for the application of this document. For dated references, only the edition cited applies. For undated references, the latest edition of the referenced document (including any amendments) applies.

ISO 14270, *Specimen dimensions and procedure for mechanized peel testing resistance spot, seam and embossed projection welds*

ISO 14329, *Resistance welding — Destructive tests of welds — Failure types and geometric measurements for resistance spot, seam and projection welds*

3 Terms and definitions

For the purposes of this document, the terms and definitions given in ISO 14329 and the following apply.

3.1 chisel test

destructive or non-destructive test in which welds are tested by applying a predominantly tensile force that results in stresses primarily normal to the surface of the joint interface

NOTE The force is applied using a chisel (see Figure 1).

3.2 peel test

destructive test in which welds are tested by applying a peel force that results in stresses primarily normal to the surface of the joint interface

NOTE The test can be accomplished either manually [see Figure 2 a)], or it can be mechanized using a tensile testing machine or other suitable mechanized equipment [see Figure 2 b)].

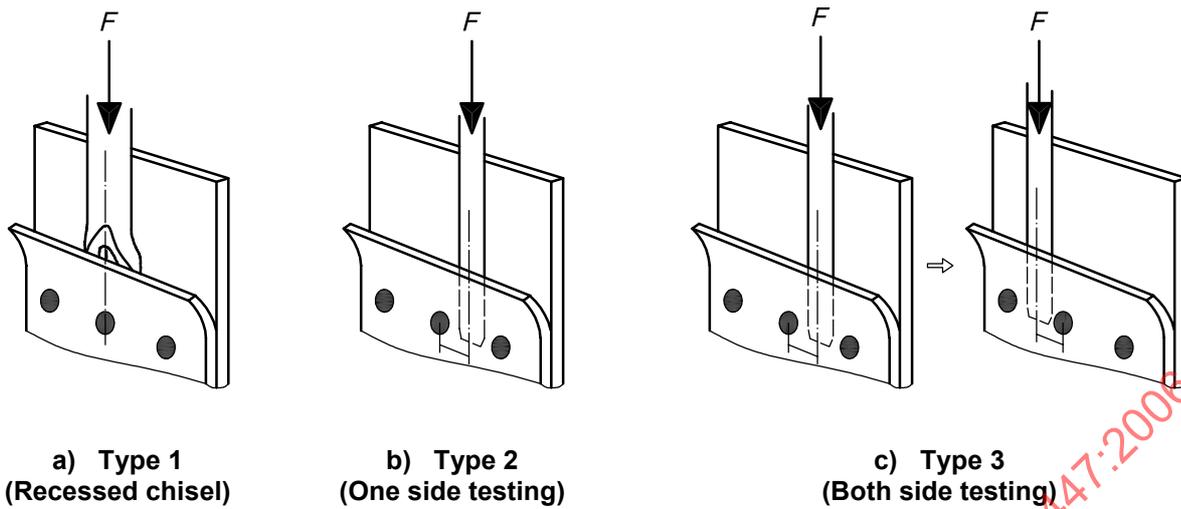


Figure 1 — Chisel routine test on resistance spot and protection welded joints

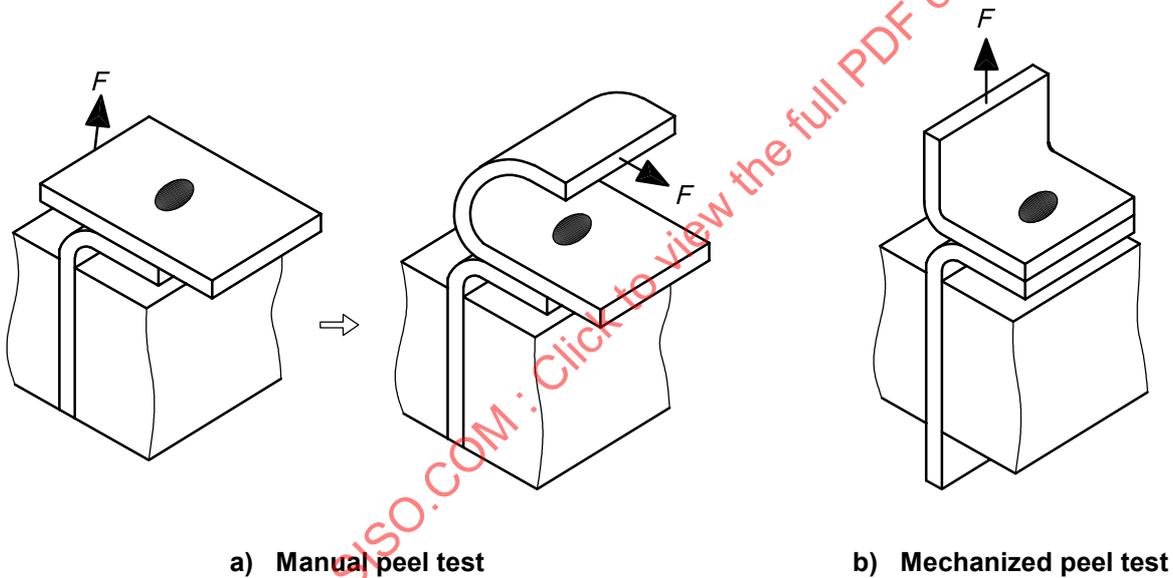


Figure 2 — Peel routine test on resistance spot and protection welded joints

4 Test specimens

When used for quality control in production, tests shall be conducted on actual components or specimens taken from actual components.


When used for setting welding parameters, where it is not practicable to use actual components, separate welded test pieces may be used. The test pieces shall be produced from the same material as used for the component, and welded under conditions adapted to simulate and produce the same weld quality as observed in the component. The effects of different shunt or impedance conditions should be taken into account when producing the test pieces, by inserting sufficient material in the throat of the machine to approximate the magnetic effect of the work piece under production conditions.

5 Test procedure


5.1 Chisel test

A chisel shall be used to separate the sheets adjacent to the weld under test. Typical chisel designs are shown in Figures 3 and 4. The chisel geometry should be chosen based on the work piece thickness and geometry, weld diameter, distance between welds, and whether the weld is to be destructively or non-destructively tested (see Table 1).

Dimensions in millimetres

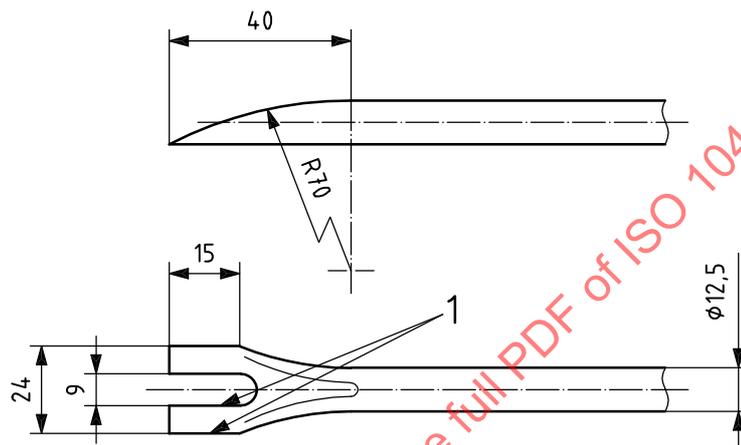

a) Chisels for weld diameter < 8 mm

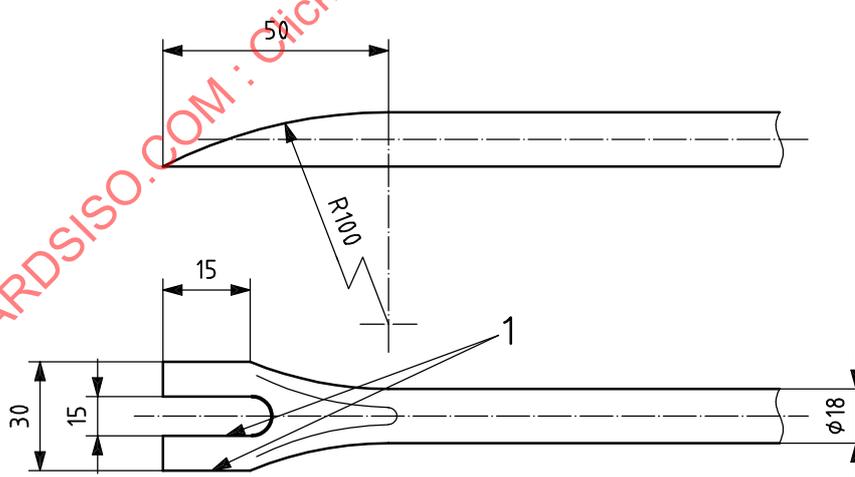


b) Chisels for weld diameter < 13 mm


Key

- 1 Burr to be removed from all corners

Figure 3 — Typical dimensions of chisels

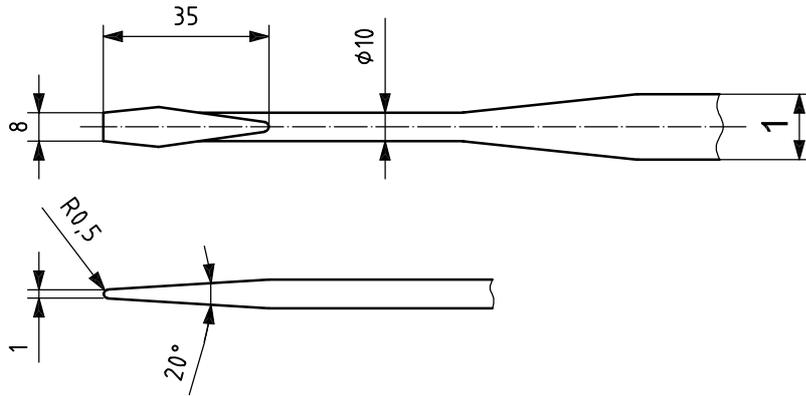

a) Chisel of type 2-1 (for thickness ≤ 2 mm)

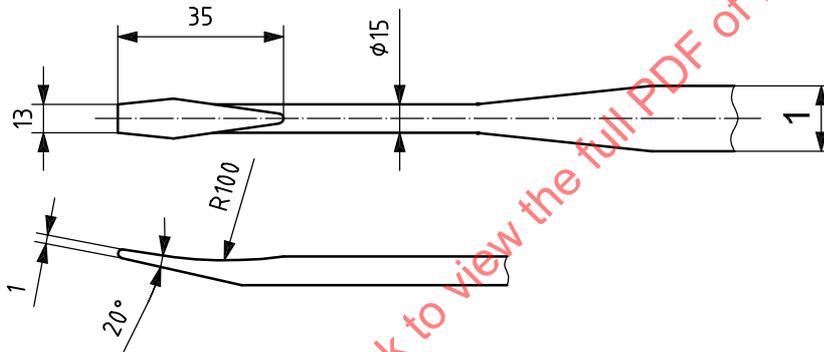

b) Chisel of type 2-2 (for thickness > 2 mm)

Key

1 arbitrary value

Figure 4 — Examples of dimensions of chisels for non-destructive test

Table 1 — Selection of recommended chisels for chisel testing

Chisel design	Test types (Destructive or non-destructive)	For testing	
		Weld diameter <i>D</i> mm	Plate thickness <i>t</i> mm
Figure 3 a)	Both	$D < 8$	—
Figure 3 b)	Both	$D < 13$	—
Figure 4 a)	Non destructive	—	$t \leq 2,0$
Figure 4 b)	Non destructive	—	$t > 2,0$

The slot in the chisels shown in Figure 3 is only necessary if the axis of the chisel is placed at the centre of the weld.

Normally, the chisel is driven between the sheets manually by a hammer or a pneumatic tool.

NOTE In chisel testing, the results can be influenced by the following factors:

- a) chisel shape – dimensions and condition,
- b) hammer type – mass and type of blow,
- c) test specimen – sheet thickness,
- d) position of the weld in relation to the sheet and its edge,
- e) position of the chisel relative to the weld, and
- f) insertion depth of chisel.

Before a chisel test is implemented in production for non-destructive testing, the effectiveness of this test shall be verified with destructive tests. The chisel test for non-destructive testing should be used with considerable caution, especially when used with high strength steels. Joint design and material thickness may also influence the results.

For the destructive test, a chisel shall be driven between the sheets and adjacent to the weld until fracture occurs in or adjacent to the weld, or until severe deformation occurs. The aim of this test is to separate the sheets so that a weld plug or interfacial fracture occurs to allow weld size to be determined. In the case of a weld between three or more sheets, the test shall be made between each adjacent pair of sheets.


For the non-destructive test, a chisel shall be driven between the sheets and adjacent to the weld until the material yields or bends near the weld. The aim of this test is to obtain an indication that a weld has been made without causing fracture to occur in or adjacent to the weld. In the case of a weld between three or more sheets, the test shall be made between each adjacent pair of sheets. If fracture has not occurred after testing, the components shall be restored to their original shape.

5.2 Peel test


The peel test is a destructive test for determining weld size and fracture mode of a welded lap joint. The sheets near the weld shall be slowly peeled apart until all welds under test are completely fractured. A roller tool, pincers, pliers, vice, or mechanized equipment (see Figures 2 and 5) are typically used. If a roller tool is used, a diameter of 30 mm is recommended for sheet thicknesses up to 1 mm [see Figure 5 a)]. For testing using a vice and pliers, see Figure 5 b). For materials that are too thick or too strong to be tested manually, mechanized equipment is recommended (see ISO 14270). The applied force may be generated by means of a normal tensile testing machine or other suitable mechanized equipment.

NOTE Fracture mode and plug size can vary depending on the direction of the applied force.

Peel testing may be applied to test specimens cut from production components or welded test pieces.

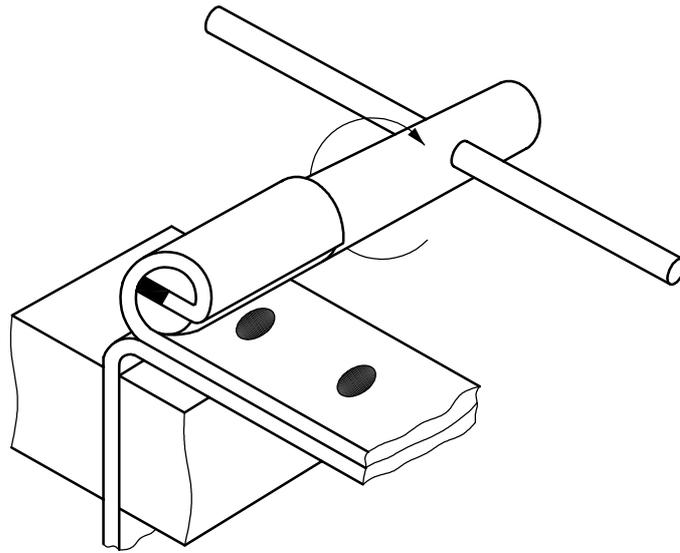

a) Example of peel testing using a vice and a roller

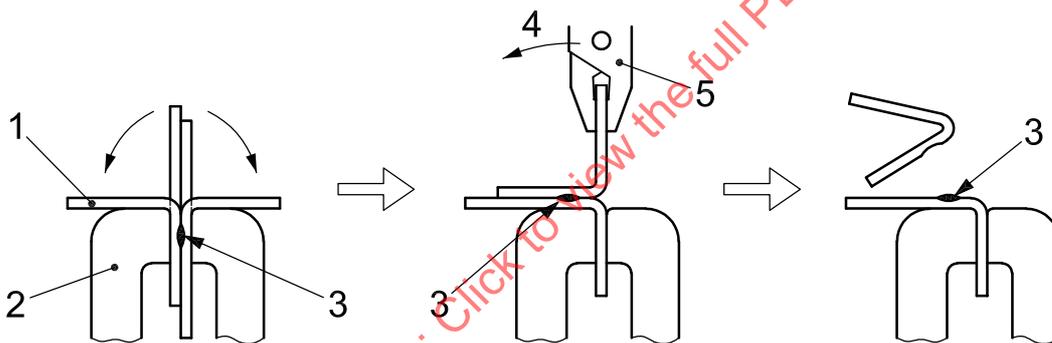

Key

- 1 test piece
- 2 vice
- 3 weld
- 4 peeling direction
- 5 pliers



b) Example using vice for peel tests

Figure 5 — Manual peel tests



5.3 Measurement of weld size

A destructive chisel test or peel test allows the measurement of the weld size and assessment of the failure type. In the case of mechanized testing, it may also be possible to measure the force at failure. Mechanized peel testing shall be performed in accordance with ISO 14270.



The maximum and minimum diameters of the weld (d_1 and d_2) shall be measured to determine the weld size [see Figures 6 and 7 b)].

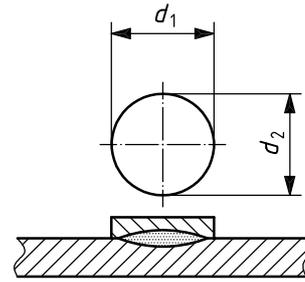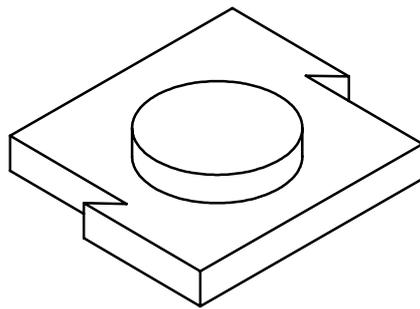

a) Symmetrical ^a

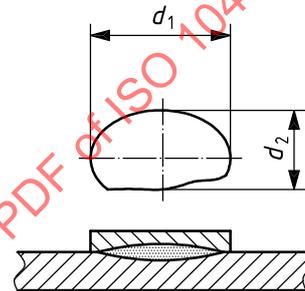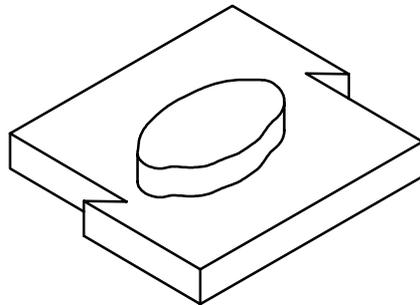

b) Asymmetrical ^a

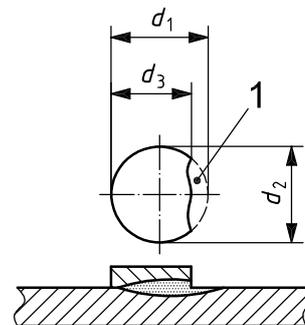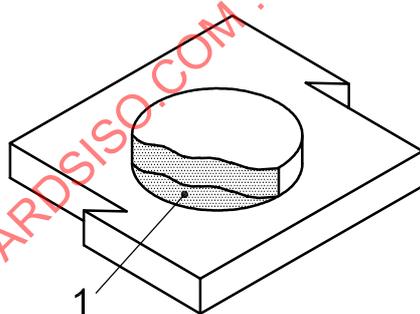

c) Partial ^b

Key

1 interfacial fracture

^a $d = d_p = (d_1 + d_2)/2$.

^b $d = (d_1 + d_2)/2$ and
 $d_p = (d_2 + d_3)/2$.

Figure 6 — Weld with plug failure