

INTERNATIONAL
STANDARD

ISO
12206

First edition
1995-02-01

**Photography — Methods for the
evaluation of the effectiveness of chemical
conversion of silver images against
oxidation**

*Photographie — Méthodes d'évaluation de l'efficacité de la conversion
chimique des images argentiques contre l'oxydation*



Reference number
ISO 12206:1995(E)

Contents

	Page
1 Scope	1
2 Normative references	1
3 Definitions	1
4 Dichromate bleach test	1
5 Hydrogen peroxide incubation test	2

Annexes

A Correction of density values	7
B Variables in silver stabilizing treatments	9
C Significance of the test methods	10
D Bibliography	12

STANDARDSISO.COM : Click to view the full PDF of ISO 12206:1995

© ISO 1995

All rights reserved. Unless otherwise specified, no part of this publication may be reproduced or utilized in any form or by any means, electronic or mechanical, including photocopying and microfilm, without permission in writing from the publisher.

International Organization for Standardization

Case Postale 56 • CH-1211 Genève 20 • Switzerland

Printed in Switzerland

Foreword

ISO (the International Organization for Standardization) is a worldwide federation of national standards bodies (ISO member bodies). The work of preparing International Standards is normally carried out through ISO technical committees. Each member body interested in a subject for which a technical committee has been established has the right to be represented on that committee. International organizations, governmental and non-governmental, in liaison with ISO, also take part in the work. ISO collaborates closely with the International Electrotechnical Commission (IEC) on all matters of electrotechnical standardization.

Draft International Standards adopted by the technical committees are circulated to the member bodies for voting. Publication as an International Standard requires approval by at least 75 % of the member bodies casting a vote.

International Standard ISO 12206 was prepared by Technical Committee ISO/TC 42, *Photography*.

Annex A forms an integral part of this International Standard. Annexes B, C and D are for information only.

STANDARDSISO.COM : Click to view the full PDF of ISO 12206:1995

Introduction

Silver-gelatin photographs have been used extensively for recording and preserving information of lasting value in all fields of human activity. The long-term stability of these records has become of increasing concern in recent years, because image and support degradation have been found with accelerating frequency in photographic collections and archives.

ISO has published documents on various aspects of the stability and preservation of black-and-white silver-gelatin photographic materials. ISO 10602:1995, *Photography — Processed silver-gelatin type black-and-white film — Specifications for stability*, provides test methods and criteria for the physical properties, permissible residual processing chemicals, and the image quality of films. ISO 5466:1992, *Photography — Processed safety photographic films — Storage practices*, deals with the conditions required for maintaining and preserving the integrity of photographic films during storage. ISO 10214:1991, *Photography — Processed photographic materials — Filing enclosures for storage*, pertains to the materials used in contact with stored photographic materials.

If photographic film meets the material and processing specifications of ISO 10602 and is stored in accordance with ISO 5466 and ISO 10214, excellent stability will be obtained. Similarly, photographic paper prints should be stored in accordance with ISO 6051:1992, *Photography — Processed photographic paper prints — Storage practices*, and processed photographic plates in accordance with ISO 3897:1992, *Photography — Processed photographic plates — Storage practices*.

However, in practical situations it is not always possible to control the storage conditions, particularly with respect to contaminants.

Atmospheric pollutants such as peroxides, sulfur dioxide, ozone and nitrogen dioxide are very detrimental to silver images^[1]. Such environmental pollutants are of increasing concern in our industrial society. They can cause oxidation of the silver with consequent silver migration. This results in image fading, silver mirroring and redox blemishes^[2]^[3]. Oxidizing agents that diffuse out of enclosure materials cause similar defects.

Recent studies have shown that silver images can be made resistant to oxidizing pollutants by chemically treating the silver to form silver sulfide^[4] or silver selenide^[5], or by substitution of the silver by gold^[6]. Such treatments are recommended when it is not possible to ensure the absence of contaminants, or when the importance of the image justifies the added expense.

This International Standard is an adjunct to the processing requirements and describes methods for evaluating the effectiveness of various treatments which impart greater stability to silver images.

Photography — Methods for the evaluation of the effectiveness of chemical conversion of silver images against oxidation

1 Scope

1.1 This International Standard describes methods for evaluating the effectiveness of chemical conversion treatments intended to increase the resistance of wet-processed silver images to oxidation. The treatment may be applied as part of the original processing, or it may be a post-processing treatment.

1.2 This International Standard applies to silver-gelatin images coated on to supports of either plastic, paper or glass.

1.3 It does not recommend general or specific treatments for silver images. Likewise, treatment temperature, times and replenishment rates are outside the scope of this International Standard. Factors to be considered in a stabilizing treatment are discussed in annex B.

1.4 This International Standard describes two test methods: the dichromate bleach test and the hydrogen peroxide incubation test^[7]. The significance of each is discussed in annex C.

2 Normative references

The following standards contain provisions which, through reference in this text, constitute provisions of this International Standard. At the time of publication, the editions indicated were valid. All standards are subject to revision, and parties to agreements based on this International Standard are encouraged to investigate the possibility of applying the most recent editions of the standards indicated below.

1) To be published. (Revision of ISO 5-3:1984)

2) To be published. (Revision of ISO 5-4:1983)

Members of IEC and ISO maintain registers of currently valid International Standards.

ISO 5-2:1991, *Photography — Density measurements — Part 2: Geometric conditions for transmission density.*

ISO 5-3:—¹⁾, *Photography — Density measurements — Part 3: Spectral conditions.*

ISO 5-4:—²⁾, *Photography — Density measurements — Part 4: Geometric conditions for reflection density.*

3 Definitions

For the purposes of this International Standard, the following definitions apply.

3.1 treated silver images: Silver images that have been given a specific treatment, either during or after processing, to increase their stability.

3.2 toned silver images: Silver images that have been given a specific treatment, either during or after processing, to modify their colour.

4 Dichromate bleach test

4.1 Principle

This test consists of dissolving the treated silver image and measuring the retained density. This retained density is proportional to the silver that has been chemically converted to a non-bleachable compound, or has been substituted by a non-bleachable element.

4.2 Reagents

4.2.1 Bleach solution

A bleach solution shall be prepared by dissolving 90 g of anhydrous potassium dichromate in 1 litre of water. Subsequently, 96 ml of concentrated sulfuric acid shall be slowly added with constant stirring.

WARNING — Avoid contact with the eyes, skin and clothing. Wash thoroughly after handling. In case of contact, flush eyes and skin with water. Obtain medical attention immediately.

Take care to dispose of dichromate bleach solution in accordance with national and local hazardous waste disposal regulations.

4.2.2 Clearing solution

The clearing solution shall be prepared by dissolving 100 g of sodium sulfite in 1 litre of water.

4.3 Specimen preparation

Six uniform-density patches shall be prepared on the treated silver material with densities (D) ranging in approximately equal increments from 0,1 above D_{\min} to D_{\max} . The exact size of the patches is not critical, provided they cover the aperture of the densitometer and are easy to handle.

4.4 Procedure

Measure the treated silver image on the six uniform-density patches and on D_{\min} for status A blue density. Densities shall be measured on a densitometer having spectral conformance to ISO 5-3. The densitometer shall have geometric conformance to ISO 5-2 for photographic films and plates, and geometric conformance to ISO 5-4 for photographic papers.

Then immerse the specimen in the bleach solution (4.2.1) for 30 s at $(20 \pm 5) ^\circ\text{C}$, rinse it in water for 2 s, and clear for 30 s in the clearing solution (4.2.2). Then rinse the specimen in water, dry it and re-measure the status A blue density.

4.5 Calculation

The percent density retention is calculated by dividing the blue density after bleaching by the original blue

density (after treatment but before bleaching) and multiplying by 100. Make this calculation for all six uniform-density patches.

With some photographic materials, particularly photographic paper prints, bleaching can cause an increase in the D_{\min} . The percent density retention shall be corrected for any D_{\min} increase, as shown in annex A.

4.6 Significance

The retained density is an approximation of the percentage of silver image that has been converted into substances which are not affected by oxidants or pollutants. A treatment which results in 65 % density retention or more after bleaching for all six density patches is considered a stable image³⁾.

5 Hydrogen peroxide incubation test

5.1 Principle

This test consists of exposing the treated silver images to hydrogen peroxide vapour and measuring the resultant change in density. A small change in density represents an image that is resistant to peroxides.

5.2 Reagents

5.2.1 Hydrogen peroxide, reagent grade, 2 % (m/m) solution, freshly prepared from a 30 % stock solution.

WARNING — Hydrogen peroxide is very corrosive. Caution should be used in handling hydrogen peroxide solutions. The stock solutions should be kept refrigerated in vertical vented bottles and kept away from combustibles. Gloves and protective clothing should be worn.

Take care to dispose of hydrogen peroxide solutions according to national and local waste disposal regulations.

5.2.2 Potassium chloride, saturated solution.

5.2.3 Potassium chloride, dry solid.

5.3 Apparatus

The components of the desiccator jar used to expose the test specimens to hydrogen peroxide vapour are

3) This density retention value is based on the fact that since two-thirds of the image will not be affected by oxidants, there would be no loss of information. Treatments which result in a lower percent density retention may also be very stable, depending upon the image density and the type of chemical conversion.

given in figure 1 and the assembled apparatus is shown in figure 2. It consists of the following elements.

5.3.1 Glass desiccator jar, having a nominal inside diameter of 150 mm and a capacity of 2 litres.

5.3.2 Ground plastic⁴⁾ desiccator lid, fitted with a fan.

The fan motor is attached to the top surface of the desiccator lid with the shaft going through the lid to the fan mounted on the inside surface. There shall be

four fan blades, each approximately 25 mm in length. The fan shall rotate at approximately 2 000 r/min.

5.3.3 Plastic⁴⁾ collar, which shall fit snugly inside the desiccator on which the specimens are mounted.

The collar shall be roughly 80 mm in height with an inside diameter of 135 mm and a wall thickness of approximately 7 mm. The collar shall be fitted with three baffles, each approximately 80 mm in length, 20 mm in depth, and 25 mm in width⁵⁾. A plan drawing of the collar and baffles is shown in figure 3.

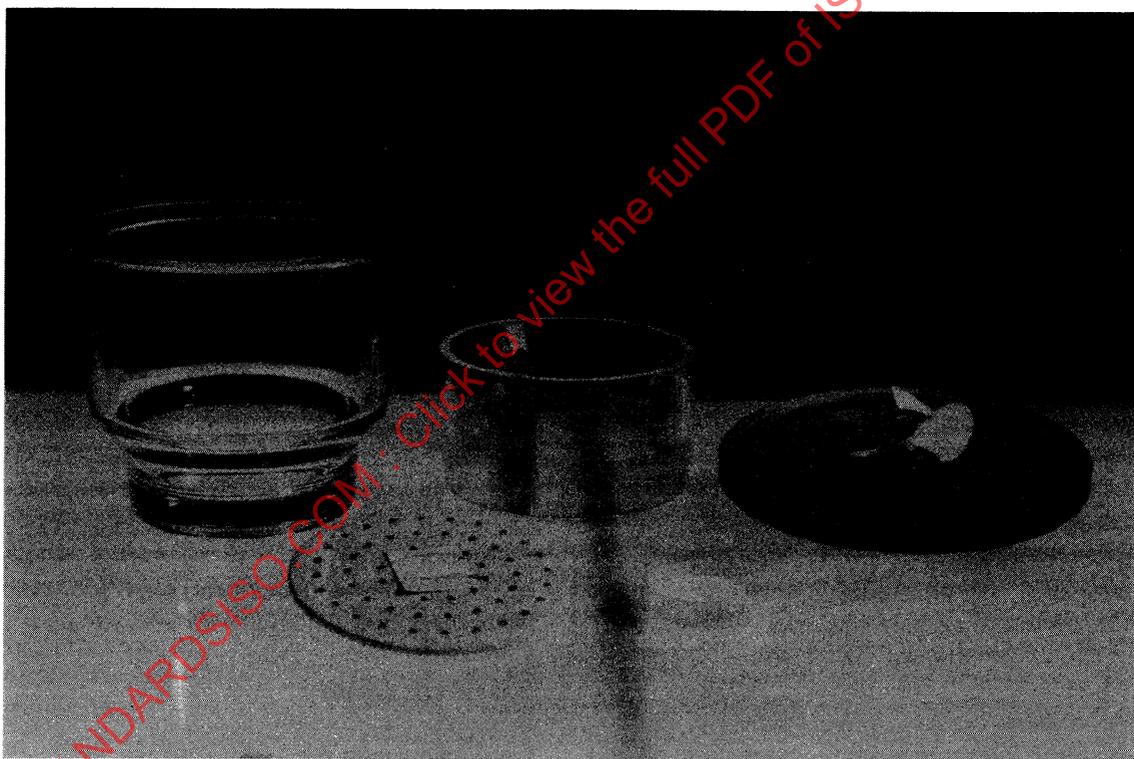


Figure 1 — Desiccator jar components

4) Poly(methyl methacrylate) has proved to be an acceptable plastic.

5) The baffles serve to provide more turbulent air movement and ensure uniform distribution of the hydrogen peroxide vapour. They may be constructed of a hydrogen-peroxide-resistant plastic, such as polycarbonate.

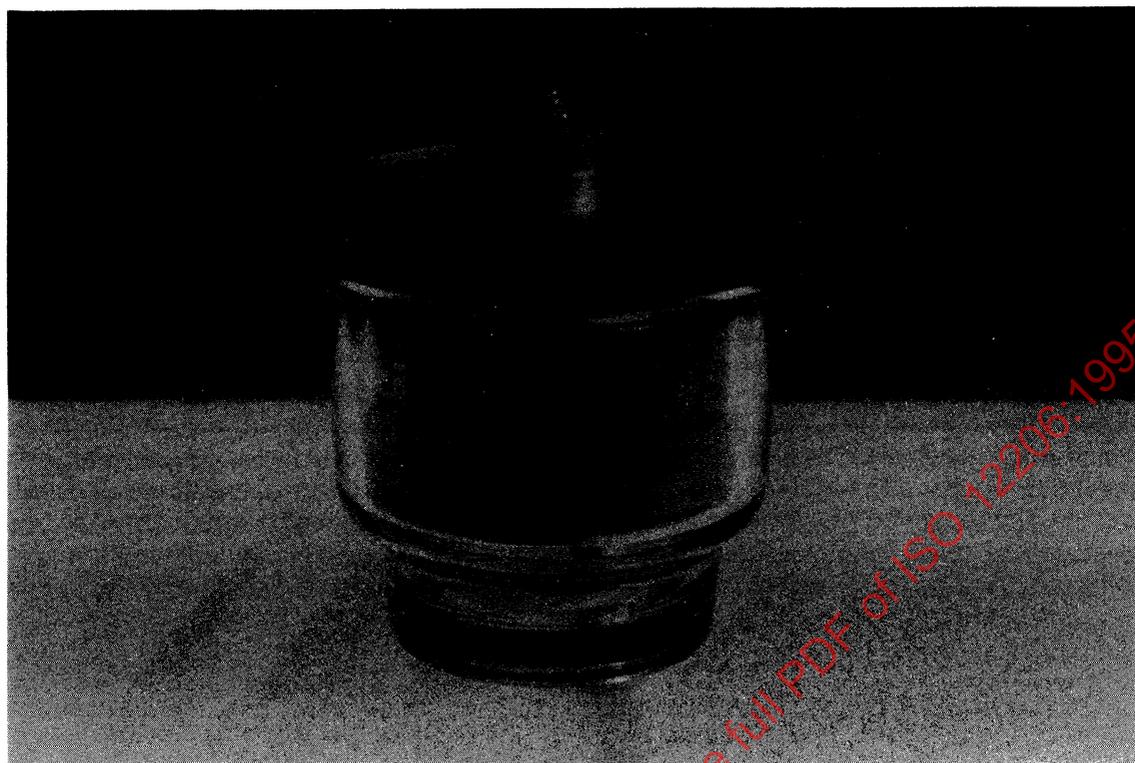


Figure 2 — Assembled desiccator jar

5.3.4 Perforated porcelain plate, of diameter 140 mm, which fits over the desiccator well.

5.3.5 Petri dish, of capacity 60 ml, which fits into the desiccator well and which holds a saturated salt solution to regulate the relative humidity.

5.3.6 Circular pad, approximately 40 mm in diameter, of 0,3 mm chromatography paper or filter paper⁶⁾, with a water flowrate of 100 mm to 150 mm per 30 min⁷⁾, which is wired to the upper side of the perforated porcelain plate with stainless steel wire.

5.3.7 Oven, fan-assisted, capable of being maintained at $50\text{ °C} \pm 2\text{ °C}$.

5.4 Specimen preparation

Six uniform-density patches shall be prepared with densities (D) ranging in approximately equal increments from 0,1 above D_{\min} to D_{\max} . The exact size of the patches is not critical, provided they cover the aperture of the densitometer and are easy to handle.

5.5 Procedure

5.5.1 Measure the status A blue density on the six uniform-density patches and on D_{\min} before treatment. Densities shall be measured on a densitometer having spectral conformance to ISO 5-3. The densitometer shall have geometric conformance to ISO 5-2 for photographic films and plates and geometric conformance to ISO 5-4 for photographic papers.

6) A suitable chromatography paper is Whatman No. 3 mm CHR paper. This information is given for the convenience of users of this International Standard and does not constitute an endorsement by ISO of the product named. Equivalent products may be used if they can be shown to lead to the same results.

7) This refers to the capillary rise of water when the paper is partially immersed in water.

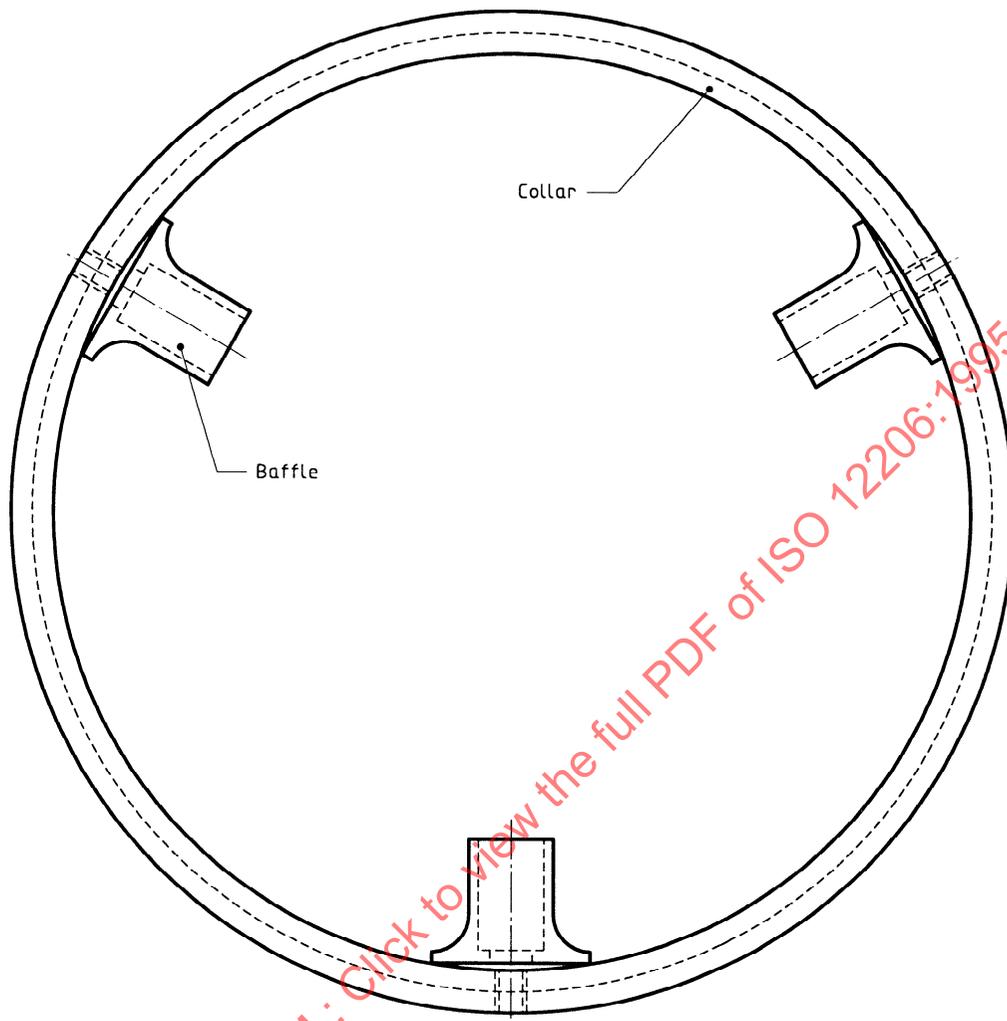


Figure 3 — Drawing of collar and baffles

5.5.2 Attach the specimens with the base side against the inside surface of the cylindrical collar⁸⁾. Take care to ensure that the specimens are snug against the collar surface.

5.5.3 Place 5 ml of a saturated solution of potassium chloride (5.2.2) in the Petri dish (5.3.5) to achieve a relative humidity of 82 %. To maintain solution saturation, add 10 g of dry potassium chloride (5.2.3) to the Petri dish.

5.5.4 Charge the desiccator by the addition of 0,12 ml of the hydrogen peroxide solution (5.2.1) to the pad of chromatography paper (5.3.6). This gives a peroxide concentration of approximately 1 000 ppm.

5.5.5 Seal the desiccator jar (5.3.1) with its cover and place it in the oven (5.3.7) set at 50 °C. The fan shall be turned on for the first 30 min to distribute the peroxide vapour uniformly.

5.5.6 Remove the jar from the oven, quickly charge it with the addition of a second 0,12 ml of freshly prepared hydrogen peroxide solution (5.2.1) without allowing the desiccator jar to cool to room temperature. Replace it in the oven set at 50 °C. Turn on the fan for a second 30 min. The desiccator jar shall then be incubated with the fan turned off for 17 h at 50 °C, resulting in a total incubation of 18 h.

5.5.7 Remove the specimens from the desiccator jar

8) If the baffles are constructed so that they are spring loaded, the specimens can be attached by inserting the edges under the baffles.

and redevelop⁹⁾ them to reduce the silver which has been ionized during the test. Then wash and dry the specimens.

5.5.8 Examine the specimens visually under $\times 10$ magnification for any evidence of red spots or redox blemishes. If there are no red spots, remeasure the specimens for status A blue density as specified in 5.5.1.

5.5.9 The change in density of the six uniform-density patches shall be corrected for the change in the D_{\min} values by subtracting the change in D_{\min} due to the treatment, as shown in annex A.

5.6 Significance

The extent to which the silver is attacked by hydrogen peroxide is evaluated by the magnitude of the change

in blue density after the peroxide incubation. This is most easily shown by a plot of the change in blue density, corrected for the change in D_{\min} , on the y -axis against the original blue density on the x -axis. The effectiveness of stabilizing treatments can be quantitatively measured by the deviation of this plot from the x -axis. A stabilizing solution which results in less than a 0,05 density change for all six uniform-density patches shall be considered to be an effective treatment against peroxides.

If the peroxide incubation results in the appearance of red spots on any of the specimens, a quantitative evaluation of the effect of the stabilizing treatment cannot be made. Therefore, such a treatment shall be considered to be not effective.

STANDARDSISO.COM : Click to view the full PDF of ISO 12206:1995

9) Redevelopment for 2 min at 25 °C in Kodak Prostar developer was found to be satisfactory for microfilms, and 30 s in Kodak Dektol developer for photographic paper prints. Developers should be at full strength. This information is given for the convenience of users of this International Standard and does not constitute an endorsement by ISO of the products named. Equivalent products may be used if they can be shown to lead to the same results.

Annex A (normative)

Correction of density values

A.1 General

The purpose of the dichromate bleach test and the hydrogen peroxide incubation test is to determine density changes in a silver image. However, changes in the D_{\min} areas caused by gelatin stain or base discoloration are outside the interest of these tests. Consequently, changes in density of the silver patches shall be corrected for changes in the D_{\min} area. This is illustrated by the examples in tables A.1 and A.2 for each test.

A.2 Dichromate bleach test

In the dichromate bleach test example shown in table A.1, the density of the 1,02 density patch decreased to 0,81 as a result of bleaching. However, there was a stain increase from 0,05 to 0,11. The net result of bleaching is different for transmission and reflection materials. For transmission, the density of the patch due to the silver is obtained by simple subtraction of the D_{\min} values. For reflection, the density of the patch due to the silver is identical to that for transmission density, except that it includes a back correction equal to one-half of the increase in the D_{\min} values. The following formula is used:

$$\begin{aligned} D_{\text{patch (corr)}} &= D_{\text{patch (after bleach)}} - D_{\min} (\text{after bleach}) + 0,5 [D_{\min} (\text{after bleach}) - D_{\min} (\text{original})] \\ &= 0,81 - 0,11 + 0,5(0,11 - 0,05) \\ &= 0,73 \end{aligned}$$

Table A.1 — Dichromate bleach test

	D_{\min}	D_{patch}	$D_{\text{patch (corr)}}$	
			Transmission	Reflection
Original	0,05	1,02	0,97	0,97
After bleaching	0,11	0,81	0,70	0,73
% Density retention	—	—	72	75

A.3 Hydrogen peroxide incubation test

As illustrated in table A.2, the value for the 0,40 density patch increased by 0,08 due to the hydrogen peroxide incubation and the D_{\min} value increased by 0,06. The effect of the peroxide vapour on the silver is corrected in the same manner as for the dichromate bleach test. The corrected density of transmission samples is obtained by simple subtraction of the D_{\min} values. For reflection samples, the following formula is used:

$$\begin{aligned} D_{\text{patch}}(\text{corr}) &= D_{\text{patch}}(\text{after test}) - D_{\min}(\text{after test}) + 0,5[D_{\min}(\text{after test}) - D_{\min}(\text{original})] \\ &= 0,48 - 0,11 + 0,5(0,11 - 0,05) \\ &= 0,40 \end{aligned}$$

Table A.2 — Hydrogen peroxide test

	D_{\min}	D_{patch}	$D_{\text{patch}}(\text{corr})$	
			Transmission	Reflection
Original	0,05	0,40	0,35	0,35
After peroxide incubation	0,11	0,48	0,37	0,40
Change due to peroxide incubation	—	—	+ 0,02	+ 0,05

Annex B (informative)

Variables in silver stabilizing treatments

The stabilizing treatments that are effective for silver images are also those that have been used for toning. In fact, the enhanced image-stability resulting from chemical treatment of the silver has been known for over a century^{[8][9]}. Chemical modification by noble metals such as gold can produce a cold or blue tone caused by some of the image silver being replaced by gold, forming an alloy of the two metals^[6]. Another type of stabilizing treatment is toning with compounds of sulfur or selenium which produce silver sulfide or silver selenide^{[4][5][9]}. Such treatments often cause a brown or sepia tone. It is therefore im-

portant to consider whether any stabilizing treatment produces an unwanted colour change in the silver image. Such changes can be evaluated by visual, red, green and blue density measurements.

A satisfactory stabilizing treatment must strike a balance between tone change of the original image, the degree of chemical conversion, unwanted stains and solution stability. Other factors to be considered are raw material costs, conversion speed, replenishment rates, toxicity, odour and the nature of effluents introduced into the waste water.

STANDARDSISO.COM : Click to view the full PDF of ISO 12206:1995

Annex C (informative)

Significance of the test methods

C.1 General

Deteriorative changes in the nature and appearance of metallic silver images over time are the result of chemical reactions which take place between the silver and a variety of contaminants. Such contaminants may be intrinsic to the photograph (for example, residual processing chemicals), or extrinsic (absorbed from the atmosphere, or from storage enclosures). Although the specific reactive species, chemical mechanisms and environmental circumstances may vary, protection of silver images against oxidation can be achieved in practice in different ways. The hydrogen peroxide fuming test and the dichromate bleach test indicate whether or not protection has been attained, by providing a surface passivation against attack by peroxides or by substantial chemical conversion of the image silver into a less easily oxidized substance.

C.2 Hydrogen peroxide fuming test

Peroxides may originate from a number of sources in the storage environment and have been identified as a major practical cause of silver-image deterioration. Attack on metallic silver by peroxides proceeds by a multistep mechanism, beginning with the catalytic decomposition of peroxide on the silver surface and the simultaneous oxidation of silver itself. The presence of adsorbed sulfide or iodide on the surface of the silver has been shown to inhibit or "poison" this initial catalytic step of the mechanism[10][11][12][13][14]. Thus, significant protection against peroxide attack can be achieved by a variety of stabilizing treatments which impart a superficial covering of silver sulfide to the image silver. Polysulfide and acidified thiourea solutions are examples of treatments which have this effect.

Because peroxides are of practical importance as a cause of deterioration, it is useful to have a reliable test method which determines the degree of peroxide resistance imparted to silver images by a stabilizing treatment. The hydrogen peroxide fuming test in this International Standard uses a relatively high concentration of peroxide, and images which do not discolour in this test have a high degree of resistance to per-

oxide attack. However, the resistance to attack demonstrated in the hydrogen peroxide fuming test is applicable only to peroxides.

C.3 Importance of the chemical conversion of silver

Good performance in the hydrogen peroxide fuming test does not necessarily indicate that a silver image will not deteriorate. Protection must also be secured against reactive species which directly oxidize metallic silver. Atmospheric ozone, nitrogen dioxide and other strong oxidants have been shown to affect silver images in spite of adsorbed surface coatings of silver sulfide[4]. Apart from direct oxidation by ozone, other pathways for corrosion exist which involve slow solubilization, migration and possible reduction of silver ions in another part of the gelatin layer[13]. In such cases, contaminants of a reducing nature or species which form complexes with silver ions can play a major role in the deterioration.

The equilibrium between metallic silver and silver ions which always exists in close proximity to image grains is disrupted when silver ions diffuse away from the grain. They may subsequently be reduced at another site or react with other species[14]. The cumulative effect of slow solubilization in this way is a gradual withering away of the original grains.

Regardless of the mechanism of oxidation, the fundamental issue is simply that the oxidation potential of silver itself is not high enough to forestall attack from real-world contaminants. Metallic silver images are not able to withstand adverse environments for long periods of time.

Stabilizing treatments to prevent oxidation of silver images by non-peroxide contaminants can therefore only be effective when they change the fundamental chemical behaviour of the image substance itself. In other words, it is necessary to convert silver chemically to a substance having a higher oxidation potential. Gold, silver sulfide and silver selenide all fit this requirement, and stabilizing treatments which achieve conversion to these substances are widely used in practice. A critical factor in the evaluation of

any such treatment is the degree to which the image is converted from silver to a less easily oxidized substance such as silver sulfide. Experiments with ozone and nitrogen dioxide atmospheres have shown that the unconverted portion of gold and polysulfide toned images is still vulnerable to attack. The extent of the conversion determines the extent of the protection in such atmospheres; the greater the conversion, the greater the resistance.

C.4 Dichromate bleach test

The dichromate bleach test specified in this International Standard is a convenient way to determine approximately the extent to which an image has been converted to a chemical form which is resistant to contaminants or slow solubilization. When little or no loss of density occurs after bleaching, the conversion of silver is nearly total. Intermediate levels of conversion can be estimated and expressed as a percentage of the original (after-treatment) density. Conversion levels of less than 100 % mean that some of the image remains as metallic silver, and thus the unconverted portion can be vulnerable to peroxide or other oxidants. Because 100 % conversion is not always practical or aesthetically desirable (significant colour changes may result when images are converted), intermediate conversion levels are often used in practice.

This explains why the two tests do not necessarily correlate. For example, an image with a high conversion to silver selenide, as determined in the bleach test, may still discolour in the peroxide test due to oxidation of the unconverted silver. Likewise, an image with a lower conversion to silver sulfide in the bleach test may show complete protection in the peroxide test due to surface passivation.

The question of what intermediate degree of conversion constitutes a stable image is a matter of individ-

ual judgement. Experience indicates that a satisfactory print or duplicate microfilm can be made from a treated and bleached film which has approximately 65 % residual blue density after bleaching. This represents an "insurance image" which is resistant to all oxidants. Images meeting this requirement can be considered to be stable, though the unconverted silver may still deteriorate to some extent in adverse environments. In applications where no loss of the information content of images is desired (i.e. where the highest achievable stability is the objective), conversion levels as high as possible are advised.

C.5 Conclusions

The two test methods in this International Standard measure different and complementary aspects of silver-image stability. The hydrogen peroxide fuming test relates to one specific oxidant type (peroxides) and is a yes/no determination of protection against that species of atmospheric contaminant only. Treated images which discolour in the peroxide test cannot be considered stable in an oxidizing environment. However, lack of discoloration in the peroxide test does not guarantee stability against a variety of other oxidizing contaminants. This can only be achieved by chemical conversion of image silver to a less easily oxidized substance. When a treated image retains 65 % or more of its original density after the dichromate bleach test and does not discolour in the peroxide test, it is considered to be stable.

Stabilizing treatments have been formulated which are completely successful in preventing peroxide attack on silver images. This is of great practical benefit, not only because of the existence of peroxides in the atmosphere, but also because of their slow release from enclosure materials such as cardboard, paper and wood. A high degree of conversion, as indicated by a high residual density in the dichromate bleach test together with complete resistance to peroxide vapour in the hydrogen peroxide incubation test, indicates that the image can withstand any plausible degree of exposure to oxidizing contaminants.

Annex D (informative)

Bibliography

- [1] WEYDE, E. A simple test to identify gases which destroy silver images. *Photographic Science and Engineering*, **16**, July/August 1972, pp. 283-286.
- [2] HENN, R.W. and WIEST, D.G. Microscopic spots in processed microfilm: Their nature and prevention. *Photographic Science and Engineering*, **7**, September 1963, pp. 253-261.
- [3] POPE, C.I. Blemish formation in processed microfilm. *Journal of Research of the National Bureau of Standards (A)*, **72A**, May 1968, pp. 251-259.
- [4] REILLY, J.M., NISHIMURA, D.W., CUPRIKS, K.M. and ADELSTEIN, P.Z. Polysulfide treatment for microfilm. *Imaging Technology*, **17**, June/July 1991, pp. 99-107.
- [5] LEE, W.E., WOOD, B. and DRAGO, F.J. Toner treatments for photographic images to enhance image stability. *Journal of Imaging Technology*, **10**, June 1984, pp. 119-126.
- [6] HENN, R.W. and WIEST, D.G. Properties of gold-treated microfilm images. *Photographic Science and Engineering*, **10**, January/February 1966, pp. 15-22.
- [7] ADELSTEIN, P.Z., REILLY, J.M., NISHIMURA, D.W. and CUPRIKS, K.M. Hydrogen peroxide test to evaluate redox blemish formation on processed microfilm. *Journal of Imaging Technology* **17**, June/July 1991, pp. 91-98.
- [8] HARDWICH, T.F. *A manual of photographic chemistry*. 2nd edition, London, 1855, pp. 227-228.
- [9] HAIST, G. *Modern photographic processing*. Vol. 2, John Wiley, New York, 1979, pp. 95-154.
- [10] BRANDT, E.S. Mechanistic studies of silver stability. 1: Redox chemistry of oxygen and hydrogen peroxide at clean and adsorbate-covered silver electrodes. *Photographic Science and Engineering*, **28**, Jan/Feb 1984, pp. 1-12.
- [11] BRANDT, E.S. Mechanistic studies of silver stability. 2: Iodide adsorption on silver in the presence of thiosulfate and the influence of adsorbed iodide on the catalytic properties of silver toward hydrogen peroxide. *Photographic Science and Engineering*, **28**, Jan/Feb 1984, pp. 13-19.
- [12] BRANDT, E.S. Mechanistic studies of silver stability. 3: oxidation of silver from the vantage point of corrosion theory. *Journal of Imaging Science*, **31**, Sept/Oct 1987, pp. 199-217.
- [13] HENDRIKS, K.B. The stability and preservation of recorded images. In: Sturge, Walworth and Shepp (eds.). *Imaging Processes and Materials*, 8th edition, Van Nostrand Reinhold, New York, 1989, pp. 637-684.
- [14] TORIGOE, M., OHMURA, K., YAGAMI, S. and IWANO, H. *Kuroshiro shashin no choki hozonho* [A challenge in preservation of black-and-white photographic images]. Scientific Publications of the Fuji Photo Film Co., 1984, pp. 31-36.