



**International  
Standard**

**ISO 12507**

**Paper and pulp — Deinkability test  
for printed paper product mixtures  
containing woodfree printed paper**

*Papier et carton — Essai de désencrabilité de mélanges de produits  
en papier imprimés contenant du papier imprimé sans bois*

**First edition  
2025-02**

STANDARDSISO.COM : Click to view the full PDF of ISO 12507:2025

STANDARDSISO.COM : Click to view the full PDF of ISO 12507:2025



**COPYRIGHT PROTECTED DOCUMENT**

© ISO 2025

All rights reserved. Unless otherwise specified, or required in the context of its implementation, no part of this publication may be reproduced or utilized otherwise in any form or by any means, electronic or mechanical, including photocopying, or posting on the internet or an intranet, without prior written permission. Permission can be requested from either ISO at the address below or ISO's member body in the country of the requester.

ISO copyright office  
CP 401 • Ch. de Blandonnet 8  
CH-1214 Vernier, Geneva  
Phone: +41 22 749 01 11  
Email: [copyright@iso.org](mailto:copyright@iso.org)  
Website: [www.iso.org](http://www.iso.org)

Published in Switzerland

# Contents

	Page
<b>Foreword</b> .....	<b>v</b>
<b>Introduction</b> .....	<b>vi</b>
<b>1 Scope</b> .....	<b>1</b>
<b>2 Normative references</b> .....	<b>1</b>
<b>3 Terms and definitions</b> .....	<b>1</b>
<b>4 Principle</b> .....	<b>2</b>
<b>5 Equipment</b> .....	<b>3</b>
5.1 General equipment.....	3
5.2 Equipment for preparation and flotation.....	3
5.3 Equipment for specimen preparation.....	3
5.4 Equipment for analysis.....	4
<b>6 Chemicals</b> .....	<b>4</b>
<b>7 Procedure</b> .....	<b>5</b>
7.1 General.....	5
7.2 Sampling and sample preparation.....	6
7.2.1 General.....	6
7.2.2 Identification.....	7
7.2.3 Non-paper material/loose and glued inserts/insertions.....	7
7.2.4 Adhesive applications.....	7
7.2.5 Accelerated ageing.....	7
7.2.6 Breaking up of samples.....	7
7.2.7 Measurement of moisture.....	8
7.2.8 Measurement of ash content.....	8
7.2.9 Determination of the required amount of sample.....	8
7.3 Preparation of dilution water and chemicals.....	8
7.3.1 General.....	8
7.3.2 Preparation of dilution water.....	8
7.3.3 Preparation of chemicals.....	9
7.4 Pulp preparation.....	10
7.4.1 Pulping.....	10
7.4.2 pH requirement.....	10
7.4.3 Storage.....	11
7.4.4 Dilution.....	12
7.5 Flotation.....	12
7.6 Yield.....	12
<b>8 Specimen preparation</b> .....	<b>13</b>
8.1 General.....	13
8.2 Filter pads.....	13
8.3 Membrane filters.....	14
8.4 Handsheets.....	14
<b>9 Analysis</b> .....	<b>15</b>
9.1 General.....	15
9.2 Reflectance measurements.....	15
9.2.1 General.....	15
9.2.2 Reflectance factors.....	15
9.3 Filtrate darkening.....	15
9.4 Dirt particle measurement.....	15
9.4.1 Scanner.....	15
9.4.2 Procedure for dirt particle measurement.....	16
<b>10 Test report</b> .....	<b>16</b>

ISO 12507:2025(en)

<b>Annex A</b> (normative) <b>Pulping devices</b> .....	<b>18</b>
<b>Annex B</b> (informative) <b>Examples of flotation cells</b> .....	<b>19</b>
<b>Annex C</b> (normative) <b>Testing the filtration time of filter papers</b> .....	<b>20</b>
<b>Annex D</b> (informative) <b>Testing the pH of smaller sample amount</b> .....	<b>21</b>
<b>Annex E</b> (normative) <b>Threshold value determination and size classification</b> .....	<b>22</b>
<b>Bibliography</b> .....	<b>23</b>

STANDARDSISO.COM : Click to view the full PDF of ISO 12507:2025

## Foreword

ISO (the International Organization for Standardization) is a worldwide federation of national standards bodies (ISO member bodies). The work of preparing International Standards is normally carried out through ISO technical committees. Each member body interested in a subject for which a technical committee has been established has the right to be represented on that committee. International organizations, governmental and non-governmental, in liaison with ISO, also take part in the work. ISO collaborates closely with the International Electrotechnical Commission (IEC) on all matters of electrotechnical standardization.

The procedures used to develop this document and those intended for its further maintenance are described in the ISO/IEC Directives, Part 1. In particular, the different approval criteria needed for the different types of ISO documents should be noted. This document was drafted in accordance with the editorial rules of the ISO/IEC Directives, Part 2 (see [www.iso.org/directives](http://www.iso.org/directives)).

ISO draws attention to the possibility that the implementation of this document may involve the use of (a) patent(s). ISO takes no position concerning the evidence, validity or applicability of any claimed patent rights in respect thereof. As of the date of publication of this document, ISO had not received notice of (a) patent(s) which may be required to implement this document. However, implementers are cautioned that this may not represent the latest information, which may be obtained from the patent database available at [www.iso.org/patents](http://www.iso.org/patents). ISO shall not be held responsible for identifying any or all such patent rights.

Any trade name used in this document is information given for the convenience of users and does not constitute an endorsement.

For an explanation of the voluntary nature of standards, the meaning of ISO specific terms and expressions related to conformity assessment, as well as information about ISO's adherence to the World Trade Organization (WTO) principles in the Technical Barriers to Trade (TBT), see [www.iso.org/iso/foreword.html](http://www.iso.org/iso/foreword.html).

This document was prepared by Technical Committee ISO/TC 6, *Paper, board and pulps*.

Any feedback or questions on this document should be directed to the user's national standards body. A complete listing of these bodies can be found at [www.iso.org/members.html](http://www.iso.org/members.html).

## Introduction

The types and sources of paper for recycling are manifold. The most significant grades by volume are packaging products from industry, trade and households, followed by graphic papers from households and to a lesser extent from offices. These printed papers are blends of a variety of individual products. Typical blends of graphic paper for recycling recovered from households contain a high content of mechanical-pulp based fibres and a minor amount of woodfree pulp fibres. Graphic paper for recycling originating from printing and converting operations is typically rather pure and may contain just one type of paper (mechanical-pulp based or woodfree). However, paper for recycling from printing and converting, as well as special grades, constitute only a minor share of the total volume of paper for recycling. Special grades (e.g. liquid packaging or label stock release liners) often require specific treatments during recycling and/or repulping.

When the blends of paper for recycling are predominantly mechanical-pulp based offset printed papers, a simple single-loop alkaline flotation deinking step can sufficiently remove the ink colorants from the paper fibres. ISO 21993 describes a simplified test method that can be used to predict the deinkability of printed paper products under alkaline conditions. However, ISO 21993 specifies testing 100% of a printed paper product of interest, whether mechanical-pulp based or woodfree, even though the proportion of woodfree paper in a deinking mill using alkaline conditions is typically small. This can possibly lead to misleading results in that a poor assessment by ISO 21993, and any related scorecard associated with it, does not necessarily mean that a particular print product cannot be deinked when present in a mixture of post-consumer papers for recycling<sup>[1]</sup>.

There is currently no test method which looks specifically at the case of woodfree printed paper as a small portion of the total blend, where the majority of the paper is mechanical-pulp based fibre<sup>[2][3][4][5]</sup>. An alternative test method, which uses a specific mixture of mechanical-pulp based and woodfree printed paper grades, can help differentiate between inks, printed papers and ink/paper combinations.

As an adjunct to the method in ISO 21993, this document describes a method for testing the deinkability of woodfree printed papers when incorporated as a small amount in a blend with mechanical pulp based printed papers. A mixture of woodfree and mechanical pulp based printed papers is more representative of typical post-consumer recycled paper streams. This approach can also support recycled paper collection from pre-consumer sources, where the amount of different grades can be controlled in the mill recipe, e.g., if woodfree printed paper is blended in at a small amount. The method described in this document, which uses a specified blend of mechanical pulp based and woodfree printed papers, has been developed to simulate the principal process steps for ink detachment and ink removal under standardised alkaline conditions at a laboratory scale. It gives an indication on how print product mixtures will perform in an industrial deinking operation where a high percentage of the printed paper for recycling comprises mechanical pulp-based fibres.

The method described in this document is not designed to model additional or alternative process steps, such as dispersing, post-flotation, washing and bleaching. Cleaning and screening stages, which are designed to remove impurities and unwanted materials in the industrial process, are also not included in this method. An alternative deinking test method with near-neutral or neutral flotation conditions can be more representative for printed papers consisting of mostly woodfree pulp fibres. However, the near-neutral or neutral flotation conditions are not within the scope of this document.

# Paper and pulp — Deinkability test for printed paper product mixtures containing woodfree printed paper

## 1 Scope

This document specifies a basic laboratory test method for deinkability of woodfree printed paper products as a mixture under alkaline conditions by means of single stage flotation deinking and fatty acid-based collector chemistry. The woodfree printed paper product of interest is tested as a mixture containing 10 % by weight of the woodfree printed paper with the balance comprising a mixture of printed wood-containing paper.

## 2 Normative references

The following documents are referred to in the text in such a way that some or all of their content constitutes requirements of this document. For dated references, only the edition cited applies. For undated references, the latest edition of the referenced document (including any amendments) applies.

ISO 187, *Paper, board and pulps — Standard atmosphere for conditioning and testing and procedure for monitoring the atmosphere and conditioning of samples*

ISO 638 (all parts), *Paper, board, pulps and cellulosic nanomaterials — Determination of dry matter content by oven-drying method*

ISO 1762, *Paper, board, pulps and cellulose nanomaterials — Determination of residue (ash content) on ignition at 525 °C*

ISO 2469:2024, *Paper, board and pulps — Measurement of diffuse radiance factor (diffuse reflectance factor)*

ISO 2470-1, *Paper, board and pulps — Measurement of diffuse blue reflectance factor — Part 1: Indoor daylight conditions (ISO brightness)*

ISO 3689, *Paper and board — Determination of bursting strength after immersion in water*

ISO 4119, *Pulps — Determination of stock concentration*

ISO 5269-1, *Pulps — Preparation of laboratory sheets for physical testing — Part 1: Conventional sheet-former method*

ISO 5269-2, *Pulps — Preparation of laboratory sheets for physical testing — Part 2: Rapid-Köthen method*

ISO 5631-1, *Paper and board — Determination of colour by diffuse reflectance — Part 1: Indoor daylight conditions (C/2°)*

ISO 12641-1:2016, *Graphic technology — Prepress digital data exchange — Colour targets for input scanner calibration — Part 1: Colour targets for input scanner calibration*

## 3 Terms and definitions

For the purposes of this document, the following terms and definitions apply.

ISO and IEC maintain terminology databases for use in standardization at the following addresses:

- ISO Online browsing platform: available at <https://www.iso.org/obp>
- IEC Electropedia: available at <https://www.electropedia.org/>

**3.1**

**deinked pulp**

pulp obtained from printed paper products, and deinked

**3.2**

**un-deinked pulp**

pulp obtained from printed paper products, pulped with added deinking chemicals, prior to flotation

**3.3**

**stock concentration**

ratio of the oven-dry organic and inorganic mass of material that can be filtered from a stock sample to the mass of the unfiltered sample

[SOURCE: ISO 4119:1995, 2.2, modified — part of the sentence “when determined as specified in this International Standard” and Note 1 were removed.]

**3.4**

**fibre concentration**

ratio of the oven-dry mass of organic material, that can be filtered from a stock sample to the mass of the unfiltered sample

Note 1 to entry: Organic material is the total material, less its ash.

Note 2 to entry: The organic material mainly consists of cellulosic fibres and fines.

**3.5**

**fibre yield**

ratio of the oven-dry mass of organic material after flotation to the oven-dry mass of organic material before flotation

Note 1 to entry: Organic material is the total material, reduced by the oven-dry mass of its ash.

Note 2 to entry: The organic material mainly consists of cellulosic fibres and fines.

**3.6**

**rate of filtration**

time taken for a defined volume of a test fluid to pass a filter

**3.7**

**mixture of printed wood-containing paper**

mix of printed paper products: 50 % newspapers, printed with coldset offset; 25 % magazines on SC paper and 25 % magazines on LWC paper, both printed with the heatset offset process

Note 1 to entry: This definition is only applicable in the context of this document.

**3.8**

**woodfree paper**

freesheet paper  
paper having, in principle, only chemical pulp in its fibre composition

Note 1 to entry: This definition can also apply to woodfree board: board having, in principle, only chemical pulp in its fibre composition.

Note 2 to entry: "chemical pulp" is defined in ISO 4046-4

## 4 Principle

Printed papers are subjected to accelerated ageing and then pulping followed by flotation deinking under defined conditions. Pulp samples from each stage are taken and converted to dry state for characterization.

## 5 Equipment

### 5.1 General equipment

**5.1.1 Drying oven** in accordance with the ISO 638 series, capable of maintaining the air temperature at  $105\text{ °C} \pm 2\text{ °C}$ , and suitably ventilated.

**5.1.2 Analytical balance** up to 150 g with an accuracy of at least 0,001 g.

**5.1.3 Balance** up to 3 000 g with an accuracy of at least 0,1 g.

**5.1.4 Beakers.**

**5.1.5 Muffle furnace** according to ISO 1762.

### 5.2 Equipment for preparation and flotation

**5.2.1 Laboratory pulping device**, capable of pulping about 150 g to 500 g of paper products under the conditions set in [7.4.1](#). Examples of suitable devices and operating conditions are listed in [Annex A](#).

**5.2.2 Temperature-controlled water bath.**

**5.2.3 Heating plate** equipped with magnetic stirrer, or commercially available water heater.

**5.2.4 Laboratory flotation deinking cell**, (see [7.6](#) and [Annex B](#)) and – if applicable – accessories.

**5.2.5 pH meter** with an accuracy of 0,1 points.

### 5.3 Equipment for specimen preparation

**5.3.1 Pulp distribution device** (volume: 10 l).

**5.3.2 Büchner funnel.**

**5.3.3 Vacuum filtration unit** for membrane filtration with 39 mm bottom inner diameter of the funnel.

**5.3.4 Vacuum device** that can produce a pressure difference  $\geq 60\text{ kPa}$ .

**5.3.5 Filter paper:** Grammage of  $(84 \pm 4)\text{ g/m}^2$ , filtration time for deionized water  $(20 \pm 4)\text{ s}$ , tested in accordance with [Annex C](#) and wet burst strength  $> 30\text{ kPa}$  in accordance with ISO 3689.

NOTE 1 The definition of the filter paper is much stricter than in ISO 3688, because the filtrate is used for further analysis (filtrate darkening).

NOTE 2 For example, the filter paper Ahlstrom Munktell 1289<sup>1)</sup> meets these requirements.

**5.3.6 Cellulose nitrate membrane filter:** nominal  $\varnothing 50\text{ mm}$ , pore  $\varnothing 0,45\text{ }\mu\text{m}$ , white, without a grid.

---

1) Ahlstrom Munktell 1289 can be obtained at Ahlstrom Germany GmbH, Bärenstein Plant, Niederschlag 1, 09471 Bärenstein, Germany. This information is given for the convenience of users of this document and does not constitute an endorsement by ISO of the product named. Equivalent products may be used if they can be shown to lead to the same results.

**5.3.7 Standard sheet former** (model: Rapid-Köthen) with dryer, in accordance with ISO 5269-2 or conventional sheet former in accordance with ISO 5269-1.

**5.3.8 Paper cover sheets** and carrier boards in accordance with ISO 5269-2.

## 5.4 Equipment for analysis

**5.4.1 Flatbed scanner** or **camera** with the following specifications:

- optical scan resolution  $\geq 600$  dpi, equivalent to a pixel size of  $\leq 42 \mu\text{m}$ ;
- colour depth 24 bit;
- optical density  $D_{\text{MAX}} \geq 4,0$ ;
- with IT8 calibration (\*.ICM-File) in accordance with ISO 12641-1 (see also Annex E IT8 7.2 calibration) and reach a mean grey value of  $115 \pm 2$  for all fields of IT8 colour calibration sheet in accordance with [Annex E](#).

**5.4.2 Image analysis software**, such as the ones described in [Annex E](#).

**5.4.3 Colour-measuring equipment**, which meets the requirements of ISO 2470-1 and ISO 5631-1.

## 6 Chemicals

**6.1 Sodium hydroxide (NaOH)**, pro analysis, CAS<sup>2)</sup> Registry Number<sup>®</sup> 1310-73-2.

**6.2 Sodium silicate** 1,3 g/cm<sup>3</sup> to 1,4 g/cm<sup>3</sup> (38° Bé to 40° Bé).

**6.3 Hydrogen peroxide (H<sub>2</sub>O<sub>2</sub>)**, e.g. 35 %.

**6.4 Oleic acid<sup>3)</sup> (C<sub>18</sub>H<sub>34</sub>O<sub>2</sub>)**, purified, CAS # 112-80-1, with the following specifications:

- acid number: 198 to 240;
- iodine number: 92 to 100;
- linoleic acid (C18:2): max. 18 %;
- oleic acid<sup>3</sup> (C18:1): min. 72 %;
- palmitic acid (C16:0): max. 8 %;
- palmitoleic acid (C16:1): max. 1 %;
- stearic acid (C18:0): max. 4 %.

**6.5 Calcium chloride dihydrate (CaCl<sub>2</sub> · 2 H<sub>2</sub>O)**, CAS # 10035-04-8.

**6.6 Saturated aluminium sulphate solution – Al<sub>2</sub>(SO<sub>4</sub>)<sub>3</sub>.**

2) CAS Registry Number<sup>®</sup> is a trademark of the American Chemical Society (ACS). This information is given for the convenience of users of this document and does not constitute an endorsement by ISO of the product named. Equivalent products may be used if they can be shown to lead to the same results.

3) Oleic acid can be obtained at VWR Chemicals, oleic acid, purified, article no. 20447.293. This information is given for the convenience of users of this document and does not constitute an endorsement by ISO of the product named. Equivalent products may be used if they can be shown to lead to the same results.

NOTE A concentration of 330 g/l is considered as a saturated aluminium sulphate solution.

## 7 Procedure

### 7.1 General

This laboratory scale method defines the essential steps of the flotation deinking process: pulping and flotation. In order to simulate the average age of printed paper recovered from households, an accelerated ageing step is part of the procedure. The whole laboratory procedure and the accepted chemicals are shown in [Figure 1](#).

The deinkability is assessed by three main quality parameters of the deinked pulp and one important process parameter.

Quality parameters:

- luminance;
- pulp shade;
- dirt specks.

Process parameter:

- filtrate darkening.

STANDARDSISO.COM : Click to view the full PDF of ISO 12507:2025

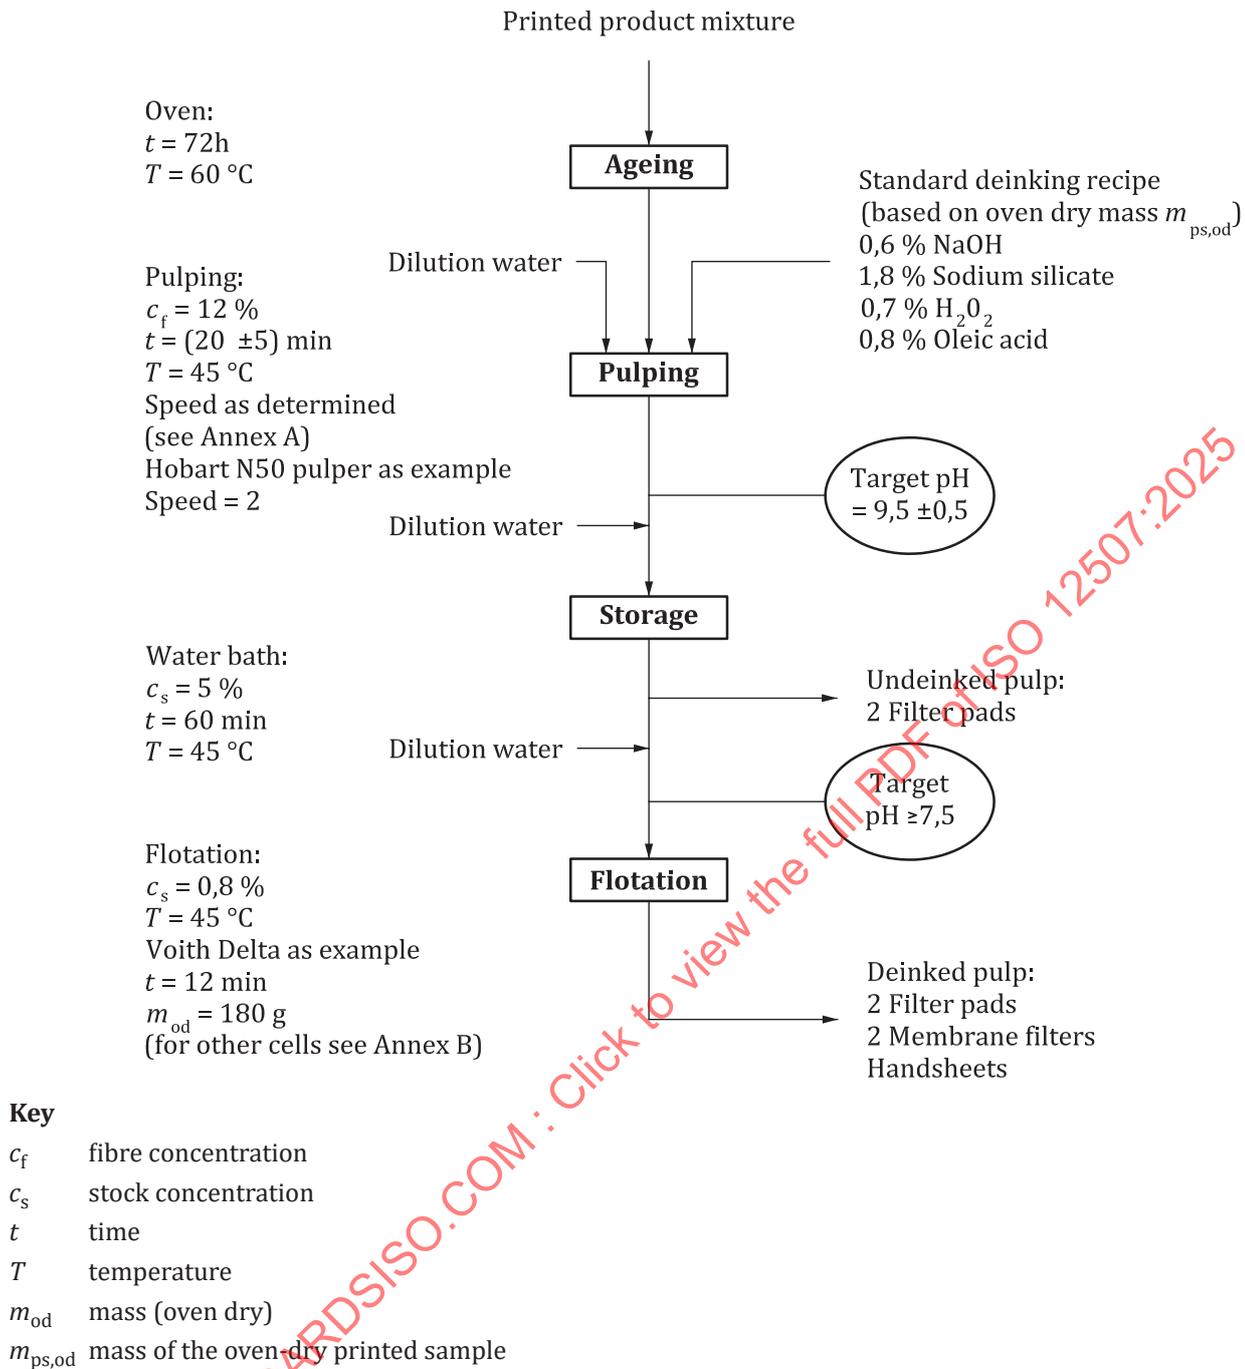


Figure 1 — Procedure for testing deinkability with standard deinking recipe

## 7.2 Sampling and sample preparation

### 7.2.1 General

Take a sample which is representative of the printed material to be tested and blend with the mixture of printed wood-containing paper as follows: 90 % of the mixture of printed wood-containing paper plus 10 % of the printed wood-free sample. The mixture of printed wood-containing paper is defined in 3.7. The recommended amount of the total mixture is 1 000 g. If available, sample also some unprinted material and

store separately for additional testing. A reference sample which comprises 90 % of the mixture of printed wood-containing paper and 10 % of unprinted wood-free paper shall also be tested.

NOTE If the same unprinted wood-free paper is not available, an unprinted wood-free paper of similar brightness can be substituted.

Other ratios of the mixture of printed wood-containing paper to the printed wood-free sample may be used, but the 90:10 ratio shall be run and reported as outlined in [Clause 10](#). It is recommended to regularly run a control test which uses 100 % of the mixture of printed wood-containing paper defined in [3.7](#). The control test results should be charted over time to monitor for any age- or source-related deviations for the key metrics that are measured as specified in [Clause 7](#) and [Clause 9](#) of this method.

### 7.2.2 Identification

Describe, if possible, full details of each printed paper in the printed material to be tested. If available, the following shall be included:

- a) identification of the wood-free printed paper product as to title, publishing company, date of issue, product category;
- b) the print process of the wood-free printed paper, printing and drying/curing parameters and press settings;
- c) the name and exact identification of inks or toner and of varnishes (if applicable) used for the wood-free printed paper;
- d) any pre- or post-treatment applied (if any);
- e) the paper grade, manufacturer and brand name, ash content of the wood-free printed paper sample.

Specify whether the printed sample contains inserts and/or supplements.

### 7.2.3 Non-paper material/loose and glued inserts/insertions

Remove any non-paper material, all inserts, glued-in inserts, stickers, sachets and similar items from the printed sample.

### 7.2.4 Adhesive applications

In order to avoid any interference with the test procedure and the results, remove any visible adhesive material – i.e. adhesives used in inserts, stickers, spines and similar – from the printed sample.

### 7.2.5 Accelerated ageing

Place the printed sample mixture in a drying oven for accelerated ageing at  $(60 \pm 3) ^\circ\text{C}$  for 72 h. Individual stacks should not contain more than 20 sheets.

NOTE 1 Accelerated ageing is necessary because the age of printed paper products can influence their deinkability. These accelerated ageing conditions correspond to 3 months to 6 months of natural ageing.

NOTE 2 If the age of the printed product is three months or higher, the accelerated ageing can be omitted. This is to be noted in the report as a deviation of the procedure.

### 7.2.6 Breaking up of samples

Tear the accelerated aged, printed mixture sample into pieces of about 2 cm × 2 cm and allow them to equilibrate with the laboratory environment.

### 7.2.7 Measurement of moisture

Determine the moisture content of the air-dry sample by testing a portion in accordance with ISO 638-1. Based on the results obtained, calculate the appropriate air-dry mass of the printed sample which corresponds to the oven-dry mass prescribed.

### 7.2.8 Measurement of ash content

Determine the ash content of the printed sample in accordance with ISO 1762. Take special care to take a representative portion of the sample if it is comprised of different paper grades with different ash contents, e.g. cover and interior part(s).

### 7.2.9 Determination of the required amount of sample

The viscosity of a pulp slurry is, among other parameters, dependent on its ash content. Low viscosity due to high ash content can result in insufficient disintegration of the sample. Therefore, the pulping procedure is defined with an oven-dry fibre concentration of 12 %. Consequently, the total amount of the printed sample for the test is not constant but has to be calculated according to its ash content (see 7.2.8) and moisture content (see 7.2.7).

Determination of the oven-dry sample mass for 200 g (oven-dry) fibre mass is calculated using [Formula \(1\)](#):

$$m_{ps,od} = \frac{100 \%}{100 \% - C_{a,ps}} \times 200 \quad (1)$$

where

$m_{ps,od}$  is the mass of the oven-dry printed sample in grams (g);

$C_{a,ps}$  is the ash content of the printed sample expressed as a percentage.

Determination of the air-dry sample mass is calculated using [Formula \(2\)](#):

$$m_{ps,ad} = m_{ps,od} \times \frac{(100 \% + C_{m,ps})}{100 \%} \quad (2)$$

where

$m_{ps,ad}$  is the mass of the air-dry printed sample in grams (g);

$m_{ps,od}$  is the mass of the oven-dry printed sample in grams (g);

$C_{m,ps}$  is the moisture content of the printed sample expressed as a percentage.

## 7.3 Preparation of dilution water and chemicals

### 7.3.1 General

All chemicals shall be dosed with a relative tolerance not exceeding  $\pm 1$  %.

### 7.3.2 Preparation of dilution water

During laboratory treatment of the printed sample (see 7.4 to 7.5), use only deionized water adjusted to a calcium hardness of 3,21 mmol/l, equivalent to 128 mg Ca<sup>2+</sup>/l.

To obtain the desired water hardness, add 472 mg/l calcium chloride dihydrate (CaCl<sub>2</sub> · 2 H<sub>2</sub>O) to deionized water. This is equivalent to 128 mg Ca<sup>2+</sup>/l.

During pulp preparation and flotation deinking, a constant temperature of  $(45 \pm 2)$  °C shall be maintained. The dilution water should therefore be stored in a temperature-controlled water bath. It is also possible to heat part of the dilution water to a considerably higher temperature by means of a water heater, successively adding cold dilution water until the desired temperature has been reached.

### 7.3.3 Preparation of chemicals

It is advisable to prepare the chemicals by mass as volume is affected by temperature. The standard deinking recipe is given in [Table 1](#).

**Table 1 — Standard deinking recipe**

Chemical	Dosage (related to oven-dry paper)
Sodium hydroxide	0,6 % (100 %) <sup>a</sup>
Sodium silicate	1,8 % (1,3 g/cm <sup>3</sup> to 1,4 g/cm <sup>3</sup> ) <sup>a</sup>
Hydrogen peroxide	0,7 % (100 %)
Oleic acid	0,8 % (100 %)

<sup>a</sup> The dosages of sodium hydroxide and of sodium silicate shall be adapted, if the pH is either too low or too high after pulping or if it is too low before flotation (see [7.4.2](#)).

Prepare of 2 000 g of deinking solution which will be sufficient for several tests. Dissolve 6 g of sodium hydroxide in approximately 600 g of deionised water, heat slowly to approximately 60 °C and proceed by adding 8 g of oleic acid. Stir until the solution is clear, then add 18 g of sodium silicate and fill up with deionised water to 2 000 g. The formation of soap reduces the alkalinity. 0,114 % of sodium hydroxide is needed to neutralise the oleic acid.

In addition, prepare 100 g of hydrogen peroxide solution for each test, using deionised cold water.

The required amount of deinking solution and of hydrogen peroxide is dependent on the sample amount used for pulping and shall be calculated individually. Do not use a deinking solution which is older than one week.

Determine of the required mass of deinking solution using [Formula \(3\)](#):

$$m_{ds} = 2 \times m_{ps,od} \quad (3)$$

where

$m_{ds}$  is the required mass of deinking solution in grams (g);

$m_{ps,od}$  is the mass of the oven-dry printed sample in grams (g).

Determine the required mass of hydrogen peroxide solution is calculated using [Formula \(4\)](#):

$$m_{H_2O_2} = 0,007 \times m_{ps,od} \quad (4)$$

where

$m_{H_2O_2}$  is the mass of hydrogen peroxide calculated with 100 % concentration in grams (g);

$m_{ps,od}$  is the mass of the oven-dry printed sample in grams (g).

## 7.4 Pulp preparation

### 7.4.1 Pulping

The total mass of material – product sample, chemicals, water – is 1 667 g. Therefore, determine the mass of dilution water using [Formula \(5\)](#):

$$m_{dw} = 1\ 667 - 100 - m_{ds} - m_{ps,ad} \quad (5)$$

where

- $m_{dw}$  is the mass of dilution water in grams (g);
- $m_{ps,ad}$  is the mass of the air-dry printed sample in grams (g);
- $m_{ds}$  is the mass of deinking solution in grams (g);
- 1 667 is the total mass of material in pulper in grams (g);
- 100 is the mass of hydrogen peroxide solution in grams (g).

Preheat the pulper with hot water in order to achieve an initial pulping temperature of  $(45 \pm 2)$  °C. Discard the water after the vessel has reached the desired temperature.

In very rare cases, the required volume of the deinking solution can be too high for the required fibre concentration. In these cases, the amount of water added during the preparation of the deinking solution should be modified to achieve the required fibre concentration.

Add the prescribed mass of printed sample to the pulper (200 g oven-dry fibres). Add the calculated amount  $m_{dw}$  of dilution water, heated to the required temperature, to the calculated amount  $m_{ds}$  of deinking solution. Add this deinking liquor into the vessel and run the pulper for a few seconds at low speed. Then stop it, brush down any scrap of paper from the vessel wall. Repeat this step as often as necessary until the sides of the vessel remain clean.

After the first stop, add the hydrogen peroxide solution (100 g). The fibre concentration is now 12 %. Immediately afterwards, pulp the stock in accordance with the instructions in [Annex A](#).

To help maintaining the required temperature and to avoid splashing losses, cover the vessel during pulping, for example with a suitably sized, tight-fitting plastic lid. In addition, a heating device may be used to maintain the required temperature.

### 7.4.2 pH requirement

The following procedure shall first be run on the reference sample which comprises 90 % of the mixture of printed wood-containing paper and 10 % of unprinted wood-free paper. The same dosages shall then be applied to the sample which comprises 90 % of the mixture of printed wood-containing paper and 10 % of the printed wood-free paper. At the end of pulping, measure the pH. For a precise measurement of pH after pulping it is necessary to create a small amount of filtrate by pressing a pulp sample.

The target pH is 9,5.

Using the standard deinking recipe described in [7.3.3 \(Table 1\)](#), the permitted range of pH is  $9,5 \pm 0,5$ . If the pH is outside this range, the sample shall be discarded and the test repeated with a modified dosage of chemicals. If the pH is too low after pulping, the dosage of the sodium hydroxide shall be increased. If the pH is too high, both sodium hydroxide and sodium silicate dosages shall be reduced by the same factor. The minimum dosage of sodium hydroxide is 0,2 %.

Beginning with an optional deinking recipe, while not proving to be in the range with the standard deinking recipe, the accepted pH is  $9,5 \pm 0,2$ .

[Figure 2](#) describes the procedure when starting with standard and optional deinking recipe.

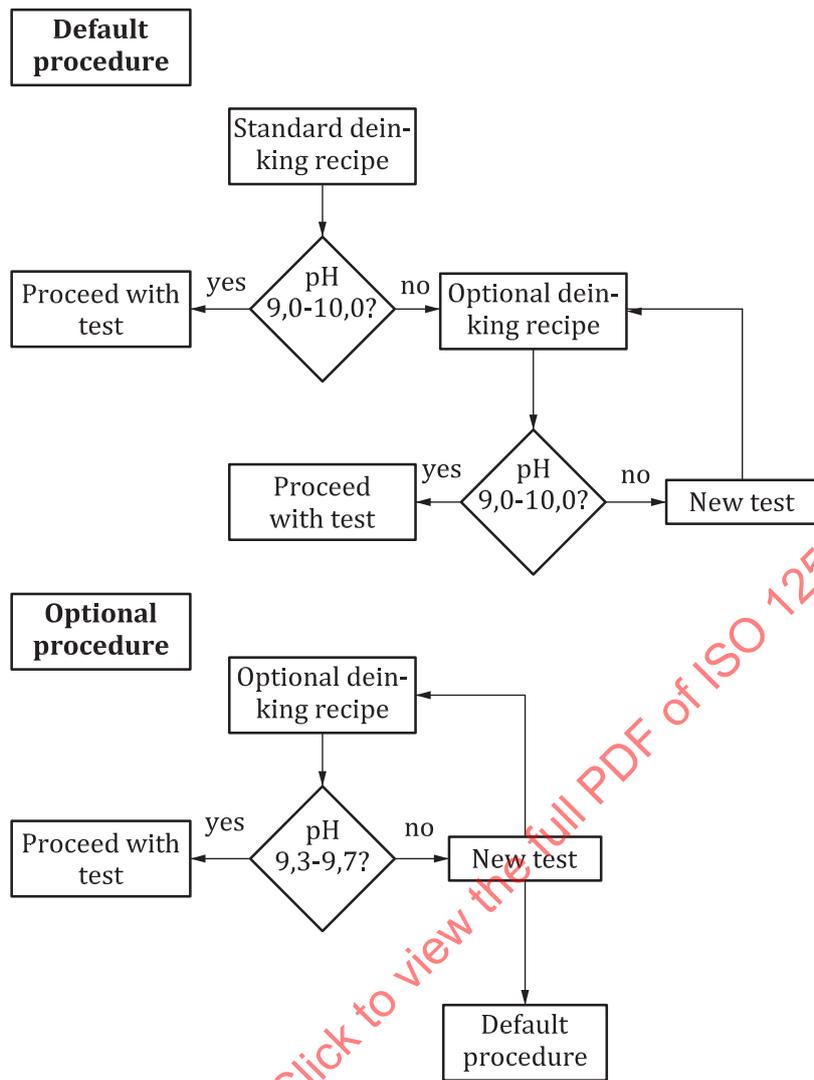


Figure 2 — Default and optional procedures with pH requirements and tolerances

[Annex D](#) describes a method to pre-test the pH after storage with a smaller sample amount. It gives an indication whether too low or too high pH have to be expected. The requirements of pH tolerances shall be fulfilled regardless of the pre-test result.

### 7.4.3 Storage

Reduce the concentration of the amount of stock required for deinking to 5 % using dilution water (7.3.2), at a temperature of  $(45 \pm 2) ^\circ\text{C}$ , and store it for 60 min in a water bath at  $(45 \pm 2) ^\circ\text{C}$ .

The amount of stock needed for the subsequent treatment steps depends on the quantities required for flotation as well as for the final handsheet and filter pad formation (see 8.2 to 8.4). Minimum stock quantities of approximately 12 g oven-dry un-deinked pulp and approximately 15 g oven-dry deinked pulp are needed.

Measure the pH at the beginning and end of the storage time. The pH can be measured with reasonable accuracy in the pulp at storage concentration. However, it is recommended that the pH at the beginning and end of the storage is measured using filtrate, without fibres in order to increase the accuracy of the measurement. This filtrate can be generated by pressing a small sieve onto the surface of the pulp. The pH electrode can then be dipped into the filtrate which forms inside the sieve.

#### 7.4.4 Dilution

After storage the stock samples shall be diluted to a stock concentration of about 1 % to terminate any relevant chemical reaction before the treatment continues. For dilution of the un-deinked pulp sample, use tap water. For dilution of the pulp sample to be deinked, use dilution water (7.3.2) with a temperature of  $(45 \pm 2)$  °C.

Measure the pH. At flotation concentration it should be equal to or higher than 7,5, provided that the defined range of the pH after pulping is met. If the pH before the flotation is below 7,5, discard the sample and repeat the test with a higher dosage of sodium hydroxide.

Start the flotation before preparing the un-deinked pulp specimens.

#### 7.5 Flotation

Heat up the cell with hot water. Pre-heat the cell with hot water close to the process temperature and then discard the water used for heating and add some of the prepared dilution water (7.3.2) of  $(45 \pm 2)$  °C to prevent the “concentrated” pulp from subsequently staying in dead corners. Determine the quantity of diluted sample required for the flotation cell used (see Annex B) and add it into the flotation cell. Add the required amount of dilution water to achieve a stock concentration of 0,8 % and proceed according to the manufacturer's instructions. The starting point for the flotation time is at which the air is introduced.

Parameters for some flotation deinking cells are available in Annex B. Set the flotation time accordingly.

If the cell is not listed in Annex B, set the stock concentration to 0,8 % at the beginning of the flotation, set the temperature to  $(45 \pm 2)$  °C and the flotation time to a value when the status of hyper-flotation is reached. The state of hyper-flotation is defined by a maximum increase of luminance of 0,3 points per minute. This shall be determined for each cell type by using a mix of printed paper products (50 % newspapers, printed with coldset offset, 25 % magazines on SC paper and 25 % magazines on LWC paper, both printed with the heatset offset process) and following the procedures described in this document.

Determine the amount of the oven-dry overflow in accordance with ISO 4119, and use this amount to calculate the overall yield and the fibre yield of the flotation. If the fibre yield is below 65 %, repeat the test with a shorter flotation time.

#### 7.6 Yield

In order to calculate yield values (overall yield and fibre yield) of the flotation, make sure to measure mass and concentration of the feed and the overflow of the flotation and the ash content of the deinked pulp.

The overall yield is calculated using Formula (6):

$$y_o = (c_{UP} \times m_{UP}) - (c_{froth} \times m_{froth}) \quad (6)$$

where

$y_o$  is the overall yield;

$c_{UP}$  is the stock concentration of undeinked pulp in %;

$m_{UP}$  is the feed mass flotation of undeinked pulp in kilograms (kg);

$c_{froth}$  is the stock concentration of overflow in %;

$m_{froth}$  is the overflow mass in kilograms (kg).

The fibre yield is calculated using [Formula \(7\)](#):

$$y_f = y_o \frac{(100 - C_{a,dp})}{(100 - C_{a,ps})} \quad (7)$$

where

$y_f$  is the fibre yield;

$y_o$  is the overall yield;

$C_{a,dp}$  is the ash content of deinked pulp expressed as a percentage;

$C_{a,ps}$  is the ash content of the printed sample expressed as a percentage.

## 8 Specimen preparation

### 8.1 General

The brightness  $R_{457}$ , the CIELab colour coordinates ( $L^*$ ,  $a^*$ ,  $b^*$  values) and the luminance  $Y$  are measured from the samples. The dirt specks particle area  $A$  is analysed using a scanner-based image analysis system. [Table 2](#) provides an overview of sample types, parameters to be measured and corresponding subclauses where more details can be found.

**Table 2 — Overview of sample types, parameters to be measured and corresponding subclause**

Sample	Specimen preparation according to subclause	Parameters
Filter pads (from pulp)	<a href="#">8.2</a>	$R_{457}$ , $L^*$ , $a^*$ , $b^*$ , $Y$
Membrane filters (from filtrate)	<a href="#">8.3</a>	$Y$ , $\Delta Y$ , $R_{457}$ , $L^*$ , $a^*$ , $b^*$
Handsheet (from deinked pulp)	<a href="#">8.4</a>	Dirt particle area $A$

For un-deinked pulp, two filter pads are required to permit an optical evaluation, and for deinked pulp, two filter pads as well as two handsheets with tap water are required to permit an optical evaluation. In addition, two membrane filter specimens are prepared from the filter pad filtrate of the deinked pulp so as to be able to assess filtrate quality.

### 8.2 Filter pads

At least two filter pads are prepared of the pulp samples respectively.

NOTE The procedure described here deviates from ISO 3688 because ISO 3688 allows too many degrees of freedom, which have an impact on the result.

The filter pad is formed using a Büchner funnel which has been covered by a moistened filter paper. The prepared filter pads shall have a basis mass of 225 g/m<sup>2</sup>. A filter paper diameter of 150 mm and a Büchner funnel diameter of 160 mm are recommended. In this case, 4,0 g oven-dry pulp material is used, and the suspension is topped up with tap water to a volume of 1 l. Other filter diameters may be used according to [Table 3](#). The diameter of the Büchner funnel corresponds to the filter diameter and should not exceed the maximum value in [Table 3](#). Usually, Büchner funnels are purchased by their nominal diameter that is identical with the filter diameter.

If a differing size of Büchner funnel and filter paper are used, the sample volume shall be adapted according to [Table 3](#). The concentration of the pulp sample remains 0,4 %.

Table 3 — Pulp volumes for Büchner funnel filtration

Diameter Büchner funnel	Diameter filter paper	Oven-dry material	Sample volume at 0,4 % stock concentration
mm	mm	g	ml
120	110	2,15	538
135	125	2,75	688
160	150	4,00	1 000
195	185	6,10	1 525

For optical assessment of the filtrate quality according to [8.3](#) and [9.3](#), collect the filtrate.

Experience has shown that the support of a thin wire made of plastic helps to avoid marks during dewatering. For this purpose, use a plastic wire with a mesh width of about 140 µm and a mesh diagonal of about 190 µm and place it under the filter paper. This option is allowed when preparing the filter pads, but not if the filtrate is analysed for filtrate darkening, because the wire can cause a small leak at the edge of the filter paper. For determination of the optical properties of the filter pad, the difference of the two ways to prepare the pads is negligible.

After filtering and carefully removing the filter paper, the wet filter pad is laid between two new paper cover sheets before drying. The paper cover sheets should not be removed from the filter pad until immediately prior to measuring the optical properties. If a Rapid-Köthen device is available (in accordance with ISO 5269-2), dry the filter pads in the integrated dryer for 10 min. If a Rapid-Köthen device is not available, dry the filter pads on a suitable hot-pressing device (e.g. photo dryer or similar) to minimize roughness of the finished filter pads. The drying temperature and time should be as low as possible to minimize yellowing effects.

### 8.3 Membrane filters

The complete filtrate obtained by dewatering the pulp for one filter pad is homogenized by shaking. 100 ml filtrate is completely drained using a cellulose nitrate membrane filter in a vacuum filtration unit. Any fibrous material found on the membrane filter can indicate that some pulp bypassed the filter paper when preparing the filter pad. In that case, discard the membrane filter as well as the filtrate and prepare a new filter pad and filtrate as described in [8.2](#).

The filtrate of two filter pads (see [8.2](#)) is filtered according to this procedure. Generally, the filtration is done without any retention aids. The result of this filtration shall be an uncoloured, clear liquid.

— Exception:

If there is still a coloured filtrate after membrane filtration, repeat the procedure with a new sample (100 ml). Add a saturated aluminium sulphate solution before membrane filtration to a pH of  $6,0 \pm 0,5$ . State in the report whether the membrane filtrate was coloured and if aluminium sulphate was used.

The membrane filters are removed from the filtration unit and dried in a desiccator.

Reference membrane filters are made in the same way but using exclusively 100 ml of tap water without pulp. Prepare a membrane filter for each test series or on at least a daily basis.

### 8.4 Handsheets

An appropriate volume of material should be taken from the pulp distribution device for each handsheet. After standard laboratory handsheet formation, dry the handsheet in such a way that the surface is as smooth as possible. In the case of Rapid-Köthen (in accordance with ISO 5269-2), dry the handsheet in the integrated dryer between carrier board and a cover sheet for 7 min. In the case of a conventional sheet former, dry the handsheet in accordance with ISO 5269-1.

The cumulative area of multiple handsheets shall be a minimum of 0,1 m<sup>2</sup> and a maximum of 0,5 m<sup>2</sup>. Within these limits, prepare enough handsheets to be able to measure 150 dirt specks or more. The oven dry grammage should amount to (42,6 ± 1,6) g/m<sup>2</sup>. In the case of Rapid-Köthen prepare two laboratory handsheets with a mass of (1,35 ± 0,05) g, related to oven-dry substance.

Protect the sheets by placing an additional sheet of paper or board on both the top and bottom of the sheet.

## 9 Analysis

### 9.1 General

The samples shall be measured with C/2° conditions while using the edge filter of 420 nm (UV filter). This applies to all reflectance measurements. The calibration for reflectance measurements shall be done in accordance with ISO 2469.

### 9.2 Reflectance measurements

#### 9.2.1 General

Prior to optical properties assessment, the prepared specimens shall be conditioned according to ISO 187.

Both sides of filter pads should be measured. Avoid measurements too near to edges, kinks or on visible non-uniformities of the filter pads.

Two samples should be measured with four measurements on each side of the un-deinked pulp and deinked pulp filter pads. Just one measurement is made on the top side of each membrane filter sample.

#### 9.2.2 Reflectance factors

Brightness is measured on the opaque filter pad according to the method described in ISO 2470-1.

The luminance  $Y$  and the CIELab colour coordinates  $L^*$ ,  $a^*$  and  $b^*$  shall be determined in accordance with the method described in ISO 5631-1 with UV cut off in accordance with ISO 2469:2024, A.6.

NOTE As an option, further reflectance factors such as  $R_{700}$  (see ISO 2469) and ERIC (see ISO 22754) can be measured.

### 9.3 Filtrate darkening

The filtrate darkening  $\Delta Y$  is the difference in luminance  $Y_{\text{filtrate}}$  of membrane filters prepared with filter pad filtrate and  $Y_{\text{reference}}$  of membrane filters prepared with tap water.

The preparation of the membrane filters is described in [8.3](#).

The luminance  $Y$  is determined (according to [9.2.2](#)) as the average value of two membrane filters each. By subtracting  $Y_{\text{filtrate}}$  from  $Y_{\text{reference}}$ , ( $\Delta Y = Y_{\text{reference}} - Y_{\text{filtrate}}$ ), all factors affecting filtrate quality and not attributable to the pulp are eliminated.

### 9.4 Dirt particle measurement

#### 9.4.1 Scanner

For the determination of the dirt particle area  $A$ , a scanner-based image analysis system is needed for optical analysis. The scanner shall be calibrated to ensure reproducibility of the measurements.

Requirements on measuring accuracy of flatbed scanner after warm-up period (see scanner manual) and under scanning conditions (see [9.4.2](#)) are described in [Annex E](#).

Repeatability of mean grey value ( $8 \pm 1$ ) bit: An ISO A4 sample shall be scanned 10 times without any movement of the sample. All mean grey value of total sample area should be within two grey values.

Deviation of colour value (RGB-8 bit)  $\leq 5$  (after calibration a scanned image of IT8-Target should not have more deviation to associated reference file than  $\pm 5$  values in every colour channel – RGB).

NOTE For suitable scanners, see [Annex E](#).

#### 9.4.2 Procedure for dirt particle measurement

The top and the bottom side of at least two laboratory handsheets per specimen shall be assessed by the image analysis system. The arithmetic mean of min. four measured values shall be calculated. This mean value shall be taken as the dirt specks area  $A$ . The results shall show at least the dirt speck area  $A$  above  $50 \mu\text{m}$  circle equivalent diameter and above  $250 \mu\text{m}$  circle equivalent diameter.

The sheets should be free of crinkles and waves to lie flat on the scanner. The sheets shall be scanned individually. As background, an opaque batch of woodfree copy paper (min. five sheets with a luminance of  $Y = 84 \pm 2$  measured with illumination  $C/2^\circ$  and 420 nm edge filter) should be used. Every handsheet should be scanned one time from top and from the bottom with 8-bit grey modus, 600 dpi and reflective light.

If the scanner is idle for more than 15 min a blank scan shall be made in advance of any new measurement.

NOTE For image analysis software parameterisation, see [Annex E](#).

## 10 Test report

The test report shall include the following information.

For items c) to f), include all information which is available. For items i) to u), the results for both the test mixture and the reference mixture which includes unprinted woodfree paper shall be reported. If other percentages of the woodfree printed paper in the mixture are tested in addition to the required 10 %, the appropriate reference mixtures shall also be tested and reported.

- a) a reference to this International standard, i.e. ISO 12507:2025;
- b) the identification of printed paper products as to title, publishing company, date of issue, product category;
- c) the print processes, printing and drying/curing parameters and press settings;
- d) the name and exact identification of inks or toner and of varnishes (if applicable);
- e) any pre- or post-treatment(s) applied (if any);
- f) the paper grades, manufacturers and brand names, ash content of the printed samples;
- g) the source and age of the mixture of printed wood-containing paper used for the reference mixture;
- h) the exact designation of the laboratory testing equipment used – pulper, flotation cell, image analysis;
- i) the pH after pulping, before and after storage and before flotation;
- j) the chemical dosage for pulping;
- k) the flotation time;
- l) the ash content of deinked pulp;
- m) the overall yield of the flotation in %;
- n) the fibre yield of the flotation in %;
- o) the overflow mass  $m_{\text{froth}}$ ;

## ISO 12507:2025(en)

- p) the overflow stock concentration  $c_{\text{froth}}$ ;
- q) the luminance  $Y$  of deinked pulp;
- r)  $L^*$ ,  $a^*$  and  $b^*$  of deinked pulp;
- s) the filtrate darkening  $\Delta Y$  of the deinked pulp sample filtrate;
- t) the dirt particle area of deinked pulp in  $\text{mm}^2/\text{m}^2$  in two categories with the dirt particle area  $> 50 \mu\text{m}$  and the dirt particle area  $> 250 \mu\text{m}$  circle equivalent diameter;
- u) any deviations from the conditions stipulated for this test method, if applicable (e.g. pulping device, specification of the laboratory flotation cell, conditions of flotation, % of woodfree paper added into the mixture);
- v) any further optical characteristics of non-deinked and deinked pulp yielded as well as their respective filtrate quality (e.g.  $R_{700}$  and/or ERIC).

STANDARDSISO.COM : Click to view the full PDF of ISO 12507:2025

**Annex A**  
(normative)

**Pulping devices**

**A.1 Determination of pulper operating conditions**

In order to determine the pulping conditions, run a pulping test with pure eucalyptus sulphate pulp instead of a printed paper product. The eucalyptus sulphate pulp shall have a Schopper-Riegler-value of  $(18 \pm 2)$  SR, a medium fibre length of  $(0,7 \pm 0,1)$  mm (arithmetic average) and a kappa number of  $< 5$ . Use 200 g of oven-dry pulp and fill it with water to a total mass of 1 667 g. Record the energy consumption for 20 min pulping time. Also, determine the no-load consumption of the equipment by operating it empty. Subtract the no-load consumption from the consumption with pulp in order to obtain the net power consumption for pulping. Set the speed to a value that the pulping process needs a net power consumption of  $(18 \pm 3)$  Wh, in  $(20 \pm 5)$  min at  $(45 \pm 2)$  °C. Priority shall be given to meeting the net power consumption target as closely as possible. If the speed adjustment of the pulper allows, the target pulping time shall also be achieved as closely as possible.

Use these settings for pulping of the printed product.

**A.2 Hobart pulper N 50**

Hobart pulper N 50<sup>4)</sup>.

Use rotor speed 2 and B-flat beater as well as a cover to prevent splashing. Additionally, it is possible to install a revolution counter, which stops the device automatically.

**A.3 Kenwood pulper KMM 020**

Kenwood Major Titanium KMM 020<sup>5)</sup>.

Typically, the pulping time is 20 min at rotor speed 3,5.

Optional heating should be used to maintain  $(45 \pm 2)$  °C during pulping.

---

4) Hobart pulper N 50 is the trade name of a product and can be obtained at Hobart Hobart, 701 South Ridge Ave., Troy, Ohio 45374, USA. This information is given for the convenience of users of this document and does not constitute an endorsement by ISO of the product named. Equivalent products may be used if they can be shown to lead to the same results.

5) Kenwood Major Titanium KMM 020 can be obtained at De'Longhi Appliances S.r.l. – Via L. Seitz, 47, 31100 Treviso, Italy. This information is given for the convenience of users of this document and does not constitute an endorsement by ISO of the product named. Equivalent products may be used if they can be shown to lead to the same results.