
**Glass in building — Tempered soda
lime silicate safety glass**

*Verre dans la construction — Verre silico-sodo-calcique de sécurité
trempé*

STANDARDSISO.COM : Click to view the full PDF of ISO 12540:2017



STANDARDSISO.COM : Click to view the full PDF of ISO 12540:2017



COPYRIGHT PROTECTED DOCUMENT

© ISO 2017, Published in Switzerland

All rights reserved. Unless otherwise specified, no part of this publication may be reproduced or utilized otherwise in any form or by any means, electronic or mechanical, including photocopying, or posting on the internet or an intranet, without prior written permission. Permission can be requested from either ISO at the address below or ISO's member body in the country of the requester.

ISO copyright office
Ch. de Blandonnet 8 • CP 401
CH-1214 Vernier, Geneva, Switzerland
Tel. +41 22 749 01 11
Fax +41 22 749 09 47
copyright@iso.org
www.iso.org

Contents

	Page
Foreword	v
Introduction	vi
1 Scope	1
2 Normative references	1
3 Terms and definitions	1
4 Glass products	3
5 Fracture characteristics	3
5.1 General.....	3
5.2 Accidental human impact.....	3
5.3 Fragmentation.....	3
6 Dimensions and tolerances	4
6.1 Nominal thickness and thickness tolerances.....	4
6.2 Width and length (sizes).....	4
6.2.1 General.....	4
6.2.2 Maximum and minimum sizes.....	5
6.2.3 Tolerances and squareness.....	5
6.2.4 Edge deformation produced by vertical tempering.....	5
6.3 Flatness.....	6
6.3.1 General.....	6
6.3.2 Measurement of overall bow.....	8
6.3.3 Measurement of wave or roller wave distortion.....	9
6.3.4 Measurement of edge lift (for horizontally tempered safety glass only).....	10
6.3.5 Measurement of perimeter deformation of glass produced by air cushion toughening process.....	11
6.3.6 Measurement of local distortion (for vertically tempered safety glass only).....	12
6.3.7 Limitation on overall bow, roller waves and edge lift for horizontally tempered safety glass.....	12
6.3.8 Limitation on overall bow, wave and perimeter deformation for tempered safety glass manufactured by air cushion process.....	13
6.3.9 Limitation on overall bow and local distortion for vertically tempered safety glass.....	13
6.3.10 Other distortions.....	14
7 Edge work, holes, notches and cut-outs	14
7.1 General.....	14
7.2 Edge working of glass for tempering.....	14
7.3 Profiled edges.....	15
7.4 Round holes.....	15
7.4.1 General.....	15
7.4.2 Diameter of holes.....	15
7.4.3 Limitations on position of holes.....	15
7.4.4 Tolerances on hole diameters.....	17
7.4.5 Tolerances on position of holes.....	17
7.5 Holes/others.....	18
7.6 Notches and cut-outs.....	18
7.7 Shaped panes.....	19
8 Fragmentation test	19
8.1 General.....	19
8.2 Dimensions and number of test specimens.....	19
8.3 Test procedure.....	19
8.4 Assessment of fragmentation.....	20
8.5 Minimum values from the particle count.....	21

8.6	Selection of the longest particle.....	22
8.7	Maximum length of the longest particle.....	22
8.8	Test report.....	22
9	Other physical characteristics.....	22
9.1	Optical distortion.....	22
9.1.1	Tempered safety glass produced by vertical tempering.....	22
9.1.2	Tempered safety glass produced by horizontal tempering.....	22
9.2	Anisotropy (iridescence).....	22
9.3	Thermal durability.....	23
9.4	Mechanical strength.....	23
9.5	Surface pre-stress.....	23
10	Marking.....	24
11	Packaging.....	24
Annex A	(normative) Pendulum impact test methods.....	25
Annex B	(informative) Alternative method for the measurement of roller wave distortion.....	26
Annex C	(informative) Example of particle count.....	28
Annex D	(informative) Method for the measurement of the surface pre-stress of tempered safety glass.....	31
Bibliography	33

STANDARDSISO.COM : Click to view the full PDF of ISO 12540:2017

Foreword

ISO (the International Organization for Standardization) is a worldwide federation of national standards bodies (ISO member bodies). The work of preparing International Standards is normally carried out through ISO technical committees. Each member body interested in a subject for which a technical committee has been established has the right to be represented on that committee. International organizations, governmental and non-governmental, in liaison with ISO, also take part in the work. ISO collaborates closely with the International Electrotechnical Commission (IEC) on all matters of electrotechnical standardization.

The procedures used to develop this document and those intended for its further maintenance are described in the ISO/IEC Directives, Part 1. In particular the different approval criteria needed for the different types of ISO documents should be noted. This document was drafted in accordance with the editorial rules of the ISO/IEC Directives, Part 2 (see www.iso.org/directives).

Attention is drawn to the possibility that some of the elements of this document may be the subject of patent rights. ISO shall not be held responsible for identifying any or all such patent rights. Details of any patent rights identified during the development of the document will be in the Introduction and/or on the ISO list of patent declarations received (see www.iso.org/patents).

Any trade name used in this document is information given for the convenience of users and does not constitute an endorsement.

For an explanation on the voluntary nature of standards, the meaning of ISO specific terms and expressions related to conformity assessment, as well as information about ISO's adherence to the World Trade Organization (WTO) principles in the Technical Barriers to Trade (TBT) see the following URL: www.iso.org/iso/foreword.html.

This document was prepared by ISO/ TC 160, *Glass in building*, Subcommittee SC 1, *Product considerations*.

Introduction

Tempered soda lime silicate safety glass has a breakage behaviour that is different to annealed glass. This behaviour is a direct result of the high surface pre-stress.

Tempered soda lime silicate safety glass has a known behaviour under accident human impact together with known mechanical and thermal stress resistance.

NOTE 1 ISO/TC 160/SC 2 produces standards for the determination of the design strength of glass and is preparing a design method.

NOTE 2 In Europe, the term “thermally toughened” is used instead of “tempered”.

STANDARDSISO.COM : Click to view the full PDF of ISO 12540:2017

Glass in building — Tempered soda lime silicate safety glass

1 Scope

This document covers product definitions, product characteristics, i.e. tolerances, flatness, edgework, etc., fracture characteristics, including fragmentation, and the physical and mechanical characteristics of flat tempered soda lime silicate safety glass for use in buildings.

This document does not cover curved (bent) glass according to ISO 11485.

Other requirements, not specified in this document, can apply to thermally toughened soda lime silicate safety glass which is incorporated into assemblies, e.g. laminated glass or insulating glass units, or undergo an additional treatment, e.g. coating. The additional requirements are specified in the appropriate glass product standard. Thermally toughened soda lime silicate safety glass, in this case, does not lose its mechanical or thermal characteristics.

2 Normative references

The following documents are referred to in the text in such a way that some or all of their content constitutes requirements of this document. For dated references, only the edition cited applies. For undated references, the latest edition of the referenced document (including any amendments) applies.

ISO 1288-3, *Glass in building — Determination of the bending strength of glass — Part 3: Test with specimen supported at two points (four point bending)*

ISO 11479-1, *Glass in building — Coated glass — Part 1: Physical defects*

ISO 16293-1, *Glass in building — Basic soda lime silicate glass products — Part 1: Definitions and general physical and mechanical properties*

ISO 16293-2:—¹⁾, *Glass in building — Basic soda lime silicate glass products — Part 2: Float glass*

ISO 16293-5:—¹⁾, *Glass in building — Basic soda lime silicate glass products — Part 5: Patterned glass*

ISO 29584, *Glass in building — Pendulum impact testing and classification of safety glass*

3 Terms and definitions

For the purposes of this document, the following terms and definitions apply.

ISO and IEC maintain terminological databases for use in standardization at the following addresses:

— IEC Electropedia: available at <http://www.electropedia.org/>

— ISO Online browsing platform: available at <http://www.iso.org/obp>

3.1

flat tempered safety glass

tempered (thermally toughened) glass which has not been deliberately given a specific profile during manufacture

1) Under preparation.

3.2

enamelled tempered safety glass

tempered (thermally toughened) glass which has a ceramic frit fired into the surface during the tempering (toughening) process

Note 1 to entry: After tempering, the ceramic frit becomes an integral part of the glass.

Note 2 to entry: The application of the ceramic frit may be by a continuous application or discontinuous, e.g. screen printing.

3.3

horizontal process

process in which the glass is supported on horizontal rollers

3.4

air cushion process

process in which the glass is supported by an air cushion with or without additional rollers

Note 1 to entry: In this process, the glass will be between horizontal and 45° of horizontal.

3.5

vertical process

process in which the glass is suspended by tongs

3.6

edge deformation

deformation of the edge caused by the tong marks

3.7

edge lift

distortion produced in horizontally tempered safety glass, at the leading and trailing edge of the plate, as a result of the glass during the tempering (toughening) process not being supported by a roller

Note 1 to entry: This is a distortion produced by a deviation from surface flatness.

Note 2 to entry: Also referred to as edge dip.

3.8

perimeter deformation

distortion around the edge of tempered safety glass manufactured by air cushion process

3.9

local distortion

local deformation of vertically tempered safety glass underneath the tong marks

3.10

overall bow

deformation of the whole pane of tempered safety glass caused by the heating and cooling process

3.11

roller wave distortion

periodic distortion produced in horizontally tempered safety glass as a result of the glass during tempering process being in contact with the rollers

Note 1 to entry: This is a surface distortion produced by a reduction in surface flatness.

3.12

wave distortion

distortion in tempered safety glass manufactured by the air cushion process as a result of the tempering process

4 Glass products

Tempered safety glass is made from a monolithic glass generally corresponding to one of the following standards:

- basic soda lime silicate glass products according to ISO 16293-1;
- float glass according to ISO 16293-2;
- patterned glass according to ISO 16293-5;
- coated glass according to ISO 11479-1.

NOTE For drawn sheet glass, an ISO standard is not available. Therefore, see EN 572-4 or national standards.

Other nominal thicknesses of glass than those covered in the above standards are possible.

5 Fracture characteristics

5.1 General

In the event of breakage, tempered safety glass fractures into numerous small pieces, the edges of which are generally blunt.

Fragmentation in service may not correspond exactly to that described in [Clause 8](#), due to restraint from fixing and external actions or due to the cause of fracture.

There can be different fragmentations if heat-strengthened glass is used in laminated glass.

5.2 Accidental human impact

5.2.1 When subjected to an accidental human impact, tempered safety glass will either not break or break in a manner that will reduce the risk of cutting and piercing injuries.

5.2.2 Tempered safety glass can be classified by the use of a pendulum impact test. When tested by this type of test, the safe breakage criteria employed for tempered safety glass is that the 10 largest crack free particles collected within 3 min after impact shall weigh no more than the mass equivalent of 6 500 mm² of the original test piece.

5.2.3 The quoted break criteria is taken from the standards given in [Annex A](#). [Annex A](#) lists the test methods presently employed to classify this product.

NOTE The safe breakage criteria are different from the fragmentation criteria used to determine that the product complies with its definition.

5.3 Fragmentation

This test method is employed to demonstrate that the tempered safety glass breaks in the manner expected of this product. The fragmentation test (see [Clause 8](#)) details the minimum number of crack-free particles that shall be in a set area, i.e. 50 mm × 50 mm, and the dimension of the largest acceptable splinter.

This fragmentation behaviour ignores any influence of support conditions and is a representation of the effect of the surface pre-stress.

These properties are not size dependent.

6 Dimensions and tolerances

6.1 Nominal thickness and thickness tolerances

The nominal thicknesses and thickness tolerances are those given in the relevant product standards (see [Clause 4](#)).

Table 1 — Nominal thicknesses and tolerances

Nominal thickness mm	Float glass tolerances mm	Patterned glass tolerances mm
2	±0,2	Not manufactured
3	±0,3	±0,5
4	±0,3	±0,5
5	±0,3	±0,5
6	±0,3	±0,5
8	±0,6	±0,8
10	±0,6	±1,0
12	±0,8	±1,5
15	±0,8	±1,5
19	±1,2	±1,5
22	±1,2	±2,0
25	±1,2	Not manufactured

The thickness of a pane shall be determined as for the basic product. The measurement shall be taken at the centre of the four sides, and away from the area of any tong marks (see [Figure 2](#)), which may be present.

6.2 Width and length (sizes)

6.2.1 General

When tempered safety glass dimensions are quoted for rectangular panes, the first dimension shall be the width, B , and the second dimension the length, H , as shown in [Figure 1](#). It shall be made clear which dimension is the width, B , and which is the length, H , when related to its installed position.

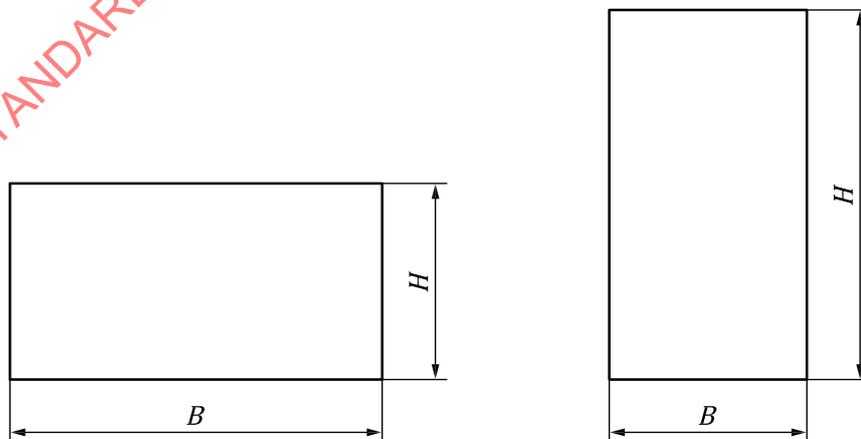


Figure 1 — Examples of width, B , and length, H , relative to the pane shape

For tempered safety glass manufactured from patterned glass, the direction of the pattern should be specified relative to one of the dimensions.

6.2.2 Maximum and minimum sizes

For maximum and minimum sizes, the manufacturer should be consulted.

6.2.3 Tolerances and squareness

The nominal dimensions for width and length being given, the finished pane shall not be larger than the nominal dimensions increased by the tolerance, *t*, or smaller than the nominal dimensions reduced by the tolerance, *t*. Limits are given in [Table 2](#).

The squareness of rectangular glass panes is expressed by the difference between its diagonals. The difference between the two diagonal lengths of the pane of glass shall not be larger than the deviation limit, *v*, as specified in [Table 3](#).

Table 2 — Tolerances, *t*, on width, *B*, and length, *H*

Dimensions in millimetres

Nominal dimension of side, <i>B</i> or <i>H</i>	Nominal glass thickness										
	2	3	4	5	6	8	10	12	15	19	25
≤ 1 000	±2					±3			±4	±5	
1 000 < <i>B</i> or <i>H</i> ≤ 2 000	±3						±4			±5	
2 000 < <i>B</i> or <i>H</i> ≤ 3 000	±4							±5			±6
3 000 < <i>B</i> or <i>H</i>	±4					±5			±6		


Table 3 — Limit deviations, *v*, for the difference between diagonals

Dimensions in millimetres

Nominal dimension of side, <i>B</i> or <i>H</i>	Nominal glass thickness										
	2	3	4	5	6	8	10	12	15	19	25
≤ 1 000	4					6			8	10	
1 000 < <i>B</i> or <i>H</i> ≤ 2 000	6						8			10	
2 000 < <i>B</i> or <i>H</i> ≤ 3 000	8							10			12
3 000 < <i>B</i> or <i>H</i>	8					10			12		

6.2.4 Edge deformation produced by vertical tempering

The tongs used to suspend the glass during tempering result in surface depressions, known as “tong marks” (see [Figure 2](#)). The centres of the tong marks are situated up to a maximum of 20 mm from the edge. A deformation of the edge less than 2 mm can be produced in the region of the tong mark and there may also be an area of optical distortion.

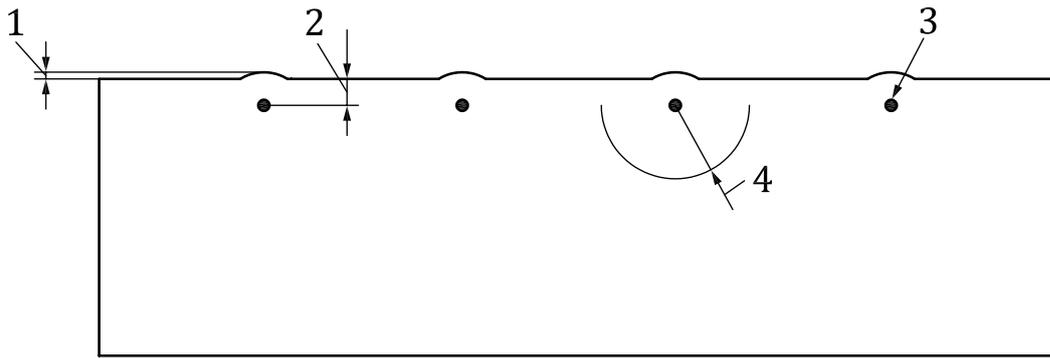

Key

- 1 deformation in the tolerances of [Table 2](#)
- 2 up to 20 mm
- 3 tong mark
- 4 100 mm radius maximum area of optical distortion

Figure 2 — Tong mark deformation

6.3 Flatness

6.3.1 General

By the very nature of the tempering process, it is not possible to obtain a product as flat as annealed glass. This difference in flatness depends on the type of glass, e.g. coated, patterned, etc., glass dimensions, i.e. the nominal thickness, the dimensions, the ratio between the dimensions and the type of the tempering process employed.


There are six kinds of distortion:

- a) overall bow (see [Figure 3](#));
- b) roller wave distortion (for horizontally tempered safety glass only) (see [Figure 4](#));
- c) edge lift (for horizontally tempered safety glass only) (see [Figure 5](#));
- d) local distortion (for vertically tempered safety glass only) (see [Figure 6](#)).

Local distortion needs to be allowed for within the glazing materials and the weather seals. For special requirements, the manufacturers should be consulted.

- e) wave distortion (for air cushion-tempered safety glass only) (see [Figure 4](#));
- f) perimeter deformation (for air cushion-tempered safety glass only) (see [Figure 10](#)).

NOTE Overall bow, roller wave, edge lift and perimeter deformation can, in general, be accommodated by the framing system.

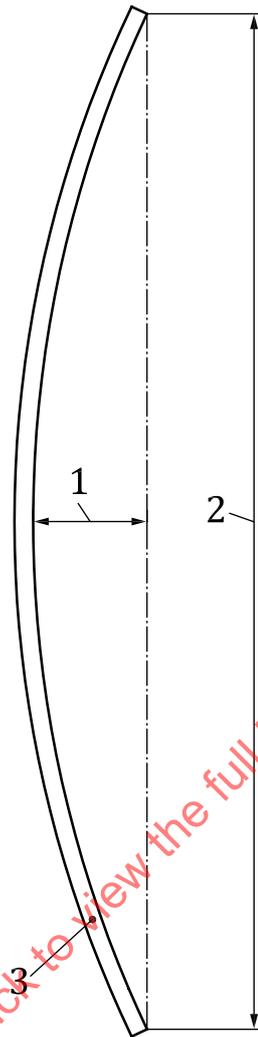

Key

- 1 deformation for calculating overall bow
- 2 *B*, or *H*, or diagonal length
- 3 tempered safety glass


Figure 3 — Representation of overall bow



Key

- 1 roller wave distortion


Figure 4 — Representation of wave or roller wave distortion

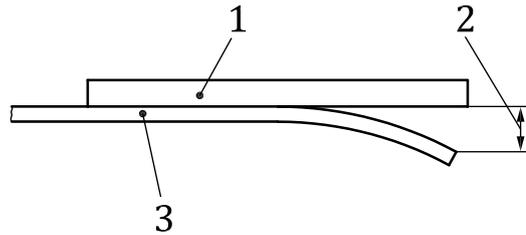

Key

- 1 straightedge
- 2 edge lift
- 3 tempered safety glass

Figure 5 — Representation of edge lift

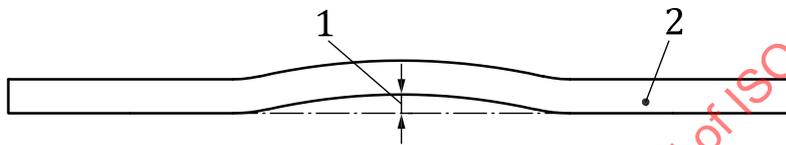

Key

- 1 local distortion
- 2 tempered safety glass

Figure 6 — Representation of local distortion

6.3.2 Measurement of overall bow


The pane of glass shall be placed in a vertical position and supported on its longer side by two load-bearing blocks at the quarter points (see [Figure 7](#)).

For glass thinner than 4 mm nominal thickness, a solid back support with an angle between 3° and 7° from the vertical can be used.

The deformation shall be measured along the edges of the glass and along the diagonals, as the maximum distance between a straight metal ruler, or a stretched wire, and the concave surface of the glass (see [Figure 3](#)).

The value for the bow is then expressed as the deformation, in millimetres, divided by the measured length of the edge of the glass, or diagonal, in millimetres, as appropriate.

The measurement shall be carried out at room temperature.

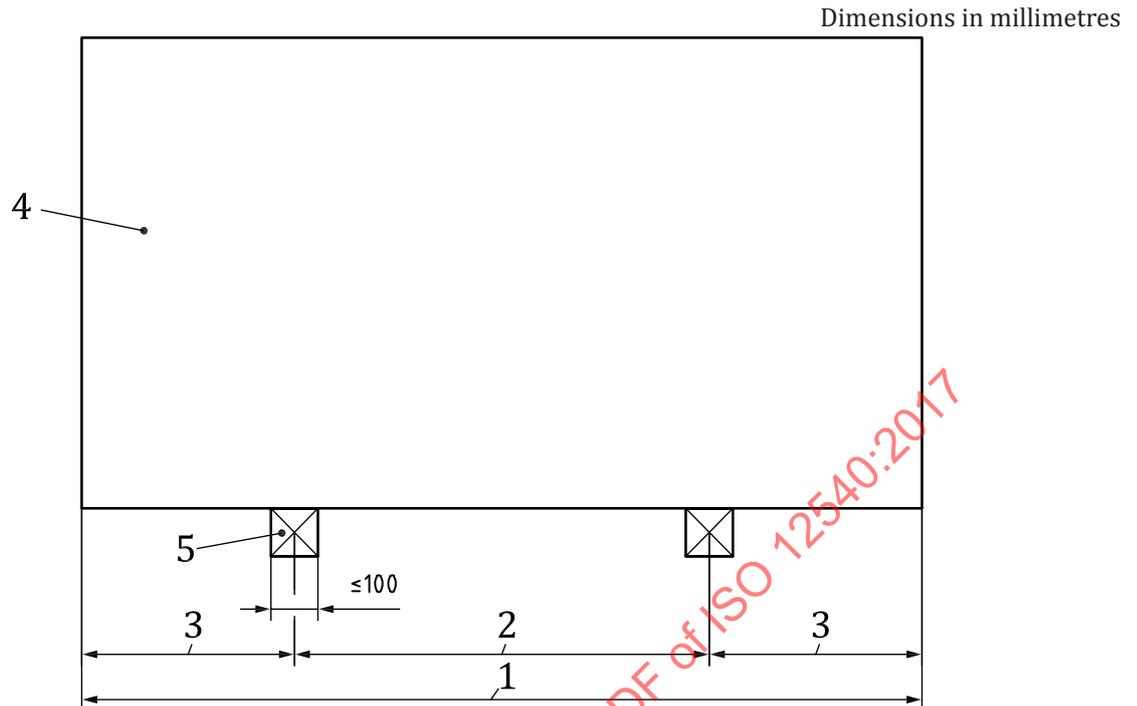**Key**

- 1 B or H
- 2 $(B$ or $H)/2$
- 3 $(B$ or $H)/4$
- 4 tempered safety glass
- 5 load-bearing blocks

Figure 7 — Support conditions for the measurement of overall bow

NOTE Special care needs to be taken for large and thin panes because they can show a buckling which is different from an overall bow caused by the tempering process. Results from this test method for glasses thinner than 4 mm can be inaccurate.

6.3.3 Measurement of wave or roller wave distortion

6.3.3.1 General

The wave or roller wave distortion is measured by means of a straightedge, or equivalent, being placed at right angles to the wave or roller wave and bridging from peak to peak of the wave (see [Figure 8](#)).

NOTE This subclause deals with measurement using a straightedge and feeler gauges. An alternative method is described in [Annex B](#).

6.3.3.2 Apparatus

6.3.3.2.1 A straightedge, length of between 300 mm and 400 mm.

NOTE The actual length of straightedge required will depend on the wavelength of the wave or roller wave.

6.3.3.2.2 Feeler gauges, various thicknesses in units of 0,05 mm.

6.3.3.3 Method

Place the straightedge so that it bridges across adjacent peaks. Insert the feeler gauge between the glass surface and the straightedge. Increase the thickness of the feeler gauges until they just fill the gap between glass surface and the straightedge. Record the thickness of feeler gauge(s) to an accuracy of 0,05 mm.


Repeat the measurement at several places over the glass surface.

The measured wave or roller wave distortion is the maximum value measured. The maximum allowable values are given in [Table 4](#) and [Table 6](#).

6.3.3.4 Limitations

The following limitations apply.

- The wave or roller wave can only be measured on panes with a dimension greater than 600 mm measured at right angles to the waves or roller waves;
- The wave or roller wave cannot be measured in an exclusion area that is 150 mm from the edges of the pane. The apparatus should not be used in the area of these 150 mm;
- Panes with an overall bow shall be laid on a flat support. This will allow gravity to flatten out the overall bow and hence give a truer result for the wave or roller wave.

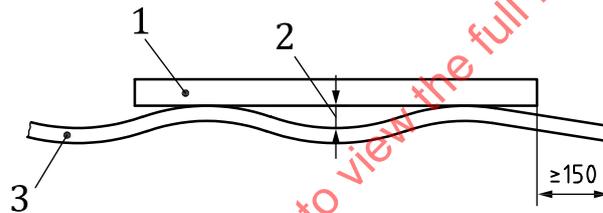

Key

- 1 straightedge
- 2 wave or roller wave distortion
- 3 tempered safety glass

Figure 8 – Measurement of wave or roller wave distortion

6.3.4 Measurement of edge lift (for horizontally tempered safety glass only)

6.3.4.1 Apparatus

6.3.4.1.1 A straightedge, length of between 300 mm and 400 mm.

NOTE The actual length of straightedge required will depend on the wavelength of the roller wave.

6.3.4.1.2 Feeler gauges, various thicknesses in units of 0,05 mm.


6.3.4.2 Method

The glass shall be placed on a flat support with the edge lift overhanging the edge of the support. The overhanging distance should be between 5 cm and 10 cm.

The straightedge is placed on the peaks of the roller waves and the gap between the ruler and the glass measured using a feeler gauge (see [Figure 9](#)).

The maximum values for edge lift are given in [Table 5](#).

The values in [Table 5](#) only apply to tempered safety glass having edgework complying with [Figures 12](#) to [15](#). For profiled edges or other types of edgework, contact the manufacturer.

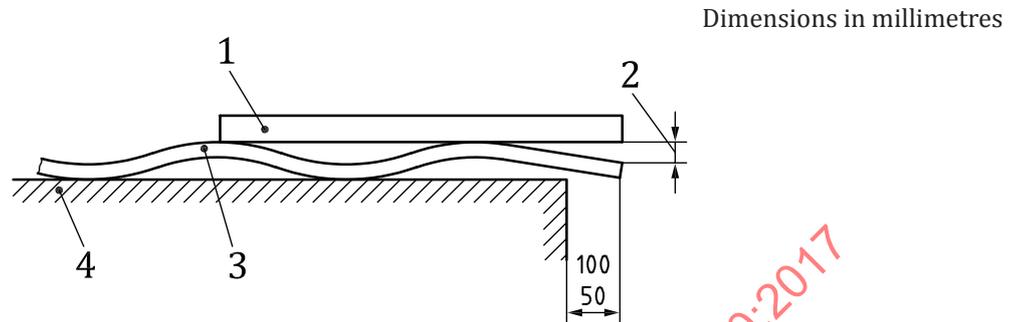

Key

- 1 straightedge
- 2 edge lift
- 3 tempered safety glass
- 4 flat support


Figure 9 — Measurement of edge lift

6.3.5 Measurement of perimeter deformation of glass produced by air cushion toughening process

Place the glass on a flat surface with the concave side facing upwards (see [Figure 10](#)).

A 100 mm straightedge is laid on the pane at right angles to the edge. The gap between the ruler and the glass is measured using a feeler gauge (see [Figure 10](#)). The perimeter deformation is the maximum distance between the surface of the pane and the straightedge.

The maximum allowable values for perimeter deformation are given in [Table 7](#).

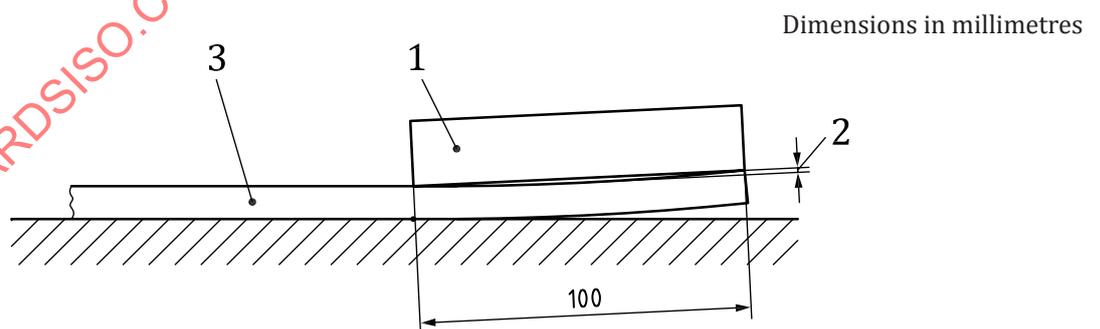

Key


- 1 straightedge
- 2 perimeter deformation
- 3 tempered safety glass

Figure 10 — Measurement of perimeter deformation

6.3.6 Measurement of local distortion (for vertically tempered safety glass only)

Local distortion can occur over relatively short distances on the edges with tong mark of the vertically tempered safety glass that contained the tong marks (see Figure 2) of the glass. Local distortion shall be measured over a limited length of 300 mm by using a straight ruler, or a stretched wire, parallel to the edge at a distance of 25 mm from the edge of the glass (see Figure 11).

Local distortion is expressed as millimetres/300 mm length.

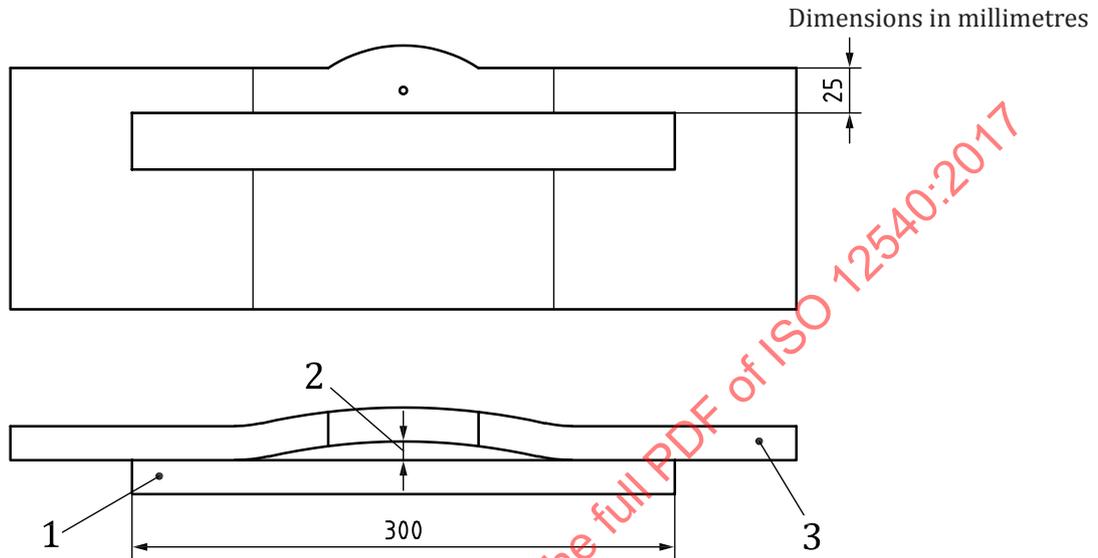

- Key**
- 1 straightedge
 - 2 local distortion
 - 3 tempered safety glass

Figure 11 — Measurement of local distortion

For patterned glass, local distortion shall be determined by using a straight ruler resting on the high points of the pattern and measuring to a high point of the pattern.

6.3.7 Limitation on overall bow, roller waves and edge lift for horizontally tempered safety glass

The maximum allowable values for the overall bow, when measured according to 6.3.2, for roller waves, when measured according to 6.3.3, and edge lift, when measured according to 6.3.4, are given in Tables 4 and 5. These values only apply to tempered safety glass without holes and/or notches and/or cut-outs.

Table 4 — Maximum allowable values of overall bow and roller wave distortion for horizontally tempered safety glass

Glass type	Maximum allowable value for distortion	
	Overall bow mm/m	Roller wave mm
Uncoated float to ISO 16293-2	3,0	0,4
Others ^a	4,0	0,5

Dependent on the wavelength of the roller wave, an appropriate length of straightedge has to be used.

^a For enamelled glass which is not covered over the whole surface, the manufacturer should be consulted.

Table 5 — Maximum allowable values of edge lift for horizontally tempered safety glass

Type of glass	Thickness of glass	Maximum allowable values
	mm	mm
Uncoated float to ISO 16293-2	3	0,5
	4 to 5	0,5
	6 to 25	0,3
Others ^a	all	0,5

Dependent upon the wavelength of the roller wave, an appropriate length of straightedge has to be used.

^a For enamelled glass which is not covered over the whole surface the manufacturer should be consulted.

6.3.8 Limitation on overall bow, wave and perimeter deformation for tempered safety glass manufactured by air cushion process

The maximum allowable values for the overall bow, when measured according to 6.3.2, for waves, when measured according to 6.3.3, and perimeter deformation, when measured according to 6.3.5, are given in Tables 6 and 7. These values only apply to tempered safety glass without holes and/or notches and/or cut-outs.

Table 6 — Maximum allowable values of overall bow and wave distortion for tempered safety glass manufactured by air cushion process

Glass type	Maximum allowable value for distortion	
	Overall bow mm/m	Wave mm
Uncoated float to ISO 16293-2 and coated float glass ISO 11479-1	3,0	0,3
Others ^a	4,0	0,5

For other glass types, the manufacturer should be consulted.

^a For enamelled glass which is not covered over the whole surface, the manufacturer should be consulted.

Table 7 — Maximum allowable values of perimeter deformation for tempered safety glass manufactured by air cushion process

Type of glass	Thickness of glass	Maximum allowable values
	mm	mm
Uncoated float to ISO/DIS 16293-2 and coated float glass ISO 11479-1	up to 12	0,3
Others ^a	up to 12	0,5

For other glass types, the manufacturer should be consulted.

^a For enamelled glass which is not covered over the whole surface, the manufacturer should be consulted.

6.3.9 Limitation on overall bow and local distortion for vertically tempered safety glass

The maximum allowable values for the overall bow, when measured according to 6.3.2, and the local distortion, when measured according to 6.3.6, are given in Table 8. These values only apply to tempered safety glass without holes and/or notches and/or cut-outs.

Table 8 — Maximum allowable values of overall bow and local distortion for vertically tempered safety glass

Glass type	Maximum allowable value for distortion	
	Overall bow mm/m	Local distortion mm/300 mm
All ^a	5,0	1,0
^a For enamelled glass which is not covered over the whole surface, the manufacturer should be consulted.		

6.3.10 Other distortions

The incorporation of holes and/or notches in a plate gives the possibility of distortions being produced during the tempering process as a result of the absence of glass and/or an increase in unsupported edges. The magnitude of these distortions will generally be less than edge lift in horizontally tempered safety glass or local distortion in vertically tempered safety glass.

7 Edge work, holes, notches and cut-outs

7.1 General

Tempered safety glass should not be cut, sawed, drilled, edge worked or surface finished (e.g. sandblasting, acid etching) after tempering because the risk of breakage is increased or the glass can be destroyed immediately. Glasses cut, sawed, drilled, edge worked or surface finished (e.g. sandblasting, acid etching) after tempering are not covered by this document.

No modification that will affect its structural characteristics or integrity as specified in the document shall be made.

NOTE Marking, according to [Clause 10](#), in the corner of a product after tempering is allowed.

7.2 Edge working of glass for tempering

The simplest type of edge working is the arrissed edge (see [Figure 12](#)). Other common types are shown in [Figures 13](#) to [15](#). For specialist edge work, such as “water jet cutting,” the manufacturers should be consulted. Corners need not to be treated unless required by the customer.

NOTE Correctly cut edges may be tempered without further edge working.

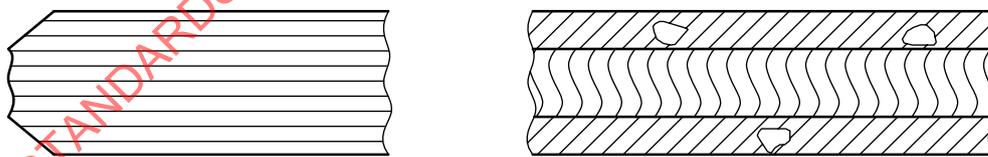


Figure 12 — Arrissed edge (with blank spots)

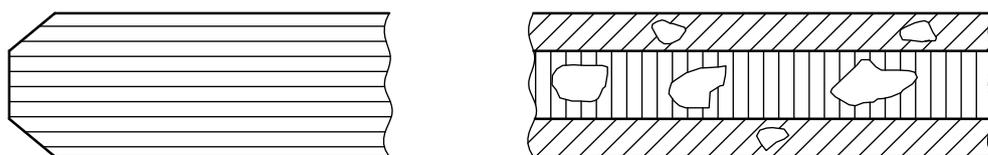


Figure 13 — Ground edge (with blank spots)

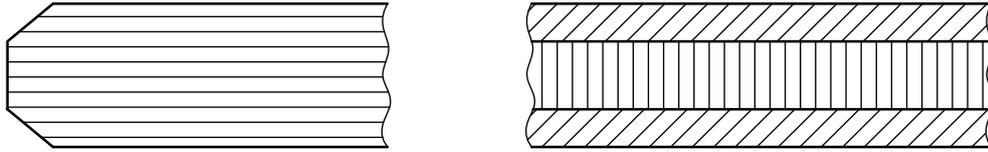


Figure 14 — Smooth ground edge (no blank spots)




Figure 15 — Polished edge

7.3 Profiled edges

Various other edge profiles can be manufactured with different types of edgework. This kind of product is not covered by [Table 5](#) due to the influence of the profile.

7.4 Round holes

7.4.1 General

This document considers only round holes in glass that is not less than 4 mm nominal thickness. For holes in glasses thinner than 4 mm, the manufacturers should be consulted. The manufacturers should be consulted about edge working of holes.

7.4.2 Diameter of holes

The diameter of holes, \emptyset , shall not, in general, be less than the nominal thickness of the glass. For smaller holes, the manufacturers should be consulted.

7.4.3 Limitations on position of holes

In general, the limitations on hole positions relative to the edges of the glass pane, the corners of the glass pane and to each other depends on

- a) the nominal glass thickness (d),
- b) the dimensions of the pane (B , H),
- c) the hole diameter (\emptyset),
- d) the shape of the pane, and
- e) the number of holes.

Glasses produced following the recommendations given below are assumed to satisfy the requirements of this document.

- 1) The distance, a , of the edge of a hole to the glass edge should not be less than $2d$.

$$a \geq 2d$$

NOTE For holes less than $2d$ from the edge, consult the manufacturer.

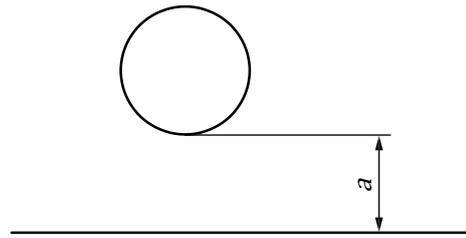


Figure 16 — Relationship between hole and edge of pane

- 2) The distance, b , between the edges of two holes should not be less than $2d$ with a minimum distance of $b = 10$ mm.

$$b \geq 2d$$

NOTE For hole separation (b) less than $2d$ from the edge, consult the manufacturer.

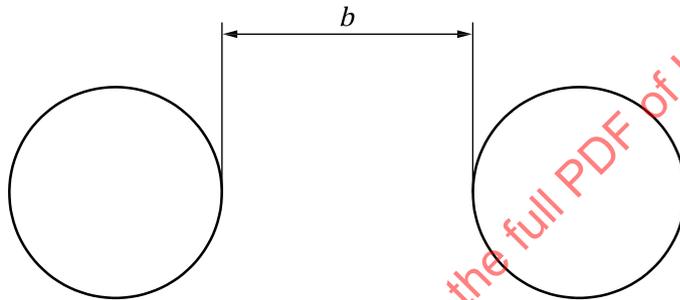


Figure 17 — Relationship between two holes

- 3) The distance, c , of the edge of a hole to the corner of the glass should be not less than $6d$.

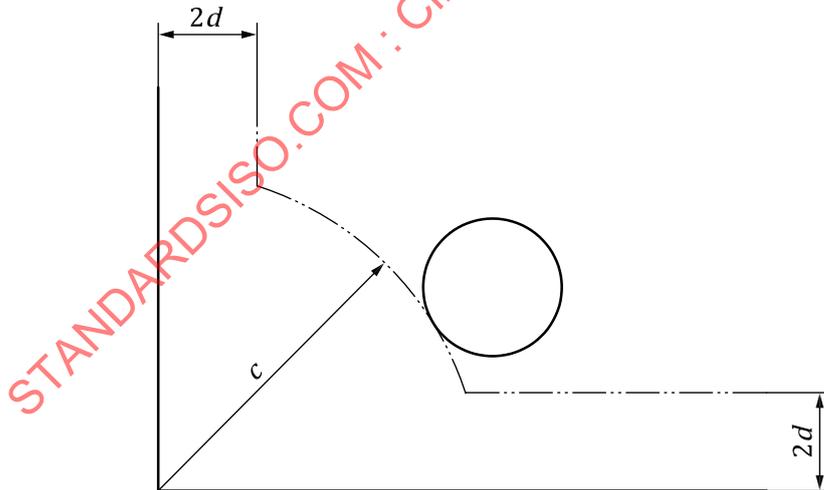


Figure 18 — Relationship between hole and corner of pane

For a distance c less than $6d$, the manufacturer should be consulted.

If one of the distances from the edge of the hole to the edge of the glass is less than 35 mm, it may be necessary to position the hole asymmetrically with respect to the corner. The manufacturers should be consulted.

7.4.4 Tolerances on hole diameters

The tolerances on hole diameters are given in [Table 9](#).

Table 9 — Tolerances on hole diameters

Dimensions in millimetres

Nominal hole diameter \varnothing	Tolerances
$4 \leq \varnothing \leq 20$	$\pm 1,0$
$20 < \varnothing \leq 100$	$\pm 2,0$
$100 < \varnothing$	consult the manufacturer

7.4.5 Tolerances on position of holes

The tolerances on positions of holes are given in [Table 10](#). The positions of holes are measured in two directions at right angles (x - and y -axes) from a reference point to the centre of the holes. The datum point is generally chosen as a real or virtual corner of the pane (see [Figure 19](#) for examples).


The position of a hole (X, Y) is $(x \pm t, y \pm t)$, where x and y are the required dimensions and t is the tolerance from [Table 10](#).

Table 10 — Tolerances on positions of holes

Dimensions in millimetres

Nominal dimension of side, B or H	Tolerance t	
	Nominal glass thickness $d \leq 12$	Nominal glass thickness $d > 12$
$< 2\ 000$	$\pm 2,5$ (horizontal and air cushion tempering) $\pm 3,0$ (vertical tempering)	$\pm 3,0$
$2\ 000 < H$ or $B < 3\ 000$	$\pm 3,0$	$\pm 4,0$
$< 3\ 000$	$\pm 4,0$	$\pm 5,0$

The manufacturers should be consulted if tighter tolerances on hole positions are required.

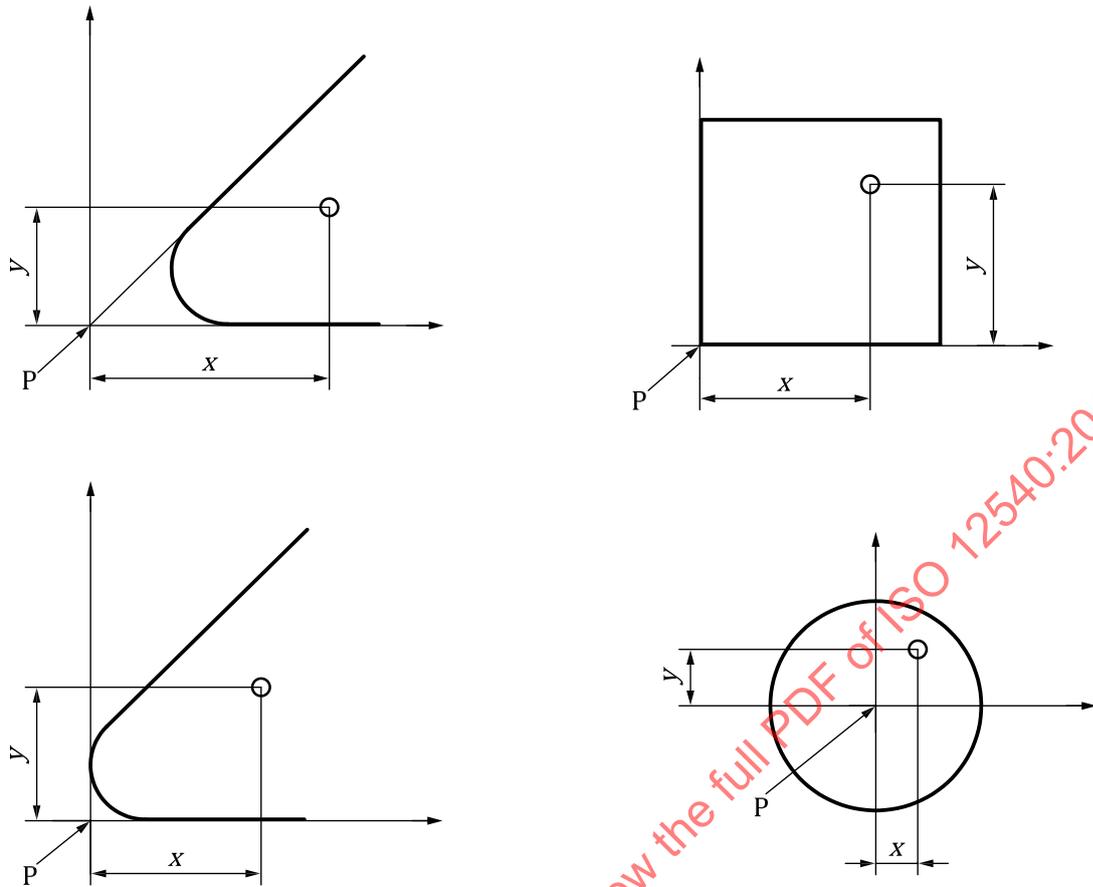

Key
 P datum point

Figure 19 — Examples of the positioning of holes relative to the reference point

7.5 Holes/others

There are available countersunk holes (see [Figure 20](#)). The manufacturer shall be consulted for the tolerances on hole position, hole shape/dimensions and edge work.

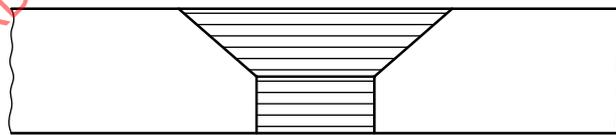


Figure 20 — Countersunk hole

7.6 Notches and cut-outs

Many configurations of notches and cut-outs can be supplied. See [Figure 21](#) for examples.

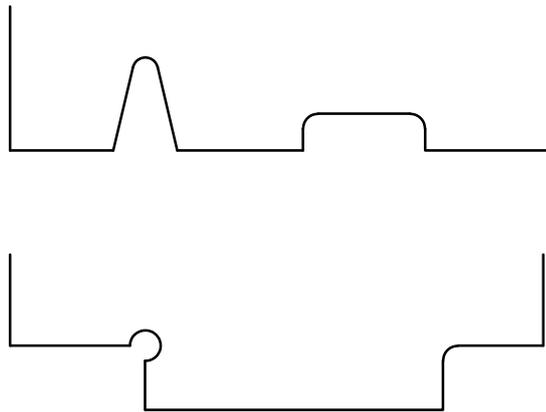


Figure 21 — Examples of notches and cut outs

The manufacturer should be consulted about edge working of notches and cut-outs.

7.7 Shaped panes

Many non-rectangular shapes can be manufactured and manufacturers should be consulted.

8 Fragmentation test

8.1 General

The fragmentation test determines whether the glass breaks in the manner prescribed for a tempered safety glass. This fragmentation test shows the behaviour of breakage of a tempered safety glass without any stress of external action only by the pre-stress. In service, the real breakage behaviour can be different.

8.2 Dimensions and number of test specimens

The dimensions of the test specimens shall be 360 mm × 1 100 mm, without holes, notches or cut-outs.

Five specimens shall be tested.

8.3 Test procedure


Each test specimen shall be impacted, using a pointed steel tool, at a position 20 mm in from the longest edge of the test specimen at the mid-point of that edge, until breakage occurs (see [Figure 22](#)).

NOTE 1 The fragmentation characteristics of glass are unaffected by temperatures between -50 °C and +100 °C.

Examples of steel tools are a hammer of about 75 g mass, a spring-loaded centre punch or other similar appliance with a hardened point. The radius of curvature of the point should be approximately 0,2 mm.

The test specimen shall be laid flat on a table without any mechanical constraint. In order to prevent scattering of the fragments, the specimen shall be simply held at the edges, e.g. by a small frame, adhesive tape, etc., so that the fragments remain interlocked after breakage yet extension of the specimen is not hindered.

NOTE 2 The use of adhesive backed polymeric films is not recommended as it could constrain the glass when broken.

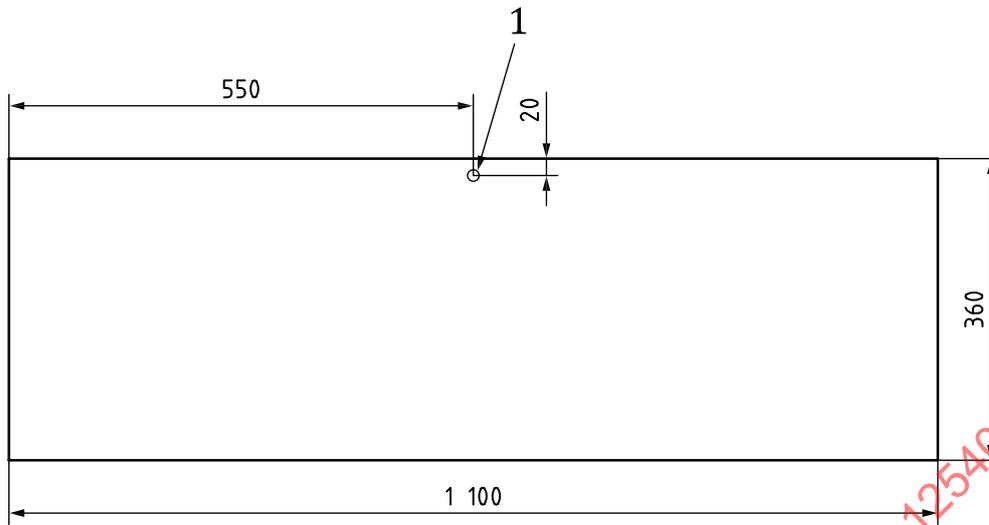

Key

1 impact point


Figure 22 — Position of impact point

For tempered safety glass manufactured by vertical tempering, the impact point shall not be on the tong mark edge.

8.4 Assessment of fragmentation

Counting starts 3 min after fracture and should be finished 5 min after fracture. An area of radius 80 mm, centred on the impact point, and a border of 25 mm, round the edge of the test specimen (see [Figure 23](#)), shall be excluded from the assessment.

The particle count shall be made in the region of coarsest fracture (the aim being to obtain the minimum value). The particle count shall be made by placing a mask of $(50 \pm 1) \text{ mm} \times (50 \pm 1) \text{ mm}$ on the test piece (see [Annex C](#)). The number of crack-free particles within the mask shall be counted. A particle is “crack-free” if it does not contain any cracks which run from one edge to another (see [Figure 24](#)).

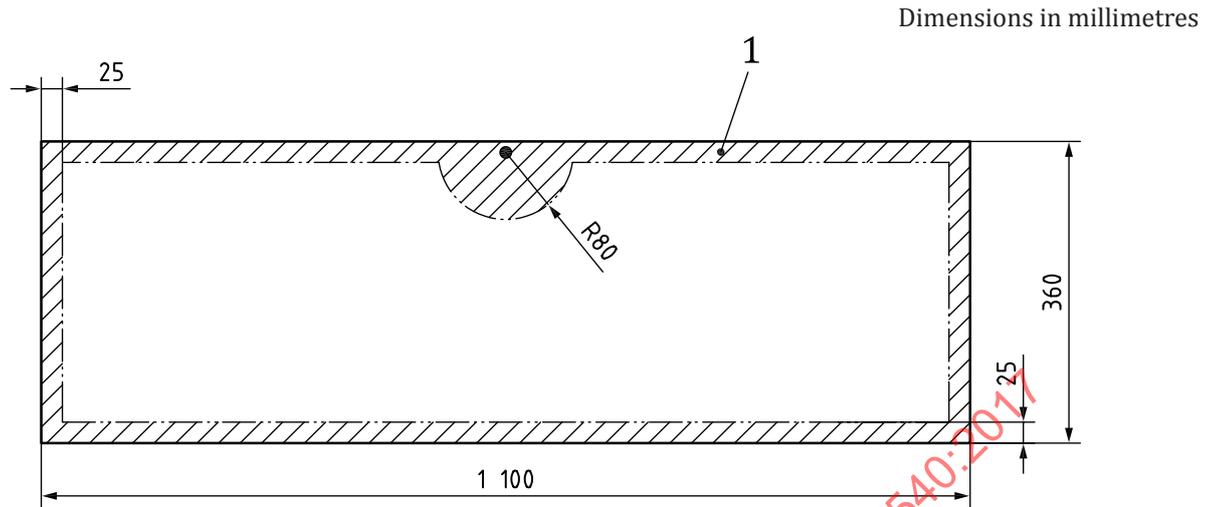

Key
 1 excluded area

Figure 23 — Area to be excluded from the particle count determination and largest particle measurement

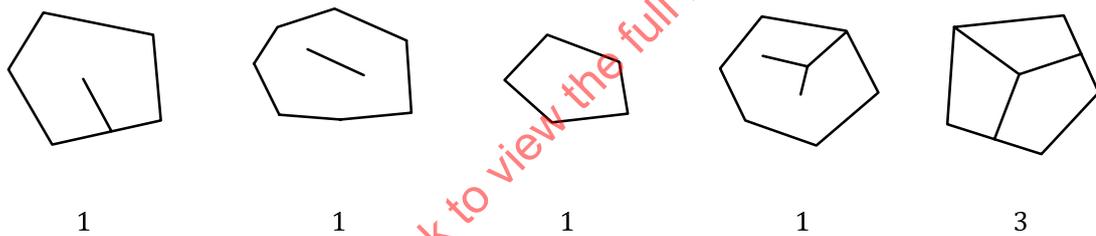


Figure 24 — Examples of crack free particles and the assessment regarding the number

In the particle count, all particles wholly contained within the area of the mask shall be counted as one particle each and all the particles which are partially within the mask shall be counted as 1/2 particle each (see Annex C).

8.5 Minimum values from the particle count

The particle count of each test specimen shall not be less than the values given in Table 11.

Table 11 — Minimum particle count values

Glass type	Nominal thickness <i>d</i> mm	Minimum particle count
Float	less than 2	15
Float	2 and 3	30
Patterned	2 and 3	15
All glass types	4 to 12	40
All glass types	15 to 25	30

8.6 Selection of the longest particle

The longest particle shall be chosen from the body of the test specimen.

It shall not be measured in the excluded area (see [8.4](#)). If the splinter is in both areas, the length of the splinter in the counting area is measured.

8.7 Maximum length of the longest particle

The length of the longest particle shall not exceed 100 mm.

8.8 Test report

The following information shall be reported:

- a) identification of the specimen;
- b) particle count of the fractured test specimen;
- c) the longest particle length;
- d) date and time of the test;
- e) names and positions of personnel carrying out or supervising the test.

Each page of the report shall be signed and dated by the person responsible for the test.

9 Other physical characteristics

9.1 Optical distortion

9.1.1 Tempered safety glass produced by vertical tempering

The tong marks can produce additional optical distortion which is generally in an area of radius 100 mm centred on the tong mark (see [Figure 2](#)).

9.1.2 Tempered safety glass produced by horizontal tempering

While the hot glass is in contact with the rollers during the tempering process, a surface distortion is produced by a deviation from surface flatness, known as “roller wave”. Roller wave is generally noticed in reflection. See also [6.3.3](#).

Small imprints may be shown in the surface of the glass (“roller pick-up”).

9.2 Anisotropy (iridescence)

The tempering process produces areas of different stress in the cross section of the glass. These areas of stress produce a birefringent effect in the glass, which is visible in polarised light.

When tempered safety glass is viewed in polarised light, the areas of stress show up as coloured zones, sometimes known as “leopard spots”.

Polarised light occurs in normal daylight. The amount of polarised light depends on the weather and the angle of the sun. The birefringent effect is more noticeable when the tempered safety glass is examined either at a glancing angle or through polarised spectacles.

Anisotropy is a visible physical effect but not a defect.

9.3 Thermal durability

The mechanical properties of tempered safety glass are unchanged for continuous service up to 250 °C and are unaffected by sub-zero temperatures. Tempered safety glass is capable of resisting both sudden temperature changes and temperature differentials up to 200 K.

NOTE The resistance against temperature difference is sufficient to withstand the temperature differential which occurs in glazing exposed to solar radiation, usually below 100 K.

9.4 Mechanical strength

The value of mechanical strength can only be given as a statistical value associated with a particular probability of breakage and with a particular type of loading, i.e. four-point bending test according to ISO 1288-3.

NOTE These values are determined in accordance with ISO 1288-3.

Table 12 — Minimum values for the characteristic bending strength of tempered safety glass

Type of glass	Minimum values for characteristic bending strength MPa
Float: clear tinted coated	120
Enamelled float (based on the enamelled surface under tensile stress)	75
Patterned glass and drawn sheet	90

NOTE The values in [Table 12](#) represent the strength of tempered safety glass which meets the requirements of [8.5](#).

At least 10 specimens of tempered safety glass shall be tested according to ISO 1288-3. The 5 % breakage probability, statistically evaluated at the lower limit of the 95 % confidence interval, shall be not less than the value in [Table 12](#).

9.5 Surface pre-stress

To achieve a bending strength of 120 MPa, as determined according to ISO 1288-3, for a single float glass pane between 4 mm and 12 mm, a minimum value for surface pre-stress of 80 MPa is needed.

Additionally, to achieve 40 particles in the fragmentation test the minimum value for surface pre-stress (see [Annex D](#)) of 90 MPa is needed for float glass between 4 mm and 12 mm.

Table 13 — Possibilities of measurement during manufacturing

Surface pre-stress test MPa	Four-point bending test is necessary MPa	Fragmentation test is necessary
90	no	no ^a
80	no	yes
no	120	yes

^a Only applicable for glass of nominal thickness 4 mm to 12 mm.

10 Marking

Tempered safety glass conforming to this document shall be permanently marked. The marking shall give the following information:

- a) name or trademark of manufacturer;
- b) the number of this document, i.e. ISO 12540.

11 Packaging

Tempered safety glasses shall be packaged by using an appropriated buffer material.

STANDARDSISO.COM : Click to view the full PDF of ISO 12540:2017

Annex A (normative)

Pendulum impact test methods

A.1 General

ISO 29584 classifies pendulum impact test methods.

A.2 Pendulum test methods employed around the world for the classification of thermally tempered safety glass against accidental human impact

A.2.1 Japan

Lead shot filled leather shot bag, weight $(45 \pm 0,1)$ kg as per JIS R 3206.

A.2.2 Australia, New Zealand

Lead shot filled leather shot bag, weight $(46 \pm 0,1)$ kg as per AS/NZS 2208.

A.2.3 United States of America

Lead shot filled leather shot bag, weight $(45,4 + 0,2)$ kg as per ANSI Z97.1.

NOTE Federal regulation CPSC 16 CFR 1201 also details a pendulum test method similar to ANSI Z97.1.

A.2.4 Canada

Lead shot filled leather shot bag, weight $(45,4 + 0,2)$ kg as per CAN/CGSB 12.1-M 90.

A.2.5 Europe

Twin tyre impactor, weight $(50 \pm 0,1)$ kg as per EN 12600.

Annex B (informative)

Alternative method for the measurement of roller wave distortion

B.1 Apparatus

This is a 350 mm long aluminium channel with a centrally mounted deflection gauge/dial gauge ([Figure B.1](#)).

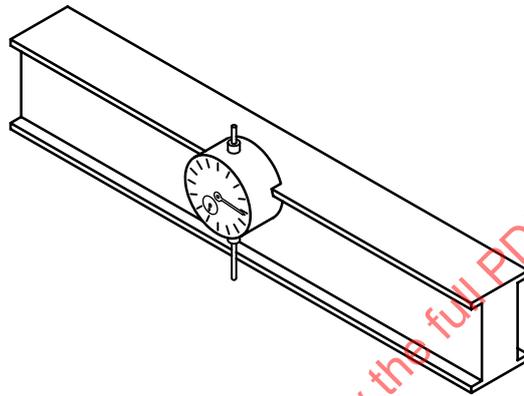


Figure B.1 — Roller wave measurement apparatus

B.2 Method

The apparatus is placed on the glass at right angles to the roller wave, so that it can bridge from peak to peak of the wave ([Figure B.2](#)).




Figure B.2 — Place the apparatus across the roller wave

The apparatus is then moved along its axis until the dial gauge reads the highest value ([Figure B.3](#)).




Figure B.3 — Set the zero of the gauge on a peak of the roller wave

At this point, the dial gauge is resting on a peak of the roller wave. The scale of the gauge is positioned (rotated) so that the needle points to 0 (zero) on the scale. The apparatus is then moved again along its axis until the gauge reads the lowest value ([Figure B.4](#)). At this point, the dial gauge is resting in the lowest point of the trough. The reading is then taken, and the depth of the roller wave is the difference between the zero point and the reading.

The dial gauge scale is usually arranged so that a positive value is obtained by raising the post. Care should be taken to not misread the depth of the roller wave.