
**Copper, lead and zinc sulfide
concentrates — Determination of
transportable moisture limits —
Flow table method**

*Concentrés sulfurés de cuivre, de plomb et de zinc — Détermination des
limites d'humidité transportable — Méthode de la table d'écoulement*

STANDARDSISO.COM : Click to view the full PDF of ISO 12742:2000



PDF disclaimer

This PDF file may contain embedded typefaces. In accordance with Adobe's licensing policy, this file may be printed or viewed but shall not be edited unless the typefaces which are embedded are licensed to and installed on the computer performing the editing. In downloading this file, parties accept therein the responsibility of not infringing Adobe's licensing policy. The ISO Central Secretariat accepts no liability in this area.

Adobe is a trademark of Adobe Systems Incorporated.

Details of the software products used to create this PDF file can be found in the General Info relative to the file; the PDF-creation parameters were optimized for printing. Every care has been taken to ensure that the file is suitable for use by ISO member bodies. In the unlikely event that a problem relating to it is found, please inform the Central Secretariat at the address given below.

STANDARDSISO.COM : Click to view the full PDF of ISO 12742:2000

© ISO 2000

All rights reserved. Unless otherwise specified, no part of this publication may be reproduced or utilized in any form or by any means, electronic or mechanical, including photocopying and microfilm, without permission in writing from either ISO at the address below or ISO's member body in the country of the requester.

ISO copyright office
Case postale 56 • CH-1211 Geneva 20
Tel. + 41 22 749 01 11
Fax + 41 22 734 10 79
E-mail copyright@iso.ch
Web www.iso.ch

Printed in Switzerland

Foreword

ISO (the International Organization for Standardization) is a worldwide federation of national standards bodies (ISO member bodies). The work of preparing International Standards is normally carried out through ISO technical committees. Each member body interested in a subject for which a technical committee has been established has the right to be represented on that committee. International organizations, governmental and non-governmental, in liaison with ISO, also take part in the work. ISO collaborates closely with the International Electrotechnical Commission (IEC) on all matters of electrotechnical standardization.

International Standards are drafted in accordance with the rules given in the ISO/IEC Directives, Part 3.

Draft International Standards adopted by the technical committees are circulated to the member bodies for voting. Publication as an International Standard requires approval by at least 75 % of the member bodies casting a vote.

Attention is drawn to the possibility that some of the elements of this International Standard may be the subject of patent rights. ISO shall not be held responsible for identifying any or all such patent rights.

International Standard ISO 12742 was prepared by Technical Committee ISO/TC 183, *Copper, lead and zinc ores and concentrates*.

Annex A forms a normative part of this International Standard.

STANDARDSISO.COM : Click to view the full PDF of ISO 12742:2000

Copper, lead and zinc sulfide concentrates — Determination of transportable moisture limits — Flow table method

WARNING — This International Standard may involve hazardous materials, operations and equipment. It is the responsibility of the user of this International Standard to establish appropriate health and safety practices and determine the applicability of regulatory limitations prior to use.

1 Scope

This International Standard specifies a flow table method for the determination of the transportable moisture limit (TML) of copper, lead and zinc concentrates which may liquefy during transport.

This International Standard is applicable to the determination of the TML of concentrates containing 10 % (m/m) to 80 % (m/m) of lead, or 10 % (m/m) to 65 % (m/m) of zinc, or 10 % (m/m) to 55 % (m/m) of copper. It is applicable to TMLs in the range 3 % (m/m) to 28 % (m/m).

2 Normative references

The following normative documents contain provisions which, through reference in this text, constitute provisions of this International Standard. For dated references, subsequent amendments to, or revisions of, any of these publications do not apply. However, parties to agreements based on this International Standard are encouraged to investigate the possibility of applying the most recent editions of the normative documents indicated below. For undated references, the latest edition of the normative document referred to applies. Members of ISO and IEC maintain registers of currently valid International Standards.

ISO 10251:1997, *Copper, lead and zinc sulfide concentrates — Determination of mass loss in bulk material on drying.*

ISO 12743:1998, *Copper, lead and zinc sulfide concentrates — Sampling procedures for determination of metal and moisture content.*

3 Principle

Adjustment of the moisture content of the sample by mixing with water. Conversion of the mixture to a conical shape using a mould and tamper. Placement of the sample on the flow table and removal of the mould. Determination of the flow characteristic by repeated dropping of the flow table while observing the behaviour of the sample. When sufficient water has been added to the sample so that plastic deformation occurs during the dropping of the flow table, the sample is considered to be at its flow moisture point.

Calculation of the TML as 90 % of the flow moisture point.

4 Apparatus

NOTE Copper, lead and zinc concentrates may gain or lose moisture rapidly when exposed to air. The laboratory should be designed so that excessive temperatures, air currents and humidity variations are avoided.

4.1 Flow table and frame, as specified in annex A.

The flow table mounting shall be as specified in Figure A.1.

4.2 Mould, as specified in Figure A.1.

4.3 Tamper.

The required tamping pressure may be achieved by using calibrated, spring-loaded tampers or some other suitable design of tamper that allows a controlled pressure to be applied via a 30 mm diameter tamper head as specified in Figure A.2.

4.4 Balance, top loading, having the sensitivity specified in Table 1.

Table 1 — Sensitivity of balance and precision of weighing

Mass of sample plus tray g	Precision of balance and weighing g
100	0,01
200	0,02
300	0,03
400	0,04
500	0,05

4.5 Measuring cylinder, 100 ml to 200 ml capacity.

4.6 Burette, 10 ml capacity.

4.7 Water applicator, for adding a fine spray of water to the sample, having a capacity greater than 200 ml and 5 ml calibration divisions.

4.8 Mixing bowl, hemispherical of 30 cm diameter.

4.9 Rubber gloves.

4.10 Drying trays or pans, having dimensions that permit the sample to be spread to a thickness of less than 30 mm.

The trays shall be made of corrosion-resistant and heat-resistant material such as stainless steel, glass or enamel plate.

4.11 Drying oven, ventilated, with forced circulation of air or inert gas, regulated at a temperature of $105\text{ °C} \pm 5\text{ °C}$.

5 Sampling

5.1 General

TML figures are required to be updated on a periodic basis, usually six monthly or when there is a known change to the process used to produce the material. The reported figure should be the mean of samples taken during the period.

To ensure that the TML result is representative, increments of the material shall be taken either

- a) while a stockpile is being built up or broken down or
- b) while loading or discharging a vessel.

These increments are combined to form the sample used to determine TML.

NOTE 1 The sample used to determine TML should not be used to determine moisture.

NOTE 2 Stationary sampling of stockpiles should never be used for the determination of TML. This method of sampling can only be used to provide an indicative moisture value for use during the planning of shipping schedules.

5.2 Laboratory sample

Samples for the determination of TML shall be taken in accordance with ISO 12743. The laboratory sample shall not weigh less than 5 kg. To minimize changes to the flow characteristics of the sample it shall not be oven dried or ground during its preparation.

5.3 Separation of test sample into test portions

Place the laboratory sample in the mixing bowl (4.8) and gently mix it thoroughly. Remove four test portions (A, B, C and D) from the mixing bowl as follows:

- a) Test portion A

Take approximately 1,2 kg of sample which is to be used for determining the moisture content of the sample "as received". This test is performed in accordance with ISO 10251. With routine samples, the result of this test provides the operator with a guide as to how much water to add to the samples, thereby speeding up the TML test.

- b) Test portion B

Take approximately 1,2 kg of sample. This sample is to be used for the preliminary TML test. Store this sample in an appropriately labelled airtight container.

- c) Test portion C

Take approximately 1,2 kg of sample. This sample is to be used for the first duplicate of the final TML test. Store this sample in an appropriately labelled airtight container.

- d) Test portion D

Take approximately 1,2 kg of sample. This sample is to be used for the second duplicate of the final TML test. Store this sample in an appropriately labelled airtight container.

6 Procedure

6.1 General

Copper, lead and zinc concentrates may undergo rapid changes in moisture when exposed to air, so all stages of the test should be accomplished in the shortest time period and shall definitely be completed within the day of commencement. Where possible, sample containers should be covered with plastic film or any other suitable airtight cover.

As more accurate results are obtained when the moisture of the test portion is close to the flow moisture point, a preliminary test shall be carried out. The result of this test is used to adjust the moisture of the final test portion to 1 % to 2 % below the flow moisture point.

6.2 Preparation of test portions

6.2.1 General

Test portions B, C and D are prepared, with test portion B prepared first to determine the preliminary flow moisture point in accordance with 6.2.2 to 6.3.5.

Once the preliminary flow moisture point has been determined, test portions C and D are then prepared and the main flow moisture point determined in accordance with 6.4.2 to 6.4.6.

6.2.2 Filling the mould

Place the mould on the centre of the flow table and fill it in three stages with the test portion as follows:

- a) the first charge, after tamping, shall aim to fill the mould to approximately one third of its depth;
- b) the second charge, after tamping, shall fill the mould to about two thirds of its depth;
- c) the third and final charge, after tamping, shall reach to just below the top of the mould (see Figure 1).

The quantity of test portion required to achieve each of these stages will vary from one material to another, but is readily established after experience has been gained on the packing characteristics of the material being tested.

6.2.3 Tamping pressure

The aim of tamping is to simulate the amount of compaction prevailing at the bottom of a shipboard cargo for the material being tested. The correct pressure to be applied via the tamper is calculated as follows:

$$p_T = \rho_D \times d_{\max} \times g \quad (1)$$

where

- p_T is the tamping pressure, in pascals;
- ρ_D is the bulk density, in kilograms per cubic metre;
- d_{\max} is the maximum depth of the cargo, in metres;
- g is the acceleration due to gravity (= 981 cm/s²).

If, when calculating the tamping pressure, there is no information available concerning the cargo depth use the maximum likely depth.

Alternatively, the pressure may be estimated from Table 2.

Table 2 — Tamping pressures for selected concentrates ^a

Typical concentrate type	Bulk density kg/m ³	Maximum cargo depth			
		2 m	5 m	10 m	20 m
Copper	2000	39 [2,8]	98 [6,9]	196 [13,9]	392 [27,7]
Lead	2100	41 [2,9]	103 [7,3]	206 [14,6]	412 [29,1]
Zinc	1950	38 [2,7]	96 [6,8]	192 [13,5]	384 [27,1]

^a Values in brackets are equivalent kgf when applied via a 30 mm diameter tamper head.

6.2.4 Tamping procedure

The number of tamping actions (applying the correct, steady pressure each time) should be about 35 for the bottom layer, 25 for the middle layer and 20 for the top layer. Tamping shall be performed successively over the complete area including the edges of the sample, to form a uniform surface for each layer (see Figure 1).

6.2.5 Removal of the mould

Tap the mould on its side until it becomes loose, leaving the material in the shape of a truncated cone on the flow table.

6.3 Determination of flow moisture point

6.3.1 General

The determination of the flow moisture point is carried out by controlled dropping of the flow table and observation of the sample, followed by addition of water if necessary as outlined in the following steps.

6.3.2 Dropping the flow table

Immediately after removing the mould, raise and drop the flow table up to 50 times through a height of 12,5 mm at a rate of 25 times/min. Whilst the flow table is going through these cycles, observe the behaviour of the material using the information provided in 6.3.3 as a guide for determining the flow state.

6.3.3 Identification of the flow state

The impacting action of the flow table causes the grains of the material to re-arrange themselves to produce compaction of the mass. As a result, the fixed volume of moisture contained in the material at any given level increases as a percentage of the total volume. A flow state is considered to have been reached when the moisture content and compaction of the material produce such a level of saturation that plastic deformation occurs. At this stage, the moulded sides of the cone may deform, giving a convex or concave profile (see Figure 2). With repeated action of the flow table, the cone continues to slump and to flow outwards. In certain materials, cracks may also develop on the top surface.

Further criteria to use when determining if the flow state has been reached are as follows:

- a) Cracking with the appearance of free moisture is not an indication of development of a flow state. In most cases, measurement of the deformation is helpful in deciding whether or not plastic flow has occurred. A template which, for example, will indicate an increase in diameter of up to 3 mm in any part of the cone, is a useful guide for this purpose.
- b) Measuring the diameter of the cone, at the base or at half height, will always be useful. By addition of water in increments of 0,3 % to 0,5 % by mass and applying 25 drops of the flow table, the first diameter increase will generally be between 1 mm and 5 mm and after a further increment in water content the base diameter would have expanded to between 5 mm to 10 mm.
- c) When the moisture content is approaching the flow moisture point, the cone begins to show a tendency to stick to the mould.
- d) When the cone is pushed off the table, it may leave tracks (stripes) of moisture on the table. If such stripes are seen, the moisture content may be above the flow moisture point. Slight deformation of the cone may appear at moisture contents lower the flow moisture point, but in that case the test portion will leave no moisture tracks when removed.

6.3.4 Determination of preliminary flow moisture point

If the material exhibits any of the properties described in 6.3.3, then the flow moisture point has been reached. Stop the flow table and immediately take a $200\text{ g} \pm 20\text{ g}$ portion of the material on the flow table and place in a pre-weighed drying tray or pan (4.10). Immediately weigh the sample and tray and determine the moisture as described in 6.5. When the moisture has been determined proceed with the main flow moisture point determination as described in 6.4.

If the material does not exhibit any of the properties described in 6.3.3 or simply crumbles and bumps off in fragments with successive drops of the table (see Figure 3), the flow moisture point has not been reached and more water needs to be added to the sample as described in step 6.3.5.

6.3.5 Addition of water for preliminary flow moisture point test

Once it has been ascertained that the material is not at the flow moisture point, stop the flow table and return the material to the mixing bowl. Using the water applicator (4.7) add between 5 ml and 10 ml of water; if necessary more water may be added. Thoroughly mix this added water into the material, either with rubber gloved fingers or an automatic mixer. Fill the mould again and repeat steps 6.2.2 to 6.3.4 until a flow state is reached.

NOTE The addition of water can also be achieved by measuring the mass of water added rather than the volume of water.

6.4 Procedure for the main flow moisture point determination

6.4.1 General

Once the preliminary flow moisture point has been determined on test portion B, the moisture content of test portions C and D are adjusted to approximately the last value that did not cause the flow state in the preliminary test.

6.4.2 Preparation of test portions for main flow moisture point determination

Prepare test portion C for the main flow moisture point test according to steps 6.2.2 to 6.2.5.



Figure 1 — Example of third stage of filling the mould



Figure 2 — Example of the material at the flow point

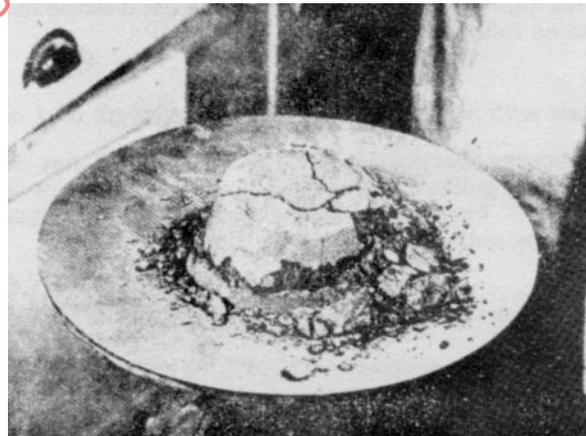


Figure 3 — Example of material crumbling but not at the flow point

6.4.3 Determination of main flow moisture point

Determine if the flow state has been reached according to 6.3.1 to 6.3.3. When these steps have been completed, stop the flow table and immediately take a 200 g ± 20 g portion of the material on the flow table and place in a pre-weighed drying tray or pan (4.10). Immediately weigh the sample and tray, cover and retain for moisture determination if required. When there are three 200 g samples, the oldest (lowest moisture) one can be returned to the mixing bowl.

If the material exhibits any of the properties described in 6.3.3 then the flow moisture point has been reached. Proceed to step 6.4.5.

If the material does not exhibit any of the properties described in 6.3.3 or simply crumbles and bumps off in fragments with successive drops of the table (see Figure 3), the flow moisture point has not been reached and more water needs to be added to the sample as described in 6.4.4.

6.4.4 Addition of water for main flow moisture point determination

Once it has been ascertained that the material is not at the flow moisture point, return any material remaining after the 200 g portion has been removed to the mixing bowl (4.8). Using the water applicator (4.7), add no more than 0,5 % of the mass of the test material (the lower the "preliminary" flow moisture point the smaller the increments). Thoroughly mix this added water into the material, either with rubber gloved fingers or an automatic mixer. Fill the mould again and repeat 6.4.2 and 6.4.3 until a flow state is reached.

NOTE The addition of water can also be achieved by measuring the mass of water added rather than the volume of water.

6.4.5 Selection of samples for moisture determination

When the flow state has been reached, select the last two 200 g moisture test portions. These shall be the moisture test portions taken just before and just after the flow state was achieved. Determine the moisture on these two samples as described in 6.5.

6.4.6 Duplicate main flow moisture point test

Determine the flow moisture point in test portion D following steps 6.4.2 to 6.4.5.

6.5 Moisture determination

Determine the moisture of the appropriate 200 g test portions using the procedure described in ISO 10251.

7 Calculation

Calculate the flow moisture point using the following equation:

$$\text{FMP} = \frac{M_{1C} + M_{2C} + M_{1D} + M_{2D}}{4} \quad (2)$$

where

FMP is the flow moisture point, in percent (*m/m*);

M_{1C} is the moisture content of test portion C, just below the flow moisture point, in percent (*m/m*);

M_{2C} is the moisture content of test portion C, just above the flow moisture point, in percent (*m/m*);

M_{1D} is the moisture content of test portion D, just below the flow moisture point, in percent (*m/m*);

M_{2D} is the moisture content of test portion D, just above the flow moisture point, in percent (m/m).

Calculate the transportable moisture limit using the following equation:

$$\text{TML} = \text{FMP} \times 0,9 \quad (3)$$

where TML is the transportable moisture limit, in percent (m/m).

8 Test report

The test report shall include the following information:

- a) identification of the sample;
- b) reference to this International Standard, i.e., ISO 12742;
- c) the transportable moisture limit (TML) of the sample, expressed as a percentage of the sample by mass;
- d) the moisture content of the test portions, just above and just below the flow moisture point, expressed as a percentage of the sample by mass;
- e) the tamping pressure used or simulated conditions attempted.

STANDARDSISO.COM : Click to view the full PDF of ISO 12742:2000

Annex A (normative)

Description of equipment used to determine TML

A.1 Scope

This annex describes the design of equipment suitable for determining TML by the flow table method.

A.2 Design requirements for the flow table and frame

The flow table apparatus shall be constructed in accordance with Figure A.1. The apparatus shall consist of an integrally cast iron frame and a circular rigid table top $254 \text{ mm} \pm 2,5 \text{ mm}$ in diameter, with a shaft attached perpendicular to the table top by means of a screw thread. The table top, to which the shaft with its integral contact shoulder is attached, shall be mounted on a frame in such a manner that it can be raised and dropped vertically through the specified height with a tolerance in height of $\pm 0,13 \text{ mm}$ for new tables and $\pm 0,39 \text{ mm}$ for tables in use, by means of a rotating cam. The table top shall have a fine machined plane surface, free of blowholes and surface defects, and shall be as shown in Figure A.1. The table top shall be of cast brass or bronze having a Rockwell hardness number not less than HRB 25 with an edge thickness of 8 mm, and shall have six integral radial stiffening ribs. The table top and attached shaft shall weigh $4 \text{ kg} \pm 0,05 \text{ kg}$ and the mass shall be symmetrical around the centre of the shaft.

The cam and vertical shaft shall be of medium carbon tool steel, hardened where indicated in Figure A.1. The shaft shall be straight and the difference between the diameter of the shaft and the diameter of the bore of the frame shall be not less than 0,05 mm and not more than 0,08 mm for new tables and shall be maintained at between 0,05 mm and 0,26 mm for tables in use. The end of the shaft shall not fall upon the cam at the end of the drop, but shall make contact with the cam not less than 120° from the point of drop. The face of the cam shall be a smooth spiralled curve of uniformly increasing radius from 13 mm to 32 mm in 360° and there shall be no appreciable jar as the shaft comes into contact with the cam. The cam shall be so located and the contact faces of the cam and shaft shall be such that the table does not rotate more than one revolution in 25 drops. The surfaces of the frame and of the table which come into contact and the end of the drop shall be maintained smooth, plane, horizontal and parallel with the upper surface of the table and shall make continuous contact over a full 360° .

The supporting frame of the flow table shall be integrally cast of fine-grain, high grade cast iron. The frame casting shall have three integral stiffening ribs extending the full height of the frame and located 120° apart. The top of the frame shall be chilled to a depth of approximately 6,4 mm and the face shall be ground and lapped square with the bore to give 360° contact with the shaft shoulder. The underside of the base of the frame shall be ground to secure a complete contact with the steel plate beneath.

The flow table may be driven by a motor, connected to the cam shaft through an enclosed worm gear speed reducer and flexible coupling. The speed of the cam shaft shall be approximately $1,666 \text{ s}^{-1}$ (100 rpm). The motor drive mechanism shall not be fastened or mounted on the table base plate or frame.

The performance of a flow table shall be considered satisfactory if, in calibration tests, the table gives a flow value that does not differ by more than five percentage points from flow values obtained with a suitable calibration material.

A.3 Design requirements for the flow table mounting

The flow table frame shall be tightly bolted to a cast iron or steel plate at least 25 mm thick and 250 mm square. The top surface of this plate shall be machined to a smooth plane surface. The plate shall be anchored to the top of a concrete pedestal by four 13 mm bolts that pass through the plate and are embedded at least 150 mm in the pedestal. The pedestal shall be cast inverted on the base plate. A positive contact between the base plate and the

pedestal shall be maintained at all points. No nuts or other such levelling devices shall be used between the plate and the pedestal. Levelling shall be effected by suitable means under the base of the pedestal.

The pedestal shall be 250 mm to 275 mm square at the top and 375 mm to 400 mm square at the bottom, 625 mm to 750 mm in height and shall be of monolithic construction, cast from concrete weighing at least 2 240 kg/m³. A stable gasket cork pad 13 mm thick and approximately 102 mm square, shall be inserted under each corner of the pedestal. The flow table shall be checked frequently for levelness of the table top, stability of the pedestal, and tightness of the bolts and nuts in the table base and the pedestal plate. A torque of 27 N·m is recommended when tightening those fastenings.

The table top, after the frame has been mounted on the pedestal, shall be level along two diameters at right angles to each other, in both the raised and lowered positions.

A.4 Flow table lubrication

The vertical shaft of the table shall be kept clean and shall be lightly lubricated with a light oil (SAE-10). Oil shall not be present between the contact faces of the table top and the supporting frame. Oil on the cam face will lessen wear and promote smoothness of operation. The table should be raised and permitted to drop a dozen or more times just prior to use if it has not been operated for some time.


A.5 Design requirements for the mould

The mould for casting the flow specimen shall be of cast bronze or brass, constructed as shown in Figure A.1. The Rockwell hardness number of the metal shall be not less than HRB 25. The diameter of the top opening shall be 69,8 mm ± 0,5 mm for new moulds and 7 mm + 1,3 mm and – 0,05 mm for moulds in use. The surfaces of the base and top shall be parallel and at right angles to the vertical axis of the cone. The mould shall have a minimum wall thickness of 5 mm. The outside of the top edge of the mould shall be shaped to provide an integral collar for convenient lifting of the mould. All surfaces shall be machined to a smooth finish. A circular shield approximately 254 mm in diameter, with a centre opening approximately 102 mm in diameter, made of non-absorbing material not attacked by the test material, shall be used with the flow mould to prevent mortar from spilling on the table top.

A.6 Design requirements for the spring-loaded tamper

Figure A.2 shows a suitable spring-loaded tamper design. Any spring-loaded tamper shall allow a controlled pressure to be applied via a 30 mm diameter tamper head.


Dimensions in millimetres

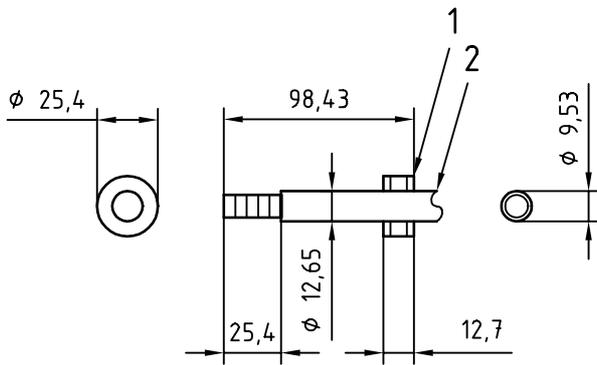

Key

- 1 Set screw
- 2 To flexible shaft

a) Cam shaft in medium-carbon tool steel

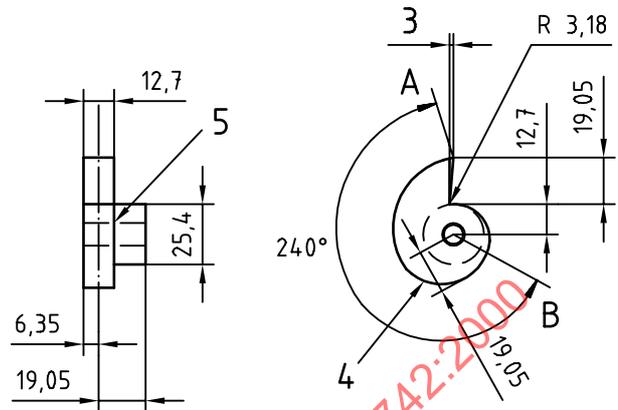


Key

- 3 Undercut 1,59
- 4 Working face of cam
- 5 9,53 Tap

NOTE The curve from 'B' to 'A' is a smooth spiral of uniformly increasing radius from 12,7 to 31,75 in 360°.

b) Cam in medium-carbon tool steel


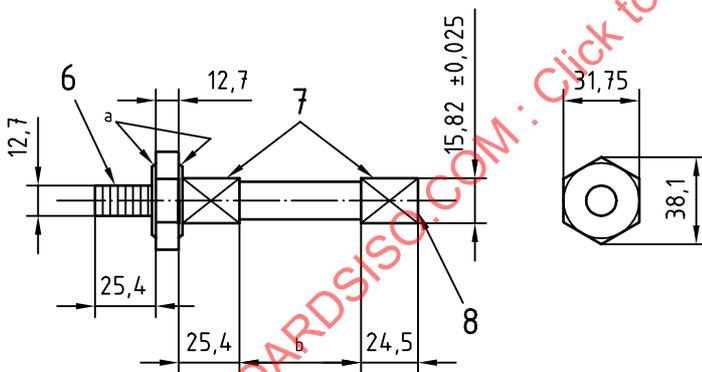


Key


- 6 Thread 0,5 - 20, UNF-2A
- 7 Bearings
- 8 Hardened end surface

- ^a Machine and lap square with shaft to give a 360° contact
- ^b Approximately 28,58 adjusted to give a drop of 12,7 ± 0,127

c) Shaft in medium-carbon tool steel

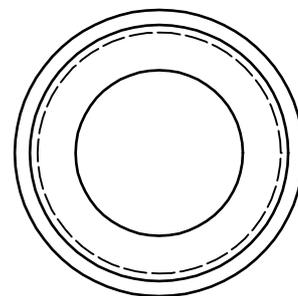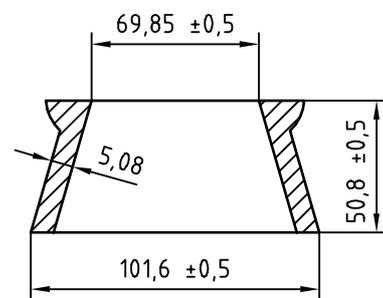

d) Mould in bronze at Rockwell HRB 25

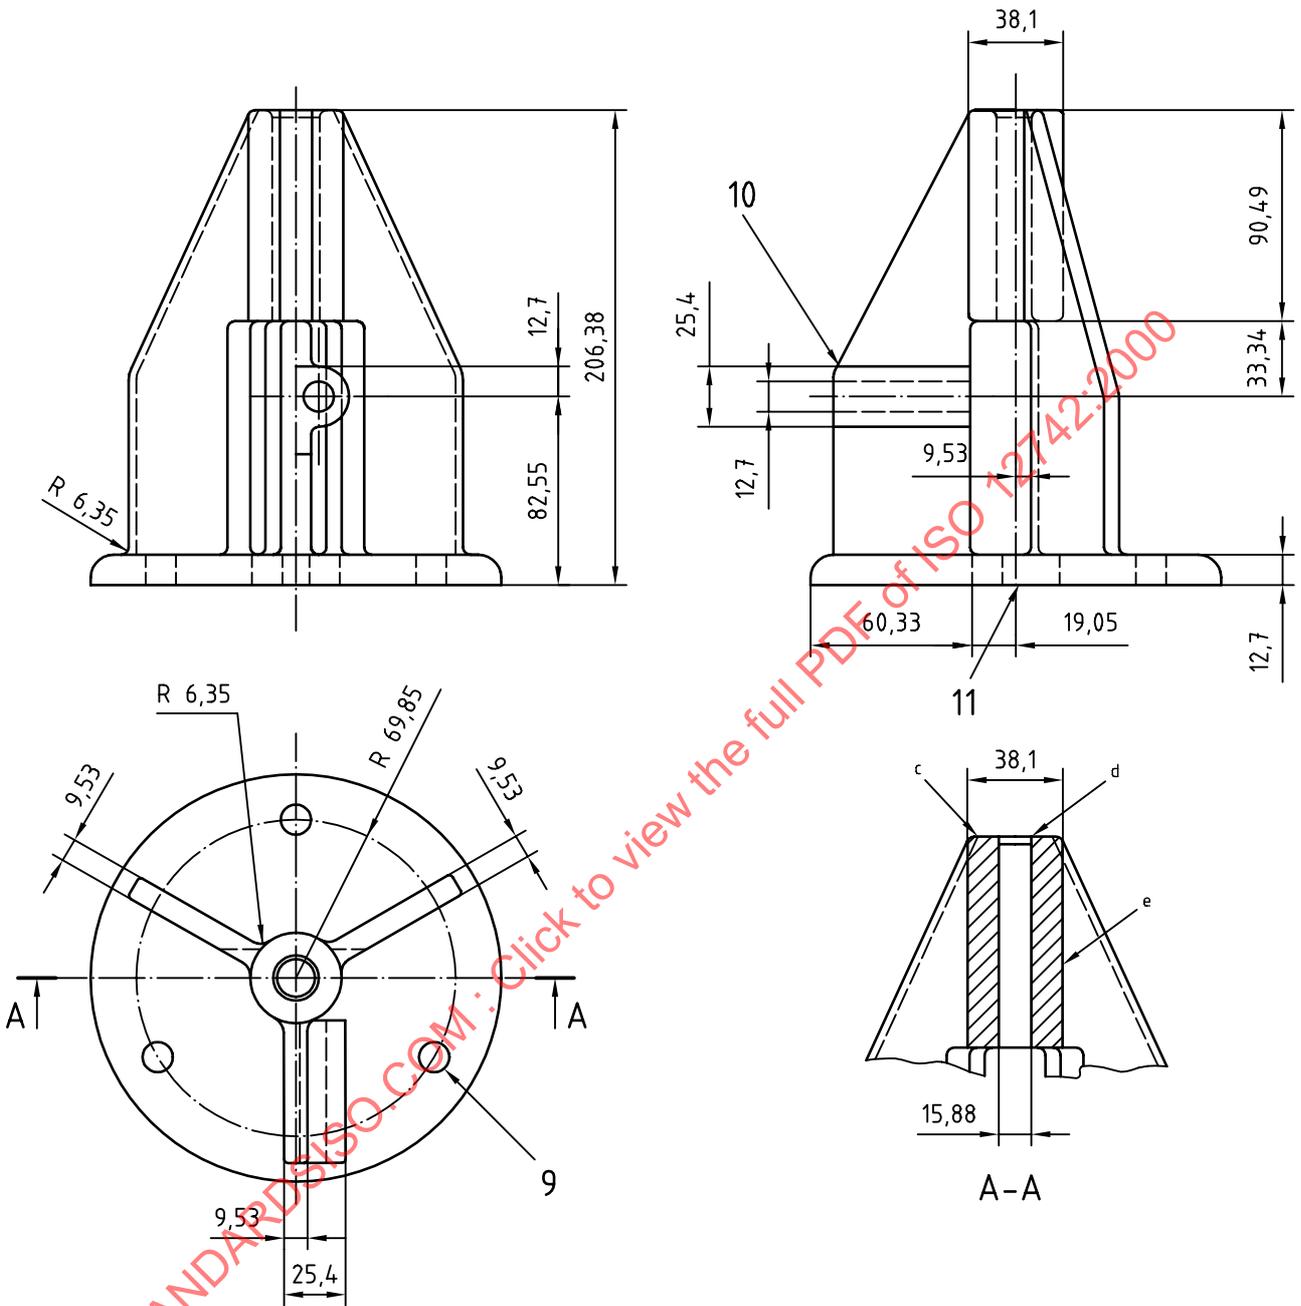

Key

- 9 11,11 holes
- 10 Spot face
- 11 8,1 hole in base

^c Chill to a depth of approximately 6,35; grind and lap face square with bore to give a 360° contact with shaft shoulder

^d Bevel to a depth of 1,5 at 45°

^e Bore and ream

e) Stand in fine-grain, high-grade cast iron