
**Textile floor coverings —
Determination of mass loss, fibre bind
and stair nosing appearance change
using the Lisson Tretrad machine**

*Revêtements de sol textiles — Détermination de la perte de masse,
de la sensibilité au défibrage et du changement d'aspect au nez de
marche à l'aide la machine Lisson Tretrad*

STANDARDSISO.COM : Click to view the full PDF of ISO 12951:2020



STANDARDSISO.COM : Click to view the full PDF of ISO 12951:2020



COPYRIGHT PROTECTED DOCUMENT

© ISO 2020

All rights reserved. Unless otherwise specified, or required in the context of its implementation, no part of this publication may be reproduced or utilized otherwise in any form or by any means, electronic or mechanical, including photocopying, or posting on the internet or an intranet, without prior written permission. Permission can be requested from either ISO at the address below or ISO's member body in the country of the requester.

ISO copyright office
CP 401 • Ch. de Blandonnet 8
CH-1214 Vernier, Geneva
Phone: +41 22 749 01 11
Fax: +41 22 749 09 47
Email: copyright@iso.org
Website: www.iso.org

Published in Switzerland

Contents

	Page
Foreword	iv
1 Scope	1
2 Normative references	1
3 Terms and definitions	1
4 Principle	2
5 Apparatus	2
5.1 Lisson Tretrad machine	2
5.1.1 General	2
5.1.2 Bed plate	3
5.1.3 Tretrad assemblies	3
5.1.4 Vacuum cleaning system	3
6 Sampling and selection of test specimens	5
7 Atmosphere for conditioning and testing	5
8 Calibration	6
8.1 Choice of the calibration carpet	6
8.1.1 Method 1	6
8.1.2 Method 2	6
8.2 Calibration of the apparatus	6
9 Procedure	7
9.1 General	7
9.2 Test A — Determination of mass loss of textile floor coverings	7
9.3 Test B — Determination of stair nosing: appearance change of textile floor coverings	8
9.4 Test C — Determination of fibre bind on synthetic loop pile carpets	8
9.5 Test D — Determination of fibre bind (hairiness) on needled floorcoverings and floor coverings without pile	9
10 Calculation and expression of results	9
10.1 Test A	9
10.2 Test B	10
10.3 Test C	10
10.4 Test D	10
10.5 Unusual phenomena	11
11 Test report	11
Annex A (informative) Examples of failure at 400 cycles	12

Foreword

ISO (the International Organization for Standardization) is a worldwide federation of national standards bodies (ISO member bodies). The work of preparing International Standards is normally carried out through ISO technical committees. Each member body interested in a subject for which a technical committee has been established has the right to be represented on that committee. International organizations, governmental and non-governmental, in liaison with ISO, also take part in the work. ISO collaborates closely with the International Electrotechnical Commission (IEC) on all matters of electrotechnical standardization.

The procedures used to develop this document and those intended for its further maintenance are described in the ISO/IEC Directives, Part 1. In particular, the different approval criteria needed for the different types of ISO documents should be noted. This document was drafted in accordance with the editorial rules of the ISO/IEC Directives, Part 2 (see www.iso.org/directives).

Attention is drawn to the possibility that some of the elements of this document may be the subject of patent rights. ISO shall not be held responsible for identifying any or all such patent rights. Details of any patent rights identified during the development of the document will be in the Introduction and/or on the ISO list of patent declarations received (see www.iso.org/patents).

Any trade name used in this document is information given for the convenience of users and does not constitute an endorsement.

For an explanation of the voluntary nature of standards, the meaning of ISO specific terms and expressions related to conformity assessment, as well as information about ISO's adherence to the World Trade Organization (WTO) principles in the Technical Barriers to Trade (TBT), see www.iso.org/iso/foreword.html.

This document was prepared by Technical Committee ISO/TC 219, *Floor coverings*, in collaboration with the European Committee for Standardization (CEN) Technical Committee CEN/TC 134, *Resilient, textile and laminate floor coverings*, in accordance with the Agreement on technical cooperation between ISO and CEN (Vienna Agreement).

This third edition cancels and replaces the second edition (ISO 12951:2015), which has been technically revised.

The main changes compared to the previous edition are as follows:

- two different methods are described for calibrating the apparatus;
- a better description of how to assess test C is provided;
- examples of failure are given in [Annex A](#).

Any feedback or questions on this document should be directed to the user's national standards body. A complete listing of these bodies can be found at www.iso.org/members.html.

Textile floor coverings — Determination of mass loss, fibre bind and stair nosing appearance change using the Lisson Tretrad machine

1 Scope

This document specifies four methods of test for textile floor coverings (with or without an underlay, see [Clause 9](#)) using the Lisson Tretrad machine.

- test A: determination of mass loss of textile floor coverings, also used to assess fibre bind of synthetic pile carpets;
- test B: determination of stair nosing appearance change of textile floor coverings;
- test C: determination of fibre bind on synthetic loop pile carpets;
- test D: determination of fibre bind (hairiness) on needled floor coverings and floor coverings without pile.

2 Normative references

The following documents are referred to in the text in such a way that some or all of their content constitutes requirements of this document. For dated references, only the edition cited applies. For undated references, the latest edition of the referenced document (including any amendments) applies.

ISO 139, *Textiles — Standard atmospheres for conditioning and testing*

ISO 1765, *Machine-made textile floor coverings — Determination of thickness*

ISO 1957, *Machine-made textile floor coverings — Selection and cutting of specimens for physical tests*

ISO 2424, *Textile floor coverings — Vocabulary*

ISO 8543, *Textile floor coverings — Methods for determination of mass*

ISO 9405, *Textile floor coverings — Assessment of changes in appearance*

EN 1307:2014+A3:2018, *Textile floor coverings — Classification*

3 Terms and definitions

For the purposes of this document, the terms and definitions given in ISO 2424 and the following apply.

ISO and IEC maintain terminological databases for use in standardization at the following addresses:

- ISO Online browsing platform: available at <https://www.iso.org/obp>
- IEC Electropedia: available at <http://www.electropedia.org/>

3.1

mass loss per unit area

m_v

difference between the sample mass before and after the wear test, related to the tested area

Note 1 to entry: See [10.1](#).

3.2 relative mass loss

m_{rv}
 <pile carpet> ratio of the *mass loss per unit area* (3.1), as a percentage of the mass of pile per unit area above the substrate

Note 1 to entry: The mass of pile per unit area above the substrate is determined in accordance with ISO 8543.

4 Principle


The specimens of a textile floor covering are exposed, at constant load and slippage and for a prescribed number of double passages, to the action of a four-footed wheel (Tretrad), the feet of which are fitted with interchangeable sole coverings.

5 Apparatus

5.1 Lisson Tretrad machine

5.1.1 General

A Lisson Tretrad machine comprises a bed plate, a vacuum cleaning system, and two Tretrad assemblies (see Figure 1).

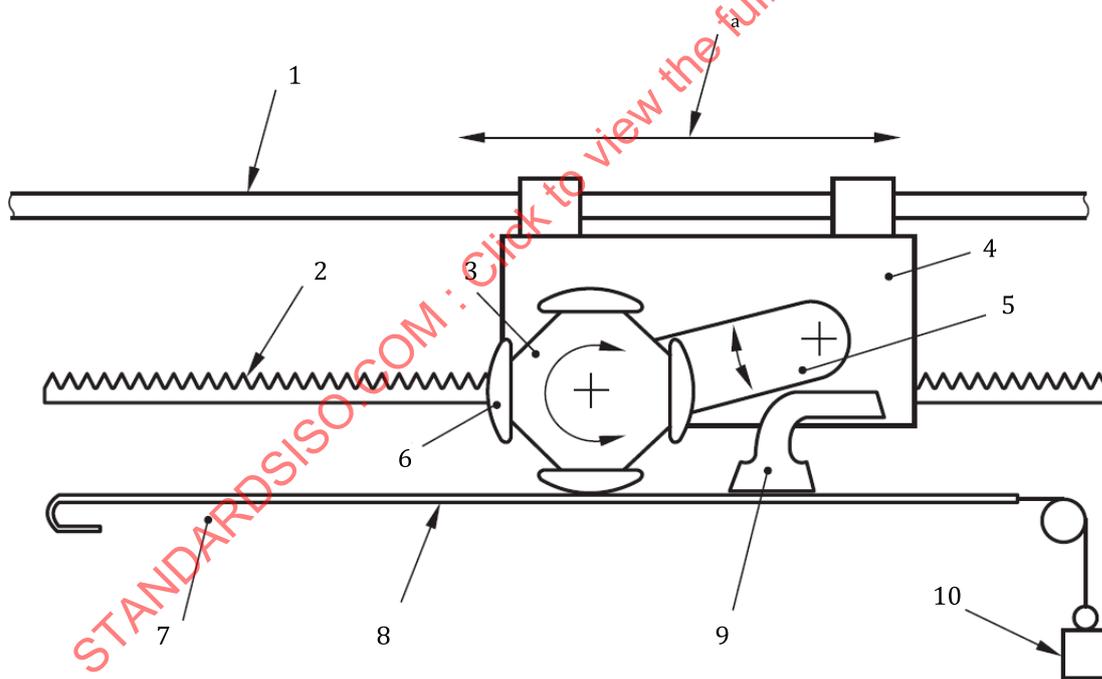

Key

- | | |
|-----------------|----------------------------|
| 1 support | 7 bed plate |
| 2 cog bar | 8 specimen |
| 3 Tretrad wheel | 9 vacuum suction nozzle |
| 4 frame | 10 tension weight |
| 5 drive | a Movement of the Tretrad. |
| 6 foot | |

Figure 1 — Lisson Tretrad machine

5.1.2 Bed plate

The bed plate faces are parallel to the track travelled by the Tretrad feet and the front edge of the plate is rounded with a 10 mm radius to simulate a stair nosing.

The test surface is formed by the width of the Tretrad feet and the length of the track over which the Tretrad runs. The track length shall be determined for each machine by measuring the distance between the front edge of the bed plate and the perpendicular projection of the Tretrad axis at its furthestmost point of reversal. The length of track shall be (800 ± 40) mm.

Two clamps mounted at each end of the bed plate are used to hold each specimen under tension. The tension is applied by means of a weighted third clamp, each specimen being subjected to a tension weight of (20 ± 2) kg.

5.1.3 Tretrad assemblies

The Lisson Tretrad machine has two Tretrad assemblies, each of which comprises a Tretrad mounted in a frame that is free to rotate around an axis that is 135 mm to 140 mm above the upper surface of the bed plate.

Each Tretrad comprises four equally spaced legs with rigidly attached feet platforms.

The surface of the foot platform has a radius of curvature of $(112,5 \pm 1,0)$ mm, a circumferential length of $(100,0 \pm 1,0)$ mm, and a width of $(55,0 \pm 0,5)$ mm. The ends of the contact surfaces of the platforms are rounded with a radius of $(4,0 \pm 0,5)$ mm.

The vertical weight applied by the Tretrad feet, in the stationary state, shall be $(15,0 \pm 2,0)$ kg measured without the soles in position.

The linear speed of the Tretrad is $(0,28 \pm 0,02)$ m/s and the peripheral speed of the Tretrad with sole coverings is $(20,0 \pm 2,0)$ % greater than the linear speed. This causes slippage of the feet on the test specimen in addition to the compressive action.


At the front edge of the bed plate, the Tretrad runs beyond the bed and is held horizontally by a height adjustable stopper, in such a way that the lower edge of the foot (without sole covering material) can be adjusted between 5 mm below and 5 mm above the level of the surface of the bed plate.

At the points of reversal, the Tretrad remains stationary for approximately 1 s; during this stoppage at the forward point of reversal, the Tretrad is rotated through an angle (should be around 45°) to ensure that the feet walk evenly over the length of the test area.

5.1.4 Vacuum cleaning system

Suction nozzles follow the horizontal movement of the Tretrad assemblies. The nozzles are flexibly mounted and are equipped on their undersides with slides that rest on the edges of the test specimens, thereby not imposing any wear on the specimens.

Each nozzle has the dimensions shown in [Figure 2](#) and is connected to the vacuum cleaner to extract the abraded fibre.

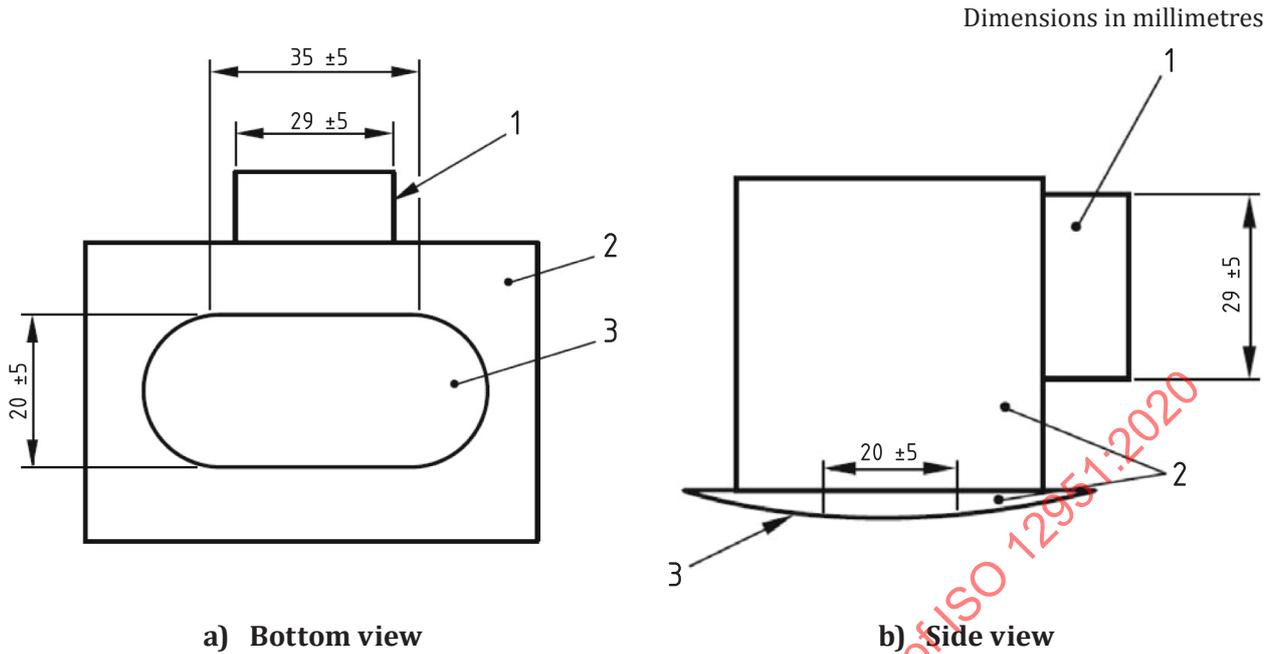

Key

- 1 connection to vacuum cleaner
- 2 nozzle casing
- 3 nozzle mouth

Figure 2 — Vacuum inlet

The vacuum cleaner performance shall be such as to produce airflow of at least 30 l/s measured at the connection point of the nozzles by an appropriate anemometer in order to remove loose fibre from the surface of the specimens.

5.2 Other equipment.

5.2.1 Sole coverings. The sole coverings¹⁾ shall be made from vulcanized styrene butadiene rubber (SBR) with silicic acid-based white filler additives and meet the requirements specified in [Table 1](#). The sole coverings shall have a wave profile, which is the wear surface, on one face.

The sole covering material shall be stored in the dark and air exchange shall be avoided. After long storage (e.g. two years), the sole coverings shall be validated by the calibration procedure (calibration carpet).

Table 1 — Properties of sole coverings for Lisson Tretrad machine

Size	minimum (190 ± 2) mm long by (55 ± 0,5) mm wide
Thickness	(2,5 ± 0,3) mm
Hardness	(90 ± 5) Shore A
Wavelength	(13,0 ± 0,5) mm
Amplitude	(2,0 ± 0,5) mm
Profile height	(0,6 ± 0,1) mm

1) Sole coverings are available from TFI Aachen GmbH — Charlottenburger Allee 41, DE-52068 Aachen, Germany. This information is given for the convenience of users of this document and does not constitute an endorsement by ISO of these products. Equivalent products may be used if they can be shown to lead to similar results.

5.2.2 Balance, with a reading accuracy of 0,01 g.

5.2.3 External vacuum cleaner, equipped with a rotating brush, with or without beaters.

5.2.4 Reference photographs, for assessment of fibre bind of loop pile carpets²⁾.

5.2.5 Reference photographs, for assessment of fibre bind on needled floor coverings³⁾.

6 Sampling and selection of test specimens

Select the specimens in accordance with ISO 1957.

Test A: Sample at least four specimens, each 1 500 mm in the direction of manufacture (machine direction) by 100 mm in the across-machine direction. In the case of floor coverings without pile, two specimens shall be sampled in the machine direction (1 500 mm) and two specimens shall be sampled in the across-machine direction (1 500 mm).

Test B: Sample at least four specimens, each 1 500 mm in the direction of manufacture (machine direction) by 100 mm in the across-machine direction.

Test C: Sample at least four specimens, each 1 500 mm in the direction of manufacture (machine direction) by 100 mm in the across-machine direction.

Tests D: Sample two specimens, each 1 500 mm in the machine direction by 100 mm in the across machine direction; and two specimens, each 100 mm in the machine direction by 1 500 mm in the across machine direction.

Tiles intended for test A to D shall be cut and assembled into the appropriate dimensions of the required specimens. Where appropriate, unsealed cut edges shall be sealed to prevent edge tuft loss during the test.

7 Atmosphere for conditioning and testing

The specimens shall be conditioned for at least 48 h in the standard atmosphere for testing textiles specified in ISO 139, prior to testing in the same atmosphere. The specimens shall be laid out singly, use surface uppermost.

2) These standard photographs are available from TFI Aachen GmbH — Charlottenburger Allee 41, DE-52068 Aachen, Germany. This information is given for the convenience of users of this document and does not constitute an endorsement by ISO of these products. Equivalent products may be used if they can be shown to lead to similar results.

3) These standard photographs are available from CSTB, 84 Avenue Jean Jaurès, Champs sur Marne, 77447 Marne la Vallée Cedex 2, France. This information is given for the convenience of users of this document and does not constitute an endorsement by ISO of these products. Equivalent products may be used if they can be shown to lead to similar results.

8 Calibration

8.1 Choice of the calibration carpet

8.1.1 Method 1

The test apparatus shall be checked with a calibration carpet⁴⁾ and calibrated by adjusting the number of to and fro transverse cycles set for that calibration carpet. This calibration covers the whole apparatus. If the calibration fails, the separate settings shall be checked.

8.1.2 Method 2

The test apparatus shall be checked with a control carpet, which has been tested on at least two to three different Lisson Tretrad machines and where the mass loss has been set. This is calibrated by adjusting the number of to and fro transverse cycles set for that control. This calibration covers the whole apparatus. If the calibration fails, the separate settings shall be checked.

8.2 Calibration of the apparatus

The Tretrad machine shall be calibrated against the mass loss of the calibration carpet described in 8.1. The number of cycles is adjusted to result in a mass loss (in g/m²) to correspond within a tolerance spread of $\pm 7,5\%$ to the mass loss (in g/m²) of the calibration carpet.

The tests shall be carried out at standard atmosphere (ISO 139). For conditioning, hang up the specimens singly or lay them out singly with the use-surface uppermost in the same atmosphere for at least 48 h. Test specimens shall be conditioned twice, i.e. at the beginning and after the Tretrad test, before the mass of the specimens is measured. The conditioning, including after the test, is extremely important for the determination of the correct number of treads at the calibration.

Determine the exact area treated by the Tretrad machine. The stressed area is the product of the width of the Tretrad feet (5,5 cm) and the track length of the wheels. The traverse length is the measure from the stair edge in the front of the table to the opposite stop position of the wheels.

Take for this measure the point below the wheel axis and calculate the average after a least 10 movements. The traverse length shall be (80 ± 4) cm. If not, correct the machine accordingly by changing the position of the metal strip for the contact switch.

The specimens are signed crossways with a line on one end on the pile side. Always clamp the specimens on the machine in such a way that the specimen end with the line is next to the stair edge of the table.

The specimens have to be stretched again with the 20 kg weight of the machine after the first 500 cycles.

The vacuum cleaner of the machine shall work continuously. Ensure the nozzle is positioned symmetrically above the stressed area and is always in contact with the specimen surface. If not, provide the machine for a longer pair of plastic tubes.

Start the calibration at the first run with 2 000 cycles on the stop counter. If the average mass loss of the first two specimens corresponds within a tolerance spread of $\pm 7,5\%$ to the mass loss (in g/m²) of the calibration carpet, continue testing with another two calibration specimens for confirmation. If the first two results are not within this range, correct the number of cycles appropriately at the next tests. The number of treads shall not be lower than 1 800 and not higher than 2 200.

The outcome of the calibration procedure gives a number of cycles necessary to obtain a mass loss of the calibration carpet corresponding to the mass loss that is set for the calibration carpet (within the

4) A standard carpet, supplied with calibration details, is available from TFI Aachen GmbH — Charlottenburger Allee 41, DE-52068 Aachen, Germany. This information is given for the convenience of users of this document and does not constitute an endorsement by ISO of this product. Equivalent products may be used if they can be shown to lead to similar results.

specified tolerance spread of $\pm 7,5 \%$). These test conditions (number of treads) then shall be applied for the normal testing.

The calibration shall be repeated regularly, especially after a repair and after a new delivery of sole covering material.

9 Procedure

9.1 General

Prior to testing, clean the specimen with the vacuum cleaner (5.2.3), giving four passes in each direction.

Fit the test specimen over the leading 10 mm radius rounded edge of the Lisson Tretrad bed plate (5.1.2) to the forward mount and clamp on the table under a tension of (20 ± 2) kg.

Test specimens that can become distorted during the test shall be stabilized by fixing them to the bed plate or to an additional plate where sample can be glued on. For this purpose, first fix single-sided tape to the underside of the specimens and then attach the specimens to the bed plate by means of double-sided tape. This allows for removal of the specimens without mass change (in this case, omit the pretension).

Specimens with a distinct pile lay shall be fitted to the bed plate with the pile lay in the direction of the bed plate leading edge.

9.2 Test A — Determination of mass loss of textile floor coverings

This test is also used to assess fibre bind of synthetic pile carpets.

In case of floor coverings without pile, two specimens shall be sampled in the machine direction and two specimens shall be sampled in the cross-machine direction.

Weigh the test specimens individually to determine m_1 (see 10.1) to the nearest 0,01 g, and then mount them on the bed plate as described in 9.1.

If the floor covering is usually fitted with an underlay, then the specimen shall be mounted over the underlay it is intended to be used with.

Adjust the height of each Tretrad in relation to the bed plate in accordance with Table 2.

Fit new sole coverings to the Tretrad before each test.

The tests shall be performed with the vacuum cleaner turned on continuously.

Subject the specimens to 500 double passages of the Tretrad. Then, readjust the clamping tension to (20 ± 2) kg. Operate the machine to the remaining number of the calibrated total double passages of the Tretrad.

Table 2 — Adjustment of wheel height, test A

Total thickness of specimen measured according to ISO 1765 mm	Adjustment of wheel height in relation to surface of bed plate mm
$\leq 10,0$	-5
$> 10,0$	0
$\leq 10,0$ plus underlay	0
$> 10,0$ plus underlay	+5

At the end of the test, clean the specimens with four passages of the vacuum cleaner (5.2.3), then lay the specimen use-surface uppermost in the standard atmosphere. After about 48 h, weigh the specimen to determine m_2 (see 10.1) to the nearest 0,01 g.

9.3 Test B — Determination of stair nosing: appearance change of textile floor coverings

Mount the test specimens on the bed plate as described in 9.1.

Specimens with a distinct pile lay shall be fitted to the bed plate with the pile lay in the direction of the bed plate leading edge. In the case of patterned carpets, significant parts of the pattern shall be placed at the leading edge.

If the floor covering is usually fitted with an underlay on stairs, then the specimen shall be mounted over the underlay it is intended to be used with.

Adjust the height of each Tretrad in relation to the bed plate in accordance with Table 3.

Fit new sole coverings to the Tretrad before each test.

The tests shall be performed with the vacuum cleaner turned on continuously.

Subject the specimen to 500 double passages of the Tretrad. Then, readjust the clamping tension to (20 ± 2) kg. Operate the machine to the remaining number of the calibrated total double passages of the Tretrad.

Table 3 — Adjustment of wheel height, test B

Total thickness of specimen measured according to ISO 1765 mm	Adjustment of wheel height in relation to surface of bed plate mm
≤ 10,0	-5
> 10,0	0
≤ 10,0 plus underlay	0
> 10,0 plus underlay	+5

At the end of the test, clean the specimens with four passages of the vacuum cleaner (5.2.3), then lay the specimen, use surface uppermost, in the standard atmosphere for 24 h.

9.4 Test C — Determination of fibre bind on synthetic loop pile carpets

Mount the test specimens on the bed plate as described in 9.1.

Adjust the height of each Tretrad in relation to the bed plate in accordance with Table 4.

Fit new sole coverings to the Tretrad before each test.

The tests shall be performed with the vacuum cleaner turned off and the nozzles raised above the surface of the specimens.

Subject the specimens to 400 double passages and then assess in accordance with 10.3.

Table 4 — Adjustment of wheel height, test C

Total thickness of specimen measured according to ISO 1765 mm	Adjustment of wheel height in relation to surface of bed plate mm
≤ 10,0	-5
> 10,0	0

9.5 Test D — Determination of fibre bind (hairiness) on needed floorcoverings and floor coverings without pile

Two specimens shall be sampled in the machine direction and two specimens shall be sampled in the cross-machine direction. Mount the test specimens on the bed plate as described in 9.1.

Adjust the height of each Tretrad in relation to the bed plate in accordance with Table 5.

Fit new sole coverings to the Tretrad before each test.

The tests shall be performed with the vacuum cleaner turned off and the nozzles raised above the surface of the specimens.

Subject the specimens to 200 double passages and then assess in accordance with 10.4.

Table 5 — Adjustment of wheel height, test D

Total thickness of specimen measured according to ISO 1765 mm	Adjustment of wheel height in relation to surface of bed plate mm
≤ 10,0	-5
> 10,0	0

10 Calculation and expression of results

10.1 Test A

Calculate the mass loss per unit area m_v in g/m² according to Formula (1):

$$m_v = (m_1 - m_2)/A \quad (1)$$

where

m_1 is the mass of the initial conditioned specimen, in grams;

m_2 is the mass of the final conditioned specimen, in grams;

A is the tested area of the specimen in square meter [width of Tretrad foot (55 ± 0,5) mm × length of Tretrad track according to 5.1.2].

Calculate the mean.

When $m_2 > m_1$, then let $m_v = 0$.

In the case of pile carpets, calculate the I_{TR} index according to Formula (2):

$$I_{TR} = 0,19 \sqrt{m_{AP}} \times \left(\frac{100 - m_{rv}}{100} \right) \quad (2)$$

where

ISO 12951:2020(E)

m_{AP} is the mass per unit area above the substrate in grams per square metre, determined in accordance with ISO 8543;

m_{rv} is the relative mass loss expressed as a percentage, $m_{rv} = (m_v/m_{AP}) \times 100$.

10.2 Test B

Assess the appearance of each specimen using at least three independent assessors according to the criteria given in Annex C of EN 1307:2014+A3:2018

Perform the assessment under the lighting conditions given in ISO 9405, each specimen being bent at an angle of 90° to simulate a stair edge.

Give individual results for each specimen.

Report the median of all results.

10.3 Test C

Assess the appearance using at least three independent assessors.

Assess against the most appropriate reference photographs (5.2.4) that show borderline of acceptability for fibre bind.

The reference photographs show

- a) fine gauge loop pile, and
- b) coarse gauge loop pile carpets, and
- c) hairiness + forming rolls, purely forming rolls which are sticking onto the floor covering or tufts torn out (see [Figures A1](#), [A2](#) and [A3](#)).

Perform the assessment by close inspection under the lighting conditions given in ISO 9405.

The specimen shall be bent through 180° with a radius of 15 mm to 20 mm.

On the specimen, select an area which is the most representative of the tested area and assess against the reference photographs.

Report whether the specimen is better or worse than the photographs, to either pass or fail the test.

Report the median of all results.

10.4 Test D

Assess separately the specimens sampled in the machine direction and the specimens sampled in the cross-machine direction.

Assess the appearance using at least three independent assessors.

Assess the appearance against the standard reference photographs (5.2.5) that show five grades of different hairiness.

Perform the assessment by close inspection under the lighting conditions given in ISO 9405.

Specimens shall be bent through 180° with a radius of 15 mm to 20 mm.

Assessment shall be carried out in three places (missing out the length of sample over the stair nosing) by each assessor.

Report the median of all results.