



**International
Standard**

ISO 13061-13

**Physical and mechanical properties
of wood — Test methods for small
clear wood specimens —**

**Part 13:
Determination of radial and
tangential shrinkage**

*Propriétés physiques et mécaniques du bois — Méthodes d'essais
sur petites éprouvettes de bois sans défauts —*

Partie 13: Détermination des retraits radial et tangentiel

**Second edition
2024-02**

STANDARDSISO.COM : Click to view the full PDF of ISO 13061-13:2024



COPYRIGHT PROTECTED DOCUMENT

© ISO 2024

All rights reserved. Unless otherwise specified, or required in the context of its implementation, no part of this publication may be reproduced or utilized otherwise in any form or by any means, electronic or mechanical, including photocopying, or posting on the internet or an intranet, without prior written permission. Permission can be requested from either ISO at the address below or ISO's member body in the country of the requester.

ISO copyright office
CP 401 • Ch. de Blandonnet 8
CH-1214 Vernier, Geneva
Phone: +41 22 749 01 11
Email: copyright@iso.org
Website: www.iso.org

Published in Switzerland

Contents

	Page
Foreword	iv
Introduction	v
1 Scope	1
2 Normative references	1
3 Terms and definitions	1
4 Principle	1
5 Apparatus	1
6 Preparation of test pieces	2
6.1 General.....	2
6.2 Test pieces for determining radial and tangential shrinkage.....	2
6.3 Inclination of annual rings of test pieces.....	2
6.4 Marking of measurement points.....	2
7 Procedure	3
7.1 Determination of the dimensions of test pieces in green or fully saturated condition.....	3
7.2 Determination of the dimensions of test pieces at oven-dry state.....	3
8 Calculation and expression of results	3
9 Test report	3

STANDARDSISO.COM : Click to view the full PDF of ISO 13061-13:2024

Foreword

ISO (the International Organization for Standardization) is a worldwide federation of national standards bodies (ISO member bodies). The work of preparing International Standards is normally carried out through ISO technical committees. Each member body interested in a subject for which a technical committee has been established has the right to be represented on that committee. International organizations, governmental and non-governmental, in liaison with ISO, also take part in the work. ISO collaborates closely with the International Electrotechnical Commission (IEC) on all matters of electrotechnical standardization.

The procedures used to develop this document and those intended for its further maintenance are described in the ISO/IEC Directives, Part 1. In particular, the different approval criteria needed for the different types of ISO document should be noted. This document was drafted in accordance with the editorial rules of the ISO/IEC Directives, Part 2 (see www.iso.org/directives).

ISO draws attention to the possibility that the implementation of this document may involve the use of (a) patent(s). ISO takes no position concerning the evidence, validity or applicability of any claimed patent rights in respect thereof. As of the date of publication of this document, ISO had not received notice of (a) patent(s) which may be required to implement this document. However, implementers are cautioned that this may not represent the latest information, which may be obtained from the patent database available at www.iso.org/patents. ISO shall not be held responsible for identifying any or all such patent rights.

Any trade name used in this document is information given for the convenience of users and does not constitute an endorsement.

For an explanation of the voluntary nature of standards, the meaning of ISO specific terms and expressions related to conformity assessment, as well as information about ISO's adherence to the World Trade Organization (WTO) principles in the Technical Barriers to Trade (TBT), see www.iso.org/iso/foreword.html.

This document was prepared by Technical Committee ISO/TC 218, *Timber*.

This second edition of cancels and replaces the first edition (ISO 13061-13:2016), which has been technically revised.

The main changes are as follows:

- changes in the sizes and measurements of test pieces.

A list of all parts in the ISO 13061 series can be found on the ISO website.

Any feedback or questions on this document should be directed to the user's national standards body. A complete listing of these bodies can be found at www.iso.org/members.html.

Introduction

The main purpose of this document is to establish the common international point of member countries of the International Organization for Standardization (ISO), concerning testing methods for small clear wood specimens and general requirements for determining physical and mechanical properties of wood.

STANDARDSISO.COM : Click to view the full PDF of ISO 13061-13:2024

STANDARDSISO.COM : Click to view the full PDF of ISO 13061-13:2024

Physical and mechanical properties of wood — Test methods for small clear wood specimens —

Part 13: Determination of radial and tangential shrinkage

1 Scope

This document specifies a method for the determination of linear shrinkage in the radial and tangential directions of wood.

2 Normative references

The following documents are referred to in the text in such a way that some or all of their content constitutes requirements of this document. For dated references, only the edition cited applies. For undated references, the latest edition of the referenced document (including any amendments) applies.

ISO 3129, *Wood — Sampling methods and general requirements for physical and mechanical testing of small clear wood specimens*

ISO 24294, *Timber — Round and sawn timber — Vocabulary*

3 Terms and definitions

For the purposes of this document, the terms and definitions given in ISO 24294 apply.

ISO and IEC maintain terminology databases for use in standardization at the following addresses:

- IEC Electropedia: available at <https://www.electropedia.org/>
- ISO Online browsing platform: available at <https://www.iso.org/obp>

4 Principle

The linear shrinkage is determined by measuring dimensions of a test piece in radial and tangential directions of wood before and after drying to a constant mass. The linear shrinkage is calculated as the change of the dimension in given direction expressed as a percentage of the original dimension. The initial measurements shall be taken on test pieces in green or fully saturated condition. The final measurements shall be taken on test pieces in oven-dry state.

5 Apparatus

5.1 Measuring instruments, capable of determining dimensions of the test piece to the nearest 0,02 mm, fitted with parallel flat ends each of diameter 5 mm to 8 mm, and applying a clamping force which will not cause any deformation greater than the precision of the instrument.

5.2 Forced convection oven that can be maintained at a temperature of (103 ± 2) °C throughout the drying chamber for the time required to dry the specimen to the end point shall be used. The oven shall be vented to allow the evaporated moisture to escape.

5.3 **Desiccator**, a vapour-tight container with absorbent material (e.g. silica gel, calcium chloride, etc.) to maintain the air dry.

5.4 **Vessel**, containing distilled water.

5.5 **Balance**, accurate to 0,001 g.

6 Preparation of test pieces

6.1 General

The selection, preparation and the minimum number of test pieces shall be in accordance with ISO 3129.

6.2 Test pieces for determining radial and tangential shrinkage


6.2.1 Test pieces shall be cut from wood in green condition in the form of rectangular prisms.

6.2.2 The size of the prism shall be at least 20 mm square in radial and tangential directions and at least 5 mm along the grain to allow for both radial and tangential shrinkage measurements on the same test piece.

NOTE If the shrinkage in different directions is measured separately, the size of the prism can be greater in the direction of the measurement.

6.3 Inclination of annual rings of test pieces

The angle of inclination of annual rings to a pair of opposite tangential faces of the test pieces shall not exceed 10° (see [Figure 1](#)).

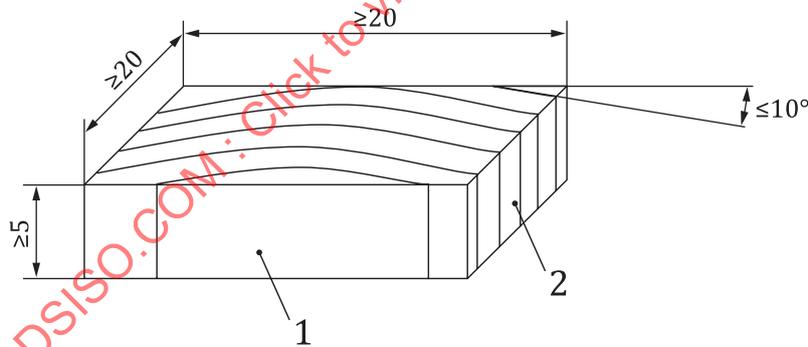

Key

- 1 tangential face
- 2 radial face

Figure 1 — Inclination of annual rings of a test piece

6.4 Marking of measurement points

Measurement points shall be marked in the middle of each tangential and radial surface for determining the dimension in radial and tangential directions, respectively.

7 Procedure

7.1 Determination of the dimensions of test pieces in green or fully saturated condition

The moisture content of test pieces shall be at or above the fibre saturation point (FSP). When the moisture content is below FSP, soak the test pieces in distilled water at a temperature of (20 ± 2) °C until no further change in dimensions occurs. Check the changes in dimensions every 3 d through repeated measurements at the same points until the difference between two successive measurements does not exceed 0,02 mm. In this case, it shall be reported that the results are obtained on test pieces which have been previously soaked. Measure the radial and tangential dimensions, l_{r1} and l_{t1} , of each test piece to an accuracy of 0,02 mm.

7.2 Determination of the dimensions of test pieces at oven-dry state

After air-seasoning, the test pieces shall be open-piled and dried to constant mass at a temperature of (103 ± 2) °C in the oven, ensuring no checks distorting their dimensions and shape occur. Check the changes in mass of two or three control test pieces after 8 h of drying and repeat the measurements every 8 h or longer until the difference between two successive weighing does not exceed 0,2 % of the test pieces or when the difference between two successive measurements does not exceed 0,02 mm of the corresponding dimension of the test piece. Test pieces in which checks occurred during the test period shall be disregarded. Cool the test pieces to room temperature in the desiccator. Measure the radial and tangential dimensions, l_{r2} and l_{t2} , of each test piece to an accuracy of 0,02 mm.

8 Calculation and expression of results

Calculate the total linear shrinkage, β , as a percentage, by the following [Formulae \(1\)](#) and [\(2\)](#):

a) for the radial direction:

$$\beta_r = \frac{l_{r1} - l_{r2}}{l_{r1}} \times 100 \quad (1)$$

b) for the tangential direction:

$$\beta_t = \frac{l_{t1} - l_{t2}}{l_{t1}} \times 100 \quad (2)$$

where

l_{r1} and l_{t1} are the dimensions, in millimetres, of the green or fully saturated test piece, measured in the radial and tangential directions, respectively;

l_{r2} and l_{t2} are the dimensions, in millimetres, of the test piece at absolutely dry (oven-dry) condition, measured in the radial and tangential directions, respectively.

Express the results to the nearest 0,1 %.

The mean and the standard deviation of the results obtained for the individual test pieces in a sample shall be calculated to an accuracy of 0,1 %.

9 Test report

The test report shall include the following information:

- a reference to this document, i.e. ISO 13061-13:2024;
- the sampling details in accordance with ISO 3129;
- the details pertaining to measurements of test pieces;