
**Vitreous and porcelain enamels —
Determination of crack formation
temperature in the thermal shock
testing of enamels for the chemical
industry**

*Émaux vitrifiés — Détermination de la température de fissuration par
choc thermique d'émaux pour l'industrie chimique*

STANDARDSISO.COM : Click to view the full PDF of ISO 13807:2022



STANDARDSISO.COM : Click to view the full PDF of ISO 13807:2022



COPYRIGHT PROTECTED DOCUMENT

© ISO 2022

All rights reserved. Unless otherwise specified, or required in the context of its implementation, no part of this publication may be reproduced or utilized otherwise in any form or by any means, electronic or mechanical, including photocopying, or posting on the internet or an intranet, without prior written permission. Permission can be requested from either ISO at the address below or ISO's member body in the country of the requester.

ISO copyright office
CP 401 • Ch. de Blandonnet 8
CH-1214 Vernier, Geneva
Phone: +41 22 749 01 11
Email: copyright@iso.org
Website: www.iso.org

Published in Switzerland

Contents

	Page
Foreword.....	iv
1 Scope	1
2 Normative references	1
3 Terms and definitions	1
4 Designation	1
5 Principle	2
6 Apparatus	2
7 Specimens	2
7.1 Shape and preparation of specimens.....	2
7.2 Number of specimens.....	3
8 Procedure	3
9 Expression of results	4
10 Test report	4
Annex A (informative) Explanatory notes	5

STANDARDSISO.COM : Click to view the full PDF of ISO 13807:2022

Foreword

ISO (the International Organization for Standardization) is a worldwide federation of national standards bodies (ISO member bodies). The work of preparing International Standards is normally carried out through ISO technical committees. Each member body interested in a subject for which a technical committee has been established has the right to be represented on that committee. International organizations, governmental and non-governmental, in liaison with ISO, also take part in the work. ISO collaborates closely with the International Electrotechnical Commission (IEC) on all matters of electrotechnical standardization.

The procedures used to develop this document and those intended for its further maintenance are described in the ISO/IEC Directives, Part 1. In particular, the different approval criteria needed for the different types of ISO documents should be noted. This document was drafted in accordance with the editorial rules of the ISO/IEC Directives, Part 2 (see www.iso.org/directives).

Attention is drawn to the possibility that some of the elements of this document may be the subject of patent rights. ISO shall not be held responsible for identifying any or all such patent rights. Details of any patent rights identified during the development of the document will be in the Introduction and/or on the ISO list of patent declarations received (see www.iso.org/patents).

Any trade name used in this document is information given for the convenience of users and does not constitute an endorsement.

For an explanation of the voluntary nature of standards, the meaning of ISO specific terms and expressions related to conformity assessment, as well as information about ISO's adherence to the World Trade Organization (WTO) principles in the Technical Barriers to Trade (TBT), see www.iso.org/iso/foreword.html.

This document was prepared by Technical Committee ISO/TC 107, *Metallic and other inorganic coatings*, in collaboration with the European Committee for Standardization (CEN) Technical Committee CEN/TC 262, *Metallic and other inorganic coatings, including for corrosion protection and corrosion testing of metals and alloys*, in accordance with the Agreement on technical cooperation between ISO and CEN (Vienna Agreement).

This second edition cancels and replaces the first edition (ISO 13807:1999), which has been technically revised. It also incorporates the Technical Corrigendum ISO 13807:1999/Cor 1:2000.

The main changes are as follows:

- the normative references have been updated;
- the method for measuring coating thickness has been updated;
- the thickness requirements for the vitreous enamel coating have been updated;
- the specimen heating temperature requirements have been updated.

Any feedback or questions on this document should be directed to the user's national standards body. A complete listing of these bodies can be found at www.iso.org/members.html.

Vitreous and porcelain enamels — Determination of crack formation temperature in the thermal shock testing of enamels for the chemical industry

1 Scope

This document specifies a test method for the determination of the crack formation temperature of enamels for the chemical industry by subjecting enamelled steel specimens to thermal shock using cold water.

The value of the crack formation temperature measured according to this test method does not apply to the finished component (see [Annex A](#)). It is a parameter of vitreous and porcelain enamels for comparing the relative quality of different enamel formulations.

2 Normative references

The following documents are referred to in the text in such a way that some or all of their content constitutes requirements of this document. For dated references, only the edition cited applies. For undated references, the latest edition of the referenced document (including any amendments) applies.

ISO 2178, *Non-magnetic coatings on magnetic substrates — Measurement of coating thickness — Magnetic method*

ISO 2746, *Vitreous and porcelain enamels — High voltage test*

ISO 3819, *Laboratory glassware — Beakers*

ISO 19496-1, *Vitreous and porcelain enamels — Terminology — Part 1: Terms and definitions*

3 Terms and definitions

For the purposes of this document, the terms and definitions given in ISO 19496-1 and the following apply.

ISO and IEC maintain terminology databases for use in standardization at the following addresses:

- ISO Online browsing platform: available at <https://www.iso.org/obp>
- IEC Electropedia: available at <https://www.electropedia.org/>

3.1

crack formation temperature

thermal shock temperature (3.2) at which the first damage to the enamel occurs in the form of cracks and/or chipping

3.2

thermal shock temperature

temperature of the specimen immediately before quenching with cold water

4 Designation

The test method for the determination of the crack formation temperature of enamels for the chemical industry by the thermal shock test described in this document is designated as follows:

Test ISO 13807

5 Principle

The specimen is heated to the thermal shock temperature in a drying oven. After reaching the thermal shock temperature, the enamelled surface is covered by water at a temperature between 10 °C and 30 °C. Then, the specimen is dried and visually examined for damage. To make cracks visible, the entire enamel surface is sprayed with electrostatically charged talcum powder. If no damage to the enamel is found after the first thermal shock test, the test shall be repeated at a thermal shock temperature 10 °C higher than in the previous test.

6 Apparatus

- 6.1 **Drying oven**, capable of maintaining temperatures of at least 300 °C.
- 6.2 **Low-form beaker**, having a capacity of 2 000 ml and meeting the requirements of ISO 3819.
- 6.3 **Spray gun**, equipped with a hard-rubber nozzle for electrostatically charging the talcum powder.

7 Specimens

7.1 Shape and preparation of specimens

Specimens shall be either square sheet metal plates with a thickness of at least 10 mm and an edge length of 150 mm that have been enamelled on one side, or made of 10MnTi3 low-alloyed enamelling structural steel (as shown in [Figure 1](#)). The steel shall have the following nominal composition (% mass fraction):

- carbon, ≤0,12 %;
- manganese, 0,40 % to 1,00 %;
- titanium, 0,10 % to 0,16 %;
- phosphorus, ≤0,035 %;
- sulfur, ≤0,030 %.

During the enamelling process, these specimens shall be held in the horizontal position by means of a rod inserted in the 5 mm hole. The vitreous enamel ground coat shall cover the entire surface. The vitreous enamel cover coat may be applied only to the top and convex surface (radius 8 mm).

Dimensions in millimetres
Roughness values in micrometres

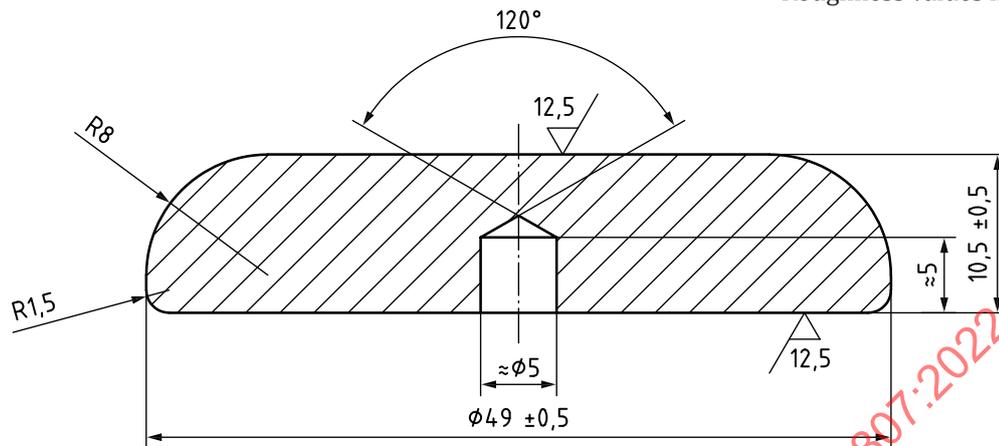


Figure 1 — Steel specimen for determination of the crack formation temperature of enamels by thermal shock

Prepare the specimens by the same enamelling process used for the enamelled product, including the pre-treatment, type of vitreous enamel ground coat, vitreous enamel cover coat, application technique, firing temperature and thickness of the vitreous enamel ground coat. After each firing step, the specimens are removed from the oven and may be cooled in air. However, the specimens shall be submitted to controlled cooling after the last vitreous enamel coating or directly after the last firing. Heat the specimens up to 600 °C in an oven, maintain this temperature for at least 20 min, then cool to 250 °C at a cooling rate of ≤ 1 °C/min (see [Annex A](#)).

The overall thickness of the vitreous enamel coating measured by the method given in ISO 2178 shall be between 1,1 mm and 1,4 mm.

The finished vitreous enamel coating shall be free from defects. This shall be checked visually, as well as with the high voltage test at 12 kV, described in ISO 2746.

Specimens of other shapes or manufacture may be used, when specified by the purchaser. The use of specimens having different shapes or manufacture shall be noted in the test report.

7.2 Number of specimens

Two specimens of the same type shall be used for each determination.

8 Procedure

8.1 Place the two enamelled specimens with the enamelled surface upwards in the drying oven ([6.1](#)) heated to the thermal shock temperature. The thermal shock temperature shall be about 20 °C below the expected crack formation temperature. If necessary, determine the crack formation temperature by a preliminary test.

8.2 Determine by a preliminary test, the time span necessary for heating the specimens to the thermal shock temperature. After the specimens have reached the thermal shock temperature, open the drying oven ([6.1](#)) and remove one specimen by means of a fork or other tool, without touching the enamel surface. Hold the specimen horizontally and cover the centre of it by pouring 2 l of water at a temperature between 10 °C and 30 °C, pouring the water at a rate of approximately 100 ml/s. From the moment the drying oven ([6.1](#)) is opened until the cold water is poured on to the specimen, no more than 3 s shall elapse.

8.3 After the first specimen has been removed from the drying oven (6.1), leave the second specimen in the oven until it has again reached the thermal shock temperature, then repeat the thermal shock step with the second specimen, by the procedure described in 8.2.

8.4 Check the dried specimens visually for damage to the enamel initially. Following the visual check, to make cracks easier to detect, spray the enamel with electrostatically charged talcum powder using the spray gun (6.3). This technique makes even fine cracks easy to detect.

8.5 If no damage to the enamel is detected on one or both specimens after the thermal shock test, repeat the test on the same specimens at a thermal shock temperature that is 10 °C higher than in the first test.

8.6 If the difference in the crack formation temperature as determined by the above procedure is greater than 10 °C, the test shall be repeated with two new specimens.

9 Expression of results

Average the crack formation temperatures that do not differ by more than 10 °C.

10 Test report

The test report shall include the following information:

- a) the type of enamel tested;
- b) the International Standard used (including its year of publication);
- c) the designation (see Clause 4) of this test method, i.e. Test ISO 13807;
- d) the thickness of the enamel coating;
- e) the material code or designation of the basis metal;
- f) if applicable, the shape of the specimen, if specified by the purchaser (see Clause 7);
- g) the description of the damage to the enamel coating;
- h) the individual values of the crack formation temperatures, in °C;
- i) the arithmetic mean of the crack formation temperature, in °C;
- j) any deviations from the procedure specified;
- k) any unusual features observed;
- l) the date of the test.