

INTERNATIONAL
STANDARD

ISO
13967

First edition
1998-07-15

**Thermoplastics fittings — Determination
of ring stiffness**

*Raccords en matières thermoplastiques — Détermination de la rigidité
annulaire*

STANDARDSISO.COM : Click to view the full PDF of ISO 13967:1998



Reference number
ISO 13967:1998(E)

Contents		Page
1	Scope	1
2	Definitions	1
3	Symbols	3
4	Principle	3
5	Apparatus	3
6	Test pieces	4
6.1	Preparation	4
6.2	Number	4
6.3	Determination of dimensions	5
6.3.1	Inside diameter	5
6.3.2	Calculation length of normal bends	5
6.3.3	Calculation length of branches	6
6.4	Age	7
7	Conditioning	7
8	Test temperature	7
9	Procedure	8
10	Calculation of ring stiffness	10
11	Test report	10
Annexe A (informative) Comments on the use of this test method ..		12

STANDARDISO.COM : Click to view the full PDF of ISO 13967:1998

© ISO 1998

All rights reserved. Unless otherwise specified, no part of this publication may be reproduced or utilized in any form or by any means, electronic or mechanical, including photocopying and microfilm, without permission in writing from the publisher.

International Organization for Standardization
Case postale 56 • CH-1211 Genève 20 • Switzerland
Internet iso@iso.ch

Printed in Switzerland

Foreword

ISO (the International Organization for Standardization) is a worldwide federation of national standards bodies (ISO member bodies). The work of preparing International Standards is normally carried out through ISO technical committees. Each member body interested in a subject for which a technical committee has been established has the right to be represented on that committee. International organizations, governmental and non-governmental, in liaison with ISO, also take part in the work. ISO collaborates closely with the International Electrotechnical Commission (IEC) on all matters of electrotechnical standardization.

Draft International Standards adopted by the technical committees are circulated to the member bodies for voting. Publication as an International Standard requires approval by at least 75 % of the member bodies casting a vote.

International Standard ISO 13967 was prepared by Technical Committee ISO/TC 138, *Plastics pipes, fittings and valves for the transport of fluids*.

Annex A of this International Standard is for information only.

STANDARDSISO.COM : Click to view the full PDF of ISO 13967:1998

STANDARDSISO.COM : Click to view the full PDF of ISO 13967:1998

Thermoplastics fittings — Determination of ring stiffness

1 Scope

This International Standard specifies a method of determining the ring stiffness of bends and branches made from thermoplastic material and for use with plastics pipes having a circular cross-section.

The method can be used to determine the stiffness of bends, equal branches and unequal branches, provided that the fitting allows a ring deflection of at least 4 %.

If a fitting has the same wall thickness, wall construction, material and diameter as a pipe being tested, then, because of its geometry, its stiffness will be equal to or greater than that of the pipe tested. In this case, the fitting can be classified as having the same stiffness class as the pipe, without testing.

Any unequal branch may be expected to have at least the same stiffness as an equal branch, provided that it has the same main diameter, wall construction and material as the equal branch.

NOTE — The result of the test reflects the resistance the fitting has against deflection when installed. Advice on the significance of the test result is given in annex A.

2 Definitions

For the purposes of this International Standard, the following definitions apply.

2.1

ring stiffness

S

a mechanical characteristic of a fitting which is a measure of the resistance to ring deflection under an external force, as determined in accordance with this International Standard

NOTE 1 This method uses a deflection of 3 % as the reference at which to determine this characteristic.

NOTE 2 Although technically incorrect, throughout this standard the term "ring stiffness" has been used. In the ISO standard that describes a method of determining the stiffness of a plastics pipe, the word "ring" is appropriate and is used to differentiate the circumferential stiffness or ring stiffness from the axial stiffness or longitudinal stiffness. The pipe test pieces have the shape of rings. Although fittings do not have the shape of rings, to emphasize the relationship between the two standards and to stress that in both cases the stiffness is related to the resistance of the product to diametrical deflection, the word "ring" has been retained in this standard for the determination of the stiffness of fittings.

2.2

compressive force

F

the force which causes the vertical deflection during testing in accordance with this International Standard

NOTE — Although technically incorrect, in some clauses the word "load" has been used instead of "force" as it was felt that this reduced the possibility of misunderstanding.

2.3
vertical deflection

y
the change in vertical diameter caused by a compressive force

2.4
percent deflection

the vertical deflection y expressed as a percentage of the inside diameter d_i of the fitting, i.e.

$$\frac{y}{d_i} \times 100$$

2.5
fitting wall height

e_c
the overall thickness of the wall of a fitting, measured across the entire cross-section of the wall

NOTE — For examples of fitting wall heights, see figure 1.

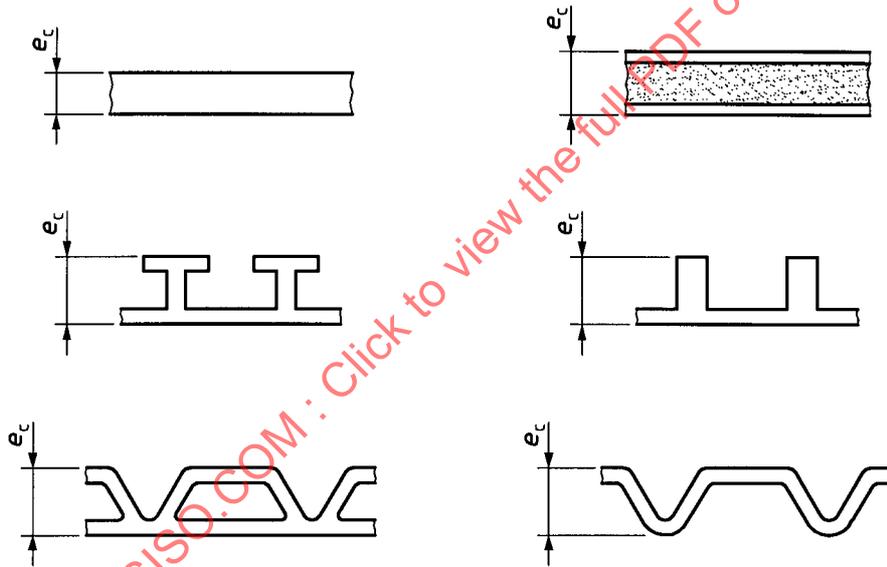


Figure 1 — Typical fitting wall heights e_c

2.6
calculation length

L
the external free length of a fitting, excluding sockets, spigots, inlet zones and half of the transition zones between body and sockets, measured along a line parallel to the fitting axis

NOTE 1 See clause 6 and figures 3, 4 and 5.

NOTE 2 The length of loading is normally slightly shorter than the calculation length. This difference has no significant influence on the result of the test.

3 Symbols

Symbol	Description	Unit
d_i	Inside diameter of fitting	mm
d_n	Nominal diameter of fitting	mm
e_c	Height of fitting wall	mm
F	Force	N
L	Calculation length	mm
S	Calculated ring stiffness	kN/m ²
S_a	Ring stiffness of test piece "a"	N/m ²
S_b	Ring stiffness of test piece "b"	N/m ²
S_c	Ring stiffness of test piece "c"	N/m ²
y	Vertical deflection	mm

NOTE — The calculation length depends on the geometry of the fitting, as specified in clause 6.

4 Principle

Test pieces are compressed across their diameter at a constant rate of deflection between two parallel plates. Force versus deflection data is generated.

The force is applied as a load distributed along the body of the fitting without loading the spigot(s) and/or socket(s).

The ring stiffness is calculated as a function of the force necessary to produce a 3 % diametric deflection of the fitting.

NOTE — As fittings will normally be installed with socket and spigot connections — creating zones of high stiffness — the load is only applied to the body of the fitting, and the equation used to calculate the stiffness uses the length of the body and not the overall length of the fitting.

5 Apparatus

5.1 Compression-testing machine, capable of a constant rate of crosshead movement appropriate to the nominal diameter of the fitting in accordance with table 1, with sufficient force and travel to produce the specified diametric deflection via a pair of bearing plates.


5.2 Bearing plates, capable of transferring the force and movement of the test machine (5.1) to the test piece and comprising a pair of bearing plates alone or in combination with insert plates as described below. If the fitting has a ribbed or structured wall construction, the plates shall make initial contact only with the top(s) of the ribs or structures (see figure 2).

a) Bearing plates

The plates shall be flat and clean. The stiffness of the plates shall be sufficient to prevent them from deforming during the test. The geometry of the plates shall be such that the force is equally distributed over the loaded area of the test piece when the test piece is compressed over the length of loading (see figures 3, 4 and 5), e.g. by means of insert plates. The width of the bearing plates shall be at least 50 mm. When equal branches are tested without the use of insert plates, the width of the bearing plates shall be (50 ± 1) mm.

b) Insert plates

When insert plates are needed in order to distribute the force equally over the loaded area of the test piece (see figures 3, 4 and 5), they shall be flat and clean. The stiffness of the plates shall be sufficient to prevent them from deforming during the test. The geometry of the plates shall be appropriate to the type of fitting and shall be such that the force is applied evenly to the fitting without loading the socket(s) and/or spigot(s). The width of the plates shall be at least 50 mm. When equal branches are tested, the width shall be (50 ± 1) mm.

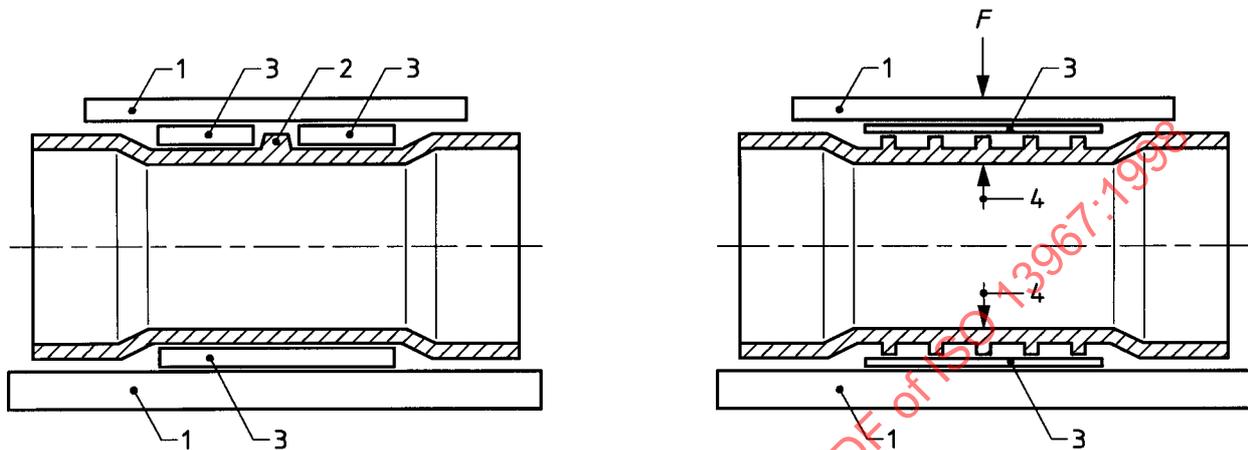

Key

- 1 Bearing plate
- 2 Injection-moulding point
- 3 Insert plate
- 4 Deflection measurement point

Figure 2 — Typical bearing plates and insert plates

5.3 Dimension-measuring instruments, capable of determining the following dimensions:

- the individual values of the lengths defined in 6.3, to within 1 mm;
- the inside diameter of the test piece, to within 0,5 %;
- the change in inside diameter in the direction of loading, to an accuracy of within 0,1 mm or 1 % of the deflection, whichever is the greater.

5.4 Force-measuring instrument, capable of determining, to within 2 %, the force necessary to cause diametric deflection of the test piece over a range from 1 % to 4 %.

6 Test pieces

6.1 Preparation

Each test piece shall comprise a complete fitting with its attachments, such as retaining caps or rings. To improve the linearity of the test curve, small protrusions on the fitting which would come into contact with the deflection plates may be removed. Alternatively, insert plates adapted to the geometry of the fitting may be used (see figure 2).

6.2 Number

The test shall be carried out on three test pieces. They shall be marked "a", "b" and "c".

6.3 Determination of dimensions


6.3.1 Inside diameter

The vertical inside diameter of each test piece shall be determined at the deflection measurement point (which is at the mid-point of the overall length of the body) (see figures 3, 4 and 5) to an accuracy of within 0,5 % or 0,1 mm, whichever is the greater.

6.3.2 Calculation length of normal bends

The calculation length L of a normal bend shall be determined as the length $L_1 + L_2$ as shown in figure 3 in which L_s is the spigot length as defined by the manufacturer. If L_s is not provided by the manufacturer, it shall be taken as the length L_x .

The values of L_1 , L_2 and L_s shall be taken from the product drawing provided by the manufacturer or shall be measured from the product. When measured from the product, the values of L_1 and L_2 shall be determined to an accuracy of within 1 % or 1 mm, whichever is the greater.

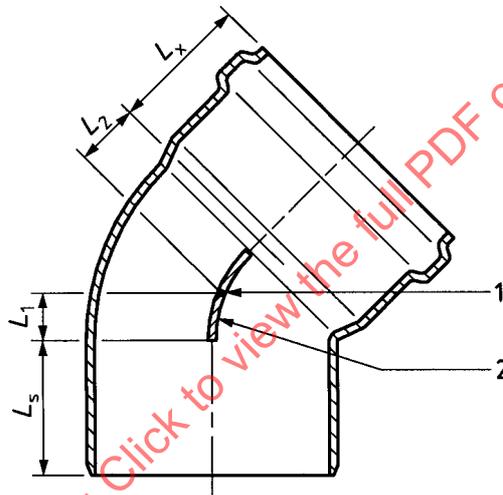

Key

- 1 Deflection measurement point
- 2 Length of loading

$$L = L_1 + L_2$$


Figure 3 — Calculation length L of a normal bend

The calculation length L of a long-radius bend shall be determined in the same way as for normal bends, except that the following shall be observed:

- if the radius R of the bend is greater than 1,5 times the nominal diameter of the fitting, the length of the arch shall be calculated using the dimensions shown in figure 4 and the following equation:

$$L = \frac{2\pi R\alpha}{360} + L_1 + L_2$$

- if in a long-radius bend it is impractical to measure the change in inside diameter at the mid-point of the body, the average value of the change in inside diameter at two other points each at $\alpha/3$ from the mid-point may be taken (see figure 4).

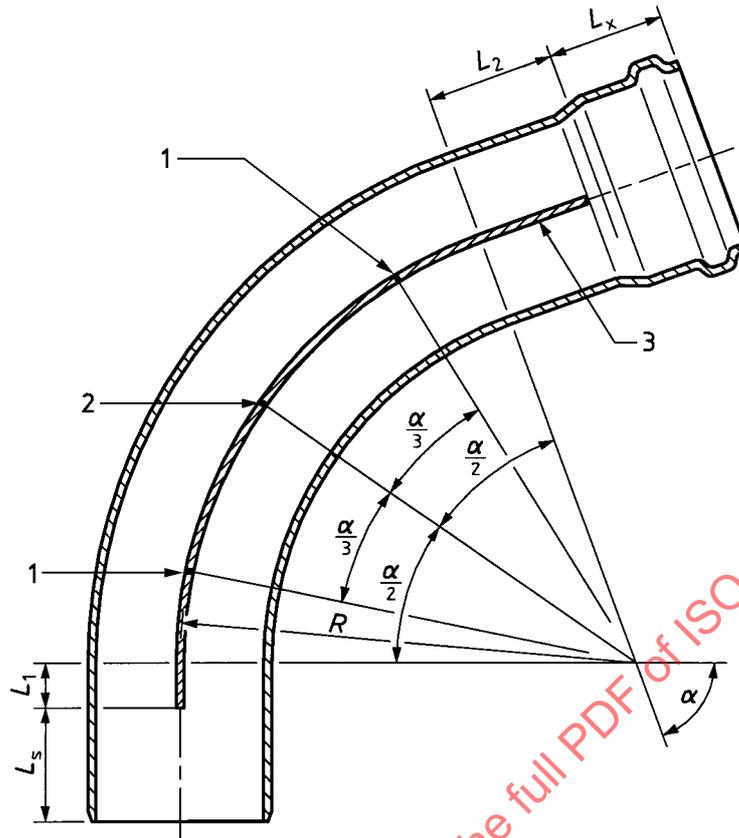

Key

- 1 Alternative deflection measurement point
- 2 Normal deflection measurement point
- 3 Length of loading

α = Angle of fitting, in degrees

Figure 4 — Calculation length L of a long-radius bend


6.3.3 Calculation length of branches

The calculation length L_1 of a branch ($L = L_1$) shall be determined as shown in figure 5, in which L_s is the spigot length as defined by the manufacturer.

The values of L_1 and L_s shall be taken from the product drawing provided by the manufacturer or shall be measured from the product.

When measured from the product, the values of L_1 and L_s shall be measured to an accuracy of within 1 % or 1 mm, whichever is the greater.

If L_s cannot be determined, it shall be taken as the length L_x .

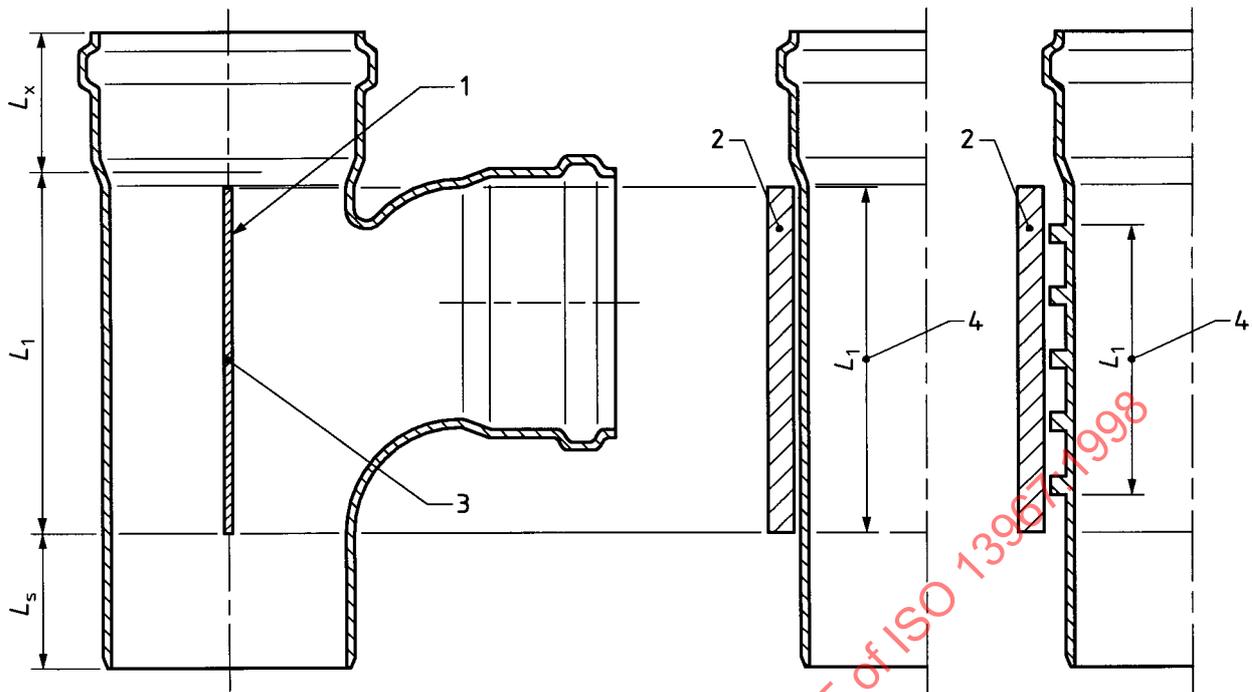

Key

- 1 Length of loading
- 2 Insert plate
- 3 Deflection measurement point
- 4 Examples of length of loading L_1

$$L = L_1$$

Figure 5 — Calculation length L of a branch

6.4 Age

At the start of testing in accordance with clause 9, the age of the test pieces shall be at least 24 h.

For type testing, and in cases of dispute, the age of the test pieces shall be (21 ± 2) days.

7 Conditioning

The test pieces shall be conditioned in air at the test temperature (see clause 8) for at least 24 h immediately prior to testing in accordance with clause 9.

8 Test temperature

Unless otherwise specified, thermoplastics fittings shall be tested at (23 ± 2) °C or, in countries where 27 °C is used as the standard laboratory temperature, at (27 ± 2) °C. In cases of dispute, (23 ± 2) °C shall be used.

9 Procedure

9.1 Place lower insert plates (see note) on the lower bearing plate of the test machine so that they follow the shape of the body of the test piece and so that the socket(s) do not make contact with the bearing plates during the test.

NOTE — When the design of the bearing plates is such that contact between the bearing plates and the socket(s) or spigot(s) can be avoided without insert plates, the latter are not required.

When a fitting has a ribbed or structured wall construction, ensure that only the tops of the ribs or structures will be in initial contact with the insert plates or bearing plates (see figure 2).

Position a test piece with its longitudinal axis parallel to the bearing plates and centre it laterally in the test machine.

Unless otherwise specified, the axes of the inlets of branches shall be parallel to the bearing plates.

Place upper insert plates (see note) on top of the body of the test piece so that they do not make contact with the socket(s) during the test.

Bring the upper bearing plate into contact with the upper insert plates. Use only sufficient force to hold the insert plates in position. Ensure that the contact between all the insert plates and the bearing plates is as uniform as possible.

9.2 Compress the test piece at a constant speed in accordance with table 1, recording the force and deflection continuously as described below until a deflection of at least 4 % is reached.

Table 1 — Deflection speed as a function of nominal diameter of fitting

Nominal diameter d_n	Deflection speed (mm/min)
$d_n \leq 100$	$2 \pm 0,4$
$100 < d_n \leq 200$	5 ± 1
$200 < d_n \leq 400$	10 ± 2
$400 < d_n \leq 1\,000$	20 ± 2
$1\,000 < d_n$	50 ± 5

The force versus deflection plot shall be generated by measuring the change in inside diameter of the test piece and the corresponding load. The vertical change in d_1 shall be measured at the centre of the body of the fitting.

Provided the fitting wall height e_c (see figure 1) is not reduced to less than 90 % of the original fitting wall height during the test, the force versus deflection plot may be generated by measuring the displacement of one of the bearing plates.

9.3 The force versus deflection plot is typically a smooth curve. Use its uncorrected origin to determine the corrected origin and the 3 % deflection force as follows (see figure 6):

a) Draw a vertical line at a distance of 2,5 % deflection from the uncorrected origin ($d_{2,5}$).

Determine the point of intersection of this line with the force-deflection curve (point D 2,5).


b) Draw a second vertical line at a distance of 3,5 % deflection from the uncorrected origin ($d_{3,5}$).

Determine the point of intersection of this line with the force-deflection curve (point D 3,5).

- c) Draw a straight line through points D 2,5 and D 3,5. Take the point of intersection of this line with the horizontal axis as the corrected origin (point 0,0).
- d) Draw a vertical line at a distance of 3 % deflection from the corrected origin (d_3).

Determine the point of intersection of this line with the curve, and read the corresponding force F_3 off the vertical axis.

- 9.4 Repeat the procedure given in 9.1, 9.2 and 9.3 for the remaining test pieces, identifying the individual results "a", "b" and "c" respectively.

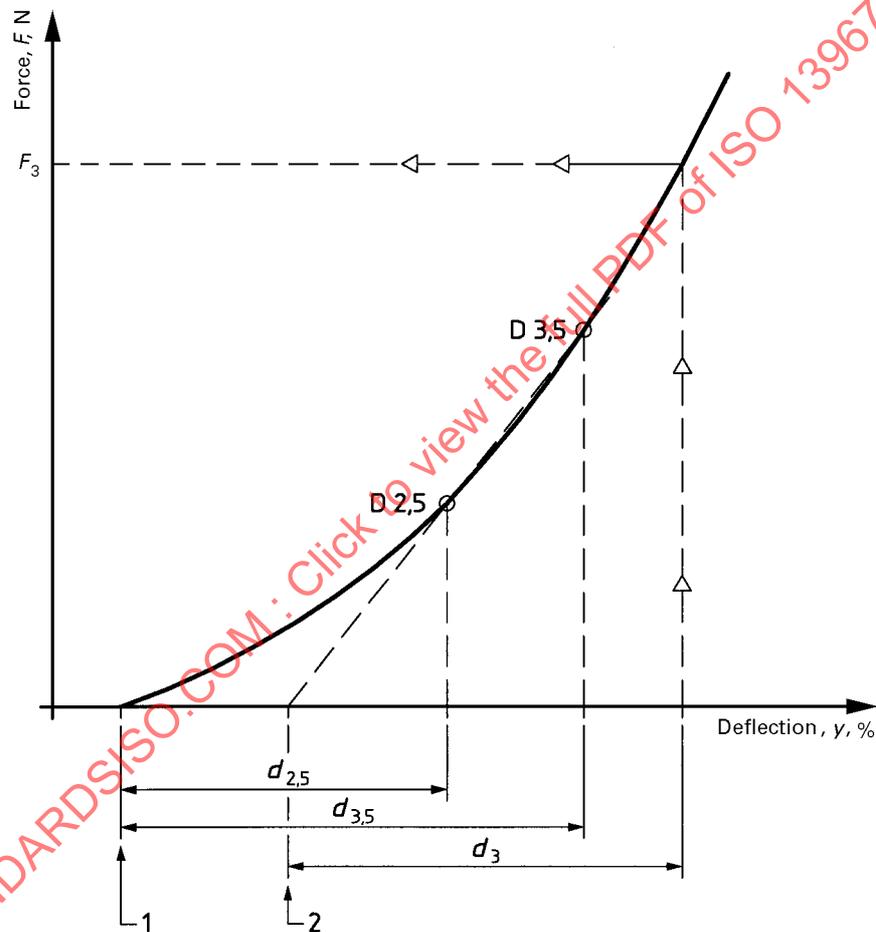

Key

- 1 Uncorrected origin
2 Corrected origin (point 0,0)

Figure 6 — Method of correcting the origin and determination of the 3 % deflection force

10 Calculation of ring stiffness

Calculate the ring stiffness of the three individual test pieces, in newtons per square metre (N/m²), using the following equations:

$$S_a = 18\,600 \frac{F_{3,a}}{L_a \times y_a}$$

$$S_b = 18\,600 \frac{F_{3,b}}{L_b \times y_b}$$

$$S_c = 18\,600 \frac{F_{3,c}}{L_c \times y_c}$$

where

F_3 is the force, in newtons, that corresponds to 3 % deflection of the fitting;

L is the calculation length of the test piece, in millimetres, determined in accordance with 6.3;

y is the deflection, in millimetres, that corresponds to 3,0 % deflection.

Calculate the ring stiffness of the fitting as the arithmetic average of the three calculated values, expressed in kilonewtons per square metre (kN/m²):

$$S = \frac{S_a + S_b + S_c}{3\,000}$$

Round the result to three significant figures.

11 Test report

The test report shall include the following information:

- a) a reference to this International Standard and to the referring standard, if any;
- b) all details necessary for identification of the fitting, including:
 - 1) the manufacturer,
 - 2) the type of fitting and the fitting material,
 - 3) the dimensions, including at least d_i , e_c and the pitch of the structures when a structured-wall fitting has been tested,
 - 4) the nominal stiffness and/or the pressure class,
 - 5) the date of production,
 - 6) the age of the fittings at the date of the test,
 - 7) the identification marking on the fitting (if any);
- c) the calculation length L determined in accordance with 6.3.2 or 6.3.3;