

Second edition
2014-06-01

Corrected version
2014-07-15

Gears — Surface temper etch inspection after grinding, chemical method

*Engrenages — Contrôle par attaque chimique des zones surchauffées
lors de la rectification*

STANDARDSISO.COM : Click to view the full PDF of ISO 14104:2014



Reference number
ISO 14104:2014(E)

© ISO 2014

STANDARDSISO.COM : Click to view the full PDF of ISO 14104:2014



COPYRIGHT PROTECTED DOCUMENT

© ISO 2014

All rights reserved. Unless otherwise specified, no part of this publication may be reproduced or utilized otherwise in any form or by any means, electronic or mechanical, including photocopying, or posting on the internet or an intranet, without prior written permission. Permission can be requested from either ISO at the address below or ISO's member body in the country of the requester.

ISO copyright office
Case postale 56 • CH-1211 Geneva 20
Tel. + 41 22 749 01 11
Fax + 41 22 749 09 47
E-mail copyright@iso.org
Web www.iso.org

Published in Switzerland

Contents

	Page
Foreword	iv
Introduction	v
1 Scope	1
2 Equipment	1
3 Reagents	2
4 Procedure	3
4.1 General.....	3
4.2 Cleaning.....	4
4.3 Etching.....	6
5 Inspection criteria	8
5.1 Visual appearance and classification.....	8
5.2 Surface hardness effects.....	8
6 Temper etch discoloration removal	9
7 Rework of surface-tempered parts	9
8 Operator qualification	9
9 Maintenance and control	9
10 Safety and environmental precautions	15
11 Specifications and documentation	16
11.1 Specifications.....	16
11.2 Documentation.....	16
Bibliography	17

STANDARDSISO.COM : Click to view the full PDF of ISO 14104:2014

Foreword

ISO (the International Organization for Standardization) is a worldwide federation of national standards bodies (ISO member bodies). The work of preparing International Standards is normally carried out through ISO technical committees. Each member body interested in a subject for which a technical committee has been established has the right to be represented on that committee. International organizations, governmental and non-governmental, in liaison with ISO, also take part in the work. ISO collaborates closely with the International Electrotechnical Commission (IEC) on all matters of electrotechnical standardization.

The procedures used to develop this document and those intended for its further maintenance are described in the ISO/IEC Directives, Part 1. In particular the different approval criteria needed for the different types of ISO documents should be noted. This document was drafted in accordance with the editorial rules of the ISO/IEC Directives, Part 2 (see www.iso.org/directives).

Attention is drawn to the possibility that some of the elements of this document may be the subject of patent rights. ISO shall not be held responsible for identifying any or all such patent rights. Details of any patent rights identified during the development of the document will be in the Introduction and/or on the ISO list of patent declarations received (see www.iso.org/patents).

Any trade name used in this document is information given for the convenience of users and does not constitute an endorsement.

For an explanation on the meaning of ISO specific terms and expressions related to conformity assessment, as well as information about ISO's adherence to the WTO principles in the Technical Barriers to Trade (TBT) see the following URL: Foreword - Supplementary information

The committee responsible for this document is ISO/TC 60, *Gears*, Subcommittee SC 2, *Gear capacity calculation*.

This second edition cancels and replaces the first edition (ISO 14104:1995), of which it constitutes a technical revision with the following changes:

- use of a grey scale card to qualify varying degrees of surface temper damage;
- inclusion of sample photographs which are intended to provide the user of this International Standard with indications of typical surface temper damage.

This corrected version of ISO 14104:2014 incorporates the following corrections: additional recommendations in [2.5](#) and [3.5](#); editorial corrections to [Tables 2](#) and [3](#); modification of the recommendation on abrasive pads and addition of a related warning in [Clause 9](#).

Introduction

This International Standard explains the materials and procedures necessary to determine, evaluate, and describe localized overheating on ground surfaces. A system to describe and classify the indications produced during this inspection is included. However, specific acceptance or rejection criteria are not contained.

An industry-wide survey was conducted to establish common solutions in time that were acceptable to the greatest number of users. The safety and environmental precautions were included therein for those not familiar with storage, handling, use, and disposal of concentrated acids, alkalis, and solvents. These precautions, however, do not supersede the latest applicable requirements.

STANDARDSISO.COM : Click to view the full PDF of ISO 14104:2014

STANDARDSISO.COM : Click to view the full PDF of ISO 14104:2014

Gears — Surface temper etch inspection after grinding, chemical method

1 Scope

This International Standard specifies procedures and requirements for the detection and classification of localized overheating on ground surfaces by chemical etch methods.

The process described in this International Standard is typically used on ground surfaces; however, it is also useful for the detection of surface anomalies that result from post-heat treatment machining such as hard turning, milling, and edge breaking (deburring) processes. Surface metallurgical anomalies caused by carburization or decarburization are also readily detectable with this process.

Some methods which have been used in the past are no longer recommended. Specifications are intended to be changed to use the methods in this International Standard. These etching methods are more sensitive to changes in surface hardness than most hardness testing methods.

This International Standard applies to steel parts such as gears, shafts, splines, and bearings. It is not applicable to nitrided parts and stainless steels. Alternative methods should be considered.

NOTE This process, although at times called “nital etch”, is not intended to be confused with other processes also known as “nital etch”.

The surface temper etch procedure is to be performed after grinding and before additional finishing operations such as superfinishing, shot peening, and honing.

2 Equipment

2.1 Container materials.

Container materials shall not react with the solutions contained, nor damage the parts to be processed. All containers shall be labelled with the solution contained and covered when not in use. Containers should be labelled according to local regulations.

2.2 Inspection area.

The area to be inspected shall be sufficiently illuminated to be free of shadows and reflections. A minimum light intensity of 2 200 lx (~200 foot candles) at the inspection level is recommended.

2.3 Cleaner.

An alkaline cleaner, vapour degreaser, solvent wash, or equivalent cleaning process shall be used.

2.4 Timing device.

A suitable timing device shall be used for the uniform processing of all parts in a group.

2.5 Grey scale reference.

A suitable grey scale reference should be used, such as Tiffen Color Separation Guide and Gray Scale Q13 (small) or Q14 (large).¹⁾

[Figure 1](#) is an example of a suitable grey scale reference. Use of a sample part with known indications to exhibit surface tempering is also recommended.

[Figure 1](#) is an approximate reproduction of a commercially available grey scale. The reproduction shown in this image is not accurate due to variance in graphic reproduction quality and is provided for reference only. It shall not be used for inspection in conformity with this International Standard.

The grey scale card should be replaced at regular intervals.

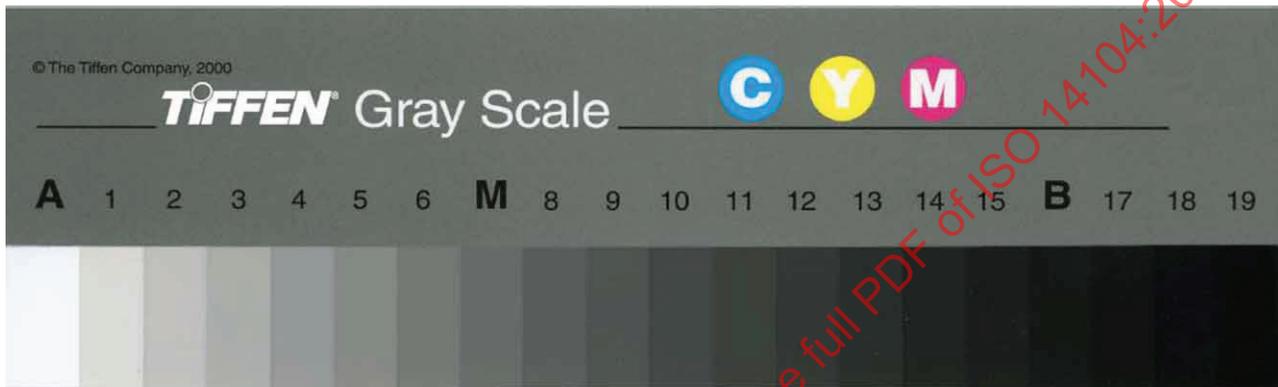


Figure 1 — Gray scale card (reprinted with the permission of The Tiffen Company)

3 Reagents

All chemicals shall be technical grade or better.

3.1 Cleaning materials, which ensure removal of all dirt, grit, grease, and oil, to obtain a “water break”-free surface. A “water break”-free surface is one which maintains a continuous water film for a minimum period of 15 s after having been rinsed in clean water at a temperature below 40 °C.

3.2 Nitric acid.

See [Tables 2](#) and [3](#).

3.3 Hydrochloric acid.

See [Tables 2](#) and [3](#).

3.4 Alcohol, methanol or denatured ethanol, clean and free of contaminants such as oil.

3.5 Water, clean and free of contaminants. Distilled water preferred, but not required.

3.6 Alkaline solution, a solution such as 4 % to 6 % sodium hydroxide in water with a minimum pH value of 10, or equivalent.

1) Tiffen Gray Scale is the trade name of a product supplied by Tiffen. This information is given for the convenience of users of this document and does not constitute an endorsement by ISO of the product name. Equivalent products may be used if they can be shown to lead to the same results.

3.7 **Rust-preventive oil**, suitable for displacing water, and which does not mask the results of etching.

4 Procedure

4.1 General

As shown in [Figure 2](#), clean the part first (see [4.2](#) and [Table 1](#)) then etch it using one of the procedures shown in either [Table 2](#) or [Table 3](#), whichever is appropriate for the type of steel being inspected. Unless otherwise specified, selection of the specific procedure shall be at the supplier's option.

Table 1 — Examples of cleaning methods

Type of contaminant	Method of cleaning
Dyes and inks	Alcohol, methyl ethyl ketone, or equivalent
Oil and grease	Vapour degreasing
Soaps	Alkaline cleaner (60 °C to 80 °C) or ultrasonic cleaner

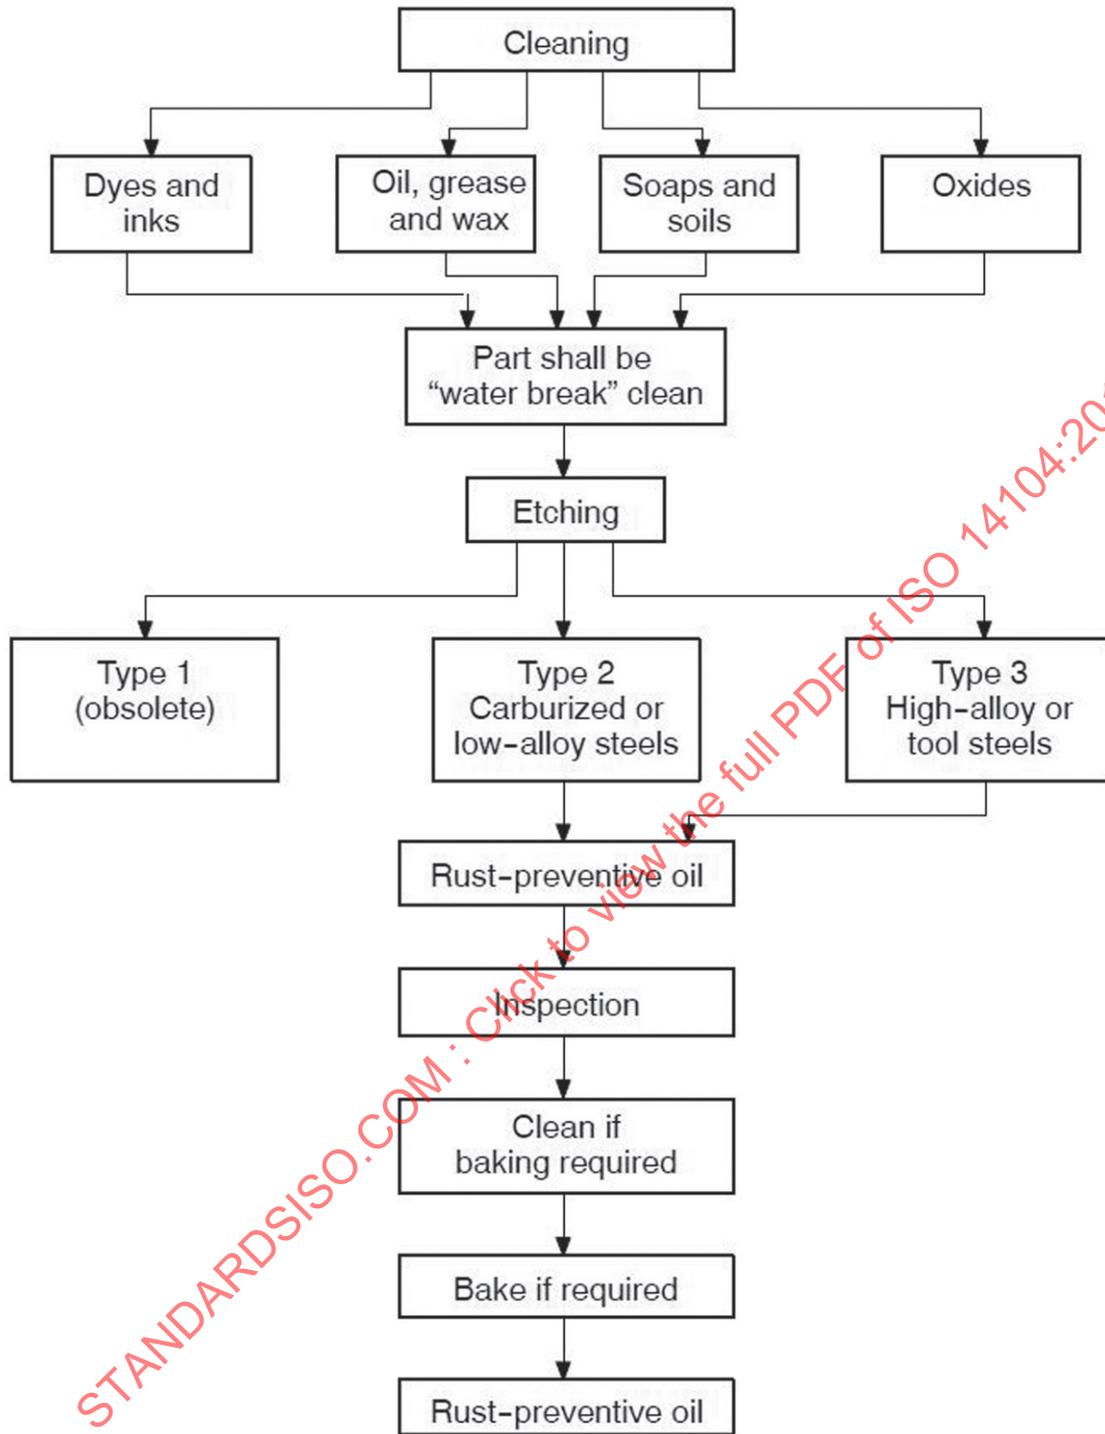


Figure 2 — Procedure flow chart

4.2 Cleaning

Proper cleaning is mandatory for parts to be etched and inspected. Satisfactory cleaning will be evidenced by the absence of “water breaks” on the clean parts after immersion in water. The cleaning procedure shall be chosen by the supplier. The exact method depends on the type of contaminant present. [Table 1](#) lists contaminants and corresponding methods of cleaning in common use.

Additional processes can be required to remove residues from the parts prior to etching. Thorough cleaning of parts prior to etching is imperative in order to obtain good results. Improper cleaning will

result in non-uniform discoloration and staining which can lead to difficult interpretation of etching results. A typical (recommended) cleaning procedure consists of:

- vapour degreasing or solvent cleaning;
- abrasive cleaning: select particle size, media, and blasting procedure to maintain surface finish and dimensions; avoid damage and handle parts with clean white gloves;
- alkaline or ultrasonic clean;
- rinsing in water and examining for water breaks after cleaning. If water break occurs, reclean and re-examine for water break until water break free.

Table 2 — Type 2 etching

Step ^a	Process	Solution ^b	Recommended time ^c	Remarks
1	Nitric acid etch ^d Grey scale Tank 7(M) to 11, Swab 7(M) to 15	Nitric acid, 1,5 % to 5 % (by vol- ume): — in alcohol — in water	30 s to 60 s 10 s to 30 s	Exact time to develop black oxide film will vary; time should be established and reproduced.
2	Rinse	Water	As required	Removes acid
3	Alcohol dip ^e	Alcohol	Dip	Removes water
4	Bleach ^d Grey scale Tank 6 to 10, Swab 2 to 10	Hydrochloric acid, 2 % to 6 % (by volume): — in alcohol — in water	30 s to 60 s	Part should be immersed for a sufficient time to cause a uniform brownish-grey colour on the part; exact bleaching time should be established by test and reproduced.
5	Rinse	Water	As required	Removes acid
6	Neutralize	Alkali solution with pH of 10 minimum	10 s to 60 s	Agitate parts while immersed.
7	Rinse	Water	As required	Removes caustic solvents
8	Dry ^{fg}	Alcohol or hot water	Dip and dry	Removes water
9	Oil	Rust-preventive	As required	Prevents corrosion and aids in colour contrast

^a Uniform agitation of the parts while immersed in the respective baths and rinses is required to avoid a spotty etching condition as well as to accomplish complete neutralization. Multiple rinses can be used in steps 2, 5, and 7.

^b All solutions are used at ambient temperature.

^c It is permissible to deviate from these recommended times.

^d Areas with close tolerances which do not require surface temper etch inspection should be suitably masked to avoid damage and stock removal. Approximately 0,003 mm of stock per surface is removed by etching each time this process is performed.

^e Step 3 is optional if step 1 is acid in alcohol.

^f Typical procedures include alcohol dip or hot water rinse at 65 °C minimum, followed by contaminant-free air blast.

^g Step 8 is not mandatory if in step 9 a water-displacing oil is used.

Table 3 — Type 3 etching

Step ^a	Process	Solution ^b	Recommended time ^c	Remarks
1	Hydrochloric acid clean ^d	Hydrochloric acid, 2 % to 6 % (by volume): — in alcohol — in water	1,5 min to 3,5 min 30 s to 60 s	Exact time to be established by test
2	Rinse	Water	As required	Removes acid
3	Alcohol dip ^e	Alcohol	Dip	Removes water
4	Nitric acid etch ^d Grey scale 11 to 15	Nitric acid, 1,5 % to 5 % (by volume): — in alcohol — in water	1,5 min to 3,5 min 30 s to 60 s	Exact time to develop black oxide film will vary; time should be established and reproduced.
5	Rinse	Water	As required	Removes acid
6	Alcohol dip ^e	Alcohol	Dip	Removes water
7	Bleach ^{d,e} Grey scale 2 to 6	Hydrochloric acid, 2 % to 6 % (by volume): — in alcohol — in water	1,5 min to 3,5 min 30 s to 60 s	Part should be immersed for a sufficient time to cause a uniform brownish-grey colour on the part; exact bleaching time should be established by test and reproduced.
8	Rinse	Water	As required	Removes acid
9	Neutralize	Alkali solution with pH of 10 minimum	10 s to 60 s	Agitate parts while immersed.
10	Rinse	Water	As required	Removes caustic solvents
11	Dry ^{f,g}	Alcohol or hot water	Dip and dry	Removes water
12	Oil	Rust-preventive	As required	Prevents corrosion and aids in colour contrast

^a Uniform agitation of the parts while immersed in the respective baths and rinses is required to avoid a spotty etching condition as well as to accomplish complete neutralization. Multiple rinses can be used in steps 2, 5, 8, and 10.

^b All solutions are used at ambient temperature.

^c It is permissible to deviate from these recommended times.

^d Areas with close tolerances which do not require surface temper etch inspection should be suitably masked to avoid damage and stock removal. Approximately 0,003 mm of stock per surface is removed by etching each time this process is performed.

^e Step 3 is optional if step 1 is acid in alcohol. Likewise, step 6 is optional if step 4 is acid in alcohol.

^f Typical procedures include alcohol dip or hot water rinse at 65 °C minimum, followed by contaminant-free air blast.

^g Step 11 is not mandatory if in step 12 a water-displacing oil is used.

4.3 Etching

Use of a suitable grey scale reference is recommended to quantify the interpretation of temper indications. [Figure 1](#) is an example of a commercially available grey scale reference. Use of a sample part with known indications to exhibit surface tempering is also recommended. The use of a grey scale card is required in order to achieve the goal of improved reproducibility of results over time and between inspectors or laboratories, independent of the specific processing variations allowed by this International Standard.

The suggested ranges for chemical concentrations, dwell times, and grey shades are not mandatory for conformance with this International Standard provided that there is evidence that the same surface temper classification (see [Table 4](#)) results as if the recommended ranges were used. Ranges for the

shades of grey are suggested rather than maximums and minimums in order to avoid processing that results in shades of grey that are too light or too dark.

Table 4 — Surface temper classification system

Prefix code		
F = Functional surfaces; includes flanks, ground roots, bearing journals, and, if specified, other areas. N = Non-functional surfaces; includes all other ground surfaces.		
Class code ^a		
Class	Description	Visual appearance, worst area
A	No tempering	Uniform grey colour
B	Light tempering	Narrow (light) indications
(C) (Obsolete class)	(Moderate tempering)	(No longer used)
D	Heavy tempering	Wide (dark) indications
E	Rehardening (Severe overheating)	White area surrounded by black indications
Suffix code ^b		
Level	Maximum percentage of surface area affected ^a	
1	10 %	
2	25 %	
3	Unrestricted	
<p>NOTE Sample classification callouts are as follows:</p> <ul style="list-style-type: none"> — FA/NB2: No tempering is allowed on any functional surface, but light tempering on up to 25 % of the area of the worst single non-functional surface, such as a shoulder, is permitted. — FB1/ND2: Light tempering is allowed on up to 10 % of the area of the worst single functional surface. In addition, heavy tempering on up to 25 % of the area of the worst single non-functional surface, such as a shoulder, is permitted. — FB2: Light tempering is allowed on up to 25 % of the area of the worst single functional surface. In addition, it implies no restrictions on non-functional surfaces. — FB3/FD2/ND3: Light tempering of an unrestricted amount and heavy tempering on up to 25 % of the area of the worst single functional surface, such as a single tooth flank, is permitted. In addition, heavy tempering of an unrestricted amount is permitted on non-functional surfaces. <p>^a Measured on a single surface such as a tooth flank.</p> <p>^b Not applicable to Class A.</p>		

The following etching techniques are effective preparation for surface temper inspection. The type of etching should be chosen based on the material to be inspected and the ease of handling.

The type 1 (hot bleach) etching method that is sometimes described in older publications is obsolete and not covered in this International Standard.

Type 2 etching (see [Table 2](#)) is generally accepted as a good production inspection method. Type 2 is normally used for inspecting carburized steels and can also be used for surface-hardened areas of through-hardened steels. Occasionally, a part might not respond to step 1, in which case, with engineering approval, consider pre-cleaning per [Table 3](#), steps 1 to 3.

Type 3 (see [Table 3](#)) is normally used for inspecting tool steels and alloy steels, which do not respond to simple nitric acid etching and require a pre-etch using hydrochloric acid, and can be used in place of type 2. Type 3 etching procedure should be used when grey scale level cannot be developed by nitric acid in step 1 of the type 2 procedure.

Parts which cannot be immersed in tanks can be etched using other techniques such as swabbing or spraying, using the procedures described in [Table 2](#) or [Table 3](#). Use of a non-immersion technique should be agreed upon by the customer and supplier.

Inspect parts immediately following the complete etch procedure. When using the swab or spray technique, there is a risk of splashing adjacent surfaces such as teeth and critical bearing journals. Therefore, appropriate protective measures should be used.

An elevated-temperature bake to relieve hydrogen embrittlement is not required by this International Standard, but can be recommended or required to comply with other specifications. One process that can be used is SAE AMS 2759/9.^[1] If used, the maximum bake temperature shall be at least 14 °C below the final heat-treat tempering temperature in lieu of the temperatures stated in Reference [1].

CAUTION — Post surface temper etch inspection bake can also serve as a post-machining stress relief prior to subsequent plating processes (such as cadmium or silver plated). In the event that a rejectable indication is detected and requires rework, the post etch bake should not be performed until an acceptable etch is achieved. Baking could make the remnant of reworked indication(s) harder to detect after the bake and rework. This can conflict with bake delay time requirements.

5 Inspection criteria

5.1 Visual appearance and classification

The appearance of tempering indications is described in [Table 4](#). Parts with no temper indications will be uniform grey in colour when properly cleaned and etched. Localized tempered areas appear as dark grey or black areas on the etched part. Generally, the severity of temper burns increases as the colour becomes darker. If sufficient heat is generated during grinding, rehardening can result. The rehardened area will contain an area of white or light-coloured untempered martensite and can be surrounded by a black tempered area.

False indications which can be caused by smears, stains, rust, or other differences in surface conditions shall require cleaning and retesting unless it can be proven that these are false indications. Since repeated etching can result in appreciable metal removal, care shall be exercised to ensure that close tolerance dimensions are maintained. Stains can often be distinguished from actual temper indications since stains can be wiped off almost entirely. Temper indications will remain darker than the surrounding area even after wiping.

Any indications, especially rehardening burns (i.e. untempered martensite), can affect the durability of the part, but the part can still be functional.

It is good practice to magnetic particle inspect parts with temper indications, especially those with class D or E indications, which are more susceptible to cracking.

The classification system in [Table 4](#) should be used to develop the acceptance or rejection criteria.

It is recommended that users of this International Standard establish their own reference standards. See [Clause 9](#).

5.2 Surface hardness effects

These etching methods can detect surface hardness changes more readily than most hardness testing. Experience can warrant reduction in allowable stress numbers (contact), $\sigma_{H,lim}$, values for carburized surfaces with localized tempering. When possible, inspection of areas with indications can be performed using suitable hardness testing methods to supplement surface temper etch results. Due to differences in hardness test methods, the equipment type, loads, and conversion charts used should be reported. There are some portable microhardness testers available that will allow hardness testing without damaging parts. However, proper use of any hardness tester is essential to ensure accurate hardness readings and that functional surfaces are not damaged. Some areas can be inaccessible to hardness testing equipment.

6 Temper etch discoloration removal

If desired, etch discoloration can be removed for cosmetic purposes by a standard electrolytic alkaline cleaner, vapour honing, polishing, or glass-bead cleaning. The process can cause material removal or surface texture changes. Discoloration has no deleterious effects upon operation.

7 Rework of surface-tempered parts

If gear metallurgy, stock (case-hardened layer and tooth thickness tolerances), and design permit, finish ground parts found not to be acceptable by surface temper inspection can be reworked. Permission to rework parts can be required by the customer. After rework, parts shall be rechecked. An etching procedure recommended.

Magnetic particle inspection is recommended before and after rework operations.

Regrinding, refinishing, and controlled shot peening, singularly or in combination, can reduce some of the detrimental effects caused by grinding-induced tempering. Use of shot peening on surface-tempered areas shall be agreed upon by the customer and supplier.

8 Operator qualification

Test personnel should be qualified for visual testing (VT) in accordance with ISO 9712:2012^[2] or ASNT-TC-1A.^[3]

9 Maintenance and control


To check solution performance, it is recommended that parts with known temper indications be etched, as required, dependent on solution usage, or when new solutions are made. After etching and inspection, the temper etch results shall be removed from the sample as indicated in [Clause 6](#). The sample should then be protected against rust. Such samples should be replaced periodically.

The solutions shall be checked for concentration, pH value, and contamination at regular intervals, dependent on usage, and appropriately documented. The preferred method of inspecting acid solutions in alcohol is by alkali titration.

It is recommended that users of this International Standard use a sample part with grinding temper and rehardening indications as a calibration and verification aid. The sample part should be cleaned with an abrasive pad with non-metallic fibres.

WARNING — Abrasive pads with metallic fibres can cause corrosion.

If the results using the same procedure are the same shade of grey as previously observed for the same part when previously etched, the operator can proceed. A photograph of the same part previously etched is a useful reference document. If there is a difference, the baths should be rechecked and corrected before the operator can proceed. See [Figure 3](#) to [Figure 13](#) for sample photographs.

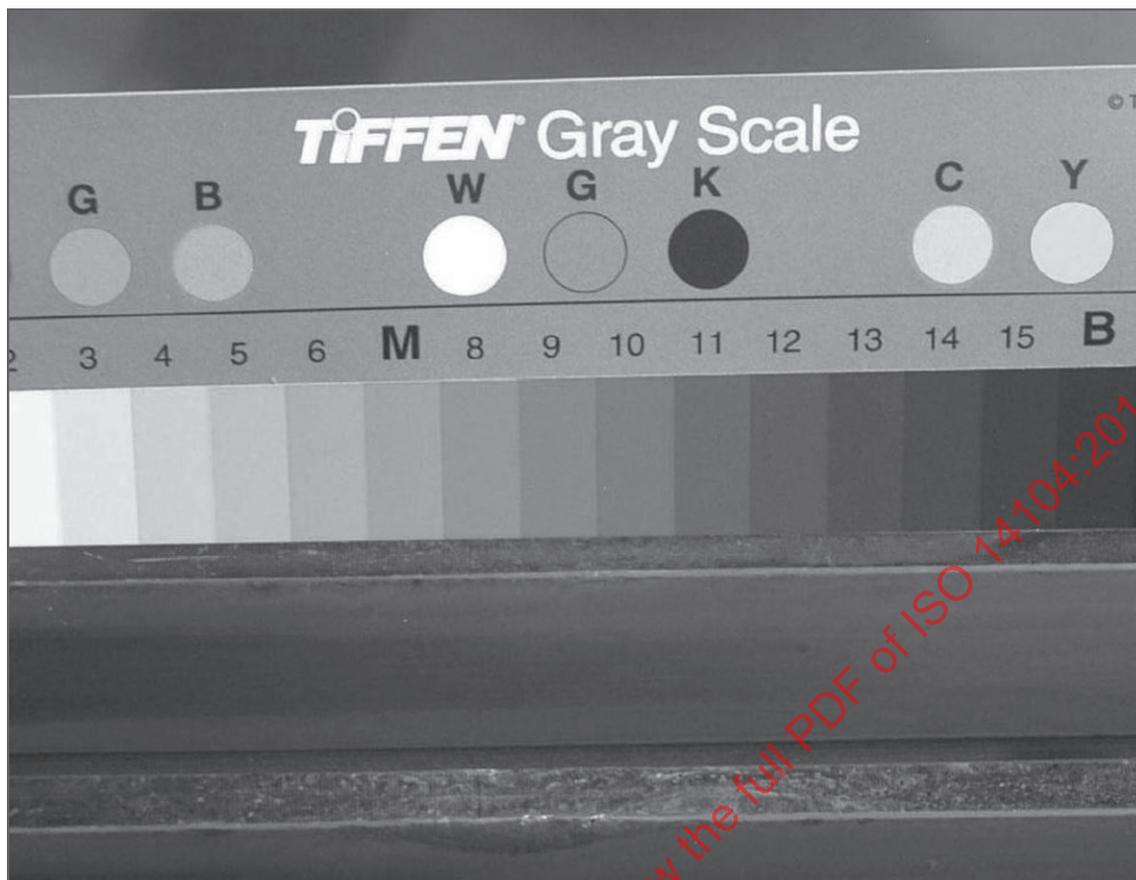


NOTE Grey scale is used for comparison of subtle colour changes across the width of the tooth from the left-hand region that is dark grey (FD) in the root area of the tooth. Surfaces not tempered appear uniform grey in colour.

Figure 3 — Example of using grey scale for progressively heavier tempering, Class FD



NOTE This shows progressive overheating in dedendum area near root area. Rehardened areas (FE) appear as white etching areas with dark grey etching overheated areas (FD) surrounding the white etching areas.

Figure 4 — Progressive tempering and rehardening (severe overheating), Class FD and Class FE

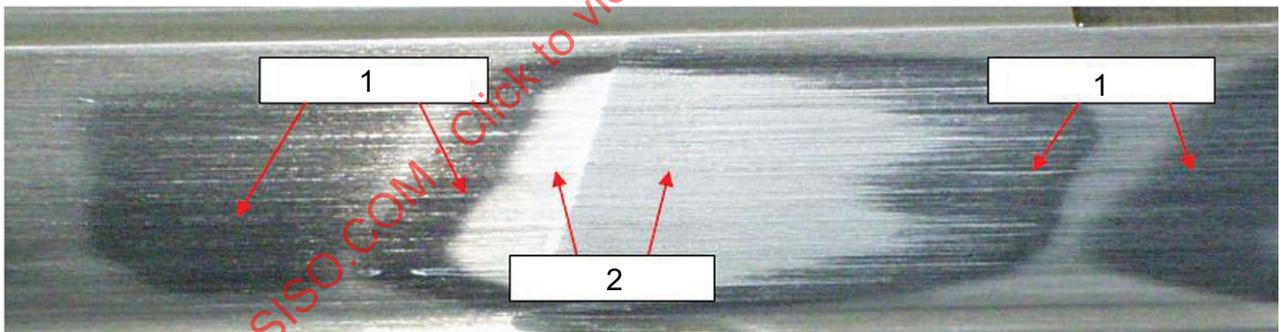


Key

- 1 heavy tempering
- 2 rehardening

Figure 5 — Class FE rehardening/severe overheating with adjacent Class FD heavy tempering



Figure 6 — Progressively worse surface temper of teeth from left with Class FA no tempering to right with Class FE rehardening surrounded by Class FD heavy tempering on four teeth at right

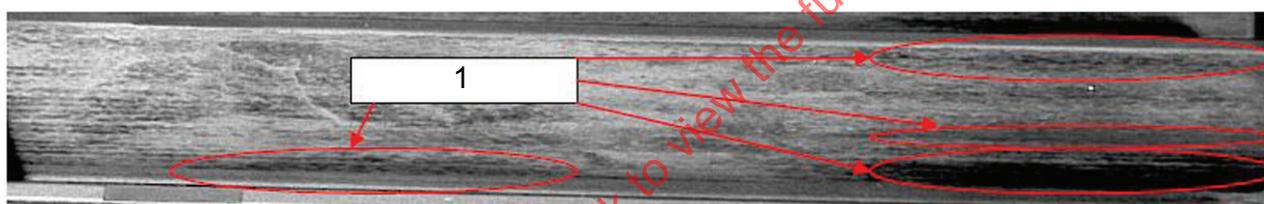

Key
1 heavy tempering

Figure 7 — From Class FB to Class FD heavy tempering



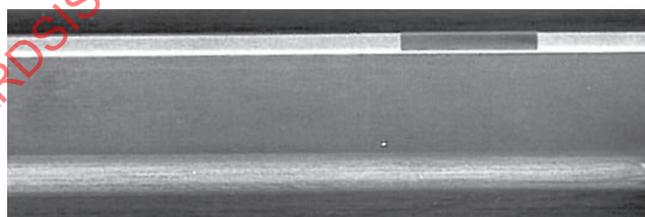


Figure 8 — Class FA no tempering

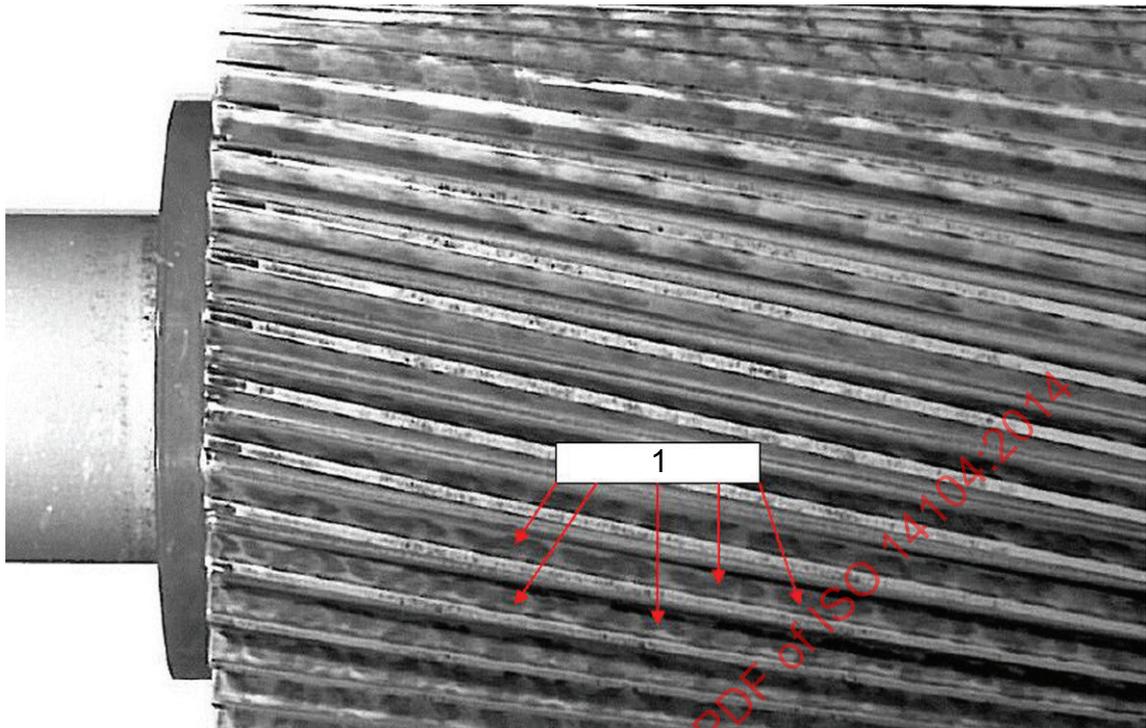

Key
 1 heavy tempering

Figure 9 — Class FD heavy tempering

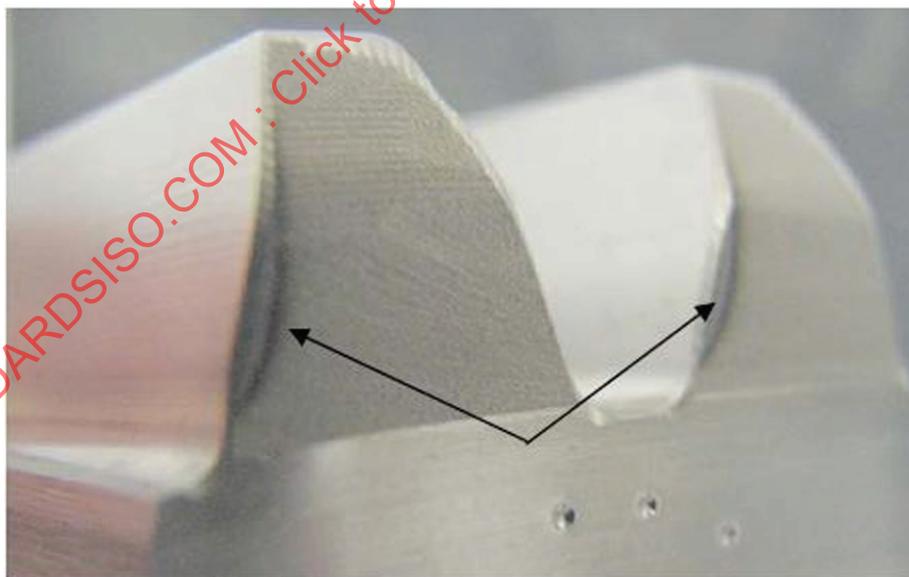

NOTE Tempering bluing on a corner of a gear tooth evident before surface temper etch inspection is a visible clue that grinding is overheating the tooth.

Figure 10 — Tempering at end of tooth