
**Space systems — Safety and
compatibility of materials —**

Part 5:

**Determination of reactivity of system/
component materials with aerospace
propellants**

Systèmes spatiaux — Sécurité et compatibilité des matériaux —

*Partie 5: Détermination de la réactivité des matériaux des systèmes/
composants avec les ergols spatiaux*

STANDARDSISO.COM : Click to view the full PDF of ISO 14624-5:2023



STANDARDSISO.COM : Click to view the full PDF of ISO 14624-5:2023



COPYRIGHT PROTECTED DOCUMENT

© ISO 2023

All rights reserved. Unless otherwise specified, or required in the context of its implementation, no part of this publication may be reproduced or utilized otherwise in any form or by any means, electronic or mechanical, including photocopying, or posting on the internet or an intranet, without prior written permission. Permission can be requested from either ISO at the address below or ISO's member body in the country of the requester.

ISO copyright office
CP 401 • Ch. de Blandonnet 8
CH-1214 Vernier, Geneva
Phone: +41 22 749 01 11
Email: copyright@iso.org
Website: www.iso.org

Published in Switzerland

Contents

	Page
Foreword	iv
Introduction	v
1 Scope	1
2 Normative references	1
3 Terms and definitions	1
4 Fluid transfer, storage and flight systems	2
4.1 General.....	2
4.1.1 Procedure.....	2
4.1.2 Safety.....	2
4.2 Test criteria.....	2
4.2.1 Screening test.....	2
4.2.2 Immersion test.....	2
4.2.3 Post-test analysis.....	2
4.3 Sample.....	3
4.3.1 Receiving inspection.....	3
4.3.2 Sample preparation.....	3
4.3.3 Sample cleaning.....	3
4.3.4 Sample inspection.....	3
4.4 Test system.....	3
4.4.1 Screening test.....	3
4.4.2 Immersion test.....	3
4.5 Procedure.....	4
4.5.1 Before testing.....	4
4.5.2 Test.....	5
4.5.3 Post-test analysis.....	5
4.6 Precision.....	6
4.7 Good laboratory practices.....	6
Annex A (informative) Example forms	7
Bibliography	10

Foreword

ISO (the International Organization for Standardization) is a worldwide federation of national standards bodies (ISO member bodies). The work of preparing International Standards is normally carried out through ISO technical committees. Each member body interested in a subject for which a technical committee has been established has the right to be represented on that committee. International organizations, governmental and non-governmental, in liaison with ISO, also take part in the work. ISO collaborates closely with the International Electrotechnical Commission (IEC) on all matters of electrotechnical standardization.

The procedures used to develop this document and those intended for its further maintenance are described in the ISO/IEC Directives, Part 1. In particular, the different approval criteria needed for the different types of ISO documents should be noted. This document was drafted in accordance with the editorial rules of the ISO/IEC Directives, Part 2 (see www.iso.org/directives).

Attention is drawn to the possibility that some of the elements of this document may be the subject of patent rights. ISO shall not be held responsible for identifying any or all such patent rights. Details of any patent rights identified during the development of the document will be in the Introduction and/or on the ISO list of patent declarations received (see www.iso.org/patents).

Any trade name used in this document is information given for the convenience of users and does not constitute an endorsement.

For an explanation of the voluntary nature of standards, the meaning of ISO specific terms and expressions related to conformity assessment, as well as information about ISO's adherence to the World Trade Organization (WTO) principles in the Technical Barriers to Trade (TBT), see www.iso.org/iso/foreword.html.

This document was prepared by Technical Committee ISO/TC 20, *Aircraft and space vehicles*, Subcommittee SC 14, *Space systems and operations*.

This second edition cancels and replaces the first edition (ISO 14624-5:2006), which has been technically revised.

The main changes are as follows:

- updated sections of [Clause 4](#).

A list of all parts in the ISO 14624 series can be found on the ISO website.

Any feedback or questions on this document should be directed to the user's national standards body. A complete listing of these bodies can be found at www.iso.org/members.html.

Introduction

This purpose of this document is to identify changes resulting from exposure of a material to an aerospace fluid that renders either the material or the fluid unsuitable for use.

This document can be used to determine the reactivity of system and component materials with aerospace fluids.

While this procedure is an excellent quick screen test for long-term propellant compatibility, it is semi-qualitative, and (if exposures exceed 12 months) long-term tests need to be used to quantify degradation as a function of time under use conditions.

STANDARDSISO.COM : Click to view the full PDF of ISO 14624-5:2023

[STANDARDSISO.COM](https://standardsiso.com) : Click to view the full PDF of ISO 14624-5:2023

Space systems — Safety and compatibility of materials —

Part 5:

Determination of reactivity of system/component materials with aerospace propellants

1 Scope

This document specifies test equipment and techniques used to identify interactions resulting from exposure of a material to an aerospace fluid.

It is applicable for determining interactive reactions between propellants and materials used in the design, construction, and operation of propellant storage, transfer, and flight systems.

2 Normative references

The following documents are referred to in the text in such a way that some or all of their content constitutes requirements of this document. For dated references, only the edition cited applies. For undated references, the latest edition of the referenced document (including any amendments) applies.

ISO 4954, *Steels for cold heading and cold extruding*

ISO 15859-3, *Space systems — Fluid characteristics, sampling and test methods — Part 3: Nitrogen*

3 Terms and definitions

For the purposes of this document, the following terms and definitions apply.

ISO and IEC maintain terminology databases for use in standardization at the following addresses:

- ISO Online browsing platform: available at <https://www.iso.org/obp>
- IEC Electropedia: available at <https://www.electropedia.org/>

3.1

degradation

adverse physical or chemical change in a substance

3.2

immersion test

test in which the fluid covers the entire sample for the duration of the test

3.3

propellant

fluid, such as hydrazine and monomethylhydrazine, and oxidizer usually used for space projects

3.4

reaction

chemical change in which a substance decomposes, combines with other substances, or interchanges constituents with other substances

4 Fluid transfer, storage and flight systems

4.1 General

4.1.1 Procedure

This procedure is applicable for determining interactive reactions between propellants and materials used in the design, construction, and operation of propellant storage, transfer, and flight systems. The sample is immersed in the test fluid for 48 h at the maximum system temperature or 71 °C, whichever is higher. This accelerated test provides semi-qualitative information. Tests used to evaluate the long-term interaction of materials with reactive fluids shall be conducted for a period of time no less than that of the anticipated time of use.

4.1.2 Safety

The proper safety equipment shall be worn by the technician performing the test. A face shield, gloves and a laboratory coat or apron shall be worn when handling the test fluids.

Test fluids shall be handled by engineering controls (e.g. operational fume hood) or as directed by the appropriate safety data sheets for the test fluids.

The laboratory conducting the tests shall have a detailed emergency plan in the event of a runaway reaction.

4.2 Test criteria

4.2.1 Screening test

Exposure of the material (screening test) to the fluid for 2 h at ambient temperature and pressure shall not visibly change either the material or the fluid.

4.2.2 Immersion test

The standard test temperature for the hydrazine propellants (see ISO 14951-6^[1] and ISO 14951-7^[2]) is (71 ± 3) °C. This temperature shall be used when the intent of the test is ranking of materials or comparison to literature information. Other temperatures may be used to test materials for specific applications. For fluids that do not decompose into gaseous products at the test temperature (e.g. nitrogen tetroxide), the pressure increase shall not be greater than the vapour pressure of the fluid after exposure to polytetrafluoroethylene (for non-metals) or ISO 4954 stainless steel (for metals).

4.2.3 Post-test analysis

After the sample has been exposed, decontaminated and dried, no visible change in colour or texture of the material or test fluid shall be apparent. In addition, the sample mass change shall not be greater than ± 2 %.

The following also applies:

- a) the mass of impurities in the fluid after exposure to the material shall not be greater than twice the mass of impurities in the identical fluid after exposure to polytetrafluoroethylene (for non-metals) or ISO 4954 stainless steel (for metals);
- b) halide (F^- , Cl^- , Br^-) concentrations in the fluid after exposure to the material shall not exceed the appropriate ISO specification for the fluid purity.

1) Withdrawn.

2) Withdrawn.

4.3 Sample

4.3.1 Receiving inspection

When received, the test material shall be accompanied by proper identification. The minimum information required is the manufacturer, trade name, composition, specification, generic name and batch/lot number (if known). A visual inspection shall be performed, and any anomalies shall be noted. A suitable material identification form is shown in [Annex A](#).

4.3.2 Sample preparation

The sample shall be tested in the intended use form (such as sheets or foams) and in the as-received thickness. Samples for the screening test shall weigh $\leq 0,25$ g. Samples for the immersion test shall have a surface area of (25 ± 10) cm².

4.3.3 Sample cleaning

Samples shall be cleaned and dried to the end-use specifications. Contamination on the surfaces of solid, nonporous samples shall be removed by washing with de-ionized water and mild detergent, rinsing with de-ionized water, and drying with filtered, gaseous nitrogen. Particulate on the surfaces of solid, porous samples shall be removed with filtered, gaseous nitrogen meeting the requirements of ISO 15859-3.

4.3.4 Sample inspection

The cleaned sample shall be inspected to ensure it is at the specified worst-case thickness. Flaws and any residual contamination shall be noted. If the flaws result from sample preparation at the test facility, new samples shall be prepared. Samples with flaws that inordinately increase the surface area to bulk mass ratios shall not be tested. Samples shall be weighed and individually identified.


4.4 Test system

4.4.1 Screening test

The test system for the screening test shall consist of a glass beaker.

4.4.2 Immersion test

The test system for the immersion test shall consist of one reference and one sample chamber and temperature- and pressure-measuring devices (see [Figure 1](#)). Differential pressure transducers may be used for fluids, such as hydrazine and monomethylhydrazine, that decompose into gases at the test temperature. Absolute pressure transducers (on the sample and reference sides of the test system) may be used for those fluids that do not decompose into gases or undergo wide pressure fluctuations. Recommended analytical instruments for the post-test analyses include a differential scanning calorimeter, gas chromatography, gas chromatography/mass spectrograph, atomic absorption spectrophotometer, inductively coupled plasma optical spectrometer, inductively coupled plasma/mass spectrometer, ion chromatography, and high-performance liquid chromatography.

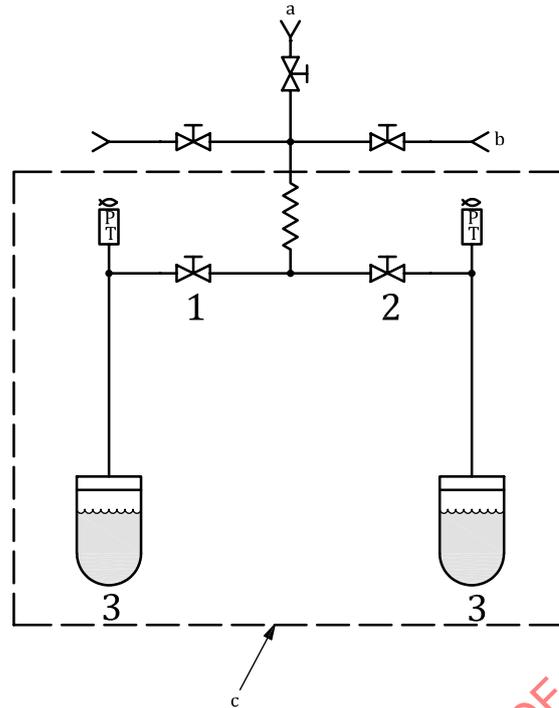

- Key**
- 1 solution valve 1
 - 2 solution valve 2
 - 3 test sample
 - a Vent to hood.
 - b Gaseous nitrogen source.
 - c Heated volume.

Figure 1 — Immersion test system

4.5 Procedure

4.5.1 Before testing

The test system shall be clean, and all measuring devices shall be in current calibration. The pretest procedure shall be as follows:

- a) Analyse the fluid to be used in testing for impurities.
- b) Verify the fluid meets the required use specifications before being exposed to the samples.
- c) Record all pertinent information for the test, such as sample identification and pretest information about the sample and fluid.
- d) Clean and dry the test and reference samples.
- e) Photograph the samples.

4.5.2 Test

4.5.2.1 Screening test

The screening test shall be as follows.

- a) Place a 0,25 g test sample in the glass beaker.
- b) Apply 10 cm³ of fluid one drop at a time to the test sample at ambient temperature and pressure.
- c) Wait 2 h, then examine the sample and fluid visually for obvious changes caused by the exposure.
- d) Complete a suitable screening test report form (see [A.2](#)).

4.5.2.2 Immersion test

The immersion test shall be as follows.

- a) Place the test sample in the sample chamber and add sufficient liquid, approximately 25 ml, to completely cover the test sample for the duration of the test. The addition of the test fluid shall be performed to rigorously exclude water and carbon dioxide in the case of the propellant hydrazines and water in the case of nitrogen tetroxide. Contamination of the test fluid by these chemicals can give false indications of reactivity.
- b) Seal the sample chamber to the sample side of the test apparatus.
- c) Add sufficient test fluid to the reference chamber to obtain the same ullage as in the sample chamber.
- d) Seal the reference chamber to the reference side of the test apparatus.
- e) Activate the temperature- and pressure-monitoring devices.
- f) Heat both chambers at a rate of less than 2 °C per minute until the test temperature, 71 °C minimum, is reached.
- g) Continue the test for 48 h or until the pressure difference between the sample and reference transducers (PT) has exceeded the vapour pressure of the fluid plus 140 kPa.
- h) Allow the temperature to lower to ambient.

4.5.3 Post-test analysis

The post-test analysis shall be as follows.

- a) Perform a post-test analysis of the material and fluid to determine the extent of changes in the physical and chemical characteristics. The removal of the test fluid from the test system shall be done in such a way as to exclude water and carbon dioxide contamination from the air.
- b) Measure changes in weight, dimension, texture and colour.
- c) Perform a comparison of the thermal properties of the material by differential scanning calorimetry for non-metals.
- d) Determine changes in the purity in the test fluid or residue by liquid chromatography, ion chromatography, atomic absorption spectrophotometer, inductively coupled plasma emission spectrometer, inductively coupled plasma/mass spectrometer, or gas chromatography/mass spectroscopy analyses.
- e) Compare the post-test fluid analysis with the appropriate fluid specification. A suitable report form is shown in [A.3](#) for a stainless-steel sample. The post-test fluid analysis shall be derived from the composition of the material being tested and have specific analytes appropriate to the composition.

- f) If required, a graph of the volume of gas evolved versus time, for both the test sample and reference sample, may be provided.

4.6 Precision

Measurements shall be made to the following precision:

- a) absolute pressure, ± 1 % of reading;
- b) temperature, ± 3 °C;
- c) sample dimensions, ± 5 % of the measurements;
- d) time, ± 5 min.

4.7 Good laboratory practices

At least every two years, the test facility shall successfully demonstrate the ability to obtain accurate and repeatable data when testing selected reference materials.

STANDARDSISO.COM : Click to view the full PDF of ISO 14624-5:2023

Annex A
(informative)

Example forms

A.1 Material identification form

Test material

Manufacturer: _____

Trade name: _____

Composition: _____

Specification: _____

Generic name: _____

Batch/lot number: _____

Use temperature (minimum): _____

Use temperature (maximum): _____

Aerospace fluid exposure time (field use): _____

Manufacturer

Name: _____

Address: _____

City: _____

State: _____

Country: _____

Supplier

Name: _____

Address: _____

City: _____

State: _____

Country: _____

Remarks: _____

A.2 Screening test report form

Test sample material description

Test conditions

Test environment: _____
Test temperature: _____
Test duration: _____

Test results, observations and comments

Pretest mass: _____
Photograph pretest samples: _____
Post-test mass: _____

Material characteristics

Component	Pretest observations	Post-test changes

Note(s): Pass Fail

Post-test photograph(s): _____

A.3 Post-test analysis report form

Test sample material description

Geometric surface area: _____

Test conditions

Test environment: _____
Test temperature: _____
Test duration: _____
Reference material: ISO 4954: _____
Geometric surface area: _____