

---

---

**Gears — FZG test procedures —**

Part 3:

**FZG test method A/2,8/50 for relative  
scuffing load-carrying capacity and wear  
characteristics of semifluid gear greases**

*Engrenages — Méthodes d'essai FZG —*

*Partie 3: Méthode FZG A/2,8/50 pour évaluer la capacité de charge au  
grippage et les caractéristiques d'usure des graisses d'engrenages  
semi-fluides*



**PDF disclaimer**

This PDF file may contain embedded typefaces. In accordance with Adobe's licensing policy, this file may be printed or viewed but shall not be edited unless the typefaces which are embedded are licensed to and installed on the computer performing the editing. In downloading this file, parties accept therein the responsibility of not infringing Adobe's licensing policy. The ISO Central Secretariat accepts no liability in this area.

Adobe is a trademark of Adobe Systems Incorporated.

Details of the software products used to create this PDF file can be found in the General Info relative to the file; the PDF-creation parameters were optimized for printing. Every care has been taken to ensure that the file is suitable for use by ISO member bodies. In the unlikely event that a problem relating to it is found, please inform the Central Secretariat at the address given below.

STANDARDSISO.COM : Click to view the full PDF of ISO 14635-3:2005

© ISO 2005

All rights reserved. Unless otherwise specified, no part of this publication may be reproduced or utilized in any form or by any means, electronic or mechanical, including photocopying and microfilm, without permission in writing from either ISO at the address below or ISO's member body in the country of the requester.

ISO copyright office  
Case postale 56 • CH-1211 Geneva 20  
Tel. + 41 22 749 01 11  
Fax + 41 22 749 09 47  
E-mail [copyright@iso.org](mailto:copyright@iso.org)  
Web [www.iso.org](http://www.iso.org)

Published in Switzerland

# Contents

Page

Foreword.....	iv
Introduction .....	v
1 Scope .....	1
2 Normative references .....	1
3 Terms and definitions.....	2
4 Brief description of method.....	4
4.1 General.....	4
4.2 Precision.....	4
5 Test materials .....	4
5.1 Test gears .....	4
5.2 Cleaning fluid .....	4
6 Apparatus .....	6
6.1 FZG spur gear test rig .....	6
6.2 Heating device.....	7
6.3 Revolution counter .....	7
6.4 Weight measurement.....	7
7 Preparation of apparatus .....	8
8 Test procedure .....	9
9 Reporting of results.....	10
Annex A (informative) Test report .....	12
Annex B (informative) Additional test procedure for the investigation of extended wear characteristics of the lubricant .....	13
Annex C (informative) Checklist for maintenance of FZG gear test rig.....	14
Bibliography .....	19

## Foreword

ISO (the International Organization for Standardization) is a worldwide federation of national standards bodies (ISO member bodies). The work of preparing International Standards is normally carried out through ISO technical committees. Each member body interested in a subject for which a technical committee has been established has the right to be represented on that committee. International organizations, governmental and non-governmental, in liaison with ISO, also take part in the work. ISO collaborates closely with the International Electrotechnical Commission (IEC) on all matters of electrotechnical standardization.

International Standards are drafted in accordance with the rules given in the ISO/IEC Directives, Part 2.

The main task of technical committees is to prepare International Standards. Draft International Standards adopted by the technical committees are circulated to the member bodies for voting. Publication as an International Standard requires approval by at least 75 % of the member bodies casting a vote.

Attention is drawn to the possibility that some of the elements of this document may be the subject of patent rights. ISO shall not be held responsible for identifying any or all such patent rights.

ISO 14635-3 was prepared by Technical Committee ISO/TC 60, *Gears*, Subcommittee SC 2, *Gear capacity calculation*.

ISO 14635 consists of the following parts, under the general title *Gears — FZG test procedures*:

- *Part 1: FZG test method A/8,3/90 for relative scuffing load-carrying capacity of oils*
- *Part 2: FZG step load test A10/16, 6R/120 for relative scuffing load-carrying capacity of high EP oils*
- *Part 3: FZG test method A/2,8/50 for relative scuffing load-carrying capacity and wear characteristics of semifluid gear greases*

## Introduction

The types of gear failure which can be influenced by the lubricant are scuffing, low-speed wear and the gear fatigue phenomena known as micropitting and pitting. In the gear design process, these types of gear damage are taken into consideration by the use of specific lubricant and service-related characteristic values. In order to provide a reasonable estimate of performance in service, adequate lubricant test procedures are required. The FZG test procedures described in ISO 14635-1, ISO 14635-2 and ISO 14635-3 can be regarded as tools for the determination of relative scuffing performance of lubricants. Characteristic values can be introduced into the load-carrying capacity calculation of gears. ISO 14635-1 FZG test method, A/8,3/90 for relative scuffing load-carrying capacity of oils, is useful for the majority of applications in industrial and marine gears. ISO 14635-2, FZG step load test A10/16, 6R/120, is related to the relative scuffing load-carrying capacity of high EP oils as used, e.g. for the lubrication of automotive driveline components such as manual transmissions. ISO 14635-3 FZG test method A/2,8/50 describes a test procedure for the determination of the relative scuffing load-carrying capacity and wear characteristics of semi-fluid greases used for enclosed gear drives. Other FZG test procedures for the determination of low-speed wear, micropitting and pitting load capacity of gears are currently being considered for standardization. They could be added later to ISO 14635 as further parts.

It has been assumed by the compilers of this test method that anyone using the method will either be fully trained and familiar with all normal engineering and laboratory practice, or will be under the direct supervision of such a person. It is the responsibility of the operator to ensure that all local legislative and statutory requirements are met.

When the rig is running, there are long-loaded shafts and highly stressed test gears turning at high speed and precaution must be taken to protect personnel. It is also necessary to provide protection from noise.



# Gears — FZG test procedures —

## Part 3:

# FZG test method A/2,8/50 for relative scuffing load-carrying capacity and wear characteristics of semifluid gear greases

## 1 Scope

This part of ISO 14635 specifies a test method based on an FZG <sup>1)</sup> four-square test machine for determining the relative load-carrying capacity of semi-fluid gear greases defined by the gear surface damage known as scuffing.

This method is useful for evaluating the scuffing load capacity potential of semi-fluid gear greases of NLGI classes 0 to 000, typically used with highly stressed gearing for enclosed gear drives. It can only be applied to greases giving a sufficient lubricant flow in the test gear box of the FZG test machine.

NOTE The test method is technically equivalent to DIN Fachbericht 74.

## 2 Normative references

The following referenced documents are indispensable for the application of this document. For dated references, only the edition cited applies. For undated references, the latest edition of the referenced document (including any amendments) applies.

ISO 1328-1, *Cylindrical gears — ISO system of accuracy — Part 1: Definitions and allowable values of deviations relevant to corresponding flanks of gear teeth*

ISO 4287, *Geometrical Product Specifications (GPS) — Surface texture: Profile method — Terms, definitions and surface texture parameters*

ISO 4964, *Steel — Hardness conversions*

ISO 5725-2, *Accuracy (trueness and precision) of measurement methods and results — Part 2: Basic method for the determination of repeatability and reproducibility of a standard measurement method*

ISO 14635-1, *Gears — FZG test procedures — Part 1: FZG test method A/8,3/90 for relative scuffing load-carrying capacity of oils*

ASTM D 235, *Specification for Mineral Spirits (Petroleum Spirits) (Hydrocarbon Dry Cleaning Solvent)*

DIN 51818, *Lubricants; consistency classification of lubricating greases; NLGI grades*

---

1) FZG = Forschungsstelle für Zahnräder und Getriebebau, Technische Universität München (Gear Research Centre, Technical University, Munich).

### 3 Terms and definitions

For the purposes of this document, the following terms and definitions apply.

**3.1 scuffing**  
particularly severe form of gear tooth surface damage in which seizure or welding together of areas of tooth surface occurs, owing to insufficient or breakdown of lubricant film between the contacting tooth flanks of mating gears, typically caused by a combination of high temperature, high pressure and other factors

NOTE 1 Scuffing is most likely when surface velocities are high. It can also occur at relatively low sliding velocities when tooth surface pressures are high enough either generally or, because of uneven surface geometry and loading, in discrete areas.

NOTE 2 Care should be taken that scuffing does not occur and is polished away before ending the running time at the higher load stages.


**3.2 wear**  
continuous removal of material occurring when two surfaces roll and slide against one another

**3.3 scuffing load-carrying capacity**  
(of a lubricant) maximum load which can be sustained under a defined set of conditions


**3.4 FZG test condition A/2,8/50**  
test condition where A is the particular tooth form of the test gears, according to Table 1, 2.8 is the speed at the pitch circle in metres per second (m/s), and 50 is the initial lubricant temperature in degrees Celsius, from load stage 4 onward in the lubricant sump

**3.5 failure load stage**  
load stage reached when the summed total width of scuffing damage on the active flank area of the 16 pinion teeth exceeds one gear tooth width, i.e. 20 mm.


NOTE For examples of failure, see Figure 1. Examples of tooth flank changes due to continuous wear are given in Figure 2. Continuous wear is not a failure criteria for the test.

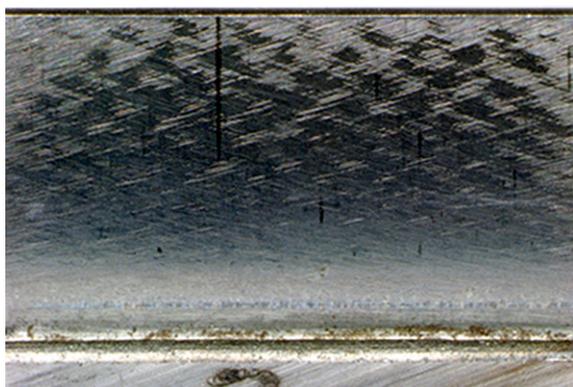

a) Marks, no failure

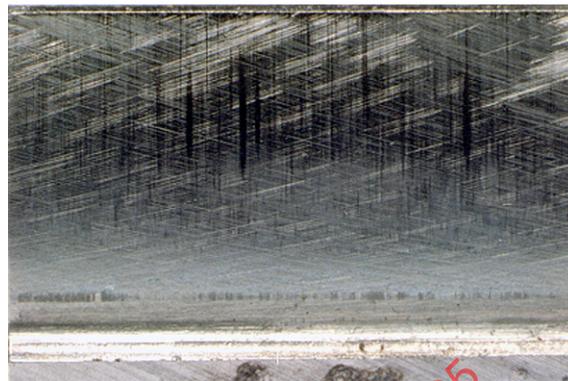


b) Marks, no failure

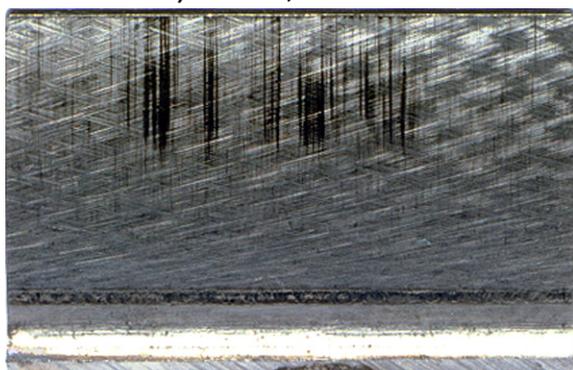

c) Approx. 5 mm failure marks




d) Approx. 15 mm failure marks

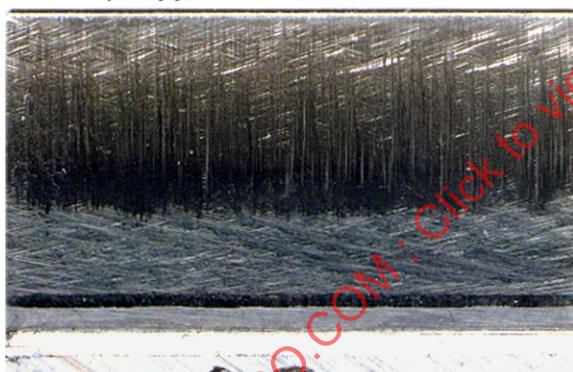


e) 20 mm failure marks



f) Approx. 2 mm failure marks

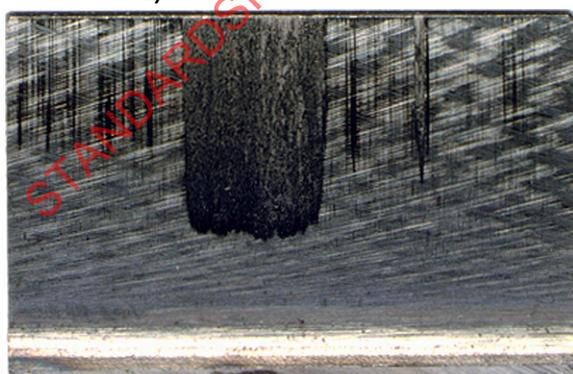

g) Approx. 6 mm failure marks

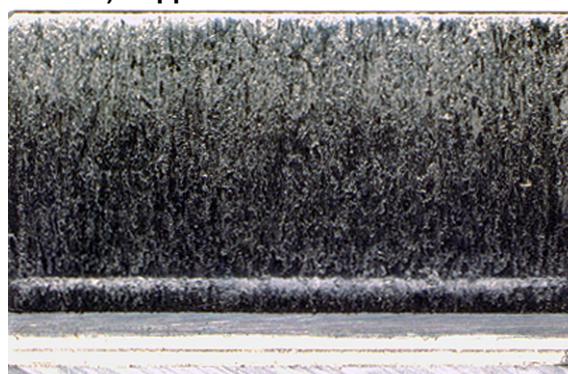

h) 20 mm failure marks

NOTE This figure describes the typical pinion tooth flank changes occurring in FZG scuffing type tests. Changes in the original surface condition (criss-cross grinding) can be described by their physical appearance. One and the same type of flank damage can be described in different places in the world by using different terminology (e.g. “scuffing”, “scoring” and “severe wear”). In order to avoid misinterpretation of the pinion tooth flank changes occurring during the test, typical examples of non-failure and failure are given.

Figure 1 — FZG A-type gear tooth face changes (flank damages)

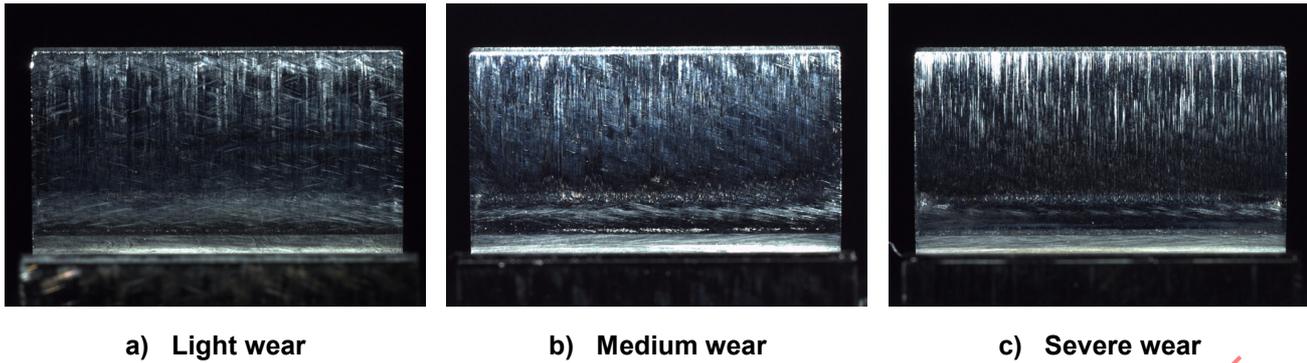


Figure 2 — FZG A-type gear tooth flank changes due to continuous wear

## 4 Brief description of method

### 4.1 General

A set of test gears as defined in Clause 5, Tables 1 and 2, weighed to the nearest 0,001 g before the test, is run with the test lubricant at constant speed for a fixed number of revolutions in dip lubrication mode. Loading of the gear teeth is increased in the steps outlined in Table 3. Beginning with load stage 5, the initial lubricant temperature is controlled between  $(50 \pm 3) ^\circ\text{C}$ . During the test run of each load stage, the lubricant temperature is allowed to rise freely. After load stage 4, the weight loss of the gear set is determined to the nearest 0,001 g and the pinion tooth flanks are inspected for surface damage. For each subsequent load stage the pinion tooth flanks are inspected for surface damage at the end of each load stage and any changes in appearance are noted. A test is considered complete when either the failure criteria has been met or when load stage 12 is run without meeting the failure criteria. If load stage 12 is reached without meeting the failure criteria, the gear set weight loss is determined to the nearest 0,001 g.

### 4.2 Precision

Values of repeatability,  $r$ , and reproducibility,  $R$ , as defined in ISO 5725-2, are not valid for this test procedure. However, experience suggests that similar methods (see ISO 14635-1) are expected to be representative. Values for ISO 14635-1 are indicated below.

$r = 1$  load stage

$R = 2$  load stages

NOTE The above precision results apply to the range of failure load stages 5 to 12.

## 5 Test materials

### 5.1 Test gears

A pair of type "A" gears with a specification according to Table 1 and Table 2 shall be used for testing. Each pair of test gears may be used twice for testing, utilizing both tooth flanks as load-carrying flanks.

### 5.2 Cleaning fluid

Petroleum spirits conforming to ASTM D 235 shall be used.

Table 1 — Details of FZG test gears type A

Dimension		Symbol	Numerical value	Unit
Shaft centre distance		$a$	91,5	mm
Effective face width		$b$	20	mm
Working pitch diameter	pinion	$d_{w1}$	73,2	mm
	wheel	$d_{w2}$	109,8	mm
Tip diameter	pinion	$d_{a1}$	88,77	mm
	wheel	$d_{a2}$	112,5	mm
Module		$m$	4,5	mm
Number of teeth	pinion	$z_1$	16	
	wheel	$z_2$	24	
Profile shift coefficient	pinion	$x_1$	0,853 2	
	wheel	$x_2$	-0,50	
Pressure angle		$\alpha$	20	Degrees
Working pressure angle		$\alpha_w$	22,5	Degrees
Pitch line velocity		$v_w$	2,8	m/s
Addendum engagement	pinion	$e_{a1}$	14,7	mm
	wheel	$e_{a2}$	3,3	mm
Sliding speed at tooth tip	pinion	$v_{ga1}$	1,85	m/s
	wheel	$v_{ga2}$	0,42	m/s
Specific sliding at tooth tip	pinion	$\xi_{E1}$	1,86	
	wheel	$\xi_{A2}$	0,34	
Specific sliding at tooth root	pinion	$\xi_{A1}$	-0,52	
	wheel	$\xi_{E2}$	-5,96	
Hertzian contact pressure		$p_c$	$14,7 \sqrt{F_{nt}}$ <sup>a</sup>	N/mm <sup>2</sup>

<sup>a</sup>  $F_{nt}$  = normal tooth load in newtons (see Table 3).

**Table 2 — Manufacturing details of FZG test gears type A**

Material	<p>Case hardening steel with restricted hardenability to 2/3 of the lower scatter band. Material composition:</p> <p>C = 0,13 % to 0,20 %                      Mo = 0,12 % max.  Si = 0,40 % max.                                Ni = 0,30 % max.  Mn = 1,00 % to 1,30 %                      Al = 0,02 % to 0,05 %  P = 0,025 % max.                              B = 0,001 % to 0,003 %  S = 0,020 % to 0,035 %                      Cu = 0,30 % max.  Cr = 0,80 % to 1,30 %</p>
Heat treatment	<p>The test gears are carburized and case hardened. The case depth at a hardness of 550 HV10 must be 0,6 mm to 0,9 mm. The surface hardness after tempering: 60 HRC to 62 HRC, core strength in tooth root centre: 1000 N/mm<sup>2</sup> to 1250 N/mm<sup>2</sup> (determined in accordance with ISO 4964, based on HB). Retained austenite should be nominally 20 %.</p>
Gear accuracy grade	Q5, according to ISO 1328-1
Arithmetic roughness of flanks, <i>Ra</i>	<p><i>Ra</i> is separately determined for left and right flanks, measured each at 3 flanks per gear across the centre of the tooth parallel to the pitch line; measuring-parameters according to ISO 4287-1:</p> <p>measured length <math>l_t = 4,8</math> mm,  cut-off length <math>\lambda_c = 0,8</math> mm,  velocity <math>v_t = 0,5</math> mm/s, using a skid.</p> <p>Average roughness (relating to manufacture batches of min. 100 gear sets)</p> <p>Pinion:                      <math>Ra = 0,35 \pm 0,1 \mu\text{m}</math>  Wheel:                      <math>Ra = 0,30 \pm 0,1 \mu\text{m}</math></p> <p>Maximum roughness (average of 3 measurements according to the described method and valid for 95 of 100 tested gears).</p> <p>Pinion and wheel:      <math>Ra = 0,5 \mu\text{m}</math></p>
Grinding	Maag criss-cross grinding (15° method), 154 r/m of generating stroke drive
Flank modification	None.

## 6 Apparatus

### 6.1 FZG spur gear test rig

**6.1.1** The FZG spur gear test machine utilizes a recirculating power loop principle, also known as a four-square configuration, to provide a fixed torque (load) to a pair of precision test gears. A schematic view of the test rig is shown in Figures 3 and 4. The slave gearbox and the test gearbox are connected through two torsional shafts. Shaft 1 contains a load coupling used to apply the torque through the use of known weights defined in Table 3 hung on the loading arm at the 0,5 m notch.

**6.1.2** The test gearbox contains heating elements for maintaining and controlling the minimum temperature of the lubricant. A temperature sensor located in the side of the test gearbox is used to control the heating system as required by the test operating conditions.

**NOTE** The heating elements typically have a maximum heat density of 3 W/cm<sup>2</sup> to 5 W/cm<sup>2</sup> for minimizing thermal degradation of the test lubricant.

**6.1.3** The test machine is driven at  $500 \text{ r/min} \pm 3 \%$  by an electric motor giving sufficient torque to carry out the test.

**6.1.4** A check list for maintenance of the FZG gear test rig is given for information in Annex B.

## 6.2 Heating device


A suitable oven or heating device is required to warm the test gears to  $60 \text{ }^\circ\text{C}$  to  $80 \text{ }^\circ\text{C}$  for assembling on the shafts.

## 6.3 Revolution counter


A suitable counter shall be used to control the number of revolutions during each load stage of the test. The counter should be capable of shutting down the test machine at the appropriate number of revolutions of the pinion.

## 6.4 Weight measurement

A suitable balance of  $1,3 \text{ kg}$  min. weight capacity with reading to the nearest  $0,001 \text{ g}$  shall be used to determine the weight of the test wheel.

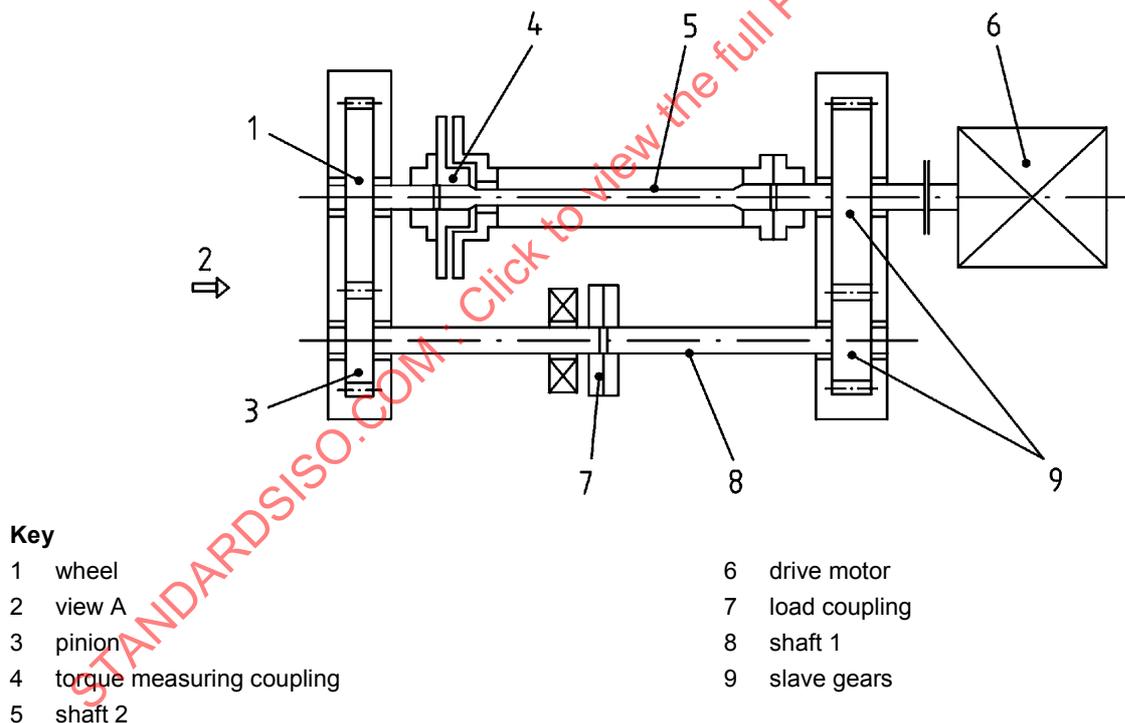

**Figure 3 — Schematic section of the FZG gear test machine**

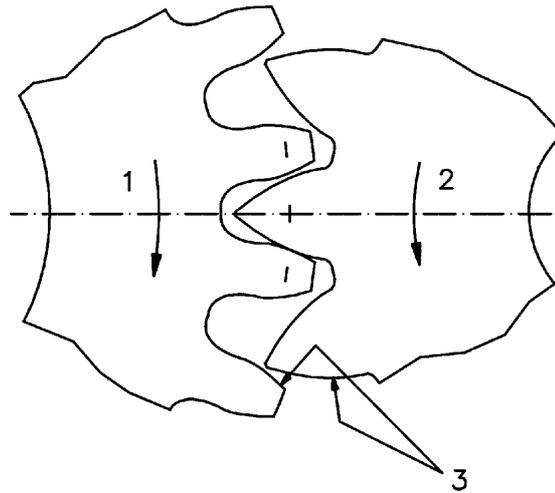

**Key**

- 1 wheel
- 2 pinion
- 3 action tooth flank

**Figure 4 — Mounting of the FZG test gears type A** (view A of Figure 3)

**7 Preparation of apparatus**

7.1 Flush the test gear case twice with petroleum spirit, ensuring that the bearings are clean of any previous lubricant, and air dry with a water-free air line.

If the previous lubricant tested contained any solid lubricant particles such as graphite or MoS<sub>2</sub>, the test machine shall be completely disassembled and cleaned carefully.

7.2 Mark the pinion and wheel as shown in Figure 4.

7.3 Clean the test gears in petroleum spirit and air dry. After cleaning, use gloves to handle gears.

7.4 With the unaided eye, inspect the gears for corrosion, rust or any other damage. Reject the gears if so damaged.

7.5 Weigh the pinion and the wheel each to the nearest 0,001 g.

7.6 Heat both the gears to between 60 °C and max. 80 °C using an appropriate heating device.

7.7 Assemble the test gear box (except the top cover) with the pinion on shaft 1 (right-hand side) and the wheel on shaft 2 (left-hand side) as shown in Figure 3. Ensure the pinion and wheel are correctly aligned, i.e. no offset. Also ensure that the locating marks are positioned as shown in Figure 4.

7.8 Switch drain cock in the CLOSED position.

7.9 Fill the test gear box with a nominal 1,25 l of test lubricant.

7.10 Plug in the heater.

7.11 Fit top cover to the test gear box.

7.12 Apply load stage 12 using the 0,5 m radius position (see Table 3) for 2 min to 3 min, without running the motor, in order to bring the test gears and the clearances in the system into correct working position.

## 8 Test procedure

**8.1** Apply load corresponding to stage 1 (see Table 3). Start the motor, switch on the heater and run for 21 700 revolutions of the motor (approximately 45 min), according to Table 4.

**8.2** Stop the motor and apply the load for stage 2. Restart and run according to Table 4 for 21 700 revolutions of the motor. Repeat for load stage 3 and load stage 4.

**8.3** At the end of load stage 4, remove the lubricant from the unit and save. Visually inspect the pinion for damage. Record the tooth condition, using the examples in Figure 1 as a guide.

**8.4** Disassemble and weigh the pinion and the wheel, each to the nearest 0,001 g.

**8.5** Re-assemble the test gear box according to 7.7 to 7.12. Ensure that the pinion teeth are immersed in the test lubricant. If needed, add a small amount of the same lubricant.

**8.6** Before starting the next higher load stage, ensure that the lubricant temperature in the test gearbox is  $(50 \pm 3) ^\circ\text{C}$ . This can be accomplished through the use of cooling water or by using the procedure given in 8.8.2. When the temperature reaches  $(50 \pm 3) ^\circ\text{C}$  turn off the cooling water and continue the test. The cooling water shall be turned off during the test.

**8.7** Continue the test with the next load stages (see Table 3). Visually inspect all the pinion teeth after each stage, ensuring the lubricant temperature is  $(50 \pm 3) ^\circ\text{C}$  before applying the next higher load stage. Continue the test until the failure load stage according to 3.5 is reached. If the failure criteria is not reached, terminate the test at the end of load stage 12.

**8.8** Determine the failure load stage by summing the flank damages on all the pinion teeth.

**8.8.1** If the failure criteria is not reached, continue the test with the next higher load stage up to a maximum of load stage 12.

**8.8.2** If the machine is shut down at the end of a load stage beyond load stage 4 for a period of time before the test is completed and the test oil temperature drops below  $47 ^\circ\text{C}$ , carry out the following before resuming the test.

a) Apply load stage 1, start the motor, switch on the heater and run until the lubricant temperature reaches  $(50 \pm 3) ^\circ\text{C}$ .

b) Stop the motor, switch off the heater and apply the next load stage in the text sequence. Continue the test according to 8.6 and 8.7, respectively.

**8.9** If the test is terminated after load stage 12 without reaching the failure criteria, weigh the pinion and the wheel each to the nearest 0,001 g and determine the weight losses during the test. If the test is terminated at or before load stage 12 because the scuffing fail criteria/limit has been reached, then the gears need not be weighed.

Table 3 — FZG load stages

Load stage no.	Pinion torque N·m	Normal tooth load N	Hertzian stress at pitch point N/mm <sup>2</sup>	Total work transmitted by test gears up to end of load stage kW·h	Load coupling loaded with:
1	3,3	99	146	0,19	$H_1$
2	13,7	407	295	0,97	$H_2$
3	35,3	1 044	474	2,96	$H_2 + K$
4	60,8	1 799	621	6,43	$H_2 + K + W_1$
5	94,1	2 786	773	11,8	$H_2 + K + W_1 + W_2$
6	135,5	4 007	929	19,5	$H_2 + K + W_1 + W_2 + W_3$
7	183,4	5 435	1 080	29,9	$H_2 + K + W_1 + W_2 + W_3 + W_4$
8	239,3	7 080	1 223	43,5	$H_2 + K + W_1 + W_2 + W_3 + W_4 + W_5$
9	302,0	8 949	1 386	60,8	$H_2 + K + W_1 + W_2 + W_3 + W_4 + W_5 + W_6$
10	372,6	11 029	1 539	82,0	$H_2 + K + W_1 + W_2 + W_3 + W_4 + W_5 + W_6 + W_7$
11	450,1	13 342	1 691	107,0	$H_2 + K + W_1 + W_2 + W_3 + W_4 + W_5 + W_6 + W_7 + W_8$
12	534,5	15 826	1 841	138,1	$H_2 + K + W_1 + W_2 + W_3 + W_4 + W_5 + W_6 + W_7 + W_8 + W_9$

Table 4 — Test conditions

Duration of each load stage:	21 700 revolutions of the motor (approx. 45 min)
Motor speed:	500 r/min ± 3 %
Direction of rotation: <sup>a</sup>	clockwise
Test lubricant volume:	1,25 l ± 0,05 l
Lubricant temperature at start of load stage 1:	Ambient
Initial lubricant temperature at start of load stage 5 and each subsequent load stage:	(50 ± 3) °C (shall be preset on the temperature-controller)
<sup>a</sup> The direction of the rotation of the gears is shown in Figure 4.	

## 9 Reporting of results

Report the load stage and the corresponding pinion torque at which the failure occurred, in accordance with 3.5. State the test conditions as A/2,8/50. If the test was completed without failure, report “Failure load stage greater than 12” and report the weight losses determined for the pinion and the wheel. If the test was terminated due to scuffing before load stage 5 was reached, report “Failure load stage less than 5”.

A typical report sheet is given in Annex A.

Calculate the specific weight loss,  $\Delta m_{sT}$ , in milligrams per kilowatt hour [mg/(kW·h)], using the equation

$$\Delta m_{sT} = \frac{\Delta m_{12} - \Delta m_4}{131,67}$$

with

$\Delta m_{12}$  is the weight loss of pinion and wheel after load stage 12;

$\Delta m_4$  is the weight loss of pinion and wheel after load stage 4.

If the specific weight loss is below 2 mg/kW·h, report "Below 2 mg/kW·h".

STANDARDSISO.COM : Click to view the full PDF of ISO 14635-3:2005

**Annex A**  
(informative)

**Test report**

Company name

Company logo

ISO 14635-3

Gears — FZG test procedures

**Part 3: FZG test method A/2,8/50 for relative scuffing load-carrying capacity and wear characteristics of semi-fluid gear greases**

**TEST REPORT**

Lubricant: .....

Origin: .....

FZG test no.: .....

FZG Test gear set no.: .....

TEST RESULT:

**Failure load stage:** .....

**Pinion torque  $T_1$  at failure load stage** ..... N·m

**Specific weight loss:** ..... mg/(kW·h)

**Individual weight losses:**

		Pinion	Wheel	Pinion + Wheel
Weight loss	after load stage 4, $\Delta m_4$ , mg	.....	.....	.....
	after load stage 12, $\Delta m_{12}$ , mg	.....	.....	.....

Remarks:

.....  
.....

Date:

Signature:

## Annex B (informative)

### Additional test procedure for the investigation of extended wear characteristics of the lubricant

#### B.1 General

For semi-fluid gear greases which have a load-carrying capacity of over load stage 12 according to the test procedure specified in this part of ISO 14635, an additional endurance test can be recommended. The lubricant temperature is not controlled during the test.

#### B.2 Test procedure

**B.2.1** Assemble the test gear box using the same gear set and flanks that completed load stage 12 according to 7.7 to 7.12. Ensure that the pinion teeth are immersed in the test lubricant. If needed, add a small amount of the same lubricant.

**B.2.2** Apply load stage 10 using the test conditions for motor speed, direction of rotation and test lubricant volume given in Table 4. Lubricant temperature at start shall be ambient temperature.

**B.2.3** Set the revolution counter to 1 500 000 revolutions of the motor, (approximately 50 h).

**B.2.4** Set the temperature control to limit the lubricant to  $(80 \pm 3) ^\circ\text{C}$  max.

**B.2.5** Start the motor. The heating device for the test gear box shall be in position "Off".

**B.2.6** At the end of the test, inspect the pinion for tooth flank changes. Record the tooth condition, using the examples in Figure 2 as a guide.

**B.2.7** Weigh the pinion and the wheel each to the nearest 0,001 g and determine weight loss  $\Delta m_{10}$  during the test.

#### B.3 Reporting results

Report the weight loss of pinion and wheel ( $\Delta m_{10} + \Delta m_{12}$ ) and report the specific weight loss  $\Delta m_{SE}$ .

$$\Delta m_{SE} = \frac{\Delta m_{10} - \Delta m_{12}}{1463} \text{ mg/(kW}\cdot\text{h)}$$

Weight losses during test:

		Pinion	Wheel	Pinion + Wheel
Weight loss	after load stage 12, $\Delta m_{12}$ , mg	.....	.....	.....
	after load stage 10, $\Delta m_{10}$ , mg	.....		.....

## Annex C (informative)

### Checklist for maintenance of FZG gear test rig

#### C.1 How to recognize malfunction

##### C.1.1 Distribution of scuffing marks

Frequently, an indication that the machine requires maintenance is given by the distribution of scuffing marks across the face width of every tooth and around the circumference after every gear-oil test.

Uneven distribution of scuffing marks across the face width indicates uneven load distribution, and, because of elastic deformations, this is more likely at low load stages than it is at high load stages. Figure C.1 shows scuffing marks distribution for perfect running operation, as also for misalignment and tumbling error indicating the malfunction.

##### C.1.2 Tooth contact pattern

From time to time (e.g. after every twentieth test), or after indication of load maldistribution, the contact pattern should be checked either by using soot or Prussian blue. Under no-load conditions, the tooth contact pattern should be uniformly distributed and should cover 70 % or more of the active flank area.

##### C.1.3 Tests with reference oil

From time to time (e.g. after every fortieth test), a duplicated scuffing test with a minimum of one of the two reference oils for the test is recommended. Deviations from the typical scuffing load stage of the reference oil, high scattering between the two tests and regular increase or decrease of scuffing load stage as compared to former reference oil tests can indicate a malfunction.

Organizations such as CEC have defined reference oils for comparison testing.

##### C.1.4 Other indications

Noise and vibrations, temperatures, bearing play, wear, etc. should be checked.

#### C.2 Parts that need maintenance

##### C.2.1 Test gear box

###### C.2.1.1 Shafts

Bearings shall have a light shrink fit on the shafts. Bearings shall not slide on or off the shaft at same (ambient) temperature of bearing and shaft. Indication of a slack fit are circumferential wear or even scoring marks on the shaft and the inner diameter of the bearing when the inner race of the bearing slides on the shaft during operation.

Gears shall have a slight shrink fit on the shafts. They shall not easily slide on or off the shaft at same temperature of gear and shaft. Possible slight fretting corrosion on the shafts is not harmful and can be polished off the shaft using e.g. a chrome polish. Tangible wear marks on the shaft cannot be tolerated.