

---

---

**Cleanrooms and associated controlled environments —**

Part 13:  
**Cleaning of surfaces to achieve defined levels of cleanliness in terms of particle and chemical classifications**

*Salles propres et environnements maîtrisés apparentés —*

*Partie 13: Nettoyage des surfaces afin d'obtenir des niveaux de propreté par rapport aux classifications particulaire et chimique*

STANDARDSISO.COM : Click to view the full PDF of ISO 14644-13:2017



STANDARDSISO.COM : Click to view the full PDF of ISO 14644-13:2017



**COPYRIGHT PROTECTED DOCUMENT**

© ISO 2017, Published in Switzerland

All rights reserved. Unless otherwise specified, no part of this publication may be reproduced or utilized otherwise in any form or by any means, electronic or mechanical, including photocopying, or posting on the internet or an intranet, without prior written permission. Permission can be requested from either ISO at the address below or ISO's member body in the country of the requester.

ISO copyright office  
Ch. de Blandonnet 8 • CP 401  
CH-1214 Vernier, Geneva, Switzerland  
Tel. +41 22 749 01 11  
Fax +41 22 749 09 47  
copyright@iso.org  
www.iso.org

# Contents

	Page
<b>Foreword</b> .....	<b>v</b>
<b>Introduction</b> .....	<b>vi</b>
<b>1 Scope</b> .....	<b>1</b>
<b>2 Normative references</b> .....	<b>2</b>
<b>3 Terms and definitions</b> .....	<b>2</b>
<b>4 General methodology</b> .....	<b>3</b>
4.1 Overview.....	3
4.2 Methodology.....	4
<b>5 Object description</b> .....	<b>6</b>
<b>6 Cleanliness specifications</b> .....	<b>7</b>
<b>7 Determination of initial contamination level</b> .....	<b>7</b>
7.1 General.....	7
7.2 Determination of initial contamination level with respect to particle concentration.....	7
7.3 Determination of initial contamination level with respect to chemical concentration.....	7
<b>8 Other requirements</b> .....	<b>8</b>
<b>9 Selection of a cleaning methodology</b> .....	<b>8</b>
9.1 Selection procedure.....	8
9.2 Cleaning methodologies.....	8
9.2.1 Cleaning method.....	8
9.2.2 Categories of cleaning techniques.....	8
9.3 Cleaning process.....	9
<b>10 Material compatibility check</b> .....	<b>9</b>
<b>11 Cleaning validation</b> .....	<b>10</b>
11.1 General.....	10
11.2 Cleaning efficiency.....	11
11.2.1 Evaluation.....	11
11.2.2 Cleaning efficiency with respect to particle concentration.....	11
11.2.3 Cleaning efficiency with respect to chemical contamination.....	12
11.3 Cleaning appropriateness.....	13
11.3.1 Assessment.....	13
11.3.2 Cleaning appropriateness with respect to particle concentration.....	13
11.3.3 Cleaning appropriateness with respect to chemical concentration.....	14
<b>12 Measurement methods</b> .....	<b>15</b>
12.1 General.....	15
12.2 Direct measurement methods.....	15
12.2.1 General.....	15
12.2.2 Direct measurement methods with respect to SCP.....	16
12.2.3 Direct measurement methods with respect to SCC.....	16
12.3 Indirect measurement methods.....	16
12.3.1 General.....	16
12.3.2 Indirect measurement methods with respect to SCP.....	16
12.3.3 Indirect measurement methods with respect to SCC.....	17
<b>13 Documentation</b> .....	<b>17</b>
<b>Annex A (informative) Aspects of cleaning</b> .....	<b>18</b>
<b>Annex B (informative) Cleaning methods</b> .....	<b>19</b>
<b>Annex C (informative) Material compatibility with cleaning agents</b> .....	<b>27</b>
<b>Annex D (informative) Cleanliness measurement</b> .....	<b>29</b>

STANDARDSISO.COM : Click to view the full PDF of ISO 14644-13:2017

## Foreword

ISO (the International Organization for Standardization) is a worldwide federation of national standards bodies (ISO member bodies). The work of preparing International Standards is normally carried out through ISO technical committees. Each member body interested in a subject for which a technical committee has been established has the right to be represented on that committee. International organizations, governmental and non-governmental, in liaison with ISO, also take part in the work. ISO collaborates closely with the International Electrotechnical Commission (IEC) on all matters of electrotechnical standardization.

The procedures used to develop this document and those intended for its further maintenance are described in the ISO/IEC Directives, Part 1. In particular the different approval criteria needed for the different types of ISO documents should be noted. This document was drafted in accordance with the editorial rules of the ISO/IEC Directives, Part 2 (see [www.iso.org/directives](http://www.iso.org/directives)).

Attention is drawn to the possibility that some of the elements of this document may be the subject of patent rights. ISO shall not be held responsible for identifying any or all such patent rights. Details of any patent rights identified during the development of the document will be in the Introduction and/or on the ISO list of patent declarations received (see [www.iso.org/patents](http://www.iso.org/patents)).

Any trade name used in this document is information given for the convenience of users and does not constitute an endorsement.

For an explanation on the voluntary nature of standards, the meaning of ISO specific terms and expressions related to conformity assessment, as well as information about ISO's adherence to the World Trade Organization (WTO) principles in the Technical Barriers to Trade (TBT) see the following URL: [www.iso.org/iso/foreword.html](http://www.iso.org/iso/foreword.html).

This document was prepared by Technical Committee ISO/TC 209, *Cleanrooms and associated controlled environments*.

A list of all parts in the ISO 14644 series can be found on the ISO website.

## Introduction

The term surface refers to the interface between two phases. For the purpose of this document, the surface is a solid. A “clean surface” is where one or more of the contamination categories (particles, chemical) are under control due to cleaning/decontamination. The degree of cleanliness is specified in the corresponding surface cleanliness classifications (see ISO 14644-9 and ISO 14644-10). Different cleaning methods are necessary depending on the degree of cleanliness (cleanliness class) required. This document gives guidance on the selection of cleaning methods to achieve specified cleanliness levels. For the selection procedure, the aspects of surface description, cleanliness specifications, types of contamination, cleaning techniques, material compatibility, and assessment methodology are taken into consideration. Most of the methods are suitable for removal of more than one contamination category at the same time; therefore, a common standard for the selection of a cleaning method for both particles, as well as chemical contamination, is needed.

STANDARDSISO.COM : Click to view the full PDF of ISO 14644-13:2017

# Cleanrooms and associated controlled environments —

## Part 13:

# Cleaning of surfaces to achieve defined levels of cleanliness in terms of particle and chemical classifications

## 1 Scope

This document gives guidelines for cleaning to a specified degree on cleanroom surfaces, surfaces of equipment in a cleanroom and surfaces of materials in a cleanroom. Under consideration are all surfaces (external or internal) that are of interest. It provides guidance on the assessment of cleaning methods for achieving the required surface cleanliness by particle concentration (SCP) and surface cleanliness by chemical concentration (SCC) classes and which techniques should be considered to achieve these specified levels.

The appropriateness of cleaning techniques will make reference to the cleanliness classes and associated test methods found in ISO 14644-9 and ISO 14644-10.

The following matters of general guidance will be provided:

- expected surface cleanliness levels;
- suitability of cleaning methods;
- compatibility of surfaces with the cleaning technique;
- assessment of cleaning appropriateness.

The following will be excluded from this document:

- classification of cleaning methods;
- product produced within a cleanroom;
- specific surface-related cleaning methods;
- detailed description of cleaning mechanisms, methods and procedures of various cleaning methods;
- detailed material characteristics;
- description of damage mechanisms by cleaning processes and time-dependent effects;
- references to interactive bonding forces between contaminants and surfaces or generation processes that are usually time-dependent and process-dependent;
- other characteristics of particles such as electrostatic charge, ionic charges, etc.;
- chemical reactions between molecular contaminants and surfaces;
- microbiological aspects of surface cleanliness;
- radioactive aspects of contamination;
- health and safety considerations;
- environmental aspects such as waste disposal, emissions, etc.;

- selection and use of statistical methods.

## 2 Normative references

The following documents are referred to in the text in such a way that some or all of their content constitutes requirements of this document. For dated references, only the edition cited applies. For undated references, the latest edition of the referenced document (including any amendments) applies.

ISO 14644-8, *Cleanrooms and associated controlled environments — Part 8: Classification of air cleanliness by chemical concentration (ACC)*

ISO 14644-9, *Cleanrooms and associated controlled environments — Part 9: Classification of surface cleanliness by particle concentration*

ISO 14644-10, *Cleanrooms and associated controlled environments — Part 10: Classification of surface cleanliness by chemical concentration*

## 3 Terms and definitions

For the purposes of this document, the terms and definitions given in ISO 14644-9, ISO 14644-10 and the following apply.

ISO and IEC maintain terminological databases for use in standardization at the following addresses:

- IEC Electropedia: available at <http://www.electropedia.org/>
- ISO Online browsing platform: available at <http://www.iso.org/obp>

### 3.1 cleanliness

<of a solid surface>condition of a solid surface where the amount of *contamination* (3.4) (particle, chemical) is controlled to a specific level

### 3.2 cleaning appropriateness

relation between the required *cleanliness* (3.1) and the accomplished cleanliness under controlled conditions

Note 1 to entry: In some languages, the term cleaning efficacy is used to indicate cleaning appropriateness.

Note 2 to entry: In case of real operational conditions or monitoring, the term cleaning effectiveness is used.

### 3.3 cleaning efficiency

fraction of specific contaminants removed from a surface by a cleaning process

Note 1 to entry: The fraction is determined by the accomplished surface cleanliness in respect to the initial surface cleanliness.

### 3.4 contamination

unwanted matter in an undesirable location

### 3.5 particle

minute piece of matter with defined physical boundaries

[SOURCE: ISO 14644-1:2015, 3.2.1]

3.6

**particle contamination**

*particles* (3.5) having the potential to affect the process, the product, the personnel or the facilities

3.7


**particle size**

diameter of a sphere that produces a response, by a given particle-sizing instrument, that is equivalent to the response produced by the *particle* (3.5) being measured

**4 General methodology**

**4.1 Overview**

Multiple aspects need to be considered for cleaning. [Figure 1](#) provides an overview of the factors that contribute to the suitability of cleaning methods to achieve a defined level of surface cleanliness. For more details, see [Annex A](#).

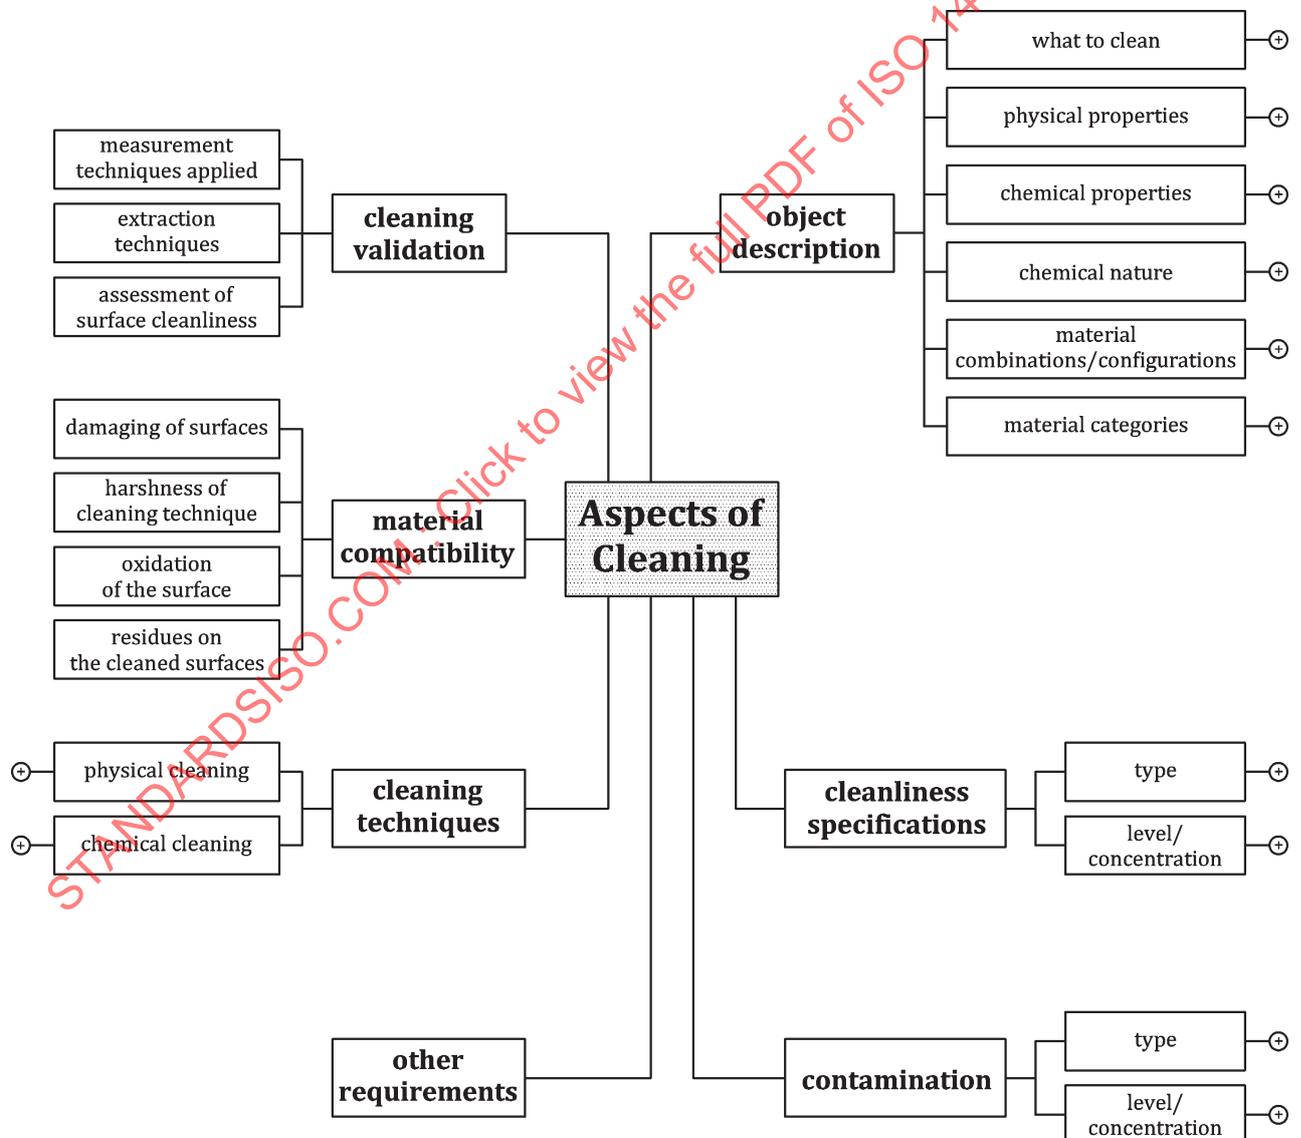

**Key**

+ more details in [Figure A.1](#)

**Figure 1 — Overview of cleaning aspects (non-exhaustive)**

## 4.2 Methodology

Appropriateness of a cleaning technique for an application depends on many factors. For complex objects, it is advised to follow the sequence described in this clause and in the decision tree (see [Figure 2](#)). By using this procedure, it can be assured that all important issues are covered. For simple objects or surfaces, deviations from the sequence are allowable, as long as the critical information is documented.

The approach starts with describing the object that has to be cleaned. The description should cover, among others, composition of materials, chemical characteristics, surface finish and shape factors like geometrical complexity and size (step 1). In the second step, the objective of the cleaning procedure is to be specified in terms of the desired cleanliness of the object. To have a starting point, the initial contamination level should be assessed (step 3) and other requirements shall be listed (step 4). Based on type of contaminants and the required removal efficiency, a cleaning technique or a combination of techniques can be selected (step 5). The cleaning methodology shall be checked against the materials from the first step in order to avoid material compatibility issues (step 6). At the last step, a validation method shall be carried out (step 7). The validation shall at least comprise methods for determination of the cleaning performance and material compatibility. The performance of the cleaning shall be checked against the specification.

STANDARDSISO.COM : Click to view the full PDF of ISO 14644-13:2017

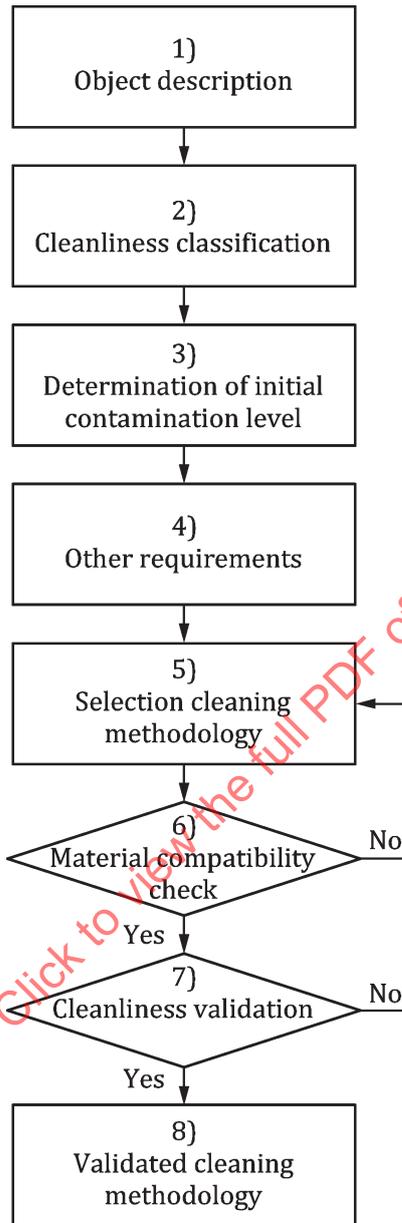


Figure 2 — Decision tree

## 5 Object description

In the object description, the following aspects shall be considered.

### Physical properties of the object:

- physical dimensions;
- form/shape/complexity of the object;
- critical surfaces.

A general description of the object shall be given. Size, shape, complexity and identification of the critical surfaces set many boundary conditions for a cleaning method.

### Surface(s):

- material composition of the object surface(s);
- complexity;
- materials/critical materials (sensitive to cleaning agents);
- thin/atomic surface layers (e.g. protective layers);
- other physical properties (e.g. electrostatic).

The composition of the object could be simple (one or more similar material(s)) or a system consisting of a range of different materials (e.g. metal/plastic/glass composition). Each individual material should be taken into account when choosing a cleaning method. Some combinations of materials can be very difficult to clean as one cleaning method may be suitable for one material but not the other. The selection of the cleaning method shall be the best compromise between minimal damage of the materials at maximum cleaning efficiency.

### Chemical properties of the surface(s):

- chemical composition;
- state of the surface (hydrophobic, hydrophilic, lipophobic, lipophilic, etc.);
- energetic state of the surface (zeta potential).

Physical and chemical properties of a surface have a large influence on the choice of a cleaning method. Choice of a method shall take into account all involved materials/chemical composition of the surface(s) and the combination of materials undergoing cleaning.

The activity of the surface is determined by the chemical configuration of the final atomic layer. This is an important parameter in determining the choice of method. These layers may be hydrophilic (water wettable-lipophobic) or hydrophobic (water repellent but oil-wettable-lipophilic). The cleaning method used can influence the surface activity. The surface activity also influences the electrostatic properties of a material — a hydrophilic surface will have fewer tendencies to electrically charge.

### Morphology:

Cleaning is influenced by the morphological aspects of a surface such as shape, size, structure, surface roughness or porosity. Morphological aspects may further complicate cleaning due to the accessibility of the surfaces to be cleaned and to the retention of cleaning agents and materials used for cleaning.

### Object specific requirements:

- intended use of the object;

- environmental conditions, both pre- and post-cleaning;
- critical surfaces — surfaces with either high importance in the application or sensitive to cleaning.

## 6 Cleanliness specifications

The rationale of determining appropriateness of the cleaning method should include the contaminants of concern, as well as acceptable levels of contamination for the application.

The required cleanliness shall be specified in terms of particle concentration according to ISO 14644-9 and/or in terms of the concentration of a specific group of chemicals according to ISO 14644-10.

The specification of the targeted cleanliness class can be determined in various ways:

- cleanliness class required by customer;
- common cleanliness class required for similar objects;
- by performing an analysis on the impact of contamination of the surface in the (future) function of a product or process where the cleaned surface will be used;
- by performing tests or simulations with various cleanliness classes of the considered surface and/or;
- by performing an analysis of the contamination that caused failure or quality loss.

## 7 Determination of initial contamination level

### 7.1 General

To select the cleaning procedure for achieving a required surface cleanliness level, the initial surface cleanliness shall be established. The initial surface cleanliness by chemical and/or particle concentration shall be determined for the surfaces of interest. This can be determined qualitatively or quantitatively.

Qualitative evaluation is a non-numerical assessment (e.g. a visual inspection).

Where the quantitative surface cleanliness is determined, it can be related to the efficiency of the cleaning procedure in respect to the required surface cleanliness by particle concentration and/or chemical concentration. The quantified contamination (particle and/or chemical) shall be related to the area of the representative surface. This evaluation allows determination of the initial cleanliness class.

### 7.2 Determination of initial contamination level with respect to particle concentration

The initial surface cleanliness by particle concentration shall be determined for the different surfaces. Depending on the required cleanliness class, a qualitative assessment of the initial cleanliness level may be sufficient. For quantitative assessment, the number and size of particles shall be characterized by a measurement method as described in [Clause 12](#). The surface cleanliness classification as outlined in ISO 14644-9 shall be applied.

The quantified particle concentration shall be related to the area of the representative surface. This evaluation allows determination of the initial cleanliness class.

### 7.3 Determination of initial contamination level with respect to chemical concentration

The initial surface cleanliness by chemical concentration shall be determined for the different surfaces. Depending on the specific application, a qualitative assessment (e.g. water break test) of the initial cleanliness level might be sufficient. For quantitative assessment of the mass and nature of the chemical contaminants, a measurement technique according to [Clause 12](#) and ISO 14644-10 shall be applicable.

The quantified chemical contamination shall be related to the area of the representative surface. This evaluation allows determination of the initial cleanliness class.

## 8 Other requirements

In addition to requirements for cleaning appropriateness and product integrity, many other elements influence the applicability of the cleaning method. In step 5 of the decision tree (see [Figure 2](#)), these other aspects shall be listed and requirements shall be defined. The contents of these requirements are strongly related to the object or surface and its application.

Typical examples for other requirements are time available for cleaning, number of items that will be cleaned, available footprint, waste, investment and labour costs, level of operator skill and environmental aspects.

## 9 Selection of a cleaning methodology

### 9.1 Selection procedure

Requirements for cleaning are defined in [Clause 5](#) to [Clause 8](#). These requirements shall be considered during the selection process for the cleaning methodology to ensure the greatest uniformity between the requirements and the method.

The final decision of the choice of cleaning methodology shall be based on a combination of all aspects to find the technically and financially optimal, most efficient solution. The customer, the clean technology supplier and the process owner of the surface/object/component to be cleaned should be involved in this selection process. The decision optimizes the various parameters and shall assure specified surface quality. [Table B.1](#) and [Table B.2](#) can aid the selection process.

### 9.2 Cleaning methodologies

#### 9.2.1 Cleaning method

A cleaning methodology consists of a cleaning technique (e.g. wiping, plasma cleaning and ultrasonic cleaning) and a cleaning process. The cleaning process is linked to the cleaning techniques and involves the amount of mechanical energy, chemical energy, temperature and process time. By using a balanced combination of these four process parameters, the optimum cleaning result can be achieved. Final cleanliness can be limited by substrate damage and/or selection criteria defined in [Clause 8](#).

The required cleanliness level and the initial cleanliness level in particle and/or chemical concentration lead to a selection of cleaning methods. In case the initial cleanliness class is high and the required cleanliness class is low, a combination of methods may be required.

#### 9.2.2 Categories of cleaning techniques

The cleaning techniques can be divided depending on the major cleaning mechanism into physical and chemical cleaning which additionally could be divided into wet and dry cleaning techniques. Whether a process is categorized as physical/chemical or as wet/dry depends on the dominant mechanism used for the cleaning. A non-exhaustive list of physical cleaning techniques can be found in [B.2](#) (mechanical cleaning), [B.3](#) (fluidic cleaning), and [B.4](#) (blasting cleaning techniques). A list of chemical cleaning techniques can be found in [B.5](#) (chemical cleaning). References to the categories of cleaning techniques are given in [Table 1](#).

**Table 1 — Categorization of cleaning techniques as described in Annex B**

Cleaning technique	Physical	Chemical
Dry	<a href="#">B.2</a> , <a href="#">B.4</a> dry	<a href="#">B.5</a> dry
Wet	<a href="#">B.3</a> , <a href="#">B.4</a> wet	<a href="#">B.5</a> wet

The numbers refer to subclauses within [Annex B](#) that provide a brief description of the major cleaning techniques.

[Table B.1](#) and [Table B.2](#) support the choice of an appropriate cleaning technique (physical/chemical) that fulfils the cleanliness specifications. With the help of feasibility tests on material compatibility (see [Clause 10](#)) and empirical values/evaluation, the best suitable technique shall be chosen for validation (see [Clause 11](#)).

### 9.3 Cleaning process

In [Table B.1](#) and [Table B.2](#), an overview is given on the working ranges for different cleaning techniques. In these ranges, optimum process conditions are assumed. Since material properties and other requirements might force use of less than optimal conditions, the actual cleaning efficiency and appropriateness might be lower. The process settings shall be defined either by an experimental investigation or from experience.

## 10 Material compatibility check

The compatibility of materials with cleaning agents shall be considered. These cleaning agents (e.g. chemicals, solvents, high pressure gas or liquid) shall be selected with respect to their compatibility with the materials or items to be cleaned and their efficiency in removing different kinds of contaminants: particle or chemical contaminants.

Detrimental effects on surfaces can be caused by the cleaning agents and/or the cleaning technique. The chemical nature of the materials of the surface — individually or in combination depending on the composition of the surface — should be evaluated technically.

The following describes such direct, indirect and long duration effects.

- Direct effects are changes of intrinsic material properties (physical and/or chemical) as a consequence of the interaction with a process parameter from the cleaning technique: chemical nature of a solvent, time of exposure and temperature.

**EXAMPLE 1** The change of the chemical surface structure may strongly change the physical behaviour. Change of the hydrophilic character of the last atomic layer to hydrophobic through the cleaning process may change the physical behaviour of the cleaned surface, i.e. wettability and electrostatic charge. Hydrophobic surface is not wettable and is easily charged which may attract particles.

**EXAMPLE 2** Change in surface roughness.

- Indirect effects can be caused by different physical-chemical mechanisms as a consequence of secondary interactions (e.g. chemical reactions with specific compounds of the substrate) or as an interaction with a non-process parameter (post-degradation or oxidation by O<sub>2</sub> of air, deposits of residues as a new contamination).

**NOTE** An indirect effect might not be observed immediately.

- Long duration effects result from a slow process (e.g. induced corrosion from chemical conversion after chemical cleaning, ageing and weakening).

[Annex C](#) gives an overview of compatibility with chemical solvents; it is a non-exhaustive list. In the case of a lack of information for a specific cleaning solvent, the chemical resistance of the material shall be assessed through an appropriate test.

## 11 Cleaning validation

### 11.1 General

To assess the suitability of a selected cleaning procedure, the cleaning efficiency and the cleaning appropriateness should be considered.


For the validation of a cleaning process to reach the required surface cleanliness with respect to particle concentration and/or chemical concentration, the achieved surface cleanliness SCP and/or SCC levels should be determined.

Other performance-related aspects, such as repeatability, reproducibility and operator influences, shall also be considered. In [Clause 8](#), a set of requirements are defined that are not related to cleaning performance. Although these requirements are taken into account during the selection of the cleaning method, the validation process shall verify that these requirements are fulfilled.


[Figure 3](#) and [Figure 4](#) are depictions of the terms cleaning efficiency and cleaning appropriateness.

Cleaning efficiency =  $1 - \text{final cleanliness level} / \text{initial cleanliness level}$  (expressed as a percentage)

Cleaning appropriateness =  $\text{required cleanliness level} / \text{final cleanliness level}$

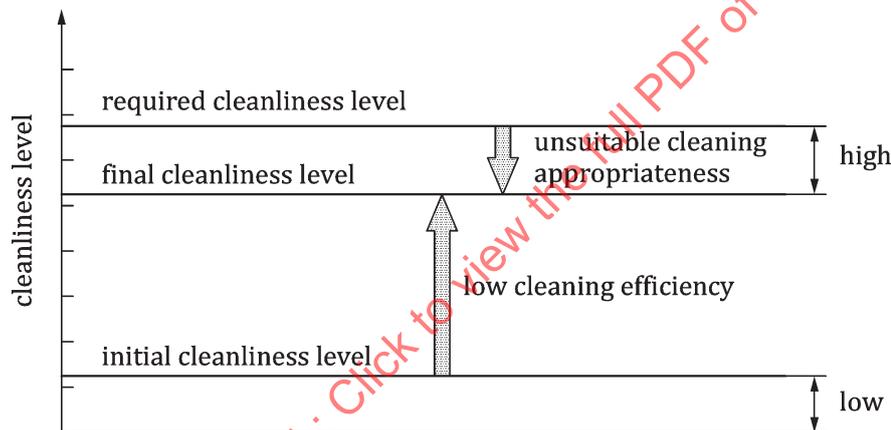

**Figure 3 — Example for a method with low cleaning efficiency leading to unsuitable cleaning appropriateness**

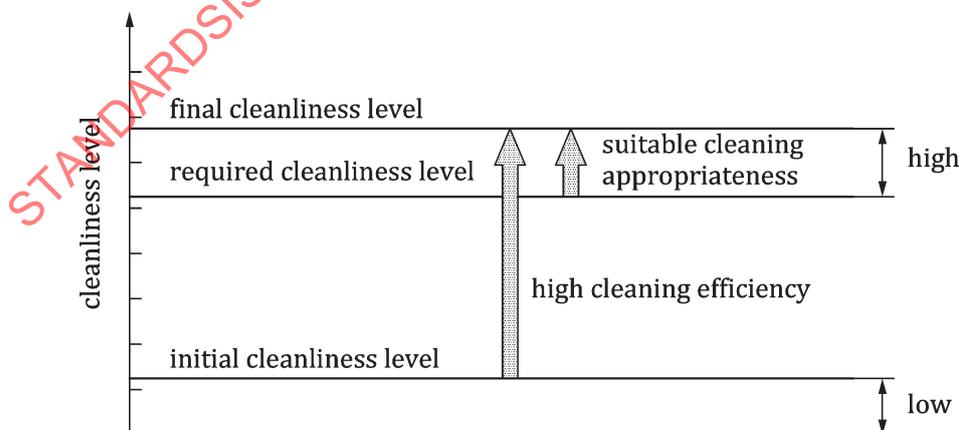

**Figure 4 — Example for a method with high cleaning efficiency leading to suitable cleaning appropriateness**

## 11.2 Cleaning efficiency

### 11.2.1 Evaluation

For evaluation of the cleaning efficiency, the initial surface cleanliness level and final cleanliness level shall be determined.

### 11.2.2 Cleaning efficiency with respect to particle concentration

The cleaning efficiency is calculated by [Formula \(1\)](#):

$$C_{\text{eff}} = 1 - \frac{C_{\text{SCP};D}^{\text{fin}}}{C_{\text{SCP};D}^{\text{ini}}} \quad (1)$$

where

$D$  is the particle size, in micrometres ( $\mu\text{m}$ );

$C_{\text{SCP};D}^{\text{ini}}$  is the initial surface concentration, in particles per square metre of surface, of particles that are equal to or larger than the considered particle size  $D$  in  $\mu\text{m}$ ;

$C_{\text{SCP};D}^{\text{fin}}$  is the final surface concentration, in particles per square metre of surface, of particles that are equal to or larger than the considered particle size  $D$  in  $\mu\text{m}$ .

In accordance with ISO 14644-9, the relation with the surface cleanliness class is given by [Formula \(2\)](#):

$$C_{\text{SCP};D} = k \frac{10^{\text{SCP};N}}{D} \quad (2)$$

where

$C_{\text{SCP};D}$  is the maximum permitted total surface concentration, in particles per square metre of surface, of particles that are equal to or larger than the considered particle size;

$\text{SCP};N$  is the SCP classification number;

$D$  is the considered particle size, in micrometres;

$k$  is the constant 1, in micrometres.

Combining [Formula \(1\)](#) and [Formula \(2\)](#) gives the cleaning efficiency in terms of SCP, in [Formula \(3\)](#):

$$C_{\text{eff}} = 1 - \frac{k \frac{10^{\text{SCP};N_{\text{fin}}}}{D}}{k \frac{10^{\text{SCP};N_{\text{ini}}}}{D}} = 1 - \frac{10^{\text{SCP};N_{\text{fin}}}}{10^{\text{SCP};N_{\text{ini}}}} = 1 - 10^{(\text{SCP};N_{\text{fin}} - \text{SCP};N_{\text{ini}})} \quad (3)$$

where

$D$  is the particle size, in micrometres;

$\text{SCP};N$  is the SCP classification number;

$\text{SCP};N_{\text{fin}}$  is the SCP classification number of the final surface cleanliness of particles;

$\text{SCP};N_{\text{ini}}$  is the SCP classification number of the initial surface cleanliness of particles.

NOTE The cleaning efficiency can also be expressed as a percentage (%).

EXAMPLE In this example, the smallest particle size that could be measured with the applied measurement method is 5 µm. Therefore, the concentration of the number of particles ≥5 µm is used.

The initial concentration of particles ≥5 µm per m<sup>2</sup>  $C_{SCP;5}^{ini}$  is 600 000. Therefore, the SCP;  $N_{ini} = \lg(600\,000 \times 5) = 6,5$ .

The initial surface cleanliness class number SCP;  $N_{ini} = 6,5$  for particles equal to or larger than 5 µm.

After cleaning, the final concentration of particles ≥5 µm per m<sup>2</sup>  $C_{SCP;5}^{fin}$  is 1 000. Therefore, the SCP;  $N_{fin} = \lg(1\,000 \times 5) = 3,7$ .

The final surface cleanliness class number SCP;  $N_{fin} = 3,7$  for particles equal to or larger than 5 µm.

The cleaning efficiency in terms of particle concentration =  $1 - (1\,000)/(600\,000) = 1 - 1/600 = 0,998$  or 99,8 % for particles ≥5 µm.

Similarly, the cleaning efficiency in respect to the SCP class numbers =  $1 - 10^{(3,7 - 6,5)} = 1 - 10^{-2,8} = 0,998\,4$  or 99,8 % for particles ≥5 µm.

### 11.2.3 Cleaning efficiency with respect to chemical contamination

The cleaning efficiency is calculated by [Formula \(4\)](#):

$$C_{eff} = 1 - \frac{C_{SCC}^{fin}}{C_{SCC}^{ini}} \quad (4)$$

where

$C_{SCC}^{ini}$  is the initial concentration of the considered chemical (g/m<sup>2</sup>);

$C_{SCC}^{fin}$  is the final concentration of the considered chemical (g/m<sup>2</sup>).

According to ISO 14644-10, the relation with the surface cleanliness class by chemical concentration (SCC) is given by [Formula \(5\)](#):

$$C_{SCC} = 10^{SCC;N} \quad (5)$$

where

SCC;  $N$  is the surface cleanliness of chemical concentration by classification number.

Combining [Formula \(4\)](#) and [Formula \(5\)](#) gives the cleaning efficiency in terms of SCC, in [Formula \(6\)](#):

$$C_{eff} = 1 - \frac{10^{SCC;N_{fin}}}{10^{SCC;N_{ini}}} = 1 - 10^{(SCC;N_{fin} - SCC;N_{ini})} \quad (6)$$

NOTE The cleaning efficiency can also be expressed as a percentage (%).

EXAMPLE The initial concentration of the hydrocarbons is 50 mg per m<sup>2</sup> for hydrocarbons.

Therefore, the

$$SCC;N_{ini} = \lg(50 \times 10^{-3}) = -1,3$$

for hydrocarbons.

The final concentration of the hydrocarbons is 10 µg per m<sup>2</sup>.

Therefore, the

$$SCC;N_{fin} = \lg(10 \times 10^{-6}) = -5,0.$$

The cleaning efficiency in terms of chemical concentration =

$$1 - 10 \times 10^{-6} / 50 \times 1\,000 \times 10^{-6} = 1 - 10 / 50\,000 = 0,999\,8 \text{ or } 99,98\% \text{ for hydrocarbons.}$$

Similarly, the cleaning efficiency in respect to the SCC classes =  $1 - 10^{(-5,0 + 1,3)} = 1 - 10^{-3,7} = 0,999\,8$  or 99,98 % for hydrocarbons.

## 11.3 Cleaning appropriateness

### 11.3.1 Assessment

For evaluation of the cleaning appropriateness, the final cleanliness level obtained shall be determined and compared to the required surface cleanliness.

### 11.3.2 Cleaning appropriateness with respect to particle concentration

The cleaning appropriateness is calculated by [Formula \(7\)](#):

$$C_{app} = \frac{C_{SCP;D}^{requ}}{C_{SCP;D}^{fin}} \quad (7)$$

where

$C_{SCP;D}^{requ}$  is the required concentration of particles equal to or larger than  $D$  µm;

$C_{SCP;D}^{fin}$  is the final particle concentration obtained of particles equal to or larger than  $D$  µm.

$D$  is the particle size, in micrometres.

According to ISO 14644-9, the relation with the surface cleanliness class is given by [Formula \(8\)](#):

$$C_{SCP;D} = k \frac{10^{SCP;N}}{D} \quad (8)$$

where

$C_{SCP;D}$  is the concentration of particles equal to or larger than  $D$  µm;

$D$  is the particle size, in micrometres;

$SCP;N$  is the SCP classification number.

Combining [Formula \(7\)](#) and [Formula \(8\)](#) gives the cleaning appropriateness in terms of SCP class numbers, in [Formula \(9\)](#):

$$C_{app} = \frac{10^{SCP;N_{requ}}}{10^{SCP;N_{fin}}} = 10^{(SCP;N_{requ} - SCP;N_{fin})} \quad (9)$$

If the cleaning appropriateness is less than 1, the chosen cleaning procedure was not suitable.

If the cleaning appropriateness is equal or greater than 1, the chosen cleaning procedure was suitable and results in a surface at the required cleanliness class.

NOTE The cleaning appropriateness can also be expressed as a percentage (%).

EXAMPLE In this example, the smallest particle size that could be measured with the applied measurement method is 10 µm. Therefore, the concentration of the number of particles ≥ 10 µm is used.

The required SCP;N<sub>requ</sub> = 4,0 for particles equal to or larger than 10 µm.

This means that  $C_{SCP;10}^{requ} (10 \mu m) = 10\ 000/10 \mu m = 1\ 000$  particles/m<sup>2</sup>.

The final concentration of particles obtained ≥ 10 µm  $C_{SCP;10}^{fin}$  is 1 250 particles/m<sup>2</sup>.

Cleaning appropriateness =  $C_{SCP;10}^{requ} / C_{SCP;10}^{fin} = 1\ 000/1\ 250 = 0,8 \rightarrow 80\ %$  for particles ≥ 10 µm.

In terms of SCP:

$SCP;N_{fin} = \lg (1\ 250 \times 10) = 4,1$ .

The cleaning appropriateness =  $10^{(4,0 - 4,1)} = 10^{-0,1} = 0,8$  or 80%.

The cleaning appropriateness does not meet the requirements.

### 11.3.3 Cleaning appropriateness with respect to chemical concentration

The cleaning appropriateness is the ratio of the required surface cleanliness by chemical concentration under controlled conditions to the (final) chemical concentration after cleaning, given by [Formula \(10\)](#):

$$C_{app} = \frac{C_{SCC}^{requ}}{C_{SCC}^{fin}} \quad (10)$$

where

$C_{SCC}^{requ}$  is the required maximum concentration of the considered chemical (g/m<sup>2</sup>);

$C_{SCC}^{fin}$  is the final concentration of the considered chemical (g/m<sup>2</sup>).

According to ISO 14644-10, the relation with the surface cleanliness class by chemical concentration (SCC) is given by [Formula \(11\)](#):

$$C_{SCC} = 10^{SCC;N} \quad (11)$$

where

$C_{SCC}$  is the maximum allowable concentration of the specified chemical substance or group of substances, expressed in g/m<sup>2</sup>;

SCC;N is the common logarithm index of concentration  $C_{SCC}$ .

Combining both [Formula \(10\)](#) and [Formula \(11\)](#) gives the cleaning appropriateness in terms of SCC, in [Formula \(12\)](#):

$$C_{\text{app}} = \frac{C_{\text{SCC}}^{\text{requ}}}{C_{\text{SCC}}^{\text{fin}}} = 10^{\left(C_{\text{SCC}}^{\text{requ}} - C_{\text{SCC}}^{\text{fin}}\right)} \quad (12)$$

where

$C_{\text{SCC}}^{\text{requ}}$  is the required maximum concentration of the considered chemical ( $\text{g}/\text{m}^2$ );

$C_{\text{SCC}}^{\text{fin}}$  is the final concentration of the considered chemical ( $\text{g}/\text{m}^2$ ).

If the cleaning appropriateness is smaller than 1, the chosen cleaning procedure was not appropriate. If the cleaning appropriateness is equal to or greater than 1, the chosen cleaning procedure was appropriate and results in a surface at the required cleanliness class.

NOTE The cleaning appropriateness can also be expressed as a percentage (%).

EXAMPLE The required  $\text{SCC};N_{\text{requ}} = -4,0$  for hydrocarbons.  $\text{SCC};N_{\text{requ}} = 10^{-4} \text{ g}/\text{m}^2 = 100 \text{ }\mu\text{g}/\text{m}^2$ .

The resulting concentration of the hydrocarbons is  $70 \text{ }\mu\text{g per m}^2$ .

Cleaning appropriateness =  $100/70 = 1,43$  is 143 %.

In terms of SCC class numbers:

$$\text{SCC};N_{\text{requ}} = \lg\left(70 \times 10^{-6}\right) = -4,15.$$

The cleaning appropriateness =  $10^{(-4,0 + 4,15)} = 10^{0,15} = 1,41$  is 141 %.

The cleaning appropriateness does meet the requirements.

## 12 Measurement methods

### 12.1 General

The particle concentration and/or concentration of chemicals on a cleaned surface can be measured in a direct or indirect way. Direct surface cleanliness measurement may be appropriate in situations where the surface is accessible. The surface under study shall be brought to the measurement instrumentation or the instrumentation shall be brought to the surface.

The area of the surface selected for measurement shall be both representative of the entire area being assessed and the level particle and/or chemical contamination present.

The selected surface cleanliness measurement method can be applied to determine the initial and/or final surface cleanliness class.

Applicable measurement methods are described in ISO 14644-9 and ISO 14644-10.

For further information on measurement methods, see [Annex D](#).

### 12.2 Direct measurement methods

#### 12.2.1 General

A direct measurement method determines the surface cleanliness with respect to particle concentration or chemical concentration on the surface of interest of the object that has been cleaned. The resulting

concentration of particles or the chemical of interest shall be expressed as either concentrations or surface cleanliness classes (SCP and SCC).

### 12.2.2 Direct measurement methods with respect to SCP

Count the number of particles  $>D$  per surface area. For  $D$ , a set of different size bins ( $D_i$  and  $D_{i+1}$ ) could be selected. The smallest size  $D_1$  shall be equal to or smaller than the particle size of interest.

By using a particular magnification by a magnifying glass or (stereo) microscope, smaller particle sizes can be counted, but the field of view will be also smaller. When the field of view is too small, the surface may need to be scanned to measure a representative surface area. A representative area is determined by the area that may contain at least 20 particles of the size of interest within the intended SCP class [see [Formula \(13\)](#)].

$$A \geq 20 \times \frac{D}{10^{SCP}} \quad (13)$$

### 12.2.3 Direct measurement methods with respect to SCC

Use a spectroscopic or advanced surface analysis technique to measure the chemical contamination of interest on the surface.

In an enclosed heating or vacuum system, the SCC can be determined by measuring the outgassing of the surface using mass spectroscopy and associated residual gas analysis techniques.

In some cases, a part of the surface could be removed from the object to fit into an advanced measurement system.

## 12.3 Indirect measurement methods

### 12.3.1 General

An indirect method should be used when the surface to be measured cannot be reached by, is too small, or too large for the available measurement system.

### 12.3.2 Indirect measurement methods with respect to SCP

For this method, particles should be removed from the surface into either another medium (air, liquid) or onto another surface.

The transfer efficiency shall be taken into account and will depend on the transfer method, particle size and surface properties.

For particles suspended in a liquid or a gas, either a filtration method with subsequent microscopic analysis or discrete particle counting method can be used. For transfer surfaces, a direct measurement method can be used.

Count the number of particles  $>D$  per surface area. For  $D$ , a set of different size bins ( $D_i$  and  $D_{i+1}$ ) could be selected. The smallest size  $D_1$  shall be equal to or smaller than the particle size of interest.

To determine the original surface contamination, the measured number of particles should be divided by the surface area from which the particles are removed.

A smaller particle size can be counted by using a higher magnification. However, the field of view will be also smaller. If the field of view is too small, the surface may need to be scanned to measure a representative surface area. A representative area is determined by an area that may contain at least 20 particles of the size of interest of the intended SCP class [see [Formula \(11\)](#)].

### 12.3.3 Indirect measurement methods with respect to SCC

To measure the concentration of chemicals of interest on the surface of an object, the chemicals can be extracted by the chemical contamination being dissolved into a solvent. The solvent containing the extracted chemicals can then be analysed by an appropriate chemical analysis technique. In a heating or vacuum system, the chemical contaminants can be concentrated in a sorbent and measured by an appropriate chemical analysis technique.

The transfer efficiency should be taken into account and depends on the transfer method, the chemicals of interest and the surface properties.

The mass of the chemicals of interest shall be divided by the surface area from which the chemicals are removed to determine the original concentration.

## 13 Documentation

The results from each step in the decision tree (see [Figure 2](#)) shall be recorded and submitted as a comprehensive report, along with a statement of compliance or non-compliance with the specified goals, as described in [Clause 5](#) to [Clause 12](#). For simple cases, steps may be combined and reported in one document.

The report shall include the following:

- a) the name and address of the executive organization;
- b) the staff identification and the date on which tests were performed or decisions were made;
- c) a reference to this document, i.e. ISO 14644-13:2017;
- d) the specified designation criteria for the object;
- e) the boundary conditions and assumptions;
- f) the applied methods and procedures, e.g. ISO 14644-9 for surface particle cleanliness and ISO 14644-8 for classification air cleanliness by chemical concentration and ISO 14644-10 surface cleanliness by chemical concentration;
- g) the measuring instruments applied and proof of calibration;
- h) the results, either from assessments/selection procedures or experimental results. For the results on cleaning validation, the documentation requirements of ISO 14644-9 and ISO 14644-8 and/or ISO 14644-10 shall be followed;
- i) a transfer statement for starting the next step.

NOTE In the decision tree (see [Figure 2](#)) assessments, selection procedures and experimental studies are involved. Therefore, the text refers to executive organization and staff identification instead of the often used terms testing organization and operator identification.

## Annex A (informative)

### Aspects of cleaning

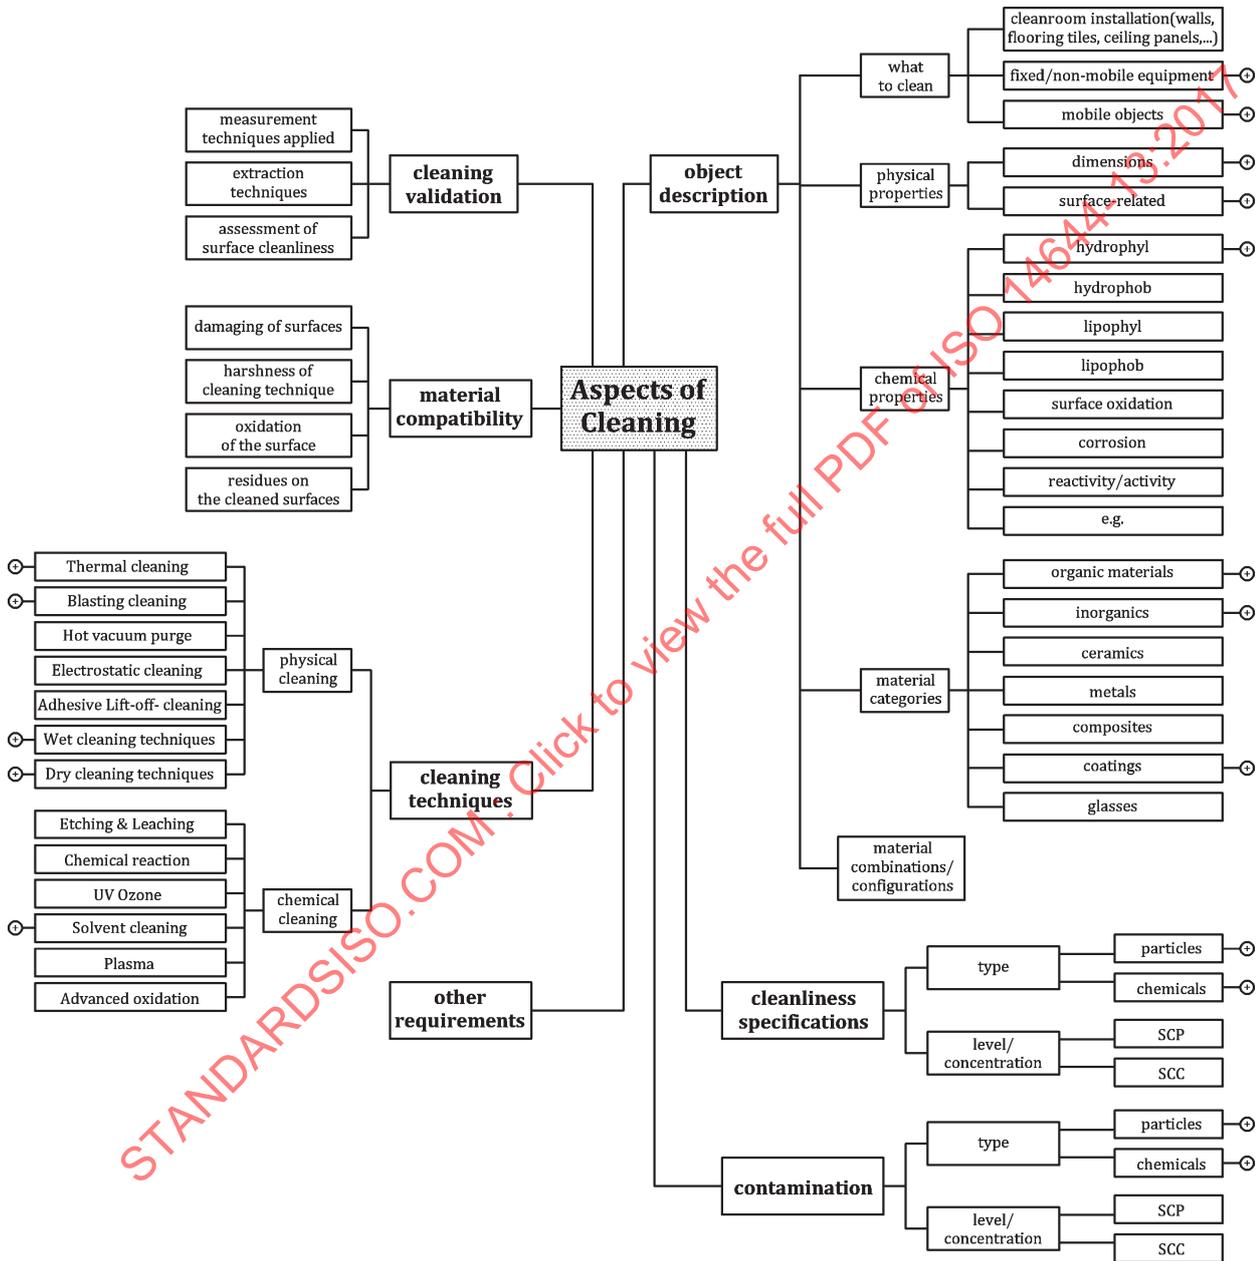


Figure A.1 — Detailed non-exhaustive overview of cleaning aspects

## Annex B (informative)

### Cleaning methods

#### B.1 General

It is important to note that some cleaning methods are only for application outside the cleanroom for pre-cleaning.

The number of available techniques is extensive. This overview gives an indication of the available cleaning methods. The methods are divided into:

- mechanical cleaning;
- fluidic cleaning;
- chemical cleaning;
- blasting cleaning techniques.

In some cases, combinations of the described cleaning methods can be applied.

For all dry cleaning techniques, tribo-electrical effects may cause charging of the surface. Electrostatic attraction plays an important role in the adhesion of dust particles to a product surface. In order to eliminate this adhesive force, an equal number of positive and negative ions can be generated in ionized air and transported to the surface of the product where they neutralize the electrostatically charged dust particles and the surface itself. By neutralizing the surface particle re-deposition is avoided.

#### B.2 Mechanical cleaning

##### B.2.1 Wiping

Principle: Soft, non-abrasive, non-cross contaminating materials can be utilized to remove lightly-adhering contaminants (dust, dirty water, etc.). If a wiping process is performed using a cleaning fluid, the chemical action of the cleaning agent is essentially responsible for the cleaning effect. In order to detach and remove contaminants with a wipe or a supported wipe, the adhesive forces between the contamination and object surface need to be overridden by frictional movements.

Areas of application: Wiping is especially effective for removing liquid and particle contamination. It is usually a manual process.

##### B.2.2 Brushing/sweeping

Principle: The cleaning technique of brushing/sweeping is the purely mechanical wiping off or abrading of generally solid contaminants from an object surface through the action of bristles. Brushes with soft bristles made of plastic or natural fibres are used to remove easily-detachable contamination, such as dust. For strongly-adhering contaminants such as oxides, scale or paint, stiffened, non-shedding bristles may be utilized. All materials which are not damaged by the chosen brush or where a minimum degree of surface abrasion is tolerated can be cleaned in this way.

Areas of application: Brushing/sweeping is frequently used to clean flat surfaces.

### B.2.3 Scraping/abrading

Principle: Scraping or abrading is a mechanical separation technique in which adhering solids are lifted up by a tool placed beneath them (e.g. blade or scraper) and then removed.

Areas of application: Scraping/abrading is implemented to remove strongly-adhering material residues from essentially smooth surfaces.

### B.2.4 Grinding

Principle: Grinding is the removal of superficial contamination by abrasion, where usually rotating grinding discs or high-speed circular grinding belts are used. Grinding is capable of removing strongly-adhering contaminants such as scales, oxides, rust, coatings or paints quickly and effectively. The fact that a certain amount of base material will be abraded as well should be taken into account.

Areas of application: As the grinding discs used are made of grains of hard material (e.g. silicon carbide, diamonds) embedded in a bonding material, the selection of the grain/bonding material is decisive for the grinding process.

## B.3 Fluidic cleaning

### B.3.1 Washing/rinsing/drying

Principle: Cleaning with the aid of liquid agents often involves washing in order to remove the detached/emulsified contamination, as well as the active ingredients of the solvent cleaning agent itself, e.g. surfactants and emulsifiers, from the object surface. This prevents contaminants from being transferred to the next cleaning step or causing re-contamination in a subsequent rinsing or drying process.

Rinsing is applied to remove unwanted residues of the washing process.

Drying is generally the final step. It removes the remains of the cleaning medium of the previous process. It does not remove contamination from the previous process.

Areas of application: Rinsing processes are principally used to achieve improved cleanliness levels after cleaning with aqueous fluids.

### B.3.2 Compressed gas cleaning

Principle: With this cleaning technique, surfaces are cleaned by the action of a jet of gas which is directed at an object at high speed via a nozzle. The gas jet exerts an aerodynamic force on the particle. If the aerodynamic resistance of a particle exceeds the adhesive force between the particle and the surface, the particle is detached from the surface and carried away with the flow of gas. In particular, the technique allows dry, loosely-adhering contaminants, such as dust, to be removed effectively. Particles in the micrometre size range can no longer solely be removed by use a high-speed jet of gas. Particles are suspended in the gas and can be re-deposited at other locations. Ionized gas can suppress the electrostatic charge of the surface.

Areas of application: If only dry contamination is present, good cleaning results can be achieved for particles larger than 5  $\mu\text{m}$ . Liquid or paste-like contamination can also be removed partially as long as higher pressures, e.g. by using supersonic (Venturi) nozzles, are applied.

### B.3.3 Vacuum cleaning

Principle: A suction nozzle is placed above the object's surface to be cleaned and being connected to a pump creates a negative pressure which causes an air flow away from the object's surface. This airflow exerts an aerodynamic force on the particle contamination. If the aerodynamic resistance of the particle exceeds the adhesive force between the particle and the surface, the particle is detached from the surface and carried away with the airflow. Vacuum cleaning is especially suitable for removing dry

contamination such as dust particles. Usually, this technique is unsuitable for removing particles in the micrometre range.

Areas of application: Vacuum cleaning is used in controlled environments and for hard to reach areas.

### **B.3.4 Sonic cleaning**

#### **B.3.4.1 Ultrasonic cleaning**

Principle: With ultrasonic cleaning, the objects to be cleaned are suspended in a bath filled with a suitable cleaning agent. Ultrasound waves are created in the cleaning bath via oscillating walls that spread longitudinally through the cleaning agent. Imploding cavitation bubbles create very high pressures of approximately 1 000 bar which will blast off contamination from surfaces which are then dissolved or dispersed into the cleaning fluid. After cleaning, the surfaces need to be rinsed and dried.

Ultrasonic action is also active at internal surfaces that are otherwise hard to clean.

Areas of application: Ultrasonic cleaning achieves extremely high quality results within a very short time, even for complex-shaped objects, crevices and drill holes. In general, ultrasonic cleaning is a gentle cleaning technique which can be used to clean delicate surfaces without damaging them.

#### **B.3.4.2 Megasonic cleaning**

Principle: Megasonic cleaning relates to the group of sonic cleaning. As megasonic cleaning uses higher frequencies (often in the range of 800 kHz to 2 000 kHz) than ultrasonic cleaning (20 kHz to 500 kHz) it creates less cavitation and therefore causes less damage to the surfaces to be cleaned. Acoustic waves in the cleaning fluid generate pressure variations which remove contamination from surfaces. Only the surface of the object facing the transducer(s) is cleaned.

Areas of application: Medical implant, flat panel and wafer manufacturing or industrial parts cleaning.

### **B.3.5 Spray cleaning**

Principle: Cleaning liquid enters under increased pressure in the cleaning environment (chamber). A wide range of cleaning agents can be used in combination with water. The cleaning action is characterized by a high impact of cleaning spray and a continuous refreshment of the cleaning agent. In a spray cleaner, either the object to be cleaned or the nozzle can be moved in order to cover the entire object surface.

Areas of application: Spray cleaning is used for a wide range of objects.

## **B.4 Blasting cleaning techniques**

### **B.4.1 General**

The blasting cleaning techniques are divided into the main medium used to deliver the blast: gas and liquid.

Blasting cleaning techniques should only be applied to robust surfaces.

### **B.4.2 Gas blasting**

#### **B.4.2.1 Compressed air blasting**

Principle: Surfaces are cleaned through the action of various blasting agents which are carried in the compressed gas blast and applied at fixed or fluctuating speeds to the object to be cleaned. The method is highly versatile as it removes contamination, debris, corrosion, scale and paint. The high kinetic energy transferred by the blasting agent impacting onto the surface may cause damage.

Areas of application: Suitable for cleaning components and structures of every size and description, only areas in direct contact with the impacting media will be cleaned properly.

#### **B.4.2.2 Wet compressed air blasting**

Principle: The method is similar to that of compressed gas blasting. However, here a blasting jet composed of air is used to accelerate water and a blasting agent.

Areas of application: The method is appropriate for cleaning surfaces and structures of every size and shape. After application, the surface to be cleaned will be covered with a slurry which needs to be removed with an air or water jet after the cleaning is completed.

#### **B.4.2.3 CO<sub>2</sub> pellet cleaning**

Principle: Dry ice pellets at approximately  $-80\text{ }^{\circ}\text{C}$  (diameter/length in millimetre range) are accelerated to almost supersonic speed (300 m/s). The rapid cooling of the surface leads to embrittlement of the surface layers. During sublimation of CO<sub>2</sub>, adhered contamination can be easily removed from the surface. It is less abrasive than pressurized fluid blasting.

Areas of application: The method can be utilized on nearly all materials. As the method has abrasive character, some "soft" surfaces might be visibly roughened.

#### **B.4.2.4 Accelerated CO<sub>2</sub> snow cleaning**

Principle: Accelerated CO<sub>2</sub> snow cleaning is a dry and solvent-free process. As carbon dioxide expands rapidly; it changes from liquid CO<sub>2</sub> to a mixture of solid CO<sub>2</sub> (dry ice) and gaseous CO<sub>2</sub>. The dry ice is then blasted onto the surface to be cleaned accelerated by pure nitrogen. CO<sub>2</sub> snow cleaning is a further development of the CO<sub>2</sub> pellet cleaning. CO<sub>2</sub> snow cleaning is less abrasive than CO<sub>2</sub> pellet cleaning.

Areas of application: CO<sub>2</sub> snow cleaning has a broad scope of usage, ranging from precision cleaning right up to the cleaning of large surface areas. It can be utilized to clean highly sensitive surfaces. Particle contamination can be removed, as well as oil films, grease, fingerprints and flux residues.

### **B.4.3 Liquid blasting**

#### **B.4.3.1 Pressurized liquid blasting**

Principle: A jet of liquid under high pressure is directed via a nozzle at the surface to be cleaned. A solid blasting material can be added to the liquid to increase the abrasive action. Ideally, even single layers of a coating system can be cleaned off. After application, the surface to be cleaned will be covered with a slurry which needs to be removed with an air or water jet after the cleaning is completed.

Areas of application: Suitable for all sizes and shapes of cleaning surfaces and structures; only the areas in direct contact with the impacting media will be cleaned properly.

#### **B.4.3.2 Low-pressure water jet blasting**

Principle: Method similar to that of compressed air blasting. However, very little water is added to the blasting agent/air mixture in front of the nozzle. In contrast with compressed air blasting, a surface prepared using this method is initially wet.

Areas of application: Suitable for all sizes and shapes of cleaning surfaces and structures; only the areas in direct contact with the impacting media will be cleaned properly. It is invariably used in cases where dust and water levels need to be kept low.

#### **B.4.3.3 Elutriation blasting**

Principle: A fine-grained material dispersed in water or other liquid is blasted at high speed onto the surface to be cleaned. In contrast to wet compressed air, the liquid accelerates the blasting agent.

Elutriation blasting is used to clean and micro-finish surfaces at the same time. After elutriation cleaning, rinsing is necessary to get rid of any adhering blasting agent residues. Elutriation blasting is suitable for producing a fine and even surface profile.

Areas of application: Precision casting, micro-/precision deburring, polishing surfaces, cleaning surgical instruments.

#### **B.4.3.4 Steam blasting**

Principle: Heated, pressurized water expands in a nozzle, resulting in a hot vapour spray being applied to surfaces. This highly efficient method for cleaning oily surfaces can be enhanced by adding detergents.

Areas of application: Steam blasting is applied where strong mechanical washing and rinsing actions are required.

### **B.5 Chemical cleaning**

#### **B.5.1 General**

With chemical cleaning techniques, a cleaning agent reacts with the contamination present to remove it. The cleaning agent then either evaporates or can be easily removed.

#### **B.5.2 Etching**

Principle: Etching is the removal of the surface layer with contamination by chemical reaction.

Areas of application: Removal of coatings and final cleaning of components.

#### **B.5.3 Chemical reaction**

Principle: Specifically selected chemicals are used in a targeted way to convert contamination through a chemical reaction into other compounds which are either volatile or easy to remove.

Areas of application: With this principle, surfaces can be descaled, for example, by using acidic aqueous solutions.

#### **B.5.4 Vapour cleaning**

Principle: Vapour cleaning is often used in combination with ultrasonic cleaning in a fast drying environment-friendly solvent. The effect can be enhanced by using a mixture of chemicals. After immersion, a film of solvent covers the surface of the object. In this film, the remaining contamination is dissolved or dispersed. By moving the object through a cold zone, the film is stripped from the surface. The object leaves this zone with a dry surface.

Areas of application: Metallic objects, electronic parts, degreasing.

#### **B.5.5 Plasma cleaning**

Principle: In plasma cleaning, a mixture of reactive species is created that sputter the surface of the object. This cleaning action releases contamination from the surface and additionally creates a reaction that transfers contamination into a gas phase which can be removed by a vacuum system.

A plasma cleaning process is executed in a vacuum system. However, there are also atmospheric solutions available. The agitation energy is either in the RF range (13,6 MHz) or in the microwave range (2,4 GHz). As a cleaning gas, several pure gases or combinations can be selected: argon, nitrogen, oxygen, halogens, etc.

Areas of application: Electronic parts, plastic objects, metallic objects, optics.

### B.5.6 Ozone cleaning

Principle: In ozone, reactive O<sub>3</sub> species are used to oxidize organic contamination. The ozone is generated and activated by UV light.

Areas of application: Flat objects like glass plates, optics.

## B.6 Working ranges of described cleaning techniques

In [Table B.1](#) and [Table B.2](#), an overview is given of typical working ranges for the applicability of some cleaning techniques. The grey area within the tables is the area where these techniques can be applied.

STANDARDSISO.COM : Click to view the full PDF of ISO 14644-13:2017

Table B.1 — Working ranges of described cleaning techniques for particle removal

Cleaning techniques										
Particle removal	high contamination				low contamination					
Technique	SCP 8				SCP 1					
<b>B.2. Mechanical cleaning</b>										
B.2.1 Wiping	←————→				■		■		■	
B.2.2 Brushing/Sweeping	←————→		■		■		■		■	
B.2.3 Scraping/Abrading	←————→		■		■		■		■	
B.2.4 Grinding	←————→		■		■		■		■	
<b>B.3. Fluidic cleaning</b>										
B.3.1 Washing/Rinsing/Drying	←————→		■		■		■		■	
B.3.2 Compressed gas cleaning	←————→		■		■		■		■	
B.3.3 Vacuum cleaning	←————→		■		■		■		■	
B.3.4 Sonic cleaning	■		■		■		■		■	
B.3.4.1 Ultrasonic cleaning	■		←————→				■		■	
B.3.4.2 Megasonic cleaning	■		←————→						■	
B.3.5 Spray cleaning	←————→		■		■		■		■	
<b>B.4. Blasting cleaning techniques</b>										
B.4.1 General	■		■		■		■		■	
B.4.2 Gas blasting	■		■		■		■		■	
B.4.2.1 Compressed air blasting	←————→		■		■		■		■	
B.4.2.2 Wet compressed air blasting	←————→		■		■		■		■	
B.4.2.3 CO <sub>2</sub> pellet cleaning	←————→		■		■		■		■	
B.4.2.4 Accelerated CO <sub>2</sub> snow cleaning	■		←————→						■	
B.4.3 Liquid blasting	■		■		■		■		■	
B.4.3.1 Pressurized liquid blasting	←————→		■		■		■		■	
B.4.3.2 Low-pressure water jet blasting	←————→		■		■		■		■	
B.4.3.3 Elutriation blasting	■		←————→				■		■	
B.4.3.4 Steam blasting	←————→		■		■		■		■	
<b>B.5. Chemical cleaning</b>										
B.5.1 General	■		■		■		■		■	
B.5.2 Etching	←————→				■		■		■	
B.5.3 Chemical reaction	←————→				■		■		■	
B.5.4 Vapour cleaning	←————→				■		■		■	

STANDARDS55.COM · Click to view the full PDF of ISO 14644-13:2017

Table B.2 — Working ranges of described cleaning techniques for chemical removal

Chemical removal	high contamination	low contamination
Technique	SCC -1	SCC -12
<b>B.3. Fluidic cleaning</b>		
B.3.1 Washing/Rinsing/Drying	←————→	
B.3.2 Compressed gas cleaning	←————→	
B.3.4 Sonic cleaning		
B.3.4.1 Ultrasonic cleaning	←————→	
B.3.4.2 Megasonic cleaning	←————→	
B.3.5 Spray cleaning	←————→	
<b>B.4. Blasting cleaning techniques</b>		
B.4.1 General		
B.4.2.3 CO <sub>2</sub> pellet cleaning	←————→	
B.4.2.4 Accelerated CO <sub>2</sub> snow cleaning	←————→	
B.4.3 Liquid blasting		
B.4.3.1 Pressurized liquid blasting	←————→	
B.4.3.2 Low-pressure water jet blasting	←————→	
B.4.3.3 Elutriation blasting	←————→	
B.4.3.4 Steam blasting	←————→	
<b>B.5. Chemical cleaning</b>		
B.5.1 General		
B.5.2 Etching	←————→	
B.5.3 Chemical reaction	←————→	
B.5.4 Vapour cleaning	←————→	
B.5.5 Plasma cleaning	←————→	
B.5.6 Ozone cleaning	←————→	

STANDARDSISO.COM : Click to view the full PDF of ISO 14644-13:2017

## Annex C (informative)

### Material compatibility with cleaning agents

Chemical compatibility of materials with cleaning liquids has been tested extensively. [Table C.1](#) gives examples of compatibility for a variety of materials with the most common organic cleaning liquids. This table gives insights into liquids that can be used for cleaning with minimal damage to the object. This table only applies for room temperature. Chemical blends, elevated temperatures and high mechanical action may still result in damage. Note that tables like [Table C.1](#) can be used only as an indication. It is strongly recommended to conduct experimental compatibility tests. Same materials (notably polymeric materials) from different suppliers are likely to behave differently. Even batch-to-batch variation can be expected.

Other sources for material compatibility are available (see Bibliography).

**Table C.1 — Examples of compatibility of various solvents with listed materials (indicative only)**

Type of material	Abbreviation	Methanol	Ethanol	Isopropyl alcohol	Acetone	Methyl Ethyl Ketone	Dichloromethane	Chloroform
<b>polymer</b>								
Acetal (polyoxymethylene)	ACL	A	A	A	A	C		A
Epoxy		B	A	A	B	C		C
Ethylene-chlorotrifluoroethylene copolymer	E-CTFE	A	A	A	B	A	C	A
Ethylene-tetrafluoroethylene	ETFE	A	A	A	B	A	B	A
Fluoroethylene propylene	FEP	A	A	A	A	A	A	A
Tetrafluoroethylene	TFE	A	A	A	A	A	A	A
Perfluoroalkoxy	PFA	A	A	A	A	A	A	A
Polyamide		D	D	D	A	A	B	C
Polycarbonates	PC	B	A	A	D	D	D	D
Low density Polyethylene	LDPE	A	B	A	D	D	D	C
High density Polyethylene	HDPE	A	A	A	D	D	C	C
Polyimide		B	B	B	B	B	B	B
Polymethyl methacrylate	PMMA	D	D	D	D	D	D	D
Polyketone	PK (PEEK)	A	A	A	A			C
Polystyrene	PS	B	A	A	D	D	D	D
Polysulfone	PSF	A	A	B	D	D	D	D
Polyethylene terephthalate	PET	A	A	A	C	A	D	D
Polypropylene	PP	A	A	A	B	B	C	D
Polyurethane	PUR	C	C	C	D	D	D	D
Polyvinylidene fluoride	PVDF	A	A	A	D	D	A	A
Silicone		A	C	A	D	D	D	D
Vinylidene fluoride - hexafluoropropylene		C	A	A	D	D		A