

---

---

**Stainless steels for general purposes —**  
**Part 1:**  
**Flat products**

*Aciers inoxydables pour usage général —*  
*Partie 1: Produits plats*

STANDARDSISO.COM : Click to view the full PDF of ISO 16143-1:2004



**PDF disclaimer**

This PDF file may contain embedded typefaces. In accordance with Adobe's licensing policy, this file may be printed or viewed but shall not be edited unless the typefaces which are embedded are licensed to and installed on the computer performing the editing. In downloading this file, parties accept therein the responsibility of not infringing Adobe's licensing policy. The ISO Central Secretariat accepts no liability in this area.

Adobe is a trademark of Adobe Systems Incorporated.

Details of the software products used to create this PDF file can be found in the General Info relative to the file; the PDF-creation parameters were optimized for printing. Every care has been taken to ensure that the file is suitable for use by ISO member bodies. In the unlikely event that a problem relating to it is found, please inform the Central Secretariat at the address given below.

STANDARDSISO.COM : Click to view the full PDF of ISO 16143-1:2004

© ISO 2004

All rights reserved. Unless otherwise specified, no part of this publication may be reproduced or utilized in any form or by any means, electronic or mechanical, including photocopying and microfilm, without permission in writing from either ISO at the address below or ISO's member body in the country of the requester.

ISO copyright office  
Case postale 56 • CH-1211 Geneva 20  
Tel. + 41 22 749 01 11  
Fax + 41 22 749 09 47  
E-mail [copyright@iso.org](mailto:copyright@iso.org)  
Web [www.iso.org](http://www.iso.org)

Published in Switzerland

# Contents

Page

Foreword.....	iv
<b>1 Scope.....</b>	<b>1</b>
<b>2 Normative references .....</b>	<b>1</b>
<b>3 Terms and definitions .....</b>	<b>2</b>
<b>4 Designation.....</b>	<b>2</b>
<b>5 Information to be supplied by the purchaser.....</b>	<b>2</b>
<b>6 Classification of grades.....</b>	<b>3</b>
<b>7 Requirements .....</b>	<b>3</b>
7.1 Manufacturing process.....	3
7.2 Delivery condition .....	3
7.3 Chemical composition.....	3
7.4 Susceptibility to intergranular corrosion .....	3
7.5 Mechanical properties .....	3
7.6 Surface quality .....	4
7.7 Internal soundness .....	4
7.8 Dimensions, tolerances on dimensions and shape .....	4
7.9 Calculation of mass and tolerance of mass.....	4
<b>8 Inspection, testing and conformance of products .....</b>	<b>4</b>
8.1 General .....	4
8.2 Inspection and testing procedures and types of inspection document .....	4
8.3 Specific inspection and testing .....	5
8.4 Test methods.....	5
8.5 Retests .....	6
<b>9 Marking.....</b>	<b>6</b>
<b>Annex A (normative) Guidelines for further treatment (including heat treatment) in fabrication.....</b>	<b>18</b>
<b>Annex B (informative) Designations of the steels given in Table 1 and of comparable grades covered in ASTM-, EN- and JIS-Standards .....</b>	<b>21</b>
<b>Annex C (informative) Comparison list of abbreviations for process route/surface finish of flat products given in Table 3 covered in ASTM- and JIS-Standards .....</b>	<b>22</b>
<b>Bibliography .....</b>	<b>23</b>

## Foreword

ISO (the International Organization for Standardization) is a worldwide federation of national standards bodies (ISO member bodies). The work of preparing International Standards is normally carried out through ISO technical committees. Each member body interested in a subject for which a technical committee has been established has the right to be represented on that committee. International organizations, governmental and non-governmental, in liaison with ISO, also take part in the work. ISO collaborates closely with the International Electrotechnical Commission (IEC) on all matters of electrotechnical standardization.

International Standards are drafted in accordance with the rules given in the ISO/IEC Directives, Part 2.

The main task of technical committees is to prepare International Standards. Draft International Standards adopted by the technical committees are circulated to the member bodies for voting. Publication as an International Standard requires approval by at least 75 % of the member bodies casting a vote.

Attention is drawn to the possibility that some of the elements of this document may be the subject of patent rights. ISO shall not be held responsible for identifying any or all such patent rights.

ISO 16143-1 was prepared by Technical Committee ISO/TC 17, *Steel*, Subcommittee SC 4, *Heat treatable and alloy steels*.

ISO 16143 consists of the following parts, under the general title *Stainless steels for general purposes*:

- *Part 1: Flat products*
- *Part 2: Semi-finished products, bars, rods and sections*
- *Part 3: Wire*

# Stainless steels for general purposes —

## Part 1: Flat products

### 1 Scope

This part of ISO 16143 specifies the technical delivery conditions for hot- or cold-rolled sheet/plate and strip for general purposes made of the most important corrosion-resistant stainless steel grades.

NOTE In the text, under the term “general purposes”, purposes other than the special purposes mentioned in the bibliographic references [1] — [4] are understood.

In addition to this part of ISO 16143, the general technical delivery requirements of ISO 404 are applicable.

This part of ISO 16143 does not apply to components manufactured by further processing of the product forms listed in paragraph 1 where quality characteristics are altered as a result of such processing.

### 2 Normative references

The following referenced documents are indispensable for the application of this document. For dated references, only the edition cited applies. For undated references, the latest edition of the referenced document (including any amendments) applies.

ISO 377:1997, *Steel and steel products — Location and preparation of samples and test pieces for mechanical testing*

ISO 404:1992, *Steel and steel products — General technical delivery requirements*

ISO 3651-2:1998, *Determination of resistance to intergranular corrosion of stainless steels — Part 2: Ferritic, austenitic and ferritic-austenitic (duplex) stainless steels — Corrosion test in media containing sulfuric acid*

ISO/TS 4949:2003, *Steel names based on letter symbols*

ISO 6506-1:1999, *Metallic materials — Brinell hardness test — Part 1: Test method*

ISO 6507-1:1997, *Metallic materials — Vickers hardness test — Part 1: Test method*

ISO 6508-1:1999, *Metallic materials — Rockwell hardness test — Part 1: Test method (scales A, B, C, D, E, F, G, H, K, N, T)*

ISO 6892:1998, *Metallic materials — Tensile testing at ambient temperature*

ISO 6929:1987, *Steel products — Definitions and classification*

ISO 9444:2002, *Continuously hot-rolled stainless steel strip, plate/sheet and cut lengths — Tolerances on dimensions and form*

ISO 9445:2002, *Continuously cold-rolled stainless steel narrow strip, wide strip, plate/sheet and cut lengths — Tolerances on dimensions and form*

ISO/TR 9769:1991, *Steel and iron — Review of available methods of analysis*

ISO 10474:1991, *Steel and steel products — Inspection documents*

ISO 14284:1996, *Steel and iron — Sampling and preparation of samples for the determination of chemical composition*

ISO/TS 15510:2003, *Stainless steels — Chemical composition*

ISO 18286:2004, *Hot-rolled stainless steel plates — Tolerances on dimensions and shape*

### 3 Terms and definitions

For the purposes of this document, the following terms and definitions apply.

**3.1**  
**corrosion-resistant stainless steels**  
steels, with at least 10,5 % (mass fraction) Cr and a maximum of 1,2 % (mass fraction) C, for which resistance to corrosion is of primary importance

**3.2**  
**product forms**  
See ISO 6929

### 4 Designation

The steel names given in Tables 1, 4, 5, 6, 7 and 8 are allocated in accordance with ISO/TS 4949.

### 5 Information to be supplied by the purchaser

It shall be the responsibility of the purchaser to specify all requirements that are necessary for products covered by this specification. Such requirements to be considered include, but are not limited to, the following:

- a) the desired quantity;
- b) the product form (strip or sheet/plate);
- c) the number of the appropriate dimensional standard (see ISO 9444, ISO 9445 and ISO 18286), the nominal dimensions, plus any choice of requirements;
- d) the type of material (steel);
- e) the number of this International Standard, i.e. ISO 16143-1;
- f) the steel name;
- g) if, for the relevant steel in Tables 4 to 8, more than one treatment condition is covered, the symbol for the desired heat treatment;
- h) the desired process route (see Table 3);
- i) if an inspection document is required, its designation in accordance with ISO 10474.

**EXAMPLE** 5 t of cold-rolled narrow strip in accordance with ISO 9445 with a specified thickness of 0,25 mm, precision thickness tolerance (P), with a specified width of 250 mm, precision tolerance on width (P) and with restricted tolerances on edge camber (R) made of steel grade X5CrNi18-9 as specified in ISO 16143-1, in process route 2D and inspection certificate 3.1.B as specified in ISO 10474 is designated as follows:

**5 t cold-rolled narrow strip ISO 9445 — 0,25P × 250P — R**  
**Steel ISO 16143-1-X5CrNi18-9 + 2D**  
**3.1 B**

## 6 Classification of grades

Corrosion-resistant stainless steels covered in this part of ISO 16143 are classified according to their structure into:

- austenitic steels;
- austenitic-ferritic steels;
- ferritic steels;
- martensitic steels;
- precipitation-hardening steels.

## 7 Requirements

### 7.1 Manufacturing process

Unless a special steelmaking process is agreed upon at the time of ordering, the steelmaking process shall be at the discretion of the manufacturer. When he so requests, the purchaser shall be informed what steelmaking process is being used.

### 7.2 Delivery condition

The products shall be supplied in the delivery condition agreed upon in the order, by reference to the process route given in Table 3 and, where different alternatives exist, to the treatment conditions given in Tables 4 to 8 (also see Annex A).

### 7.3 Chemical composition

**7.3.1** The chemical composition requirements given in Table 1 apply with respect to the chemical composition of the cast analysis.

**7.3.2** The product analysis may deviate from the limiting values for the cast analysis given in Table 1 by the values listed in Table 2.

### 7.4 Susceptibility to intergranular corrosion

Referring to resistance to intergranular corrosion as defined in ISO 3651-2, for ferritic, austenitic and austenitic-ferritic steels the specification in Tables 4, 5 and 6 apply.

NOTE The susceptibility of stainless steels to intergranular corrosion is dependent on the type of environment and therefore cannot always be clearly ascertained through standard laboratory tests. The selection of the test or tests to be agreed upon should be based on experience with the use of the selected grade of steel in the intended environment.

### 7.5 Mechanical properties

The mechanical properties at room temperature as specified in Tables 4 to 8 apply for the relevant specified heat-treatment condition. This does not apply to the process route 1U (hot rolled, not heat-treated, not descaled). If, by agreement at the time of ordering, the products are to be supplied in a non-heat-treated condition, the mechanical properties specified in Tables 4 to 8 shall be obtainable from reference test pieces which have received the appropriate heat treatment (simulated heat treatment).

NOTE Austenitic steels are insensitive to brittle fracture in the solution-annealed condition. Because they do not have a pronounced transition temperature, which is characteristic of other steels, they are also useful for application at cryogenic temperatures.

## 7.6 Surface quality

The general surface appearance with respect to soundness and surface finish shall be consistent with good production practice, for the grade and quality ordered, as determined by visual inspection. When products are delivered in coil form, the degree and extent of imperfections may be expected to be greater, due to the impracticability of removing short lengths of coil.

Where necessary, precise requirements on surface quality may be agreed upon at the time of enquiry and order.

## 7.7 Internal soundness

For the internal soundness, where appropriate, requirements together with the conditions for their verification may be agreed upon at the time of enquiry and order.

## 7.8 Dimensions, tolerances on dimensions and shape

The dimensions and the tolerances on dimensions and shape are to be agreed upon at the time of enquiry and order, as far as possible with reference to the dimensional standards ISO 9444, ISO 9445 and ISO 18286.

## 7.9 Calculation of mass and tolerance of mass

**7.9.1** The density values of the relevant grades for calculating the nominal mass of the products shall be taken from Annex B of ISO/TS 15510:2003.

**7.9.2** If the tolerances on mass are not specified in the dimensional standards mentioned in 7.8, they may be agreed upon at the time of enquiry and order.

## 8 Inspection, testing and conformance of products

### 8.1 General

The manufacturer shall carry out appropriate process control, inspection and testing to assure himself that the delivery complies with the requirements of the order.

This includes the following:

- a suitable frequency of verification of the dimensions of the products;
- an adequate intensity of visual examination of the surface quality of the products;
- an appropriate frequency and type of test to ensure that the correct grade of steel is delivered.

The nature and frequency of these verifications, examinations and tests are determined by the manufacturer, based on the degree of consistency that has been determined by the evidence of his quality system. In view of this, verifications by specific tests for these requirements are not necessary, unless otherwise agreed.

### 8.2 Inspection and testing procedures and types of inspection document

**8.2.1** For each delivery, the issue of any inspection document in accordance with ISO 10474 may be agreed upon at the time of enquiry and order.

**8.2.2** If, in accordance with the agreements made at the time of enquiry and order, a test report is to be provided, this shall cover:

- a) the statement that the material complies with the requirements of the order;
- b) the results of the cast analysis for all elements specified for the type of steel supplied.

**8.2.3** If, in accordance with the agreements in the order, an inspection certificate 3.1.A, 3.1.B or 3.1.C or an inspection report 3.2 of ISO 10474:1991 is to be provided, the specific inspections and tests described in 8.3 shall be carried out and their results shall be certified in the document.

In addition to 8.2.2 a) and b) the document shall cover

- a) the results of the mandatory tests marked in the second column of Table 9 by an "m";
- b) the results of any optional test or inspection agreed when ordering, marked in the second column of Table 9 by an "o".

### 8.3 Specific inspection and testing

#### 8.3.1 Extent of testing

The tests to be carried out, either mandatorily (m) or by agreement (o), the composition and size of the test units, and the number of sample products, samples and test pieces to be taken are given in Table 9.

#### 8.3.2 Selection and preparation of samples and test pieces

**8.3.2.1** The general conditions for selection and preparation of samples and test pieces shall be in accordance with ISO 377 and ISO 14284.

**8.3.2.2** The test samples for the tensile test shall be taken in accordance with Figure 1 in such a way that they are located halfway between the centre and a longitudinal edge.

The samples shall be taken from products in the delivery condition. If agreed, the samples may be taken before flattening. For samples to be given a simulated heat treatment, the conditions for annealing shall be agreed.

**8.3.2.3** Samples for the hardness test and for the resistance to intergranular corrosion test, where requested, shall be taken from the same locations as those for the mechanical tests. For direction of bending the test piece in the resistance to intergranular corrosion test, see Figure 2.

### 8.4 Test methods

**8.4.1** Unless otherwise agreed upon when ordering, the choice of a suitable physical or chemical method of analysis to determine the product analysis is at the discretion of the manufacturer. In cases of dispute, the analysis shall be carried out by a laboratory approved by the two parties. In these cases, the reference method of analysis shall be agreed upon, where possible, with reference to ISO/TR 9769.

**8.4.2** The tensile test at room temperature shall be carried out in accordance with ISO 6892 taking into account the additional or deviating conditions specified in footnote<sup>a</sup> of Figure 1.

Unless otherwise agreed upon, the tensile strength and elongation after fracture shall be determined and, additionally, for ferritic and austenitic-ferritic steels, the 0,2 % proof strength, and for austenitic steels, the 0,2 % and 1 % proof strengths shall be determined.

**8.4.3** The Brinell hardness test shall be carried out in accordance with ISO 6506-1. The Vickers hardness test shall be carried out in accordance with ISO 6507-1. The Rockwell hardness test shall be carried out in accordance with ISO 6508-1.

**8.4.4** The resistance to intergranular corrosion shall be tested in accordance with ISO 3651-2, unless otherwise agreed upon.

**8.4.5** Dimensions and dimensional tolerances of the products shall be verified in accordance with the requirements of the relevant dimensional standards (see 7.8).

8.5 Retests


See ISO 404.

9 Marking

The products shall be marked with the manufacturer’s symbol, the steel grade, and, if so agreed upon when ordering, with the cast number. When specific inspection is carried out, the products are to be provided additionally with an identification number which enables the test pieces to be related to the cast and product from which they stem.

Type of test piece	Product thickness mm	Direction of the longitudinal axis of the test piece in relation to the principal direction of rolling at a product width of		Distance of the test piece from the rolled surface mm
		< 300 mm	≥ 300 mm	
Tensile <sup>a</sup>	≤ 30	Longitudinal	Transverse	
	> 30			
<p><sup>a</sup> In cases of doubt or dispute, the gauge length shall be <math>L_0 = 5,65 \sqrt{S_0}</math> for test pieces from products ≥ 3 mm.</p> <p>For products &lt; 3 mm in thickness, non-proportional test pieces with a gauge length of 80 mm and a width of 20 mm shall be used, but test pieces with a gauge length of 50 mm and a width of 12,5 mm may also be applied. For products with a thickness of 3 mm to 10 mm, flat proportional test pieces with two rolled surfaces and a maximum width of 30 mm shall be used. For products with thickness &gt; 10 mm, one of the following proportional test pieces may be used:</p> <ul style="list-style-type: none"> <li>— either a flat test piece with a maximum thickness of 30 mm; the thickness may be reduced to 10 mm by machining, but one rolled surface shall be preserved;</li> <li>— or a round test piece with a diameter ≥ 5 mm, the axis of which shall be located as near as possible to a plane in the outer third of half the product thickness.</li> </ul>				

Figure 1 — Position of test pieces for flat products

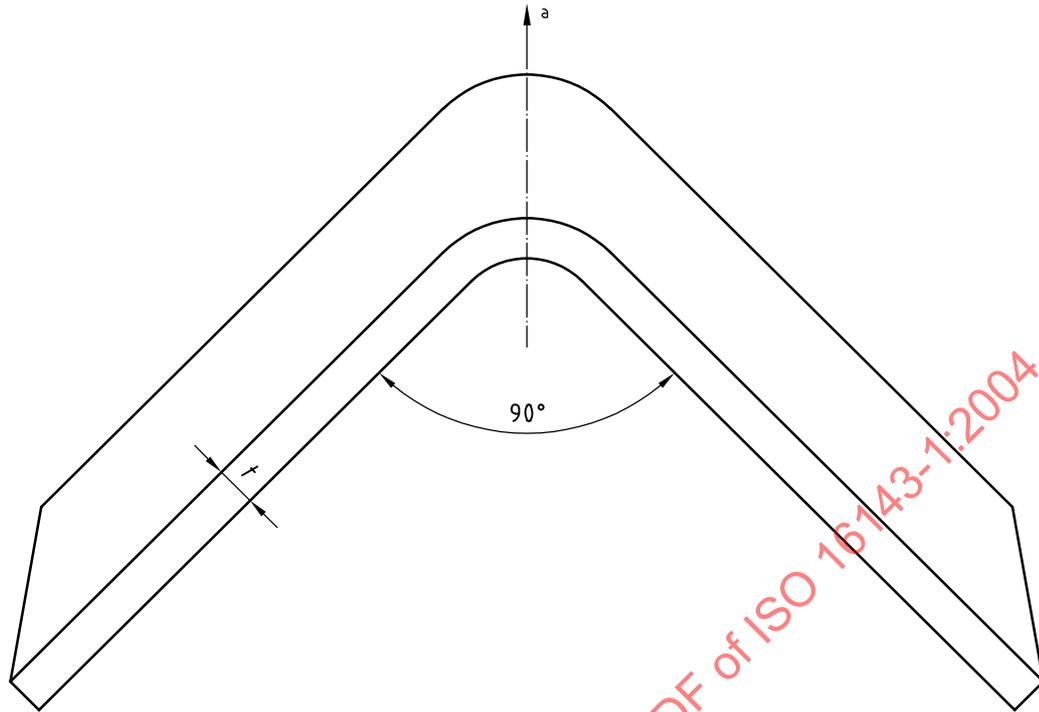

a Rolling direction.

**Figure 2 — Direction of bending the test piece in relation to the rolling direction in the resistance to intergranular corrosion test.**

Table 1 — Chemical composition (cast analysis)<sup>a</sup>

Designation	Line number of ISO/TS 15510:2003	% (mass fraction)									
		C	Si	Mn	P max.	S max.	N	Cr	Mo	Ni	Others
<b>Austenitic steels</b>											
X2CrNi18-9	1	max. 0,030	max. 1,00	max. 2,00	0,045	0,030 <sup>b</sup>	max. 0,11	17,5 to 19,5	—	8,0 to 10,0	—
X2CrNi19-11	2	max. 0,030	max. 1,00	max. 2,00	0,045	0,030 <sup>b</sup>	max. 0,11	18,0 to 20,0	—	10,0 to 12,0	—
X2CrNiN18-9	3	max. 0,030	max. 1,00	max. 2,00	0,045	0,030 <sup>b</sup>	0,12 to 0,22	17,5 to 19,5	—	8,0 to 10,0	—
X5CrNi18-9	6	max. 0,07	max. 1,00	max. 2,00	0,045	0,030 <sup>b</sup>	max. 0,11	17,5 to 19,5	—	8,0 to 10,5	—
X10CrNi18-8	11	0,05 to 0,15	max. 2,00	max. 2,00	0,045	0,030 <sup>b</sup>	max. 0,11	16,0 to 19,0	max. 0,80	6,0 to 9,5	—
X1CrNi25-21	12	max. 0,02	max. 0,25	max. 2,00	0,025	0,010	max. 0,11	24,0 to 26,0	max. 0,20	20,0 to 22,0	—
X12CrMnNiN17-7-5	13	max. 0,15	max. 1,00	5,5 to 7,5	0,045	0,030 <sup>b</sup>	0,05 to 0,25	16,0 to 18,0	3,5 to 5,5	—	—
X6CrNiTi18-10	16	max. 0,08	max. 1,00	max. 2,00	0,045	0,030 <sup>b</sup>	—	17,0 to 19,0	—	9,0 to 12,0	Ti: 5xC to 0,70
X6CrNiNb18-10	19	max. 0,08	max. 1,00	max. 2,00	0,045	0,030 <sup>b</sup>	—	17,0 to 19,0	—	9,0 to 12,0	Nb: 10xC to 1,00
X2CrNiMo17-12-2	21	max. 0,030	max. 1,00	max. 2,00	0,045	0,030 <sup>b</sup>	max. 0,11	16,5 to 18,5	2,00 to 3,00	10,0 to 13,0	—
X2CrNiMo17-12-3	22	max. 0,030	max. 1,00	max. 2,00	0,045	0,030 <sup>b</sup>	max. 0,11	16,5 to 18,5	2,50 to 3,00	10,5 to 13,0	—
X2CrNiMo18-14-3	23	max. 0,030	max. 1,00	max. 2,00	0,045	0,015	max. 0,11	17,0 to 19,0	2,50 to 3,00	12,5 to 15,0	—
X2CrNiMoN17-12-3	26	max. 0,030	max. 1,00	max. 2,00	0,045	0,030 <sup>b</sup>	0,12 to 0,22	16,5 to 18,5	2,50 to 3,00	10,5 to 13,0	—
X1CrNiMoN25-22-2	29	max. 0,020	max. 0,70	max. 2,00	0,025	0,010	0,10 to 0,16	24,0 to 26,0	2,00 to 2,50	21,0 to 23,0	—
X5CrNiMo17-12-2	30	max. 0,07	max. 1,00	max. 2,00	0,045	0,030 <sup>b</sup>	max. 0,11	16,5 to 18,5	2,00 to 3,00	10,0 to 13,0	—
X3CrNiMo17-12-3	31	max. 0,05	max. 1,00	max. 2,00	0,045	0,030 <sup>b</sup>	max. 0,11	16,5 to 18,5	2,50 to 3,00	10,5 to 13,0	—
X6CrNiMoTi17-12-2	32	max. 0,08	max. 1,00	max. 2,00	0,045	0,030 <sup>b</sup>	—	16,5 to 18,5	2,00 to 2,50	10,5 to 13,5	Ti: 5xC to 0,70
X1NiCrMoCu25-20-5	35	max. 0,020	max. 0,75	max. 2,00	0,035	0,015	max. 0,15	19,0 to 22,0	4,0 to 5,0	23,5 to 26,0	Cu: 1,20 to 2,00
X1NiCrMoCu31-27-4	36	max. 0,020	max. 0,70	max. 2,00	0,030	0,010	max. 0,11	26,0 to 28,0	3,0 to 4,0	30,0 to 32,0	Cu: 0,70 to 1,50
X1CrNiMoCuN24-22-8	38	max. 0,020	max. 0,50	2,0 to 4,0	0,030	0,005	0,45 to 0,55	23,0 to 25,0	7,0 to 8,0	21,0 to 23,0	Cu: 0,30 to 0,60
X8CrMnCuN17-8-3	40	max. 0,10	max. 2,00	6,5 to 8,5	0,040	0,030	0,15 to 0,30	16,0 to 18,0	max. 1,00	max. 2,00	Cu: 2,00 to 3,5
X1CrNiMoCuNW24-22-6	41	max. 0,020	max. 0,70	2,0 to 4,0	0,030	0,010	0,35 to 0,50	23,0 to 25,0	5,5 to 6,5	21,0 to 23,0	Cu: 1,00 to 2,00 W: 1,50 to 2,50
X2CrNiMnMoN25-18-6-5	42	max. 0,030	max. 1,00	5,0 to 7,0	0,030	0,015	0,30 to 0,60	24,0 to 26,0	4,0 to 5,0	16,0 to 19,0	Nb: max. 0,15
X11CrNiMnN19-8-6	43	0,07 to 0,15	0,50 to 1,00	5,0 to 7,5	0,030	0,015	0,20 to 0,30	17,5 to 19,5	—	6,5 to 8,5	—

Table 1 (continued)

Designation	Line number of ISO/TS 15510:2003	% (mass fraction)									
		C	Si	Mn	P max.	S max.	N	Cr	Mo	Ni	Others
X6CrNiCu17-8-2	45	max. 0,08	max. 1,70	max. 3,00	0,045	0,030	—	15,0 to 18,0	—	6,0 to 9,0	Cu: 1,00 to 3,00
X12CrNiSi18-9-3	46	max. 0,15	2,00 to 3,00	max. 2,00	0,045	0,030	—	17,0 to 19,0	—	8,0 to 10,0	—
<b>Austenitic-ferritic steels</b>											
X2CrNiN23-4	51	max. 0,030	max. 1,00	max. 2,00	0,035	0,015	0,05 to 0,20	22,0 to 24,0	0,10 to 0,60	3,5 to 5,5	Cu: 0,10 to 0,60
X2CrNiMoN22-5-3	52	max. 0,030	max. 1,00	max. 2,00	0,035	0,015	0,10 to 0,22	21,0 to 23,0	2,5 to 3,5	4,5 to 6,5	—
X2CrNiMoCuN25-6-3	53	max. 0,030	max. 0,70	max. 2,00	0,035	0,015	0,15 to 0,30	24,0 to 26,0	2,5 to 4,0	5,0 to 7,5	Cu: 1,00 to 2,50
X2CrNiMoN25-7-4	54	max. 0,030	max. 1,00	max. 2,00	0,035	0,015	0,24 to 0,35	24,0 to 26,0	3,0 to 4,5	6,0 to 8,0	—
X2CrNiMoCuWN25-7-4	56	max. 0,030	max. 1,00	max. 1,00	0,035	0,015	0,20 to 0,30	24,0 to 26,0	3,0 to 4,0	6,0 to 8,0	Cu: 0,50 to 1,00 W: 0,50 to 1,00
<b>Ferritic steels</b>											
X2CrNi12	61	max. 0,030	max. 1,00	max. 1,50	0,040	0,015	max. 0,030	10,5 to 12,5	—	0,30 to 1,10	—
X2CrTi12	62	max. 0,030	max. 1,00	max. 1,00	0,040	0,030 <sup>b</sup>	—	10,5 to 12,5	—	max. 0,50	Ti: 6x(C+N) to 0,65
X6Cr17	67	max. 0,08	max. 1,00	max. 1,00	0,040	0,030 <sup>b</sup>	—	16,0 to 18,0	—	—	—
X3CrTi17	70	max. 0,05	max. 1,00	max. 1,00	0,040	0,030 <sup>b</sup>	—	16,0 to 19,0	—	—	Ti: [4x(C+N) + 0,20] to 0,75
X3CrNb17	73	max. 0,05	max. 1,00	max. 1,00	0,040	0,015	—	16,0 to 18,0	—	—	Nb: 12xC to 1,00
<b>Martensitic steels</b>											
X12Cr13	82	0,08 to 0,15	max. 1,00	max. 1,50	0,040	0,030 <sup>b</sup>	—	11,5 to 13,5	—	max. 0,75	—
X20Cr13	84	0,16 to 0,25	max. 1,00	max. 1,50	0,040	0,030 <sup>b</sup>	—	12,0 to 14,0	—	—	—
X30Cr13	85	0,26 to 0,35	max. 1,00	max. 1,50	0,040	0,030 <sup>b</sup>	—	12,0 to 14,0	—	—	—
X39Cr13	86	0,36 to 0,42	max. 1,00	max. 1,00	0,040	0,030 <sup>b</sup>	—	12,5 to 14,5	—	—	—
<b>Precipitation-hardening steel</b>											
X7CrNiAl17-7	102	max. 0,09	max. 0,70	max. 1,00	0,040	0,015	—	16,0 to 18,0	—	6,5 to 7,8 <sup>c</sup>	Al: 0,70 to 1,50
<p><sup>a</sup> Elements not listed in this table may not be intentionally added to the steel without the agreement of the purchaser, except for finishing the cast. All appropriate precautions shall be taken to avoid the addition of such elements from scrap and other materials used in production, which would impair mechanical properties and the suitability of the steel.</p> <p><sup>b</sup> Particular ranges of sulfur content may provide improvement of particular properties. For machinability, a controlled sulfur content of 0,015 % to 0,030 % is recommended. For weldability, a controlled sulfur content of 0,008 % to 0,020 % may be beneficial. For polishability, a controlled sulfur content of 0,015 % maximum is recommended.</p> <p><sup>c</sup> By special agreement, the steel when intended for cold deformation may also be ordered with 7,00 % to 8,30 % Ni.</p>											

**Table 2 — Permissible deviations between the product analysis and the limiting values given in Table 1 for the cast analysis**

Element	Permissible maximum content in the cast analysis % (mass fraction)	Permissible deviation <sup>a</sup> % (mass fraction)
Carbon	$\leq 0,030$ $> 0,030$ $\leq 0,20$ $> 0,20$ $\leq 0,5$	$+ 0,005$ $\pm 0,01$ $\pm 0,02$
Silicon	$\leq 1,00$ $> 1,00$ $\leq 3,00$	$\pm 0,04$ $\pm 0,07$
Manganese	$\leq 1,00$ $> 1,00$ $\leq 2,00$ $> 2,00$ $\leq 10,0$	$+ 0,04$ $+ 0,07$ $\pm 0,1$
Phosphorus	$\leq 0,045$	$+ 0,005$
Sulfur	$\leq 0,015$ $> 0,015$ $\leq 0,030$	$+ 0,003$ $+ 0,005$
Nitrogen	$\leq 0,11$ $\geq 0,03$ $\leq 0,60$ $> 0,11$	$\pm 0,01$ $\pm 0,02$
Chromium	$\leq 28,0$ $\geq 10,5$	$\pm 0,2$
Molybdenum	$\leq 0,60$ $> 0,60$ $< 1,75$ $\geq 1,75$ $\leq 8,0$	$\pm 0,03$ $\pm 0,07$ $\pm 0,1$
Nickel	$\leq 1,00$ $> 1,00$ $\leq 5,0$ $> 5,0$ $\leq 32,0$	$\pm 0,04$ $\pm 0,1$ $\pm 0,2$
Aluminium	$\leq 1,50$ $\geq 0,30$	$\pm 0,1$
Copper	$\leq 1,00$ $> 1,00$ $\leq 5,00$	$\pm 0,04$ $\pm 0,1$
Niobium	$\leq 1,00$	$\pm 0,05$
Titanium	$\leq 0,75$	$\pm 0,03$
Tungsten	$\leq 2,50$	$\pm 0,05$

<sup>a</sup>  $\pm$  means that in one cast the deviation may occur over the upper value or under the lower value of the specified range in Table 1, but not both at the same time.

Table 3 — Types of process route and surface finish of flat products <sup>a</sup>

	Abbreviation <sup>b</sup>	Type of process route	Surface finish	Notes
Hot rolled	1U	Hot rolled, not heat-treated, not descaled	Covered with the rolling scale	Suitable for products which are to be further worked, e.g. strip for rerolling.
	1C	Hot rolled, heat-treated, not descaled	Covered with the rolling scale	Suitable for parts which will be descaled or machined in subsequent production or for certain heat-resistant applications.
	1E	Hot rolled, heat-treated, mechanically descaled	Free of scale	The type of mechanical descaling, e.g. coarse grinding or shot blasting, depends on the steel grade and the product, and is left to the manufacturer's discretion, unless otherwise agreed upon.
	1D	Hot rolled, heat-treated, pickled	Free of scale	Usually standard for most steel types to ensure good corrosion resistance; also common finish for further processing. It is permissible for grinding marks to be present. Not as smooth as 2D or 2B.
Cold rolled	2H	Work-hardened	Bright	Cold worked to obtain higher strength level.
	2C	Cold rolled, heat-treated, not descaled	Smooth with scale from heat treatment	Suitable for parts which will be descaled or machined in subsequent production or for certain heat-resistant applications.
	2E	Cold rolled, heat-treated, mechanically descaled	Rough and dull	Usually applied to steels with scale that is very resistant to pickling solutions. May be followed by pickling.
	2D	Cold rolled, heat-treated, pickled	Smooth	Finish for good ductility, but not as smooth as 2B or 2R.
	2B	Cold rolled, heat-treated, pickled, skin passed	Smoothen than 2D	Most common finish for most steel types to ensure good corrosion resistance, smoothness and flatness. Also common finish for further processing. Skin passing may be by tension levelling.
	2R	Cold rolled, bright annealed <sup>c</sup>	Smooth, bright, reflective	Smoothen and brighter than 2B. Also common finish for further processing.
Special finishes	1G or 2G	Ground <sup>d</sup>	See footnote <sup>e</sup>	Grade of grit or surface roughness can be specified. Unidirectional texture, not very reflective.
	1J or 2J	Brushed or dull polished <sup>d</sup>	Smoothen than ground. See footnote <sup>e</sup>	Grade of brush or polishing belt or surface roughness can be specified. Unidirectional texture, not very reflective.
	1K or 2K	Satin polish <sup>d</sup>	See footnote <sup>e</sup>	Additional specific requirements to a "J"-type finish, in order to achieve adequate corrosion resistance for marine and external architectural applications. Transverse $R_a < 0,5 \mu\text{m}$ with clean cut surface finish.
	1P or 2P	Bright polished <sup>d</sup>	See footnote <sup>e</sup>	Mechanical polishing. Process or surface roughness can be specified. Non-directional finish, reflective with high degree of image clarity.
	2F	Cold rolled, heat-treated, skin passed on roughened rolls	Uniform non-reflective matt surface	Heat treatment by bright annealing or by annealing and pickling.
	1M	Patterned	Design to be agreed upon; 2nd surface flat	Chequer plates used for floors.
	2M			A fine texture finish mainly used for architectural applications.
	2W	Corrugated	Design to be agreed upon	Used to increase strength and/or for cosmetic effect.
	2L	Coloured <sup>d</sup>	Colour to be agreed upon	
	1S or 2S	Surface coated <sup>d</sup>		Coated with e.g. tin, aluminium, titanium.

<sup>a</sup> Not all process routes and surface finishes are available for all steels.

<sup>b</sup> First digit, 1 = hot rolled, 2 = cold rolled.

<sup>c</sup> May be skin passed.

<sup>d</sup> One surface only, unless specifically agreed upon at the time of enquiry and order.

<sup>e</sup> Within each finish description, the surface characteristics can vary, and more specific requirements may need to be agreed upon between manufacturer and purchaser (e.g. grade of grit or surface roughness).

**Table 4 — Mechanical properties at room temperature for austenitic steels in the solution-annealed condition (see Table A.1)**

Designation		Product form <sup>a</sup>  (Class)	Thickness <sup>t</sup>  mm max.	Proof stress		Tensile strength  $R_m$  MPa	Elongation after fracture  $A_{80}^d$ % min. (tr.)	Resistance to intergranular corrosion <sup>e</sup>	
Name	Line number of ISO/TS 15510:2003			$R_{p0,2}$	$R_{p1,0}$			MPa min. (tr.) <sup>b, c</sup>	in the delivery condition
X2CrNi18-9	1	C (+AT1)	8	220	250	520 to 720	45	yes	yes
		C (+AT2) <sup>g</sup>		175	—	480 to 680			
		H	13,5	200	240	520 to 720	45		
		P	75 <sup>h</sup>	200	240	500 to 700	45		
X2CrNi19-11	2	C	8	220	250	520 to 720	45	yes	yes
		H	13,5	200	240	520 to 720	45		
		P	75 <sup>h</sup>	200	240	500 to 700	45		
X2CrNiN18-9	3	C	8	290	320	550 to 750	40	yes	yes
		H	13,5	270	310	550 to 750	40		
		P	75 <sup>h</sup>	270	310	530 to 730	40		
X5CrNi18-9	6	C	8	230	260	540 to 740	45 <sup>i</sup>	yes	no <sup>j</sup>
		H	13,5	210	250	540 to 740	45 <sup>i</sup>		
		P	75 <sup>h</sup>	210	250	520 to 720	45		
X10CrNi18-8	11	C	8	250	280	600 to 800	40	no	no
		H	13,5	230	270	600 to 800	40		
X1CrNi25-21	12	P	75 <sup>h</sup>	200	240	470 to 670	40	yes	yes
X12CrMnN17-7-5	13	C	8	350	380	750 to 950	45	yes	no
		H	13,5	330	370	750 to 950	45		
		P	75 <sup>h</sup>	330	370	750 to 950	40		
X6CrNiTi18-10	16	C	8	220	250	520 to 720	40	yes	yes
		H	13,5	200	240	520 to 720	40		
		P	75 <sup>h</sup>	200	240	500 to 700	40		
X6CrNiNb18-10	19	C	8	220	250	520 to 720	40	yes	yes
		H	13,5	200	240	520 to 720	40		
		P	75 <sup>h</sup>	200	240	500 to 700	40		
X2CrNiMo17-12-2	21	C (+AT1)	8	240	270	530 to 730	40	yes	yes
		C (+AT2) <sup>g</sup>		175	—	480 to 680			
		H	13,5	220	260	530 to 730	40		
		P	75 <sup>h</sup>	220	260	510 to 710	40		
X2CrNiMo17-12-3	22	C	8	240	270	530 to 730	40	yes	yes
		H	13,5	220	260	530 to 730	40		
		P	75 <sup>h</sup>	220	260	510 to 710	40		
X2CrNiMo18-14-3	23	C	6	240	270	550 to 750	40	yes	yes
		H	12	220	260	550 to 750	40		
		P	75 <sup>h</sup>	220	260	520 to 720	45		
X2CrNiMoN17-12-3	26	C	8	300	330	580 to 780	35	yes	yes
		H	13,5	280	320	580 to 780	35		
		P	75 <sup>h</sup>	280	320	580 to 780	40		
X1CrNiMoN25-22-2	29	P	75 <sup>h</sup>	250	290	540 to 740	40	yes	yes
X5CrNiMo17-12-2	30	C (+AT1)	8	240	270	530 to 730	40	yes	no <sup>j</sup>
		C (+AT2) <sup>g</sup>		205	—	520 to 720			
		H	13,5	220	260	530 to 730	40		
		P	75 <sup>h</sup>	220	260	510 to 710	40		

Table 4 (continued)

Designation		Product form <sup>a</sup> (Class)	Thickness <i>t</i> mm max.	Proof stress		Tensile strength <i>R<sub>m</sub></i> MPa	Elongation after fracture <i>A<sub>80</sub><sup>d</sup></i> % min. (tr.)	Resistance to intergranular corrosion <sup>e</sup>	
Name	Line number of ISO/TS 15510:2003			<i>R<sub>p0,2</sub></i> MPa min. (tr.) <sup>b, c</sup>	<i>R<sub>p1,0</sub></i> MPa			in the delivery condition	in the sensitized condition <sup>f</sup>
X3CrNiMo17-12-3	31	C	8	240	270	530 to 730	40	yes	no <sup>j</sup>
		H	13,5	220	260	530 to 730	40		
		P	75 <sup>h</sup>	220	260	510 to 710	40		
X6CrNiMoTi17-12-2	32	C	8	240	270	530 to 730	40	yes	yes
		H	13,5	220	260	530 to 730	40		
		P	75 <sup>h</sup>	220	260	510 to 710	40		
X1NiCrMoCu25-20-5	35	C	6	240	270	530 to 730	35	yes	yes
		H	12	220	260	530 to 730	35		
		P	75 <sup>h</sup>	220	260	510 to 710	35		
X1NiCrMoCu31-27-4	36	P	75 <sup>h</sup>	220	260	500 to 700	40	yes	yes
X1CrNiMoCuN24-22-8	38	C	8	430	470	750 to 950	40	yes	yes
		H	13,5	430	470	750 to 950	40		
		P	15	430	470	750 to 950	40		
X8CrMnCuN17-8-3	40	C	8	300	330	580 to 780	40	yes	no
		H	13,5	300	330	580 to 780	40		
X1CrNiMoCuNW24-22-6	41	P	75 <sup>h</sup>	420	460	800 to 1 000	40	yes	yes
X2CrNiMnMoN25-18-6-5	42	C	6	420	460	800 to 1 000	35	yes	yes
		H	10	420	460	800 to 1 000	35		
		P	40	420	460	800 to 1 000	35		
X11CrNiMnN19-8-6	43	C	4	340	370	750 to 950	35	yes	no
X6CrNiCu17-8-2	45	C	8	155	—	min. 450	40	no	no
		H	13,5	155	—	min. 450	40		
		P	75 <sup>h</sup>	155	—	min. 450	40		
X12CrNiSi18-9-3	46	C	8	205	—	min. 520	40	no	no
		H	13,5	205	—	min. 520	40		
		P	75 <sup>h</sup>	205	—	min. 520	40		

NOTE 1 MPa = 1 N/mm<sup>2</sup>.<sup>a</sup> C = cold-rolled strip; H = hot-rolled strip; P = hot-rolled plate.<sup>b</sup> If, in the case of strip in rolling widths < 300 mm, longitudinal test pieces are taken, the minimum values are reduced as follows:  
proof stress: minus 15 MPa  
elongation for constant gauge length: minus 5 %  
elongation for proportional gauge length: minus 2 %.<sup>c</sup> For continuously hot-rolled products, 20 MPa higher minimum values of *R<sub>p0,2</sub>* and 10 MPa higher minimum values of *R<sub>p1,0</sub>* may be agreed upon at the time of enquiry and order.<sup>d</sup> For thickness *t* < 3 mm, the values apply for test pieces with a gauge length of 80 mm and a width of 20 mm; test pieces with a gauge length of 50 mm and a width of 12,5 mm can also be used. For thickness *t* ≥ 3 mm, the values apply for test pieces with a gauge length of  $5,65 \sqrt{S_0}$ .<sup>e</sup> When tested in accordance with ISO 3651-2.<sup>f</sup> See NOTE to 7.4.<sup>g</sup> This condition is only supplied if specially agreed at the time of enquiry and order. Otherwise condition "+AT1" is supplied.<sup>h</sup> For thicknesses above 75 mm, the mechanical properties can be agreed upon.<sup>i</sup> For stretcher levelled material, the minimum value is 5 % lower.<sup>j</sup> Sensitization treatment of 15 min at 700 °C followed by cooling in air.

**Table 5 — Mechanical properties at room temperature for austenitic-ferritic steels in the solution-annealed condition (see Table A.2)**

Designation		Product form <sup>a</sup>	Thickness, <i>t</i> mm max.	0,2 % proof stress, <i>R</i> <sub>p0,2</sub> MPa min., (tr.) <sup>b, c</sup>	Tensile strength, <i>R</i> <sub>m</sub> MPa min.	Elongation after fracture, <i>A</i> <sub>80</sub> <sup>d</sup> % min. (long. + tr.)	Resistance to intergranular corrosion <sup>e</sup>	
Name	Line number of ISO/TS 15510:2003						in the delivery condition	in the sensitized condition <sup>f</sup>
X2CrNiN23-4	51	C	6	420	600	20	yes	yes
		H	12	400	600	20		
		P	75 <sup>g</sup>	400	630	25		
X2CrNiMoN22-5-3	52	C	6	480	660	20	yes	yes
		H	12	460	660	20		
		P	75 <sup>g</sup>	460	640	20		
X2CrNiMoCuN25-6-3	53	C	8	550	750	17	yes	yes
		H	13,5	530	750	17		
		P	75 <sup>g</sup>	530	730	25		
X2CrNiMoN25-7-4	54	C	6	550	750	15	yes	yes
		H	12	530	750	15		
		P	75 <sup>g</sup>	530	730	20		
X2CrNiMoCuWN25-7-4	56	P	75 <sup>g</sup>	530	730	25	yes	yes

NOTE 1 MPa = 1 N/mm<sup>2</sup>.

<sup>a</sup> C = cold-rolled strip; H = hot-rolled strip; P = hot-rolled plate.  
<sup>b</sup> If, in the case of strip in rolling widths < 300 mm, longitudinal test pieces are taken, the minimum proof stress values are reduced by 15 MPa.  
<sup>c</sup> For continuously hot-rolled products, 20 MPa higher minimum values of *R*<sub>p0,2</sub> may be agreed upon at the time of enquiry and order.  
<sup>d</sup> For thickness *t* < 3 mm, the values apply for test pieces with a gauge length of 80 mm and a width of 20 mm; test pieces with a gauge length of 50 mm and a width of 12,5 mm can also be used. For thickness *t* ≥ 3 mm, the values apply for test pieces with a gauge length of  $5,65 \sqrt{S_0}$ .  
<sup>e</sup> When tested in accordance with ISO 3651-2.  
<sup>f</sup> See NOTE to 7.4.  
<sup>g</sup> For thicknesses above 75 mm, the mechanical properties can be agreed upon.

**Table 6 — Mechanical properties at room temperature for ferritic steels  
in the annealed condition (see Table A.3)**

Designation		Product form <sup>a</sup> (Class)	Thickness <i>t</i>  mm max.	0,2 % proof stress $R_{p0,2}$ <sup>b</sup>  MPa min. (tr.)	Tensile strength $R_m$  MPa min.	Elongation after fracture $A_{80}$ <sup>c</sup>  % min. (long. + tr.)	Resistance to intergranular corrosion <sup>d</sup>	
Name	Line number of ISO/TS 15510:2003						in the delivery condition	in the welded condition
X2CrNi12	61	C	6	320	450	20	no	no
		H	12	300	450	20		
		P	25 <sup>e</sup>	280	430	20		
X2CrTi12	62	C (+A1)	6	220	380	25	no	no
		C (+A2) <sup>f</sup>		175	360	25		
		H (+A1)	12	200	380	25		
		H (+A2) <sup>f</sup>		175	360	25		
X6Cr17	67	C (+A1)	6	250	450	20	yes	no
		C (+A2) <sup>f</sup>		205	450	20		
		H (+A1)	12	230	450	20		
		H (+A2) <sup>f</sup>		205	450	20		
		P	25 <sup>e</sup>	230	430	20		
X3CrTi17	70	C (+A1)	6	240	420	23	yes	yes
		C (+A2) <sup>f</sup>		175	360	23		
		H (+A1)	12	220	420	23		
		H (+A2) <sup>f</sup>		175	360	23		
X3CrNb17	73	C	6	230	420	23	yes	yes

NOTE 1 MPa = 1N/mm<sup>2</sup>.

<sup>a</sup> C = cold-rolled strip; H = hot-rolled strip; P = hot-rolled plate.

<sup>b</sup> If, in the case of strip in rolling width < 300 mm, longitudinal test pieces are taken, the minimum proof stress values are reduced by 20 MPa.

<sup>c</sup> For thickness  $t < 3$  mm, the values apply for test pieces with a gauge length of 80 mm and a width of 20 mm. Test pieces with a gauge length of 50 mm and a width of 12,5 mm can also be used. For thickness  $t \geq 3$  mm, the values apply for test pieces with a gauge length of  $5,65 \sqrt{S_0}$ .

<sup>d</sup> When tested in accordance with ISO 3651-2.

<sup>e</sup> For thicknesses above 25 mm, the mechanical properties can be agreed upon.

<sup>f</sup> This condition is only supplied if specially agreed at the time of enquiry and order. Otherwise condition "+ A1" is supplied.

**Table 7 — Mechanical properties at room temperature for martensitic steels in the heat-treated condition (see Table A.4)**

Designation		Product form <sup>a</sup>	Thickness <i>t</i> mm max.	Heat treatment <sup>b</sup>	Hardness HWB max.	0,2 % proof stress <sup>c</sup> <i>R</i> <sub>p0,2</sub> MPa min.	Tensile strength		Elongation after fracture <sup>d</sup> <i>A</i> % min.	Hardness	
Name	Line number of ISO/TS 15510:2003						<i>R</i> <sub>m</sub> MPa min.   max.	HRC		HV	
X12Cr13	82	C	8	+A	200	—	440	600	20	—	—
		H	13,5	+A	200	—	440	600	20	—	—
		P	75 <sup>e</sup>	+QT1	—	400	550	750	15	—	—
		P	75 <sup>e</sup>	+QT2	—	450	650	850	12	—	—
X20Cr13	84	C	3	+QT	—	—	—	—	—	44 to 50	440 to 530
		C	8	+A	225	—	520	700	15	—	—
		H	13,5	+A	225	—	520	700	15	—	—
		P	75 <sup>e</sup>	+QT1	—	450	650	850	12	—	—
+QT2	—			550	750	950	10	—	—		
X30Cr13	85	C	3	+QT	—	—	—	—	—	45 to 51	450 to 550
		C	8	+A	235	—	540	740	15	—	—
		H	13,5	+A	235	—	540	740	15	—	—
		P	75 <sup>e</sup>	+QT1	—	600	800	1000	10	—	—
X39Cr13	86	C	3	+QT	—	—	—	—	—	47 to 53	480 to 580
		C	8	+A	240	—	—	760	12	—	—
		H	13,5	+A	240	—	—	760	12	—	—

NOTE 1 MPa = 1 N/mm<sup>2</sup>.

<sup>a</sup> C = cold-rolled strip; H = hot-rolled strip; P = hot-rolled plate.

<sup>b</sup> +A: Soft annealed; +QT: Quenched and tempered.

<sup>c</sup> If, in the case of strip in rolling width < 300 mm, longitudinal test pieces are taken, the minimum proof stress values are reduced by 20 MPa.

<sup>d</sup> For thickness *t* < 3 mm, the values apply for test pieces with a gauge length of 80 mm and a width of 20 mm. Test pieces with a gauge length of 50 mm and a width of 12,5 mm can also be used. For thickness *t* ≥ 3 mm, the values apply for test pieces with a gauge length of  $5,65 \sqrt{S_0}$ .

<sup>e</sup> For thicknesses above 75 mm, the mechanical properties can be agreed upon.

**Table 8 — Mechanical properties at room temperature for the precipitation-hardening steel in the heat-treated condition (see Table A.5)**

Designation		Product form <sup>a</sup>	Thickness	Heat treatment <sup>b</sup>	0,2 % proof stress	Tensile strength		Elongation after fracture
Name	Line number of ISO/TS 15510:2003					$R_{p0,2}$	$R_m$	
			mm		MPa	MPa	%	
			max.		min.	min.   max.	min.	
X7CrNiAl17-7	102	C	8	+AT			1030	19
				+P1300	1200	1300		
				+P1450	1310	1450		2
NOTE 1 MPa = 1 N/mm <sup>2</sup> .								
<sup>a</sup> C = cold-rolled strip.								
<sup>b</sup> +AT = solution-annealed; +P = precipitation-hardened.								

**Table 9 — Tests to be carried out, test units and extent of testing in specific testing**

Test	Test category <sup>a</sup>	Test unit	Product form		Number of test pieces per test sample
			Strip and sheet cut from strip (C, H), in rolling width < 600 mm   ≥ 600 mm	Rolled plate (P)	
Chemical analysis	m	Cast	The cast analysis is given by the manufacturer <sup>b</sup>		
Tensile test at room temperature or hardness test at room temperature	m	Same cast, same nominal thickness ± 10 %, same final-treatment condition (i.e. same heat treatment and/or same degree of cold deformation)	The extent of testing shall be agreed at the time of ordering	One test sample from each coil	1
Resistance to intergranular corrosion	o <sup>c</sup>		To be agreed upon at the time of ordering if intergranular corrosion is a hazard.		1
<sup>a</sup> Tests marked with an "m" (mandatory) shall be carried out as specific tests. In all cases, those marked with an "o" (optional) shall be carried out as specific tests only if agreed at the time of ordering. <sup>b</sup> A product analysis may be agreed upon at the time of ordering; the extent of testing shall be specified at the same time. <sup>c</sup> The test for resistance to intergranular corrosion is normally not carried out.					

**Annex A**  
(normative)

**Guidelines for further treatment (including heat treatment) in fabrication**

The guidelines given in Tables A.1 to A.5 are intended for hot forming and heat treatment.

Flame cutting may adversely affect edge areas; where necessary, they should be machined.

As the corrosion resistance of stainless steels is only ensured with a metallicly clean surface, layers of scale and annealing colours produced during hot forming, heat treatment or welding should be removed as far as possible before use.

Resistance to corrosion by finished parts made of steels with approximately 13 % Cr is increased by a smoother clean surface.

**Table A.1 — Guidelines on the temperatures for hot forming and heat treatment<sup>a</sup> of austenitic corrosion-resistant stainless steels**

Designation		Hot forming		Heat treatment symbol	Solution annealing	
Name	Line number of ISO/TS 15510:2003	Temperature °C	Type of cooling		Temperature <sup>b, c</sup> °C	Type of cooling
X2CrNi18-9 <sup>d</sup>	1	1 150 to 850	Air	+AT	1 000 to 1 100	Water, air <sup>e</sup>
X2CrNi19-11	2				1 000 to 1 100	
X2CrNi18-9	3				1 000 to 1 100	
X5CrNi18-9	6				1 000 to 1 100	
X10CrNi18-8	11				1 010 to 1 090	
X1CrNi25-21	12				1 030 to 1 110	
X12CrMnNiN17-7-5	13				1 000 to 1 100	
X6CrNiTi18-10	16				1 000 to 1 100	
X6CrNiNb18-10	19				1 020 to 1 120	
X2CrNiMo17-12-2 <sup>d</sup>	21				1 030 to 1 110	
X2CrNiMo17-12-3	22				1 030 to 1 110	
X2CrNiMo18-14-3	23				1 030 to 1 110	
X2CrNiMoN17-12-3	26				1 030 to 1 110	
X1CrNiMoN25-22-2	29				1 070 to 1 150	
X5CrNiMo17-12-2 <sup>d</sup>	30				1 030 to 1 110	
X3CrNiMo17-13-3	31				1 030 to 1 110	
X6CrNiMoTi17-12-2	32				1 030 to 1 110	
X1NiCrMoCu25-20-5	35				1 060 to 1 140	
X1NiCrMoCu31-27-4	36				1 070 to 1 150	
X1CrNiMoCuN24-22-8	38				1 200 to 1 000	
X8CrMnCuN17-8-3	40				1 000 to 1 100	
X1CrNiMoCuN24-22-6	41				1 040 to 1 200	
X2CrNiMnMoN25-18-6-5	42				1 200 to 950	
X11CrNiMnN19-8-6	43				1 000 to 1 100	
X6CrNiCu17-8-2	45				1 150 to 850	
X12CrNiSi18-9-3	46				1 010 to 1 150	

<sup>a</sup> The temperature of annealing shall be agreed upon for simulated heat-treated test pieces.  
<sup>b</sup> If heat treatment is carried out in a continuous furnace, the upper part of the range specified is usually preferred, or even exceeded.  
<sup>c</sup> The lower end of the range specified for solution annealing should be aimed at for heat treatment that is part of further processing, otherwise the mechanical properties might be affected. If the temperature of hot forming does not drop below the lower temperature for solution annealing, a temperature of 980 °C is adequate as a lower limit for Mo-free steels, a temperature of 1 000 °C for steels with Mo contents up to 3 % and a temperature of 1 020 °C for steels with Mo contents exceeding 3 %.  
<sup>d</sup> This procedure applies to both classes given in Table 4.  
<sup>e</sup> Rapid cooling.