
**Ships and marine technology — Loose
gear of lifting appliances on ships —
Hooks**

*Navires et technologie maritime — Accessoires mobiles des appareils
de levage sur les navires — Crocs*

STANDARDSISO.COM : Click to view the full PDF of ISO 16856:2013



STANDARDSISO.COM : Click to view the full PDF of ISO 16856:2013



COPYRIGHT PROTECTED DOCUMENT

© ISO 2013

All rights reserved. Unless otherwise specified, no part of this publication may be reproduced or utilized otherwise in any form or by any means, electronic or mechanical, including photocopying, or posting on the internet or an intranet, without prior written permission. Permission can be requested from either ISO at the address below or ISO's member body in the country of the requester.

ISO copyright office
Case postale 56 • CH-1211 Geneva 20
Tel. + 41 22 749 01 11
Fax + 41 22 749 09 47
E-mail copyright@iso.org
Web www.iso.org

Published in Switzerland

Contents

	Page
Foreword	iv
1 Scope	1
2 Normative references	1
3 Terms and definitions	1
4 Types	1
4.1 Common hook types	1
4.2 Other types (E-shaped)	1
4.3 Model designation	2
4.4 Locking device requirement	2
5 Technical requirements	2
5.1 Materials	2
5.2 Forging and heat treatment	3
5.3 Surface and internal quality of hooks	3
5.4 Tests	3
5.5 Inspection	4
5.6 Other requirements	4
6 Marking	4
7 Storage and transportation	5
8 Use and maintenance	5
Annex A (informative) Types and basic parameters of common hooks	6

STANDARDSISO.COM : Click to view the full PDF of ISO 16856:2013

Foreword

ISO (the International Organization for Standardization) is a worldwide federation of national standards bodies (ISO member bodies). The work of preparing International Standards is normally carried out through ISO technical committees. Each member body interested in a subject for which a technical committee has been established has the right to be represented on that committee. International organizations, governmental and non-governmental, in liaison with ISO, also take part in the work. ISO collaborates closely with the International Electrotechnical Commission (IEC) on all matters of electrotechnical standardization.

The procedures used to develop this document and those intended for its further maintenance are described in the ISO/IEC Directives, Part 1. In particular the different approval criteria needed for the different types of ISO documents should be noted. This document was drafted in accordance with the editorial rules of the ISO/IEC Directives, Part 2 (see www.iso.org/directives).

Attention is drawn to the possibility that some of the elements of this document may be the subject of patent rights. ISO shall not be held responsible for identifying any or all such patent rights. Details of any patent rights identified during the development of the document will be in the Introduction and/or on the ISO list of patent declarations received (see www.iso.org/patents).

Any trade name used in this document is information given for the convenience of users and does not constitute an endorsement.

For an explanation on the meaning of ISO specific terms and expressions related to conformity assessment, as well as information about ISO's adherence to the WTO principles in the Technical Barriers to Trade (TBT) see the following URL: Foreword - Supplementary information

The committee responsible for this document is ISO/TC 8, *Ships and marine technology*, Subcommittee SC 4, *Outfitting and deck machinery*.

STANDARDSISO.COM : Click to view the full PDF of ISO 16856:2013

Ships and marine technology — Loose gear of lifting appliances on ships — Hooks

1 Scope

This International Standard specifies the types and basic parameters, technical requirements, marking, storage, and transportation, use and maintenance of hooks as loose gear of lifting appliances on ships.

This International Standard is applicable to lifting appliances on ships.

2 Normative references

The following documents, in whole or in part, are normatively referenced in this document and are indispensable for its application. For dated references, only the edition cited applies. For undated references, the latest edition of the referenced document (including any amendments) applies.

ISO 1837, *Lifting hooks — Nomenclature*

ISO 16855, *Ships and marine technology — Loose gear of lifting appliances on ships — General requirements*

3 Terms and definitions

For the purposes of this document, the terms and definitions given in ISO 16855 and ISO 1837 apply.

4 Types

4.1 Common hook types

4.1.1 Shank hook with point (S-shaped)

For the shapes and dimensions of a shank hook with point, see [A.1](#).

4.1.2 Shank ramshorn hook (D-shaped)

For the shapes and dimensions of a shank ramshorn hook, see [A.2](#).


4.1.3 C-hook (C-shaped)

For the shapes and dimensions of a C-hook, see [A.3](#).

4.2 Other types (E-shaped)

Types of hooks in ISO 1837 other than common hook types that can also be used as ship hooks fall under E-shaped.

4.3 Model designation

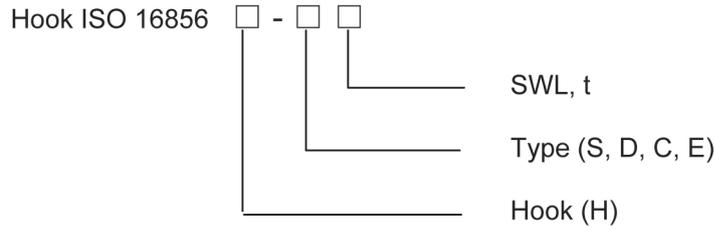

Figure

EXAMPLE Designation of a shank hook with point with 20 t SWL:

Hook ISO 16856 H-S20

4.4 Locking device requirement

Various types of hooks shall be provided with automatic locking devices.

5 Technical requirements

5.1 Materials

5.1.1 Hook materials must use solid steel manufactured by Martin furnaces, electric furnaces, or oxygen top-blown converters; it is recommended to use the electroslag remelting process.

5.1.2 For the chemical composition of hook materials, see [Table 1](#). Other materials can be used (see [5.6](#)).

Table 1 — Chemical composition of hook materials

Materials	Chemical composition (heat analysis)						
	%						
	C	Si	Mn	P	S	Cr	Al
Carbon steel	0,17–0,24	0,17–0,35	0,45–0,80	≤0,035	≤0,035	≤0,030	≥0,025
Carbon-manganese steel	0,17–0,24	0,20–0,35	1,20–1,50	≤0,035	≤0,035	≤0,030	≥0,025

5.1.3 For the mechanical properties of hook materials, see [Table 2](#). Other mechanical properties can be used (see [5.6](#)).

Table 2 — Mechanical properties of hook materials

Materials	Mechanical properties						
	Tensile strength R_m MPa	Yield point R_{eH} MPa			Elongation A %	Impact energy A_K J	
	Diameters or thicknesses of steel mm						
	≤100	≤16	>16–40	>40–60	≤50	≤100	≤60
Carbon steel	402–490	255	245	235	—	22	48
Carbon-manganese steel	510–608	353	343	333	22	—	41

NOTE 1 The values listed in this table refer to mechanical properties at normal temperature.

NOTE 2 For diameters or thicknesses > 60 mm, the impact energy and yield point under strain aging conditions are determined by the supplier and the purchaser based on demand.

If materials have no obvious yield points, the yield point R_{eH} shall be the yield strength $R_{p0,2}$.

5.1.4 When the design temperature of lifting appliances on ships is below -10 °C , the impact energy test temperature of hook materials shall satisfy the requirements of related organizations, such as classification societies.

5.2 Forging and heat treatment

5.2.1 The forging ratio of forged pieces shall be no less than 3 during the use of steel ingot and no less than 1,5 during the use of steel billet.

5.2.2 Heat treatment must be made after hook forging to achieve the properties specified in 5.1, with no more than three times of heat treatment.

5.3 Surface and internal quality of hooks

5.3.1 The surface of hooks shall be smooth and clean, without any defect such as burrs, cracks, folding, and burning.

5.3.2 Inside hooks, there shall be no cracks, fish eyes, or other defects such as impurities that affect their safe use. For other defects, such as impurities, allowed to exist, the following provisions shall be met: for single defects, the equivalent diameter shall be no more than 5 mm; for scattered defects, it is expected that the equivalent diameter shall be no more than 3 mm and the distributed length shall be no more than 30 mm.

5.3.3 Defects in hooks cannot be rewelded.

5.4 Tests

5.4.1 Every hook shall be proof tested, with test loads given in Table 3. Proof load shall be applied to each hook with a testing machine or test weight for a duration of not less than 5 min.

Table 3 — Proof load for hooks

Safe working load (SWL) kN	Proof load (PL) kN
≤245	2 × SWL
>245	1,22 × SWL + 196

5.4.2 After proof testing, each hook shall be thoroughly examined for deformation, cracks, or other defects and to ensure that its rotating parts can rotate freely.

5.4.3 The proof load can be applied to a shank ramshorn hook as indicated in [Figure 1 a\)](#) or [Figure 1 b\)](#), but in the latter case, an additional load of half the proof load is to be subsequently applied, as shown in [Figure 1 c\)](#).

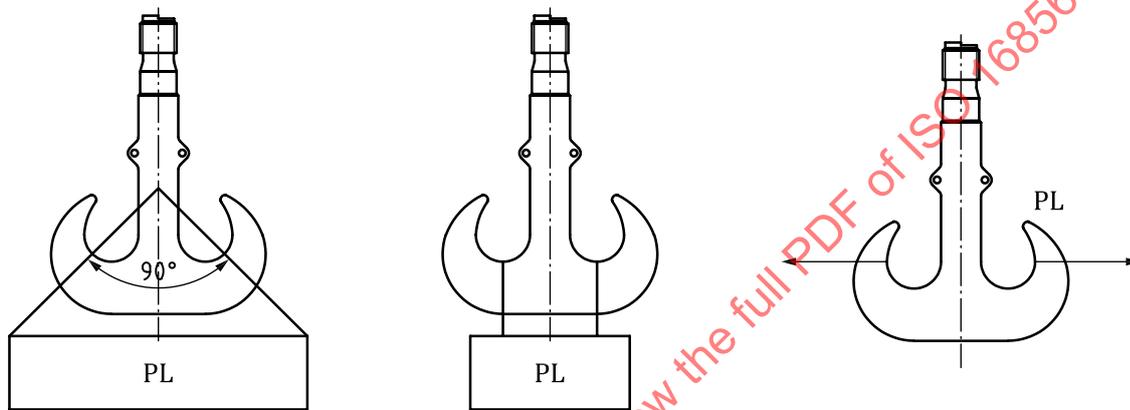


Figure 1 — Proof testing of shank ramshorn hook

5.5 Inspection

5.5.1 Inspection shall be made after the production of hooks to ensure that the surface and internal quality satisfies the requirements of [5.3](#), and the requirements of [5.4.2](#) after the test.

5.5.2 For hooks that pass the test, the manufacturer shall provide technical documents such as certifications.

5.6 Other requirements

For hooks (type or SWL, materials) beyond common types, strength shall be calculated during the design. The calculations of hook stress are checked based on the curved beam theory, in which the safety factor of the allowable stress to the yield limit of materials is no less than 1,55. Commercially available forged hooks that meet industry standards in terms of SWL, design factor, forging reduction, heat treatment, testing, and inspection are acceptable as agreed on by the supplier and the purchaser.

6 Marking

6.1 Marks of hooks shall be permanently distinct with the following items:

- a) safe working load, in t;
- b) test load, in kN;
- c) test date;

- d) hook number;
- e) manufacturer's stamp or the stamp of test unit.

6.2 Hooks shall be marked at their broad space, but not at their bends, for check.

6.3 For hooks of a small size, should the place where marking is restricted, the marks of number and date can be eliminated.

7 Storage and transportation

7.1 During storage, the machined surfaces of hooks that pass the test shall be painted with anti-rust oil, and their non-machined surfaces shall be painted with anti-rust paint.

7.2 Secure packaging shall be made for hooks to prevent collision during transportation.

8 Use and maintenance

8.1 Upon installation on the lifting appliances, hooks shall be checked before each use, with major check items as follows:

- a) wear;
- b) normal operation of moving parts;
- c) good lubrication;
- d) no abnormal conditions such as loose fixed parts or defects;
- e) no crack, scratch, and heat damage, including welding slag or arc striking mark, in hook bodies.

8.2 Hook defects found during the check shall be repaired and cannot be used until confirmation by an experienced personnel. Hooks shall be scrapped under the following circumstances:

- a) there are defects in the hooks, such as crack, heat damage, including welding slag or arc striking mark, which prevent them from use;
- b) the dimension of the worn moving part reaches 10 % of its total dimension.

Annex A (informative)

Types and basic parameters of common hooks

A.1 Shank hook with point (S-shaped)

For the shapes and dimensions of a shank hook with point, see [Figure A.1](#) and [Table A.1](#).

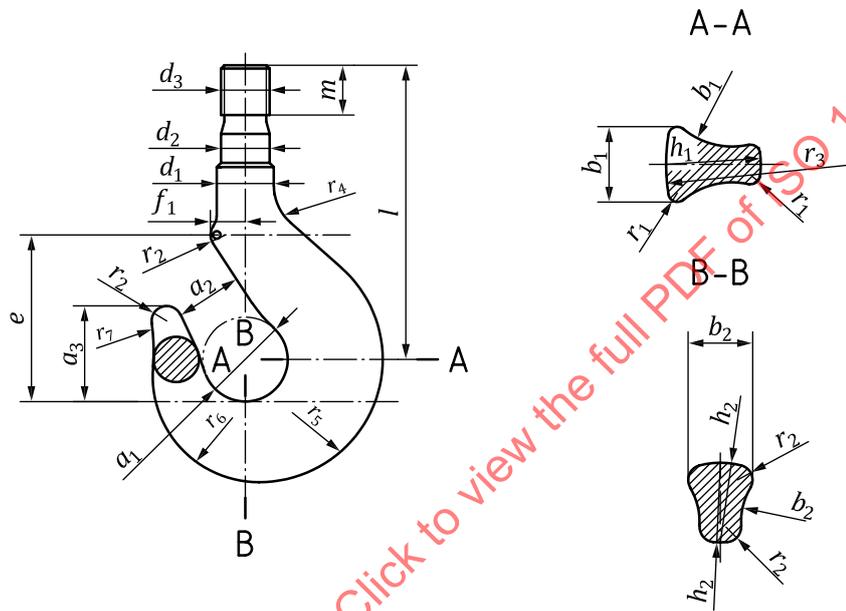


Figure A.1 — Shapes of a shank hook with point

A.2 Shank ramshorn hook (D-shaped)

For the shapes and dimensions of a shank ramshorn hook, see [Figure A.2](#) and [Table A.2](#).

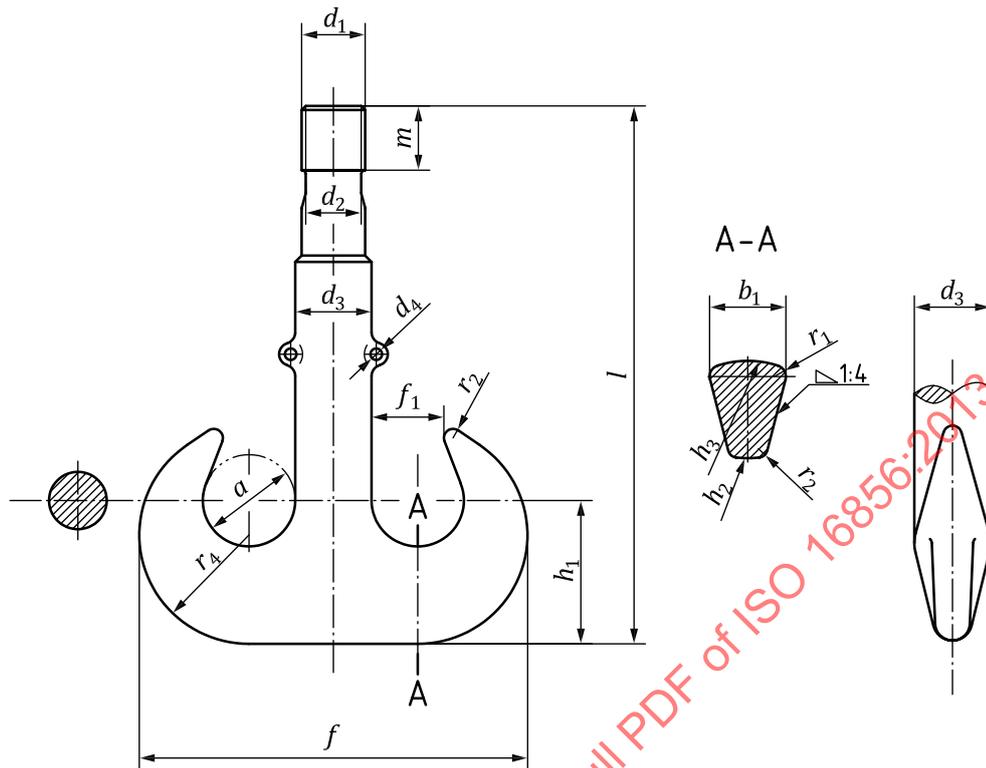


Figure A.2 — Shapes of a shank ramshorn hook

A.3 C-hook (C-shaped)

For the shapes and dimensions of a C-hook, see [Figure A.3](#) and [Table A.3](#).

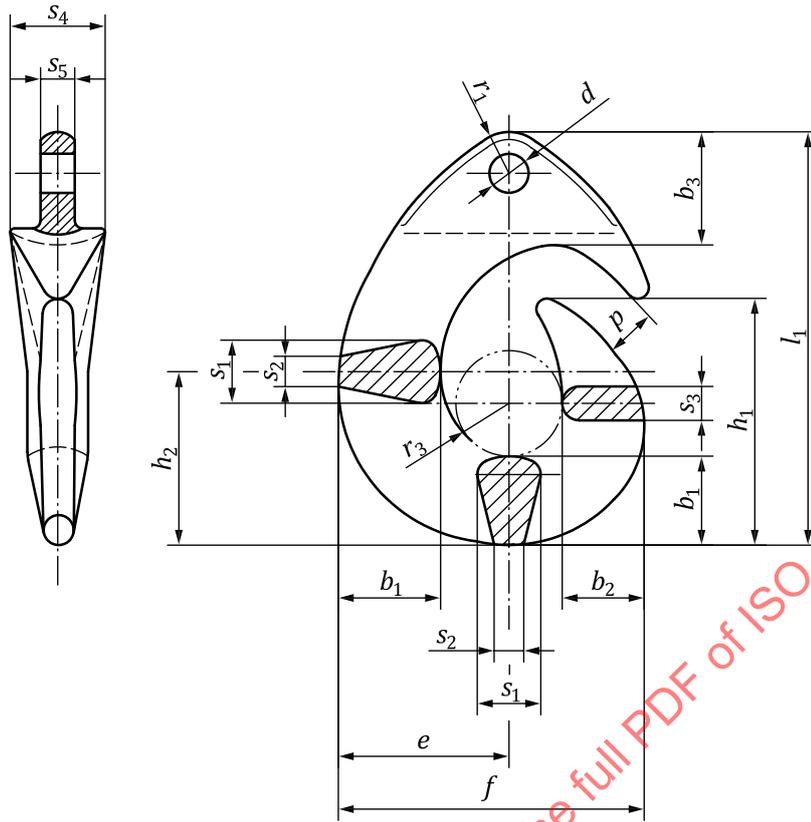


Figure A.3 — Shapes of a C-hook

STANDARDSISO.COM : Click to view the full PDF of ISO 16856:2013