

INTERNATIONAL  
STANDARD

ISO  
17231

IULTCS/IUP  
37

First edition  
2006-09-15

---

---

**Leather — Physical and mechanical tests — Determination of water repellency of garment leather**

*Cuir — Essais physiques et mécaniques — Détermination de la résistance au mouillage superficiel des cuirs pour vêtements*

STANDARDSISO.COM : Click to view the full PDF of ISO 17231:2006



Reference number  
ISO 17231:2006(E)  
IULTCS/IUP 37:2006(E)

© ISO 2006

**PDF disclaimer**

This PDF file may contain embedded typefaces. In accordance with Adobe's licensing policy, this file may be printed or viewed but shall not be edited unless the typefaces which are embedded are licensed to and installed on the computer performing the editing. In downloading this file, parties accept therein the responsibility of not infringing Adobe's licensing policy. The ISO Central Secretariat accepts no liability in this area.

Adobe is a trademark of Adobe Systems Incorporated.

Details of the software products used to create this PDF file can be found in the General Info relative to the file; the PDF-creation parameters were optimized for printing. Every care has been taken to ensure that the file is suitable for use by ISO member bodies. In the unlikely event that a problem relating to it is found, please inform the Central Secretariat at the address given below.

STANDARDSISO.COM : Click to view the full PDF of ISO 17231:2006

© ISO 2006

All rights reserved. Unless otherwise specified, no part of this publication may be reproduced or utilized in any form or by any means, electronic or mechanical, including photocopying and microfilm, without permission in writing from either ISO at the address below or ISO's member body in the country of the requester.

ISO copyright office  
Case postale 56 • CH-1211 Geneva 20  
Tel. + 41 22 749 01 11  
Fax + 41 22 749 09 47  
E-mail [copyright@iso.org](mailto:copyright@iso.org)  
Web [www.iso.org](http://www.iso.org)

Published in Switzerland

## Foreword

ISO (the International Organization for Standardization) is a worldwide federation of national standards bodies (ISO member bodies). The work of preparing International Standards is normally carried out through ISO technical committees. Each member body interested in a subject for which a technical committee has been established has the right to be represented on that committee. International organizations, governmental and non-governmental, in liaison with ISO, also take part in the work. ISO collaborates closely with the International Electrotechnical Commission (IEC) on all matters of electrotechnical standardization.

International Standards are drafted in accordance with the rules given in the ISO/IEC Directives, Part 2.

The main task of technical committees is to prepare International Standards. Draft International Standards adopted by the technical committees are circulated to the member bodies for voting. Publication as an International Standard requires approval by at least 75 % of the member bodies casting a vote.

Attention is drawn to the possibility that some of the elements of this document may be the subject of patent rights. ISO shall not be held responsible for identifying any or all such patent rights.

ISO 17231 was prepared by the Physical Test Commission of the International Union of Leather Technologists and Chemists Societies (IUP Commission, IULTCS) in collaboration with the European Committee for Standardization (CEN) Technical Committee CEN/TC 289 *Leather*, the secretariat of which is held by UNI. It was published as EN 14340. It is based on IUP 37 published in *J. Soc. Leather Tech. Chem.*, **86** (7), p. 339, 2002, and declared an official method of the IULTCS in May 2003.

IULTCS, originally formed in 1897, is a world-wide organization of professional leather societies to further the advancement of leather science and technology. IULTCS has three Commissions, which are responsible for establishing international methods for the sampling and testing of leather. ISO recognizes IULTCS as an international standardizing body for the preparation of test methods for leather.



# Leather — Physical and mechanical tests — Determination of water repellency of garment leather

## 1 Scope

This International Standard specifies a method for determining the repellency of leather to surface wetting. It is applicable to all leathers intended for use in clothing. The method does not determine the resistance of leather to water penetration.

## 2 Normative references

The following referenced documents are indispensable for the application of this document. For dated references, only the edition cited applies. For undated references, the latest edition of the referenced document (including any amendments) applies.

ISO 2418, *Leather — Chemical physical and mechanical and fastness tests — Sampling location*

ISO 2419, *Leather — Physical and mechanical tests — Sample preparation and conditioning*

ISO 3696, *Water for analytical laboratory use — Specification and test methods*

## 3 Terms and definitions

For the purposes of this document, the following terms and definitions apply.

### 3.1

#### **spray rating**

measure of the resistance of the surface of a leather to wetting


## 4 Principle

A specified volume of distilled or deionized water is sprayed onto a test piece, which has been mounted on a ring and placed at an angle of 45° so that the centre of the test piece is at a specified distance below the spray nozzle. The spray rating is determined by comparing the appearance of the test piece with descriptive and photographic standards. The mass of water absorbed by the test piece is determined by weighing before and after applying the water spray.

## 5 Apparatus

5.1 **Spray device**, as shown in Figure 1, consisting of a funnel, diameter  $150 \text{ mm} \pm 2 \text{ mm}$ , held vertically with a metal spray nozzle (5.2) connected to the end of the stem by flexible tubing of bore about 10 mm. The overall distance from the top of the funnel to the bottom of the nozzle is  $190 \text{ mm} \pm 2 \text{ mm}$ .

Dimensions in millimetres

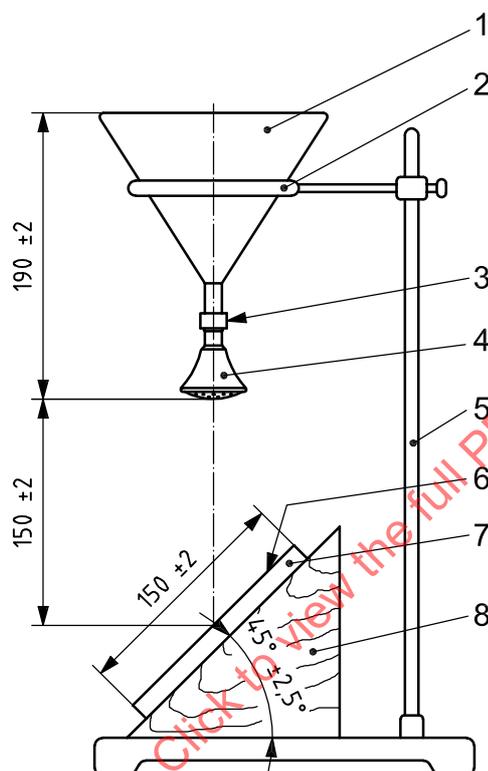


### Key

- 1 glass funnel  $\varnothing 150 \pm 2$
- 2 ring support
- 3 rubber tubing
- 4 spray nozzle
- 5 stand
- 6 specimen
- 7 specimen holder
- 8 support (e.g. wood)

Figure 1 — Apparatus for spray test

**5.2 Metal spray nozzle**, as shown in Figure 2, with approximate diameter of 33 mm, having a convex face with 19 holes of  $0,9 \text{ mm} \pm 0,05 \text{ mm}$  diameter distributed over the face of the nozzle. The duration of flow for  $250 \text{ ml} \pm 5 \text{ ml}$  of distilled or deionized water poured into the funnel shall be  $27,5 \text{ s} \pm 2,5 \text{ s}$ .

Dimensions in millimetres

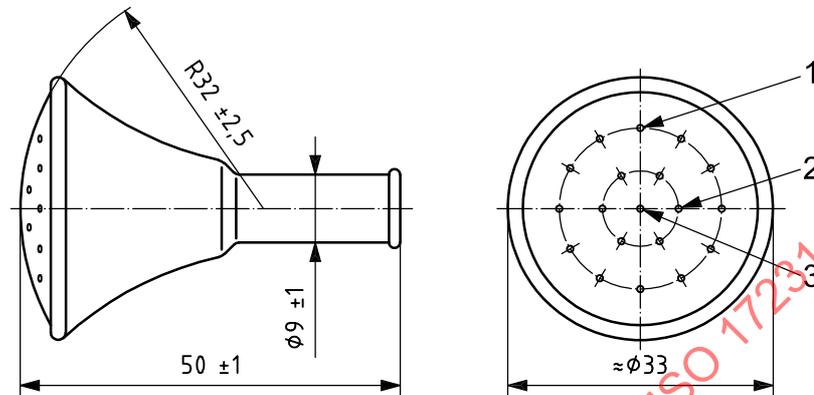

**Key**

- 1 12 holes  $\varnothing 0,9 \pm 0,05$  on a circle  $\varnothing 21,4 \pm 0,05$
- 2 6 holes  $\varnothing 0,9 \pm 0,05$  on a circle  $\varnothing 10 \pm 0,05$
- 3 1 hole  $\varnothing 0,9 \pm 0,05$  on centre

**Figure 2 — Spray nozzle**

**5.3 Test piece holder**, consisting of two metal rings which fit into each other. The inner ring is fixed and of outside diameter  $150 \text{ mm} \pm 2 \text{ mm}$ . The outer ring is adjustable so that the internal diameter can be reduced to  $150 \text{ mm}$  to allow the test piece to be securely clamped between the two rings. When in position for test, the rings rest on a suitable support so that the test piece is at an angle of  $45,0^\circ \pm 2,5^\circ$  and with the centre of the clamped area  $150 \text{ mm} \pm 2 \text{ mm}$  below the centre of the face of the metal nozzle.

**5.4 Balance**, reading to  $0,001 \text{ g}$ .

**5.5 Distilled or deionized water**, conforming to the requirements of grade 3 of ISO 3696.

## 6 Sampling and sample preparation

**6.1** Sample in accordance with ISO 2418. Cut three square test pieces of side  $182 \text{ mm} \pm 2 \text{ mm}$  ensuring that they are taken from areas free from any holes or other damage.

NOTE 1 It may be necessary to trim the wool if a woolled sheepskin is being tested to allow secure clamping of the test piece.

NOTE 2 If there is a requirement for more than two hides or skins to be tested in one batch, then only one sample need be taken from each hide or skin, provided that the overall total is not less than three test pieces.

**6.2** Condition the test pieces in accordance with ISO 2419.

**6.3** Weigh the test piece to the nearest  $0,001 \text{ g}$ .

**6.4** Carry out all further operations at a temperature of  $20^\circ \text{C} \pm 2^\circ \text{C}$  or  $23^\circ \text{C} \pm 2^\circ \text{C}$ . There is no need for further humidity control.

## 7 Procedure

7.1 Mount the test piece securely on the test piece holder (5.3) with the face of the leather which would be exposed in wear uppermost. Place the test piece holder in position below the spray nozzle.

7.2 Pour 250 ml ± 5 ml of distilled or deionized water (5.5) at the controlled temperature (6.4) into the funnel quickly but steadily so that the spraying is continuous once it has commenced.

7.3 Immediately after the spraying has ceased, remove the holder and test piece and tap two diametrically opposite points of the frame against a solid object, with the plane of the leather almost horizontal and the tested surface downwards.

7.4 Assign to the test piece the spray rating on either the following descriptive scale or the photographic scale in Annex A which best describes the degree of wetting. Intermediate ratings are not to be attempted.

- 1 Wetting of the whole of the sprayed surface.
- 2 Wetting of half of the sprayed surface. This usually occurs through the merging of small, discrete wetted areas.
- 3 Wetting of the sprayed surface only as small discrete areas.
- 4 No wetting of, but adherence of small drops to, the sprayed surface.
- 5 No wetting of and no adherence of small drops to the sprayed surface.

7.5 Examine the reverse side of the test piece and note any wetting.

7.6 Remove the test piece from the holder, blot gently to remove any water droplets which still adhere and re-weigh to the nearest 0,001 g.

## 8 Expression of results

Calculate the mass of water absorbed,  $m_w$ , in grams and the percentage of water absorbed,  $w$ , using the equations:

$$m_w = m_2 - m_1$$

$$w = \frac{(m_2 - m_1)}{m_1} \times 100\%$$

where

$m_1$  is the initial mass of the test piece, in grams;

$m_2$  is the mass of the test piece after the test, in grams.

## 9 Test report

The test report shall include the following for each test piece:

- a) a reference to this International Standard; i.e. 17231:2006;
- b) the spray rating (7.4);
- c) the mass of water absorbed,  $m_w$ , in grams;
- d) the percentage of water absorbed,  $w$ ;
- e) the standard atmosphere used for conditioning and testing as given in ISO 2419 (i.e. 20 °C/65 % RH, or 23 °C/50 % RH);
- f) any deviations from the method specified in this International Standard;
- g) full details for identification of the sample and any deviations from ISO 2418 with respect to sampling.

STANDARDSISO.COM : Click to view the full PDF of ISO 17231:2006