
**Monolithic (unshaped) refractory
products —**

**Part 7:
Tests on pre-formed shapes**

Produits réfractaires monolithiques (non façonnés) —

Partie 7: Essais sur pièces pré-formées

STANDARDSISO.COM : Click to view the full PDF of ISO 1927-7:2012



STANDARDSISO.COM : Click to view the full PDF of ISO 1927-7:2012



COPYRIGHT PROTECTED DOCUMENT

© ISO 2012

All rights reserved. Unless otherwise specified, no part of this publication may be reproduced or utilized in any form or by any means, electronic or mechanical, including photocopying and microfilm, without permission in writing from either ISO at the address below or ISO's member body in the country of the requester.

ISO copyright office
Case postale 56 • CH-1211 Geneva 20
Tel. + 41 22 749 01 11
Fax + 41 22 749 09 47
E-mail copyright@iso.org
Web www.iso.org

Published in Switzerland

Contents

	Page
Foreword	iv
1 Scope	1
2 Normative references	1
3 Terms and definitions	1
4 Principle	4
5 Apparatus	4
6 Inspection by attributes	6
6.1 Preparation of the test piece	6
6.2 Measurement of dimensions	6
6.3 Measurement of angles	6
6.4 Measurement of warpage	7
6.5 Measurement of corner defects	8
6.6 Measurement of edge defects	9
6.7 Measurement of craters and bubbles	10
6.8 Measurement of cracks	11
6.9 Measurement of protrusions and indentations	11
6.10 Measurement of fins	12
6.11 Segregations	12
6.12 Friability	12
7 Inspection by variables	12
7.1 Destructive test methods	12
7.2 Non-destructive test methods	14
8 Test report	19
Bibliography	21

STANDARDSISO.COM : Click to view the full PDF of ISO 1927-7:2012

Foreword

ISO (the International Organization for Standardization) is a worldwide federation of national standards bodies (ISO member bodies). The work of preparing International Standards is normally carried out through ISO technical committees. Each member body interested in a subject for which a technical committee has been established has the right to be represented on that committee. International organizations, governmental and non-governmental, in liaison with ISO, also take part in the work. ISO collaborates closely with the International Electrotechnical Commission (IEC) on all matters of electrotechnical standardization.

International Standards are drafted in accordance with the rules given in the ISO/IEC Directives, Part 2.

The main task of technical committees is to prepare International Standards. Draft International Standards adopted by the technical committees are circulated to the member bodies for voting. Publication as an International Standard requires approval by at least 75 % of the member bodies casting a vote.

Attention is drawn to the possibility that some of the elements of this document may be the subject of patent rights. ISO shall not be held responsible for identifying any or all such patent rights.

ISO 1927-7 was prepared by Technical Committee ISO/TC 33, *Refractories*.

ISO 1927 consists of the following parts, under the general title *Monolithic (unshaped) refractory products*:

- *Part 1: Introduction and classification*
- *Part 2: Sampling for testing*
- *Part 3: Characterization as received*
- *Part 4: Determination of consistency of castables*
- *Part 5: Preparation and treatment of test pieces*
- *Part 6: Measurement of physical properties*
- *Part 7: Tests on pre-formed shapes*
- *Part 8: Determination of complementary properties*

Monolithic (unshaped) refractory products —

Part 7: Tests on pre-formed shapes

1 Scope

This part of ISO 1927 specifies methods for the testing of as-delivered pre-formed shapes. It applies to shapes fabricated from dense and insulating castables and ramming materials as defined in ISO 1927-1.

NOTE Acceptance values for the individual test methods described should be agreed between the parties involved.

2 Normative references

The following referenced documents are indispensable for the application of this document. For dated references, only the edition cited applies. For undated references, the latest edition of the referenced document (including any amendments) applies.

ISO 1927-1, *Monolithic (unshaped) refractory products — Part 1 Introduction and classification*

ISO 1927-6, *Monolithic (unshaped) refractory products — Part 6: Measurement of physical properties*


3 Terms and definitions

For the purposes of this document, the following terms and definitions apply.

3.1

corner defect

missing corner, defined by the three dimensions a , b and c as indicated in Figure 1

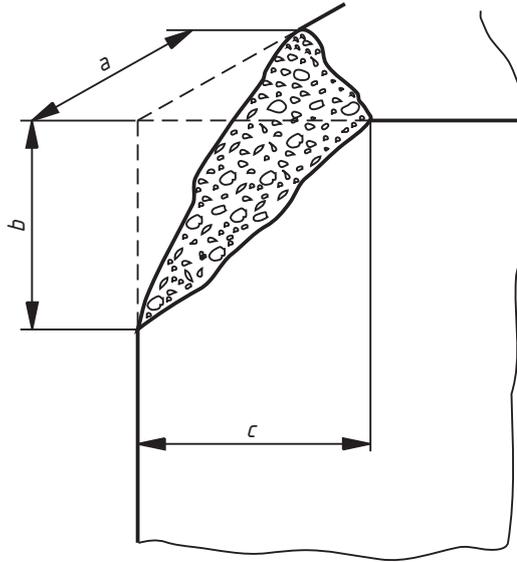


Key
a, b and c Three dimensions defining the missing corner

Figure 1 — Typical corner defect

3.2
edge defect

missing edge, defined by the three dimensions, *e*, *f*, and *g* as indicated in Figure 2

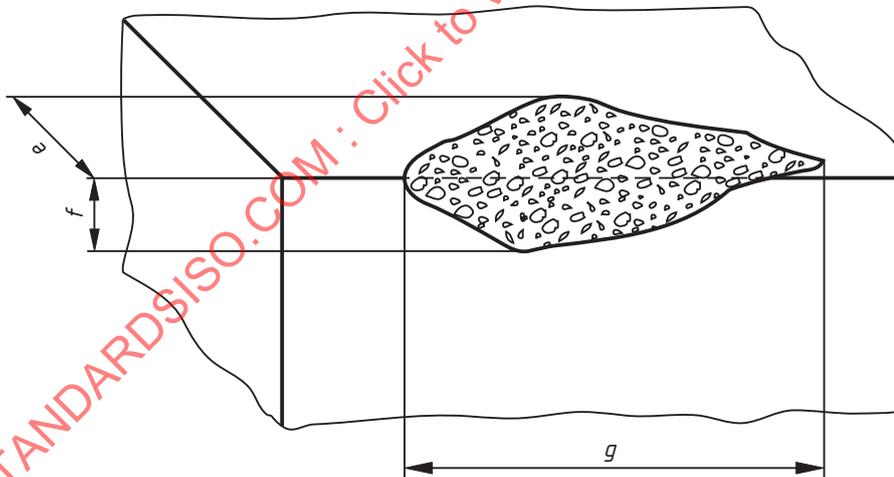

Key
e, f, and g Three dimensions defining the missing edge

Figure 2 — Typical edge defect


3.3
crater

clearly defined hole in the surface of a shape whose parameters, i.e. maximum diameter, minimum diameter and depth, can be measured

NOTE Its origin can be a bubble produced during manufacture.

3.4 hairline cracks

fine cracks visible on the surface of a shape whose length can be measured and whose width is less than or equal to 0,2 mm, see Figure 3

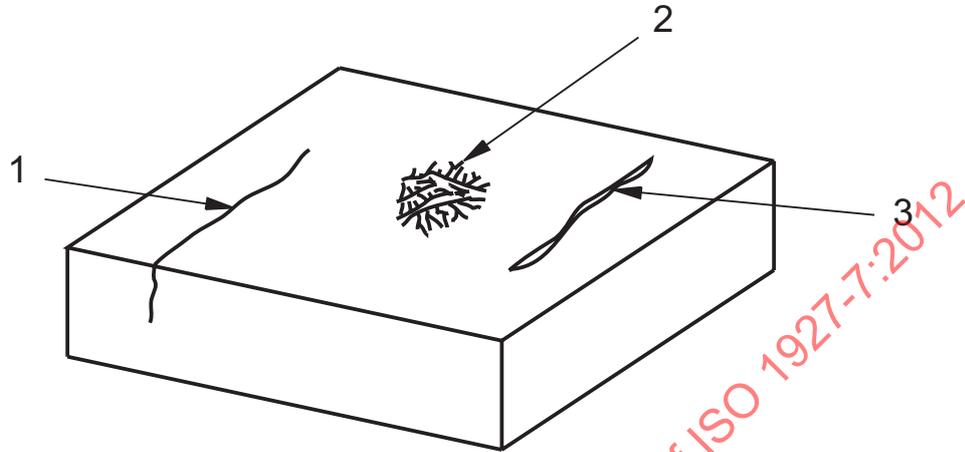

Key

- | | |
|---|-----------------|
| 1 | Hairline crack |
| 2 | Surface crazing |
| 3 | Open cracks |

Figure 3 — Typical cracks

3.5 surface crazing

network of hairline cracks confined to the surface of the shape, see Figure 3

3.6 open cracks

cracks or tears on the surface whose length is more than 10 mm and whose width is more than 0,2 mm
See Figure 3.

3.7 protrusions and indentations

imperfections that can occur during fabrication or firing, if applicable

3.8 fins

thin layer of material on the face of a shape that projects beyond the edge

3.9 segregation

separation of aggregate and fines during fabrication to leave a honeycomb appearance and/or a layer of excess fines

3.10 friability

crumbly texture due to poor consolidation and/or mould leakage

3.11 warpage

deviation of a plane surface from being flat

4 Principle

Testing of pre-formed shapes by qualitative and/or quantitative methods. These methods are of two types:

- a) **Inspection by attributes** by evaluating the integrity of a refractory shape by visual inspection of cracks or other surface defects and by conformance to dimensional tolerances;
- b) **Inspection by variables** by evaluating the quality of a refractory shape by determining physical properties using appropriate destructive or non-destructive test methods.

NOTE It is not obligatory to use all the test methods described in this part of ISO 1927 when determining the quality of a pre-formed shape.

5 Apparatus

5.1 Linear measuring devices, steel tape and/or callipers in accordance with the tolerance required and conforming to an accuracy that is twice the intended accuracy of the measurement.


NOTE Where possible, linear tolerances less than 1 mm should be measured with callipers. Steel tape measurements are accurate to the millimetre (0,5 mm can be estimated) whereas callipers are accurate to 0,1 mm.

5.2 Steel straightedge, at least 5 mm thick and of sufficient length to span the diagonal of the largest shape to be measured.


5.3 Two steel measuring wedges, which shall be either:

- a) type 1, at least 50 mm in length and 10 mm in thickness at one end, of uniform cross-section for a length of at least 10 mm from that end and then tapering to zero thickness at the other end (see for example Figure 4a), or
- b) type 2, up to 160 mm in length with an even taper from 4 mm to zero (see for example Figure 4b).

Each wedge shall be graduated and numbered along the slope to show the thickness of the wedge between the base and the slope in increments of either 0,5 mm (type 1) or 0,1 mm (type 2).

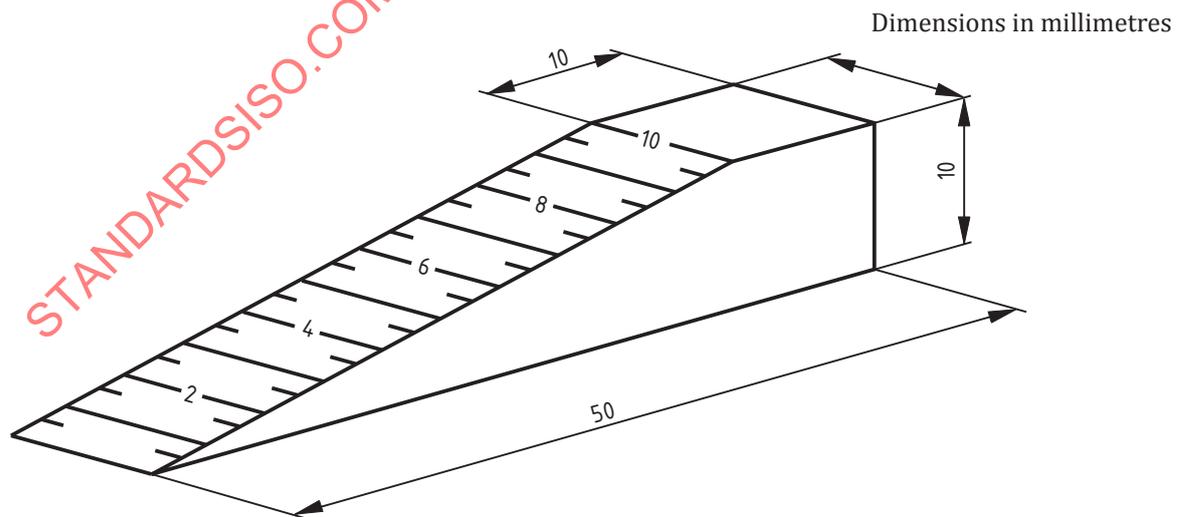

a) Type 1

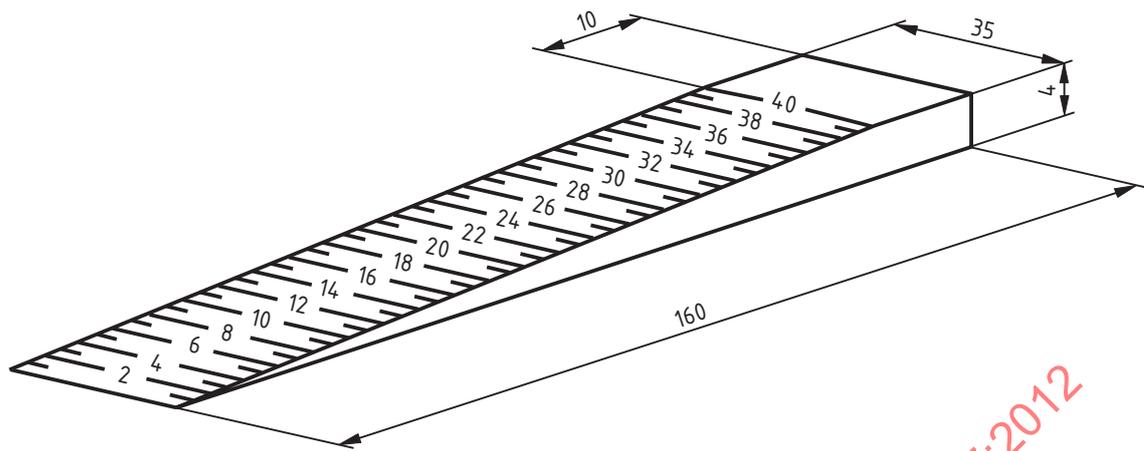

b) Type 2

Figure 4 — Two types of measuring wedge

5.4 Graticule, with 0,1 mm graduations and/or **feeler gauges** of an appropriate size and accuracy to be used for the measurement of crack width. If necessary, the gauges can be replaced by measuring wedges of appropriate accuracy.

5.5 Sliding bevel, for the measurement of angles.

5.6 Depth gauge calibrated in millimetres of depth, having a probe of 3 mm diameter.

5.7 Breakage defect sizer, with a slot, uncovering 2 mm on both surfaces, for determination of minimum defect sizes for corner and edge defects, according to Figure 5.

NOTE 1 One breakage defect sizer can be used together with a steel straightedge for the measurement of corner defects (see 6.5). Two breakage defect sizers can be used together with a linear measuring device for the measurement of edge defects (see 6.6).

NOTE 2 A breakage defect sizer permits an objective definition of the point of departure for the measurement of the size of a broken edge.

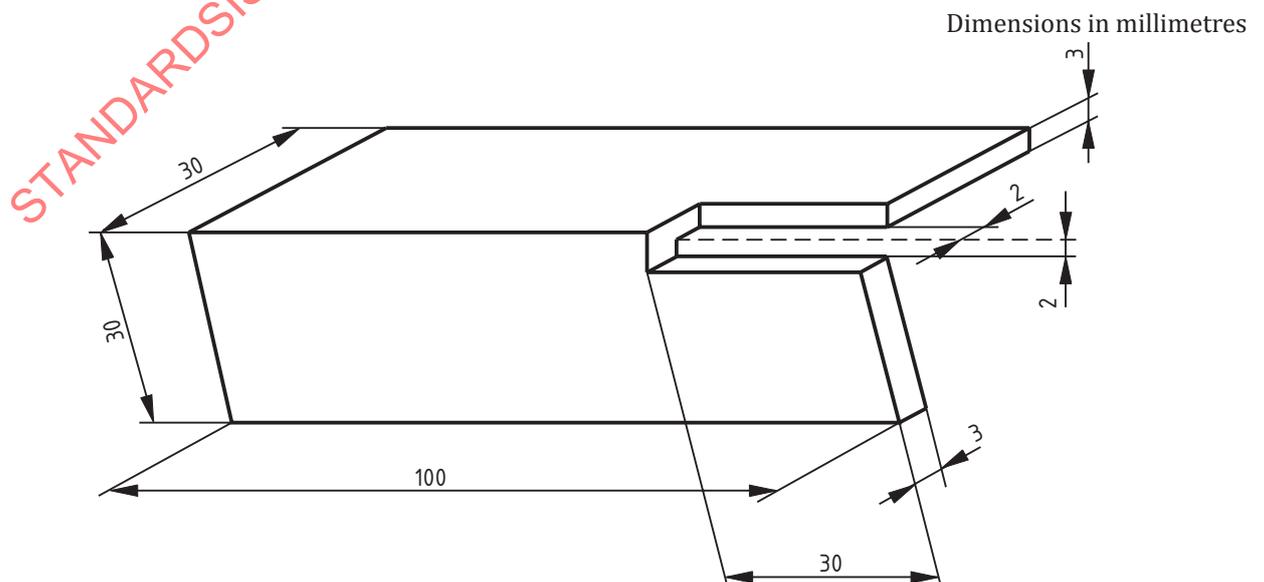


Figure 5 — Breakage defect sizer

5.8 **Balance**, capable of measuring to an accuracy of 1 %.

5.9 **Ultrasonic pulse velocity measuring equipment**.

5.10 **Equipment for determining the resonant frequency by mechanical shock**.

5.11 **Rebound hammer**.

5.12 **Drying oven**, capable of being controlled at $110\text{ °C} \pm 5\text{ °C}$.

5.13 **Furnace**, capable of operating at $1\ 050\text{ °C} \pm 25\text{ °C}$.

6 Inspection by attributes

6.1 Preparation of the test piece

The definition of edges may be improved, after any protrusions or indentations have been measured, by removing any projections such as fins or protrusions. This can normally be achieved by light abrasion.

6.2 Measurement of dimensions

Linear dimensions shall be measured by means of a linear measuring device (see 5.1), and unless otherwise agreed, shall be measured to the nearest 0,5 mm.

6.3 Measurement of angles

Angles shall be measured by adjusting the sliding bevel to fit the shape (see Figure 6) and the angle determined by the use of a protractor (see Figure 7).

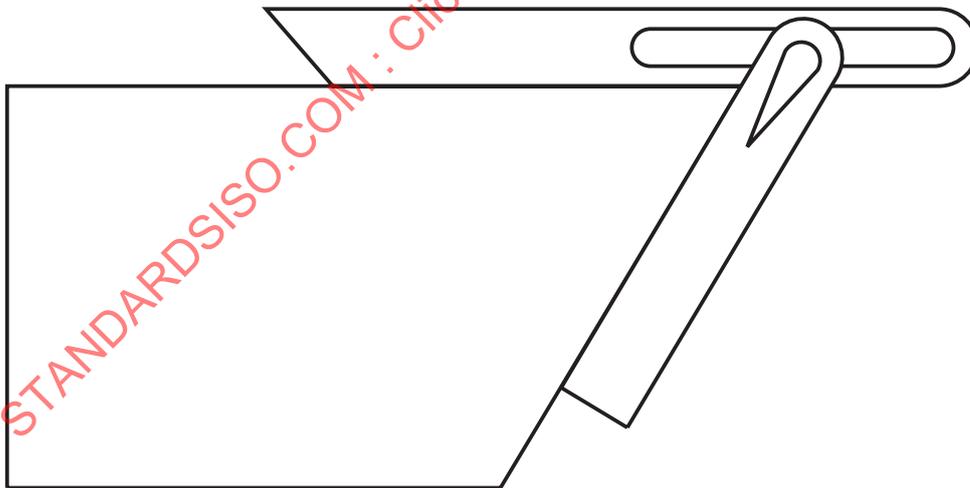


Figure 6 — Positioning the sliding bevel


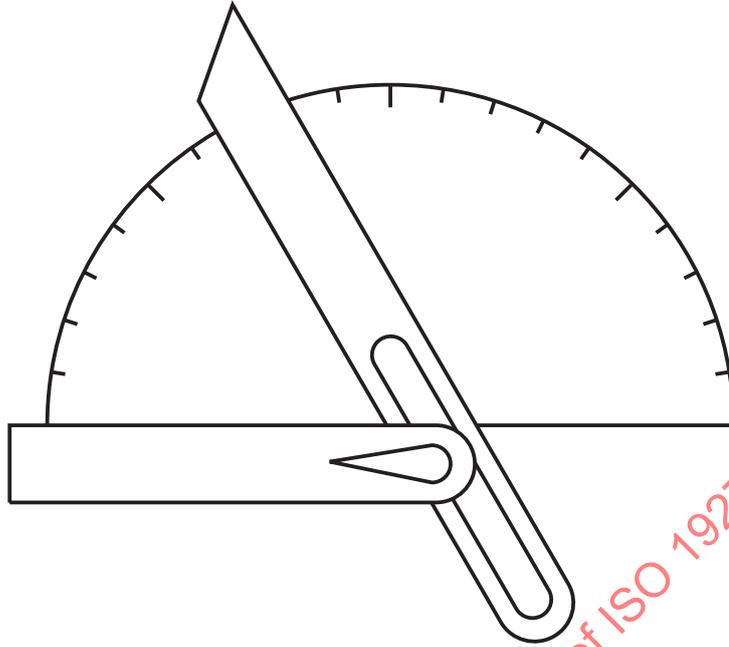


Figure 7 — Measurement of the angle

6.4 Measurement of warpage

For a concave surface, place the straightedge on edge across a diagonal of the surface being tested, insert a wedge at the point of maximum warpage (ensuring that the reading is not affected by raised imperfections on the castable surface) and record the maximum obtainable reading to the nearest 0,5 mm at the point of contact between the wedge and the straightedge.

For a convex surface, insert a wedge at each end of the straightedge and perpendicular to it as shown in Figure 8. Adjust the wedges, to a position not more than 15 mm from the corner of the shape, so that equal readings are obtained from each of them, making certain that contact is maintained by the straightedge at the point of maximum convexity. Record the readings to the nearest 0,5 mm.

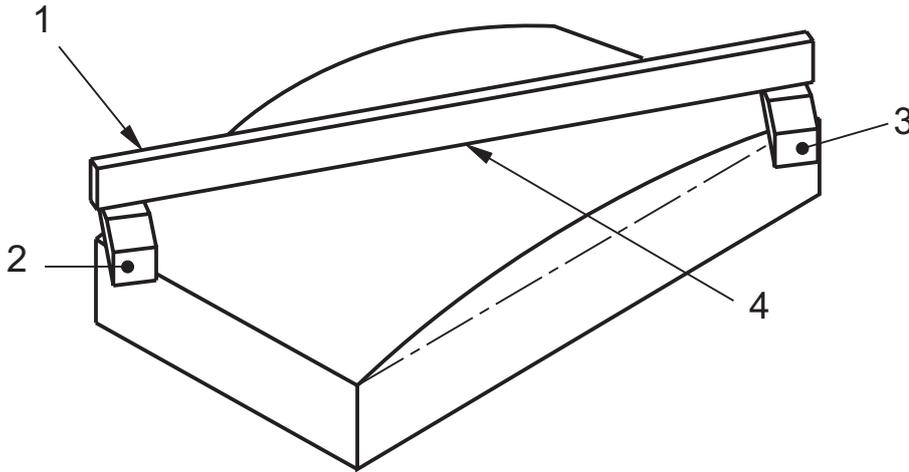

Key

- 1 Straight edge
- 2 Wedge
- 3 Wedge
- 4 Contact maintained at highest point of profile

Figure 8 — Measurement of convex warpage

Calculate the warpage ratio, W in percent, using the equation:


$$W = \frac{h}{l} \times 100$$

where


- l is the length of the diagonal of the surface being tested, in millimetres;
- h is the reading of the amount of warpage, in millimetres.

6.5 Measurement of corner defects


Measure the dimensions a , b and c of a corner defect using a steel straightedge, a breakage defect sizer and a steel tape, as indicated in Figure 9. The breakage defect sizer shall be positioned along the edge to be measured in such a way that the leading edge of the slot coincides with the broken corner on at least one surface of the shape, as shown in Figure 10. The dimensions a , b , and c are measured between the steel straightedge and the leading edge of the breakage defect sizer, to the nearest millimetre.

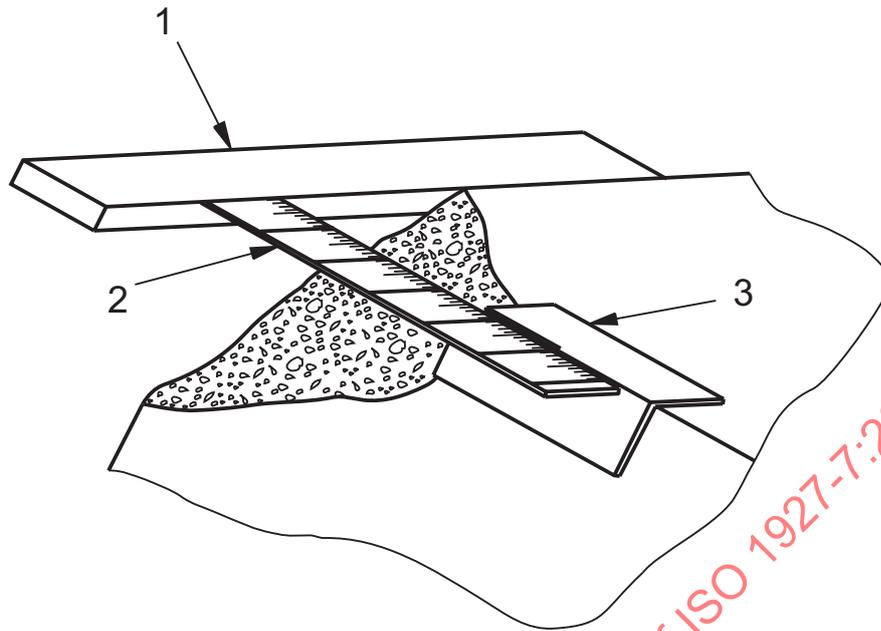**Key**

- | | |
|---|-----------------------|
| 1 | Steel straightedge |
| 2 | Steel tape |
| 3 | Breakage defect sizer |

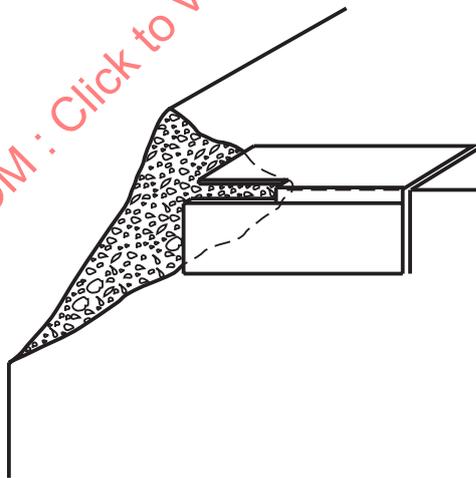Figure 9 — Measurement of a corner defect**Figure 10 — Positioning the breakage defect sizer****6.6 Measurement of edge defects**

Measure the length, g , of an edge defect using two breakage defect sizers and a steel tape, as indicated in Figure 11. Measure the depth of the edge defect as defined by e and f using a steel straightedge and a steel tape. Measure all dimensions to the nearest millimetre.

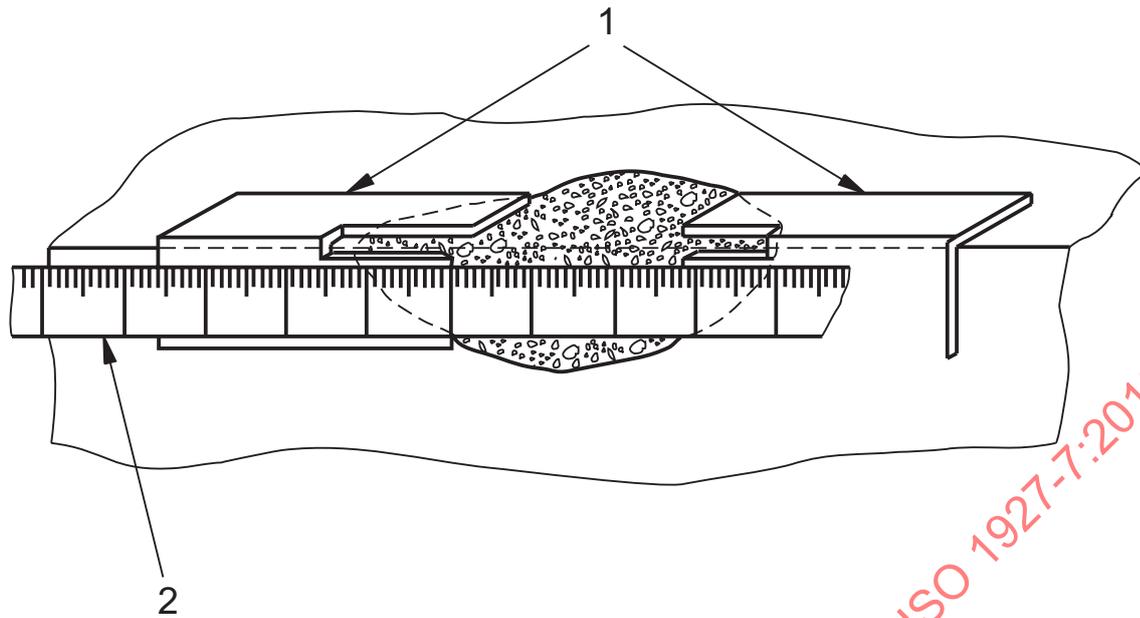

Key

- 1 Breakage defect sizers
- 2 Steel tape

Figure 11 — Measurement of the length of an edge defect

6.7 Measurement of craters and bubbles


Measure the maximum and minimum diameter of a crater using a steel tape as indicated in Figure 12. The apparent crater diameter, d_a , is given by the equation:

$$d_a = \frac{D + d}{2}$$

where

- D is the maximum diameter of the crater, in mm;
- d is the minimum diameter of the crater, in mm.

Measure the depth, h in mm, of a crater using a depth gauge as indicated in Figure 12.

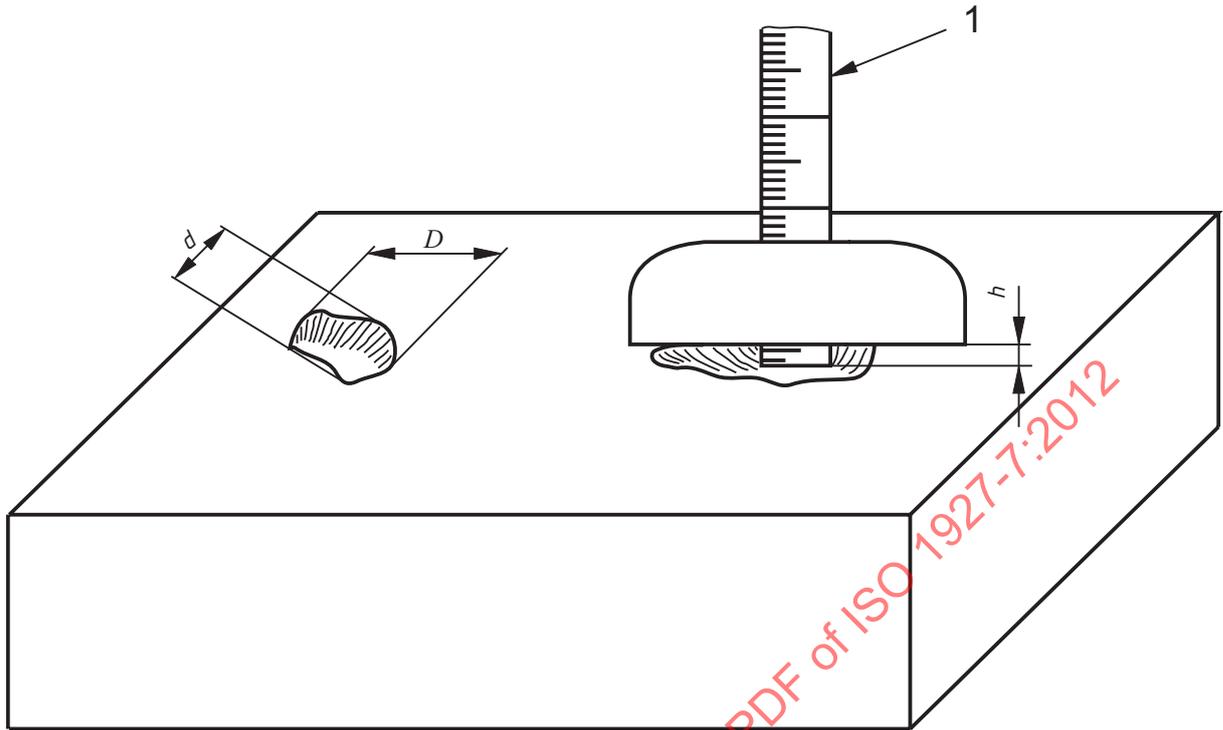**Key**

- 1 depth gauge \varnothing 3 mm
 D maximum diameter of a crater
 d minimum diameter of a crater
 h depth of a crater

Figure 12 — Measurement of craters and bubbles

6.8 Measurement of cracks

Measure the maximum visible width of a crack with a steel tape in one or more straight lines. If the crack continues on more than one surface, then the crack length is equal to the sum of the crack lengths on each surface.

Measure the width of a crack either with a graticule or with feeler gauges (see 5.4).

Table 1 — Accuracy of measurement


Measurement	Accuracy of measurement
Length of crack	1 mm
Width of open crack: between 0,2 mm and 1 mm	0,2 mm
Width of open crack: greater than 1 mm	0,5 mm

Measure the dimensions of cracks to the accuracy given in Table 1. Surface crazing (see 3.5) shall be measured using a steel tape and reported in cm^2 .

6.9 Measurement of protrusions and indentations

Measure the height of a protrusion from the surface of the shape by means of a straightedge (see 5.2) and measuring wedges (see 5.3), to the nearest 0,5 mm. Place the straightedge parallel to the surface and in contact with the protrusion and adjust the measuring wedges so that equal readings are obtained

on each of them, as indicated in Figure 13. Measure indentations using the same method as used for craters (see 6.7).

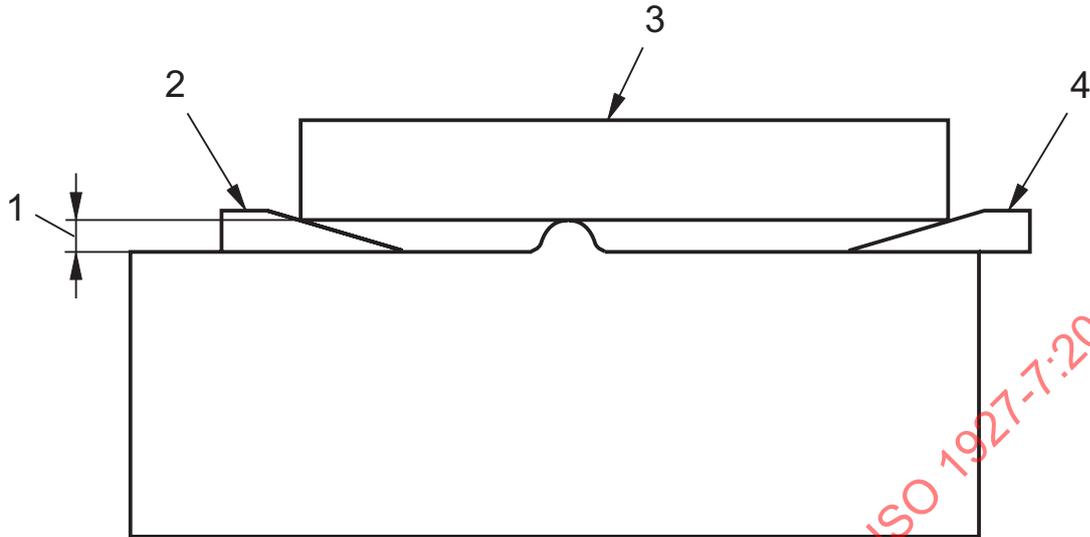

Key

1	Height
2	Measuring wedge
3	Straightedge
4	Measuring wedge

Figure 13 — Measurement of the height of a protrusion

6.10 Measurement of fins

Measure the height of fins to the nearest millimetre by the depth gauge or steel tape.

6.11 Segregations

Measure the extent of the honeycombed structure using a linear measuring device. Measure dimensions to the nearest millimetre.

NOTE If possible, the extent of fines segregation should be measured using a linear measuring device.

6.12 Friability

For dense castables, measure the extent to which areas of a block can be rubbed away using hand pressure.

7 Inspection by variables

7.1 Destructive test methods

7.1.1 General

The position in the shape from where test pieces will be taken shall be agreed between the parties involved and noted in the final report. If agreement cannot be reached, the reference for the location of the sample will be the centre of the shape. If a wet cutting method has been used to obtain a test piece from a pre-formed shape, it shall be dried immediately following preparation.

7.1.2 Physical properties

Wherever possible, the dimensions and testing of test pieces cut from pre-formed shapes shall be in accordance with ISO 1927-6. If this is not feasible, for example, if test pieces have to be cored or are of non standard dimensions, the test data will vary due to different test piece geometry.

NOTE The results obtained on testing a pre-formed shape will not equate to those obtained from a laboratory prepared test piece prepared according to ISO 1927-5..

7.1.3 Moisture content (see NOTE 2 of 7.1.4)

Weigh the shape or test piece on an appropriate sized balance to the nearest 1 %, and dry it in a drying oven at $110\text{ °C} \pm 5\text{ °C}$ to constant mass.

Calculate the loss in mass, M , as a percentage of the original mass using the equation:

$$M = \frac{m_1 - m_2}{m_1} \cdot 100$$

where

M is the moisture content, as a percentage;

m_1 is the original mass in kilograms;

m_2 is the dried mass in kilograms.

7.1.4 Loss on ignition

Dry the shape or test piece at $110\text{ °C} \pm 5\text{ °C}$ until constant mass. Allow to cool to ambient temperature and weigh to the nearest 1 %, recording the mass as m_3 . Fire at $1\ 050\text{ °C} \pm 25\text{ °C}$ until constant mass. Allow to cool and weigh to the nearest 1 %, recording the mass as m_4 .

Calculate the loss on ignition, L_1 , as a percentage of the final mass using the following equation:

$$L_1 = \frac{m_3 - m_4}{m_3} \cdot 100$$

where

L_1 is the loss on ignition, as a percentage;

m_3 is the mass after drying in kilograms;

m_4 is the final mass in kilograms.

NOTE 1 An intermediate temperature can be assigned for determining the loss on ignition. This temperature should be agreed between the parties involved prior to testing and noted in the final report.

NOTE 2 If it is not possible to determine the moisture content or the loss on ignition on a full shape then a test piece should be obtained without using wet cutting methods, for example by breaking the shape to obtain a representative test piece.

7.2 Non-destructive test methods

7.2.1 Ultrasonic testing

7.2.1.1 General

Ultrasonic testing techniques do not give commonly accepted physical properties, but are used to determine an overall quality level. The methods employed are applied to pre-dried and cooled shapes at ambient temperature.

7.2.1.2 Principle

Propagation of ultrasonic waves through a test piece and determining their velocity.


NOTE Shapes with special geometry (e.g. tubes, plates) or with irregular geometry can give spurious results. In such cases the reliability of the measurement should be checked by preliminary testing. Wherever possible, the contact surface should be greater than the area of the sensor.

7.2.1.3 Testing equipment (see Figure 14)

7.2.1.3.1 Two identical low frequency sensors, (between 40 kHz and 100 kHz) with low damping rate. One sensor shall be the emitter and the other sensor shall be the receiver.

7.2.1.3.2 A suitable contact system as a couplant between the sensors and the test pieces, e.g. silicone grease and/or rubber disks.

If possible, use a clamping device to maintain the sensors in contact with the test piece.

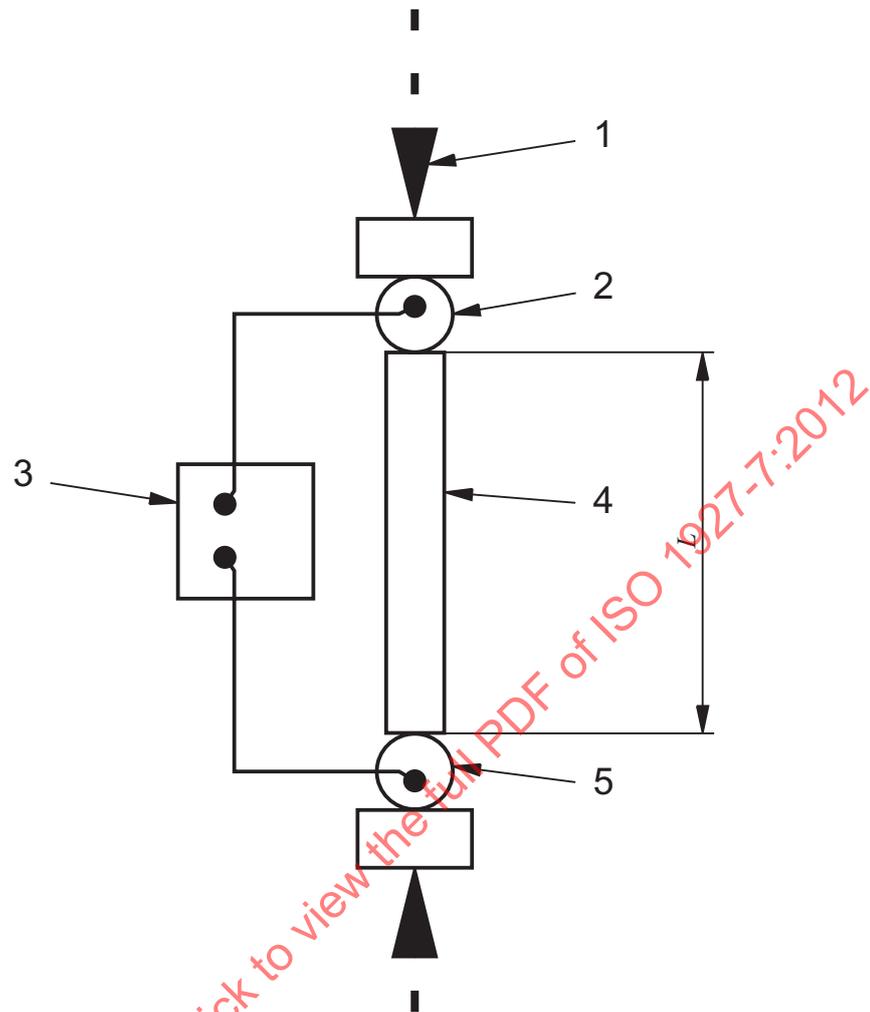**Key**

- 1 System for moderate contact force
- 2 Transmitting transducer
- 3 Pulse transit timer
- 4 Test piece
- 5 Receiving transducer
- L Dimension along which the ultrasonic waves will be transmitted

Figure 14 — Block diagram of a suitable ultrasonic pulse velocity apparatus

7.2.1.4 Procedure

Measure, to within 0,5 mm, the dimension (L) along which the ultrasonic waves will be transmitted.

Calibrate the measuring apparatus with the calibration bar supplied by the manufacturer, or with an appropriate reference material, using the sensor couplant which will be used for the test.

Set the test piece between the sensors with the appropriate couplant in place.

Maintain the sensors in contact with the test piece at the points of measurement by hand pressure or using an appropriate device. Note the displayed propagation time. Repeat the test to check reproducibility. Recalibrate the apparatus when starting, every 50 measurements or when changing operators.

NOTE The number and direction of individual measurements on the test piece will depend on the test piece geometry.

7.2.1.5 Calculation

Calculate the ultrasonic propagation velocity, V in m/s, using the equation:

$$V = \frac{L}{t}$$

where

L is the dimension along the line of propagation in metres;

t is the propagation time in seconds.

7.2.1.6 Test report

The test report shall include the following information:

- a) the reference of the ultrasonic measurement apparatus and its characteristics;
- b) the reference and characteristics of the sensors;
- c) the type of contact system;
- d) individual and mean values of propagation velocity for each measurement direction.

7.2.2 Determination of the resonant frequency by mechanical shock

7.2.2.1 Principle

Excitation of a prismatic shape with an aspect ratio greater than 3 by mechanical shock and determination of its bending fundamental resonant frequency.

7.2.2.2 Testing equipment (see Figure 15)

7.2.2.2.1 Sensor, for the detection of the resonant frequency by contact (piezo electric pen) or without contact (microphone).

7.2.2.2.2 Impact hammer, (for example, a light hammer or screwdriver which has to be appropriate for the size and the hardness of the test piece).

7.2.2.2.3 Test piece support made from acoustically insulating material (for example, a layer of polyurethane foam, rubber prisms, or cylinders).

7.2.2.2.4 Acoustic insulating support, either a blanket of polyurethane foam, or two rubber bars with triangular or circular cross-section set at a distance from the shape extremities equal to 0,224 multiplied by the length of the test piece.

To obtain reproducible results, the impact and signal receiving points shall be accurately determined.