
**Timber structures — Glued laminated
timber — Face and edge joint cleavage
test**

*Structures en bois — Bois lamellé-collé — Essai de fendage des joints
face à face et longitudinaux*

STANDARDSISO.COM : Click to view the full PDF of ISO 19993:2007



PDF disclaimer

This PDF file may contain embedded typefaces. In accordance with Adobe's licensing policy, this file may be printed or viewed but shall not be edited unless the typefaces which are embedded are licensed to and installed on the computer performing the editing. In downloading this file, parties accept therein the responsibility of not infringing Adobe's licensing policy. The ISO Central Secretariat accepts no liability in this area.

Adobe is a trademark of Adobe Systems Incorporated.

Details of the software products used to create this PDF file can be found in the General Info relative to the file; the PDF-creation parameters were optimized for printing. Every care has been taken to ensure that the file is suitable for use by ISO member bodies. In the unlikely event that a problem relating to it is found, please inform the Central Secretariat at the address given below.

STANDARDSISO.COM : Click to view the full PDF of ISO 19993:2007



COPYRIGHT PROTECTED DOCUMENT

© ISO 2007

All rights reserved. Unless otherwise specified, no part of this publication may be reproduced or utilized in any form or by any means, electronic or mechanical, including photocopying and microfilm, without permission in writing from either ISO at the address below or ISO's member body in the country of the requester.

ISO copyright office
Case postale 56 • CH-1211 Geneva 20
Tel. + 41 22 749 01 11
Fax + 41 22 749 09 47
E-mail copyright@iso.org
Web www.iso.org

Published in Switzerland

Contents

	Page
1 Scope	1
2 Terms and definitions	1
3 Principle	1
4 Apparatus	1
5 Preparation of test pieces	2
6 Procedure	3
7 Test report	4
Bibliography	5

STANDARDSISO.COM : Click to view the full PDF of ISO 19993:2007

Foreword

ISO (the International Organization for Standardization) is a worldwide federation of national standards bodies (ISO member bodies). The work of preparing International Standards is normally carried out through ISO technical committees. Each member body interested in a subject for which a technical committee has been established has the right to be represented on that committee. International organizations, governmental and non-governmental, in liaison with ISO, also take part in the work. ISO collaborates closely with the International Electrotechnical Commission (IEC) on all matters of electrotechnical standardization.

International Standards are drafted in accordance with the rules given in the ISO/IEC Directives, Part 2.

The main task of technical committees is to prepare International Standards. Draft International Standards adopted by the technical committees are circulated to the member bodies for voting. Publication as an International Standard requires approval by at least 75 % of the member bodies casting a vote.

Attention is drawn to the possibility that some of the elements of this document may be the subject of patent rights. ISO shall not be held responsible for identifying any or all such patent rights.

ISO 19993 was prepared by Technical Committee ISO/TC 165, *Timber structures*.

STANDARDSISO.COM : Click to view the full PDF of ISO 19993:2007

Introduction

This International Standard was developed by TC 165 as a factory quality-assurance test used for structural glulam and applies to the face joints of each production batch. The frequency of testing and the pass/fail criteria are detailed in ISO 12578¹⁾. However, there is nothing in principle that prevents the test method from being applied to non-structural glulam.

Dry specimens are tested under ambient conditions and wet specimens are tested under ambient conditions after a vacuum-pressure soak.

STANDARDSISO.COM : Click to view the full PDF of ISO 19993:2007

1) To be published.

STANDARDSISO.COM : Click to view the full PDF of ISO 19993:2007

Timber structures — Glued laminated timber — Face and edge joint cleavage test

1 Scope

This International Standard specifies methods of evaluating the effectiveness of glued, laminated timber-face and edge bonds within a manufacturing plant by cleaving of the glue line in both dry and wet conditions.

2 Terms and definitions

For the purposes of this document, the following terms and definitions apply.

2.1

wood failure

area of wood fibre remaining on the bond line following completion of the cleavage test expressed as a percentage of the total test area excluding any areas of wood defect (gum vein and similar)

2.2

cleavage

rupture parallel to the wood grain of a glulam face joint bond line or the adjacent adherend by the application of normal stress

3 Principle

A specimen consisting of a full cross-section of laminated timber is cleaved apart along the plane bond lines and wood failure is assessed after wet or dry conditioning.

4 Apparatus

4.1 Chisel, with a wedge angle and thickness such that the tip of the blade does not touch the bottom of the saw cut of the test specimen before cleavage failure begins to occur.

The width of the chisel shall exceed that of the specimen.

NOTE A bricklayer's bolster is a suitable implement.

4.2 Hammer or mallet, with a minimum mass 1 kg.


4.3 Wood cutting equipment, such as a panel saw, band saw or circular saw.

4.4 Autoclave or similar vessel, designed to withstand safely a pressure of at least 500 kPa, equipped with a vacuum pump capable of drawing a vacuum of at least 65 kPa (500 mm of mercury) in the vessel and a pump or other device to provide a pressure of at least 500 kPa.

5 Preparation of test pieces

A member for testing shall be manufactured to a slightly longer length than specified to allow for the removal of a representative specimen or specimens at the end of the member. The specimen(s) shall be removed from the off-cut portion at the end of the member after trimming to length. Each specimen shall be marked to identify the member from which it is cut.

The specimens shall include the full cross-section of the laminated timber to be tested, perpendicular to the grain of the wood and 25 mm long measured along the grain. Each bond line of the specimen shall be cut uniformly the full width of the specimen to a depth of 10 mm from one cross-cut face. For convenience, the specimen may be divided into smaller parts, provided the cuts are perpendicular to or well away from the bond lines, and that all parts are tested (see Figure 1).

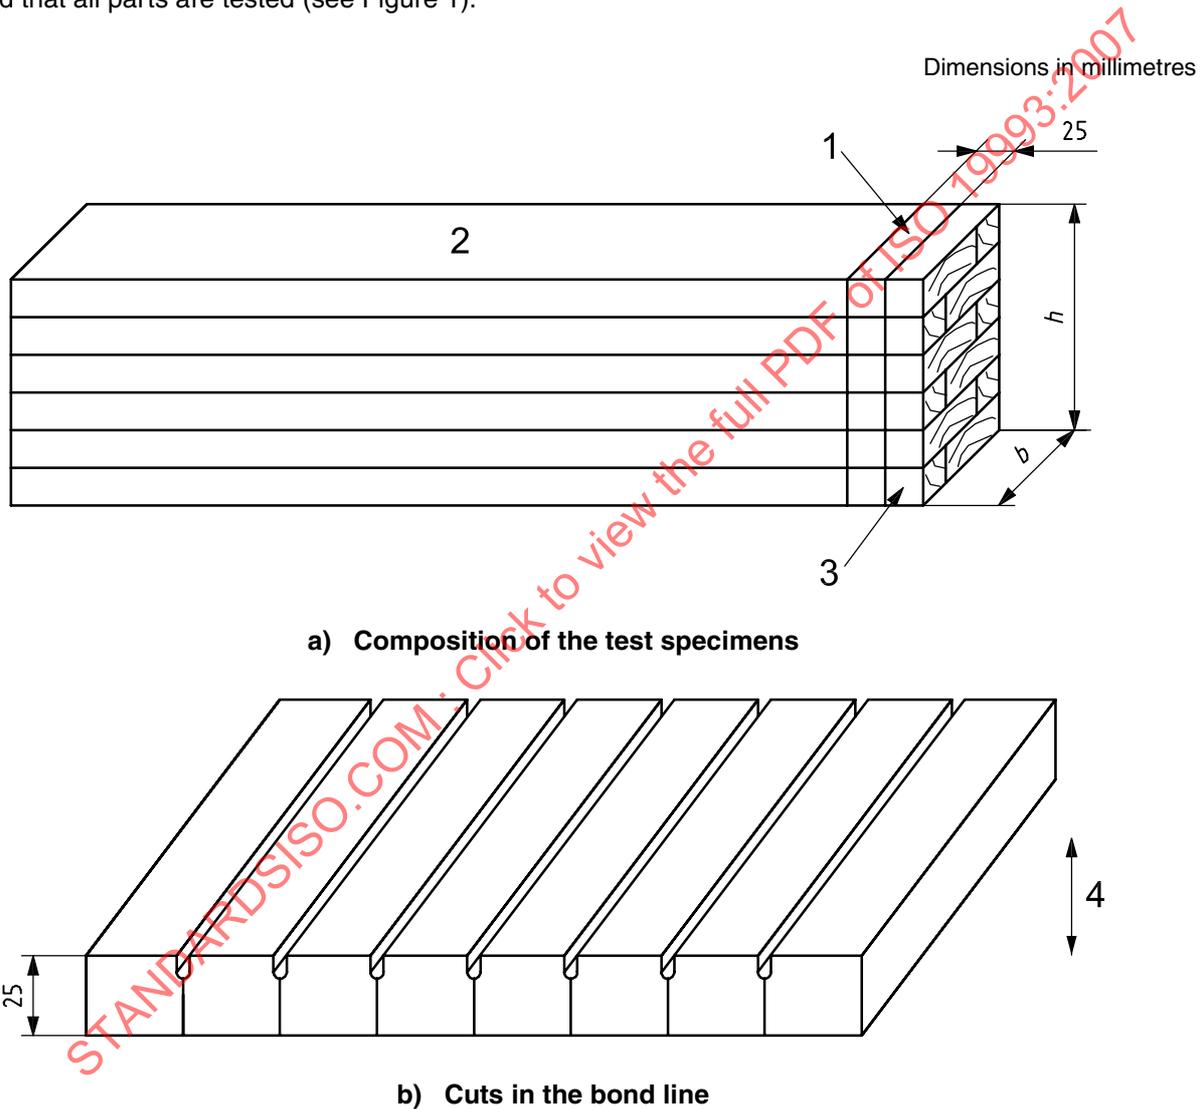

Key

- 1 test specimen
- 2 member
- 3 waste
- 4 grain direction

Figure 1 — Details of test specimen

6 Procedure

6.1 General

Apart from the conditioning, the dry and wet cleavages involve identical procedures.

6.2 Conditioning for wet cleavage

The conditioning shall be undertaken as follows.

- a) The test specimens shall be placed in the autoclave and fully immersed in water between 10 °C and 27 °C. The specimens shall be restrained so that they remain fully immersed throughout the conditioning period. The specimens shall be supported in such a manner that all end grain surfaces are exposed to the water.
- b) A vacuum of at least 65 kPa shall be drawn and held for 1,5 h, then the vacuum shall be released and pressure of 500 ± 30 kPa applied for 1,5 h. The vacuum-pressure cycle shall be repeated once more.


NOTE For higher-density species, longer pressure and vacuum cycles can be required to achieve total water penetration.

6.3 Cleaving and assessment

The following procedure shall be followed with respect to cleaving and wood failure assessment.

- a) Each bond line shall be cleaved by means of the chisel and hammer, ensuring that the tip of the chisel does not touch the bottom of the saw kerf prior to the onset of cleavage; see Figure 2.
- b) The wood failure percentage of each bond line shall be assessed to the nearest 5 %.
- c) The average wood failure percentage of all bond lines in the cross-section shall be determined from the wood failure percentage of the individual bond lines of test specimen.

NOTE Light at an oblique angle such as from a fluorescent desk lamp has been found beneficial in the assessment of wood failure.

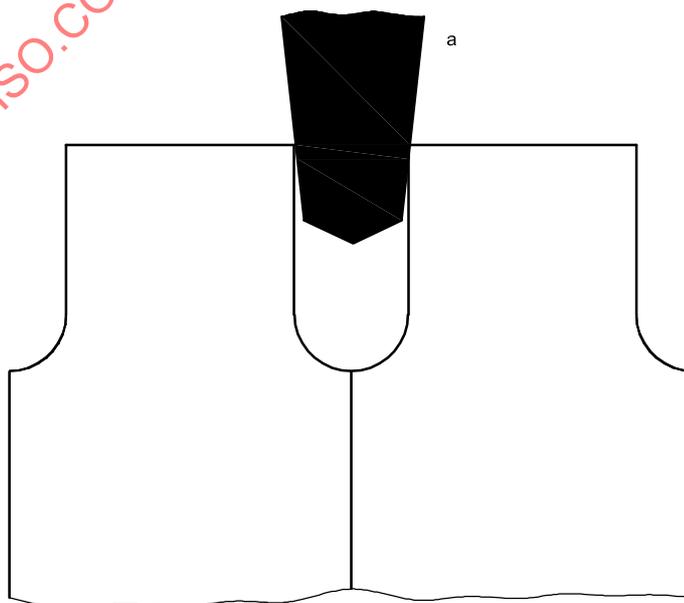

^a Chisel shall not touch bottom of saw kerf prior to onset of cleavage failure.

Figure 2 — Details of saw kerf and chisel tip