

---

---

**Method for evaluation of tensile  
properties of metallic superplastic  
materials**

*Méthode de détermination des caractéristiques de traction des  
matériaux métalliques superplastiques*

STANDARDSISO.COM : Click to view the full PDF of ISO 20032:2007



**PDF disclaimer**

This PDF file may contain embedded typefaces. In accordance with Adobe's licensing policy, this file may be printed or viewed but shall not be edited unless the typefaces which are embedded are licensed to and installed on the computer performing the editing. In downloading this file, parties accept therein the responsibility of not infringing Adobe's licensing policy. The ISO Central Secretariat accepts no liability in this area.

Adobe is a trademark of Adobe Systems Incorporated.

Details of the software products used to create this PDF file can be found in the General Info relative to the file; the PDF-creation parameters were optimized for printing. Every care has been taken to ensure that the file is suitable for use by ISO member bodies. In the unlikely event that a problem relating to it is found, please inform the Central Secretariat at the address given below.

STANDARDSISO.COM : Click to view the full PDF of ISO 20032:2007

© ISO 2007

All rights reserved. Unless otherwise specified, no part of this publication may be reproduced or utilized in any form or by any means, electronic or mechanical, including photocopying and microfilm, without permission in writing from either ISO at the address below or ISO's member body in the country of the requester.

ISO copyright office  
Case postale 56 • CH-1211 Geneva 20  
Tel. + 41 22 749 01 11  
Fax + 41 22 749 09 47  
E-mail [copyright@iso.org](mailto:copyright@iso.org)  
Web [www.iso.org](http://www.iso.org)

Published in Switzerland

**Contents**

Page

Foreword.....	iv
Introduction .....	v
1 <b>Scope</b> .....	1
2 <b>Normative references</b> .....	1
3 <b>Symbols, terms and definitions</b> .....	1
4 <b>Principle</b> .....	3
5 <b>Test piece</b> .....	4
6 <b>Apparatus</b> .....	5
7 <b>Procedure</b> .....	6
8 <b>Test report</b> .....	10

STANDARDSISO.COM : Click to view the full PDF of ISO 20032:2007

## Foreword

ISO (the International Organization for Standardization) is a worldwide federation of national standards bodies (ISO member bodies). The work of preparing International Standards is normally carried out through ISO technical committees. Each member body interested in a subject for which a technical committee has been established has the right to be represented on that committee. International organizations, governmental and non-governmental, in liaison with ISO, also take part in the work. ISO collaborates closely with the International Electrotechnical Commission (IEC) on all matters of electrotechnical standardization.

International Standards are drafted in accordance with the rules given in the ISO/IEC Directives, Part 2.

The main task of technical committees is to prepare International Standards. Draft International Standards adopted by the technical committees are circulated to the member bodies for voting. Publication as an International Standard requires approval by at least 75 % of the member bodies casting a vote.

Attention is drawn to the possibility that some of the elements of this document may be the subject of patent rights. ISO shall not be held responsible for identifying any or all such patent rights.

ISO 20032 was prepared by Technical Committee ISO/TC 164, *Mechanical testing of metals*, Subcommittee SC 2, *Ductility testing*.

STANDARDSISO.COM : Click to view the full PDF of ISO 20032:2007

## Introduction

Superplastic forming requires the characterization of metallic superplastic materials. The tensile test specified in this International Standard permits the evaluation of superplastic properties, such as superplastic elongation, flow stress, strain-rate sensitivity exponent ( $m$ -value), stress-strain relation and flow stress-strain-rate relation.

STANDARDSISO.COM : Click to view the full PDF of ISO 20032:2007



# Method for evaluation of tensile properties of metallic superplastic materials

## 1 Scope

This International Standard specifies a method for evaluating the tensile properties of metallic superplastic materials which exhibit fine-grained superplasticity, without significant work-hardening or dynamic microstructure evolution, by means of a tensile test at constant cross-head velocity, for flat-form test pieces, without an extensometer attached.

## 2 Normative references

The following referenced documents are indispensable for the application of this document. For dated references, only the edition cited applies. For undated references, the latest edition of the referenced document (including any amendments) applies.

ISO 31-0, *Quantities and units — Part 0: General principles*

ISO 783, *Metallic materials — Tensile testing at elevated temperature*

ISO 6892, *Metallic materials — Tensile testing at ambient temperature*

ISO 7500-1, *Metallic materials — Verification of static uniaxial testing machines — Part 1: Tension/compression testing machines — Verification and calibration of the force-measuring system*

IEC 60584-1, *Thermocouples — Part 1: Reference tables*

IEC 60584-2, *Thermocouples — Part 2: Tolerances*

## 3 Symbols, terms and definitions

For the purposes of this document, the symbols, terms and definitions given in Table 1 apply.

Table 1 — Symbols, terms and definitions

Symbol	Term	Definition	Unit
<b>Superplasticity</b>			
—	Superplastic state	Deformation conditions on onset of superplasticity and its continuation	—
<b>Test piece</b>			
—	R-type test piece	Test piece that has the shape of a conventional tensile test piece without its parallel portion	—
—	R portion	Principal portion of the R-type test piece to be elongated, which has an arc-like shape between grips	—
$b$	Width of parallel-sided portion or minimum width of the R portion	Original width of parallel-sided portion of the S-type test piece or original minimum width of the R portion of the R-type test piece	mm
$b_0[i]$	Original width in division, $i$ , of the R portion	Original width in a specific division, $i$ , of the R portion	mm
$b[i]$	Width in division, $i$ , of the R portion	Width in a specific division, $i$ , of the R portion after the interrupted test	mm
$A$	Superplastic elongation	Elongation at fracture in a superplastic state	%
$B_g$	Grip portion width	Width of grip portion of the S- or R-type test piece	mm
$L_0$	Original gauge length	Original distance between gauge marks measured by appropriate apparatus with an accuracy of at least 1 % of the distance or 0,01 mm, whichever is greater	mm
$L_u$	Final gauge length after fracture	Final distance between gauge marks measured after fracture with fracture surfaces placed together with care, so that the centre line of either fracture surface is on a single straight line	mm
$L_c$	Parallel length	Original length of parallel portion of the S-type test piece	mm
$L_t$	Total length of test piece	Original total length of test piece	mm
$L_g$	Grip portion length	Length of grip portion of test piece	mm
$L_R$	R portion length	Original length of the R portion	mm
$\Delta L_R$	Elongation of the R portion	Increase in the R portion length at any moment during the test	mm
$R$	Radius of fillet or R portion radius	Original radius of fillet of the S-type test pieces or original R portion radius of the R-type test piece	mm
$S_0$	Original cross-sectional area of test piece in the reduced section	Original cross-sectional area of a test piece measured by an appropriate apparatus with an accuracy not more than 2 %	mm <sup>2</sup>
$S_0[i]$	Original cross-sectional area in division, $i$ , of the R portion	Original cross-sectional area in a specific division, $i$ , of the R portion	mm <sup>2</sup>
$S[i]$	Cross-sectional area in division, $i$ , of the R portion	Cross-sectional area in a specific division, $i$ , of the R portion after the interrupted test	mm <sup>2</sup>
$t$	Thickness of test piece	Thickness of the S- or R-type test piece	mm
$t_0[i]$	Original thickness in division, $i$ , of the R portion	Original thickness in a specific division, $i$ , of the R portion	mm
$t[i]$	Thickness in division, $i$ , of the R portion	Thickness in a specific division, $i$ , of the R portion after the interrupted test	mm

Table 1 (continued)

Symbol	Term	Definition	Unit
<b>Force</b>			
$F_{10}$	10 % deformation force	Force at 10 % nominal strain	N
<b>Stress</b>			
$K$	$K$ value	A constant-with-stress dimension, which is defined by Equation (1)	MPa
$\sigma_{10}$	10 % flow stress	True stress when 10 % nominal strain is achieved	MPa
$\sigma_f$	Flow stress	True stress during superplastic deformation	MPa
$\sigma_N$	Nominal stress	A load during deformation divided by the minimum area of the original cross-section in the R portion, which is defined for the R-type test piece	MPa
$\sigma[i]$	True stress	A load during deformation divided by the cross-sectional area in a specific division, $i$ , of the R portion, which is defined for the R-type test piece	MPa
<b>Strain</b>			
$\varepsilon[i]$	True strain	True strain given by deformation in a specific division, $i$ , of the R portion	$s^{-1}$
<b>Period</b>			
$\tau_{inter}$	Period required for interrupted test	Period required from the time when the axial force starts to increase linearly against strain in the elastic deformation stage, until elongation of the R portion, $\Delta L_R$ , reaches 3 mm	s
<b>Strain rate and <math>m</math>-value</b>			
$\dot{\varepsilon}_N$	Nominal strain rate	Crosshead velocity divided by the original parallel length, $L_c$ for the S-type test piece, and divided by the original gauge length, $L_0$ for the R-type test piece	$s^{-1}$
$\dot{\varepsilon}$	True strain rate	Increment of true strain per unit time	$s^{-1}$
$\dot{\varepsilon}[i]$	True strain rate during deformation	True strain rate during deformation in a specific division, $i$ , of the R portion	$s^{-1}$
$m$	$m$ -value	Index representing the strain-rate sensitivity of flow stress in superplastic materials	—

#### 4 Principle

The test consists of straining a test piece by a tensile force, for the purpose of determining the superplastic properties, such as superplastic elongation ( $A$ ), flow stress and strain-rate sensitivity exponent ( $m$ -value).

The tensile testing is carried out at elevated temperatures and strain rates.

An S-type test piece is employed to evaluate mechanical properties for general superplastic materials, or at an early stage of deformation.

Due to the limitation of furnace length, S-type test pieces are more suitable for lower-strain superplastic testing. R-type test pieces are more suitable for higher-strain superplastic testing, as most of the strain is developed in a small section at the centre of the specimen.

### 5 Test piece

The shape and dimensions are given in Figures 1 and 2, and Tables 2 and 3, respectively. The thickness of a test piece shall be the same as the sheet thickness of the material. The dimensional tolerance of a test piece shall be in accordance with ISO 6892.

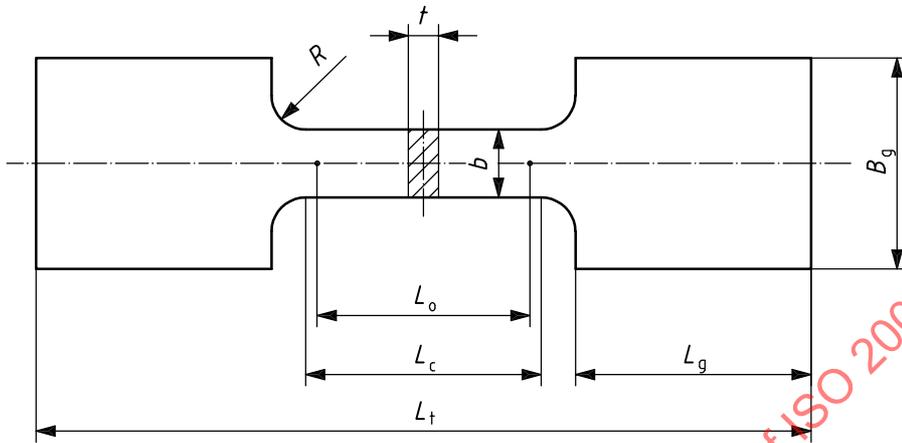


Figure 1 — Shape of flat form test piece (S-type)

Table 2 — Dimensions of S-type test piece

Dimensions in millimetres

Gauge length	Parallel length	Width of parallel-sided portion	Radius of fillet
$L_o$	$L_c$	$b$	$R$
18	24	6	Not more than 3

The recommended value should be as follows:

$$L_t = 2L_g + L_c + 2R \tag{1}$$

$$B_g = 3b \tag{2}$$

The thickness of the test piece is the same as that of the material to be used.

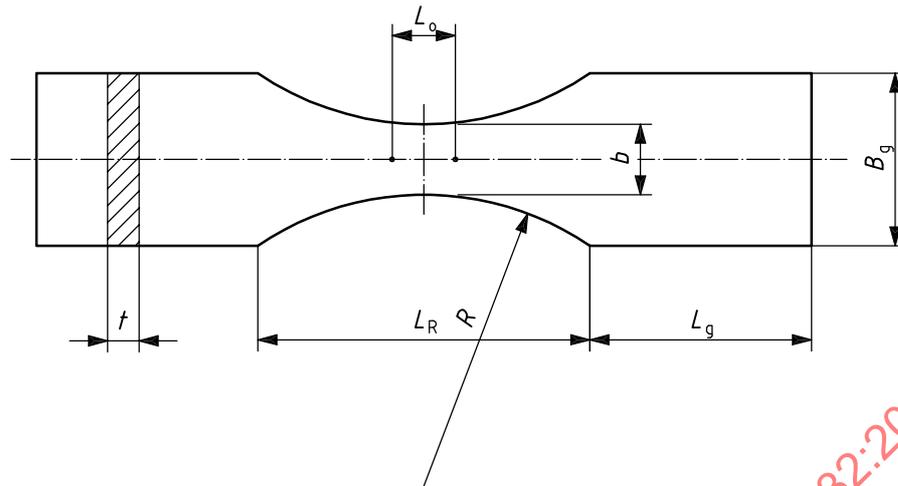


Figure 2 — Shape of R-type test piece

Table 3 — Dimensions of R-type test piece

Dimensions in millimetres

Grip portion width	Minimum width of the R portion	R portion length	R portion radius	Gauge length
$B_g$	$b$	$L_R$	$R$	$L_o$
16	6	30	25	6
$L_g$ should not be less than 20 mm.				

The thickness of the test piece is the same as that of the material to be used.

## 6 Apparatus

### 6.1 Testing machine

The testing machine used shall conform to ISO 7500-1. The machine used shall satisfy the condition of constant cross-head velocity. The appropriate class of machine range shall be selected under the agreement between interested parties.

### 6.2 Clamping device for test pieces

The clamping device shall not be plastically deformed during an elevated temperature test. A recommended method is described in 7.2.

**6.3 Heating apparatus**

A furnace with a temperature-regulator shall be used for heating the test pieces. During a test, the furnace shall be capable of keeping the test piece temperature over the gauge length uniform and constant within the allowable range of Table 4.

**Table 4 — Allowable range of test temperatures**

Temperatures in kelvins

Test temperature	≤ 473	> 473 ≤ 873	> 873 ≤ 1 073	> 1 073 ≤ 1 273	> 1 273
Allowable range	Agreed by interested parties	± 3	± 4	± 5	Agreed by interested parties

**6.4 Atmosphere**

The measurement of the test piece dimensions, especially distances between gauge marks or divisions after the test, shall be enabled and the damage of the device shall be avoided in the environment used. If the test is performed in a controlled atmosphere, the measured force should be corrected by compensating the pressure difference.

**6.5 Thermometric apparatus**

**6.5.1 General**

The thermometric apparatus consists of a measuring device and a thermocouple.

**6.5.2 Measuring device**

The measuring device shall be capable of measuring the temperature of the test piece within the allowable range given in Table 4, over the entire range of the temperature to be measured.

**6.5.3 Thermocouple**

The thermocouple shall basically conform to IEC 60584-1 and IEC 60584-2. Also, the materials used for the thermocouple shall be capable of withstanding the service temperature and environment.

When a temperature measurement instrument other than a thermocouple is used, it shall be as accurate as or more accurate than a thermocouple.

**7 Procedure**

**7.1 General**

Test procedures are described in 7.2 to 7.8. Additions that are not described in this clause shall be in accordance with ISO 6892 and ISO 783.

**7.2 Method for clamping the test piece**

The test piece shall be clamped so that only axial force is applied to the test piece during the test. No compressive or minimum tensile forces shall be applied to the clamped test piece during heating to the specified temperature and holding at this temperature before testing.

### 7.3 Measurement of the test temperature

The measurement of the test temperature shall be conducted by using thermocouples as defined in 6.5.3. The temperature to be measured should be that of the test piece. The test temperature to be measured shall be that of the atmosphere so that the measuring point of the thermocouple contacts the surface of the test piece for good heat-conduction, and that it is shielded from direct radiation of heat from the furnace. However, such measurement may be flexible if the correlative temperature between the surface of the test piece and a certain position in the furnace was initially evaluated.

For more precise temperature measurement, at least two thermocouples should be used at separate locations.

Interested parties shall agree on the time of heating the test piece to the test temperature and the holding time at the test temperature before starting the test, provided that such agreement shall be made with full assurance of uniform temperature distribution over the test piece.

The test temperature shall be maintained within the allowable range specified in Table 4 during the test.

### 7.4 Application of the force

The test shall be performed with a constant cross-head velocity.

### 7.5 Method for dimensional measurement of test pieces

The dimension of the gauge portion of the test piece shall be measured by adequate measuring equipment with a precision of at least 1 % of a specified dimension, or 0,01 mm, whichever is greater. Each end of the original gauge length shall be marked by means of fine marks or scribed lines, but not by notches which could cause premature fracture.

### 7.6 Method for determining the superplastic elongation

The gauge length prior to the test shall be 18 mm for the S-type, or 6 mm for the R-type test pieces.

The superplastic elongation shall be determined by the following equation. The value shall be rounded off to two significant figures in accordance with ISO 31-0.

$$A = \frac{L_u - L_o}{L_o} \times 100 \quad (3)$$

where

$A$  is the superplastic elongation (%);

$L_u$  is the final gauge length at fracture (mm);

$L_o$  is the original gauge length (mm).

For this purpose, carefully fit the broken pieces of the test piece back together so that their axes lie in a straight line.

### 7.7 Determination of flow stress and $m$ -value with the S-type test pieces

#### 7.7.1 Determination of flow stress

The force-elongation diagram in superplastic deformation shall be drawn by measuring changes in force against elongation during a test with adequate measuring equipment, provided that the force measured in a superplastic condition satisfies the precision of the load cell.

The 10 % flow stress shall be given by the following equation, where the force is at the 10 % nominal strain

$$\sigma_{10} = \frac{1,1F_{10}}{S_0} \quad (4)$$

where

$\sigma_{10}$  is the 10 % flow stress (MPa);

$F_{10}$  is the force at 10 % nominal strain (N);

$S_0$  is the original cross-sectional area of the test piece (mm<sup>2</sup>).

### 7.7.2 Determination of strain-rate sensitivity exponent (*m*-value)

At a given temperature and microstructure, the relation between flow stress,  $\sigma_f$  and strain rate,  $\dot{\epsilon}$ , during superplastic deformation is given in Equation (5). Strain hardening is not taken into account for the equation. This International Standard should be applied to the materials in which the strain-hardening effect can be neglected using Equation (5).

$$\sigma_f = K \dot{\epsilon}^m \quad (5)$$

Then, exponent *m* is expressed as in Equation (6).

$$m = \frac{d(\ln \sigma_f)}{d(\ln \dot{\epsilon})} \quad (6)$$

The *m*-value in Equation (6) can be obtained from the slope of the line in a double logarithmic plot of stress and strain rate. In general, the *m*-value depends on deformation conditions and materials in the range from 0 to 1, and a higher *m*-value leads to larger superplastic elongation.

Tests with five or more different cross-head velocities shall be conducted and the relationship between 10 % flow stress at each cross-head velocity and the corresponding nominal strain rate should be plotted on a log-log scale. Linear regression should be applied to this relationship by the method of least squares. Then round off the *m*-value, as the slope of a straight line, to the first decimal place in accordance with ISO 31-0. A minimum ductility of 300 % shall be achieved under conditions agreed between interested parties.

### 7.8 Determination of *m*-value with the R-type test piece

The strain-rate sensitivity exponent, *m*-value, shall be determined from the force and test-piece dimensions immediately before interruption as follows. The tensile test shall be interrupted when the elongation of the R portion reaches the specified values at two or more different cross-head velocities. The minimum and maximum cross-head velocities shall be selected in such a manner that the difference between them amounts to between twofold and tenfold. Furthermore, it is specified that the amount of elongation of the R portion shall be normally 3 mm ± 0,5 mm, that can be regarded as the elongation in the initial deformation. For each test, the true-stress  $\sigma[i]$  and true-strain rate  $\dot{\epsilon}[i]$  at each division of a scale (see Figure 4) shall be determined as described in a) to g).

- a) In the middle region of the R portion, five divisions shall be set at intervals of 3 mm in the tensile-axis direction. The test piece shall be placed with its tensile axis horizontal as shown in Figure 3. The division at the centre on the minimum cross-section of the R portion is named as division [0], those at the left side as divisions [-6] and [-3] and those at the right side as divisions [+3] and [+6].