

---

---

**Thermal-insulating materials —  
Determination of long-term water  
absorption by diffusion**

*Matériaux d'isolation thermique — Détermination de l'absorption d'eau à  
long terme par diffusion*

STANDARDSISO.COM : Click to view the full PDF of ISO 20393:2007



**PDF disclaimer**

This PDF file may contain embedded typefaces. In accordance with Adobe's licensing policy, this file may be printed or viewed but shall not be edited unless the typefaces which are embedded are licensed to and installed on the computer performing the editing. In downloading this file, parties accept therein the responsibility of not infringing Adobe's licensing policy. The ISO Central Secretariat accepts no liability in this area.

Adobe is a trademark of Adobe Systems Incorporated.

Details of the software products used to create this PDF file can be found in the General Info relative to the file; the PDF-creation parameters were optimized for printing. Every care has been taken to ensure that the file is suitable for use by ISO member bodies. In the unlikely event that a problem relating to it is found, please inform the Central Secretariat at the address given below.

STANDARDSISO.COM : Click to view the full PDF of ISO 20393:2007



**COPYRIGHT PROTECTED DOCUMENT**

© ISO 2007

All rights reserved. Unless otherwise specified, no part of this publication may be reproduced or utilized in any form or by any means, electronic or mechanical, including photocopying and microfilm, without permission in writing from either ISO at the address below or ISO's member body in the country of the requester.

ISO copyright office  
Case postale 56 • CH-1211 Geneva 20  
Tel. + 41 22 749 01 11  
Fax + 41 22 749 09 47  
E-mail [copyright@iso.org](mailto:copyright@iso.org)  
Web [www.iso.org](http://www.iso.org)

Published in Switzerland

## Foreword

ISO (the International Organization for Standardization) is a worldwide federation of national standards bodies (ISO member bodies). The work of preparing International Standards is normally carried out through ISO technical committees. Each member body interested in a subject for which a technical committee has been established has the right to be represented on that committee. International organizations, governmental and non-governmental, in liaison with ISO, also take part in the work. ISO collaborates closely with the International Electrotechnical Commission (IEC) on all matters of electrotechnical standardization.

International Standards are drafted in accordance with the rules given in the ISO/IEC Directives, Part 2.

The main task of technical committees is to prepare International Standards. Draft International Standards adopted by the technical committees are circulated to the member bodies for voting. Publication as an International Standard requires approval by at least 75 % of the member bodies casting a vote.

Attention is drawn to the possibility that some of the elements of this document may be the subject of patent rights. ISO shall not be held responsible for identifying any or all such patent rights.

ISO 20393 was prepared by Technical Committee ISO/TC 61, *Plastics*, Subcommittee SC 10, *Cellular plastics*.

STANDARDSISO.COM : Click to view the full PDF of ISO 20393:2007

[STANDARDSISO.COM](https://standardsiso.com) : Click to view the full PDF of ISO 20393:2007

# Thermal-insulating materials — Determination of long-term water absorption by diffusion

## 1 Scope

This International Standard specifies equipment and procedures for determining the long-term water absorption of test specimens by diffusion. It is intended for use with thermal-insulation products. It is designed to simulate the absorption of water by products subjected for a long period of time not only to high relative humidity, approximating to 100 %, on both sides, but also to a water vapour pressure gradient, as experienced by e.g. inverted roof or unprotected ground insulation.

The test is not applicable to all types of thermal-insulation product. The product standard should normally state whether this test is applicable to a particular product.

NOTE For unprotected ground insulation, a lower temperature might, when more data is available, replace the test temperature of 50 °C currently specified in this International Standard.

## 2 Normative references

The following referenced documents are indispensable for the application of this document. For dated references, only the edition cited applies. For undated references, the latest edition of the referenced document (including any amendments) applies.

ISO 472, *Plastics — Vocabulary*

ISO 1923, *Cellular plastics and rubbers — Determination of linear dimensions*

## 3 Terms and definitions

For the purposes of this document, the terms and definitions given in ISO 472 apply.


## 4 Principle

The long-term water absorption by diffusion is determined by measuring the increase in mass of a test specimen when it is subjected to a water vapour pressure difference and temperature gradient between its upper and lower surfaces for a period of 28 days.

## 5 Apparatus and materials

- 5.1 **Balance**, capable of determining the mass of the test specimen to within 0,1 g.
- 5.2 **Corrosion-resistant container**, with a frame supporting the test specimen.
- 5.3 **Heating device**, with a thermostat capable of controlling the water temperature at  $(50 \pm 1)$  °C.
- 5.4 **Cooling plate**, thermally insulated on the outside, operating at a temperature of  $(1 \pm 0,5)$  °C.
- 5.5 **Tap water**, kept at a temperature of  $(50 \pm 1)$  °C.

The basic principles of the apparatus are illustrated in Figure 1.

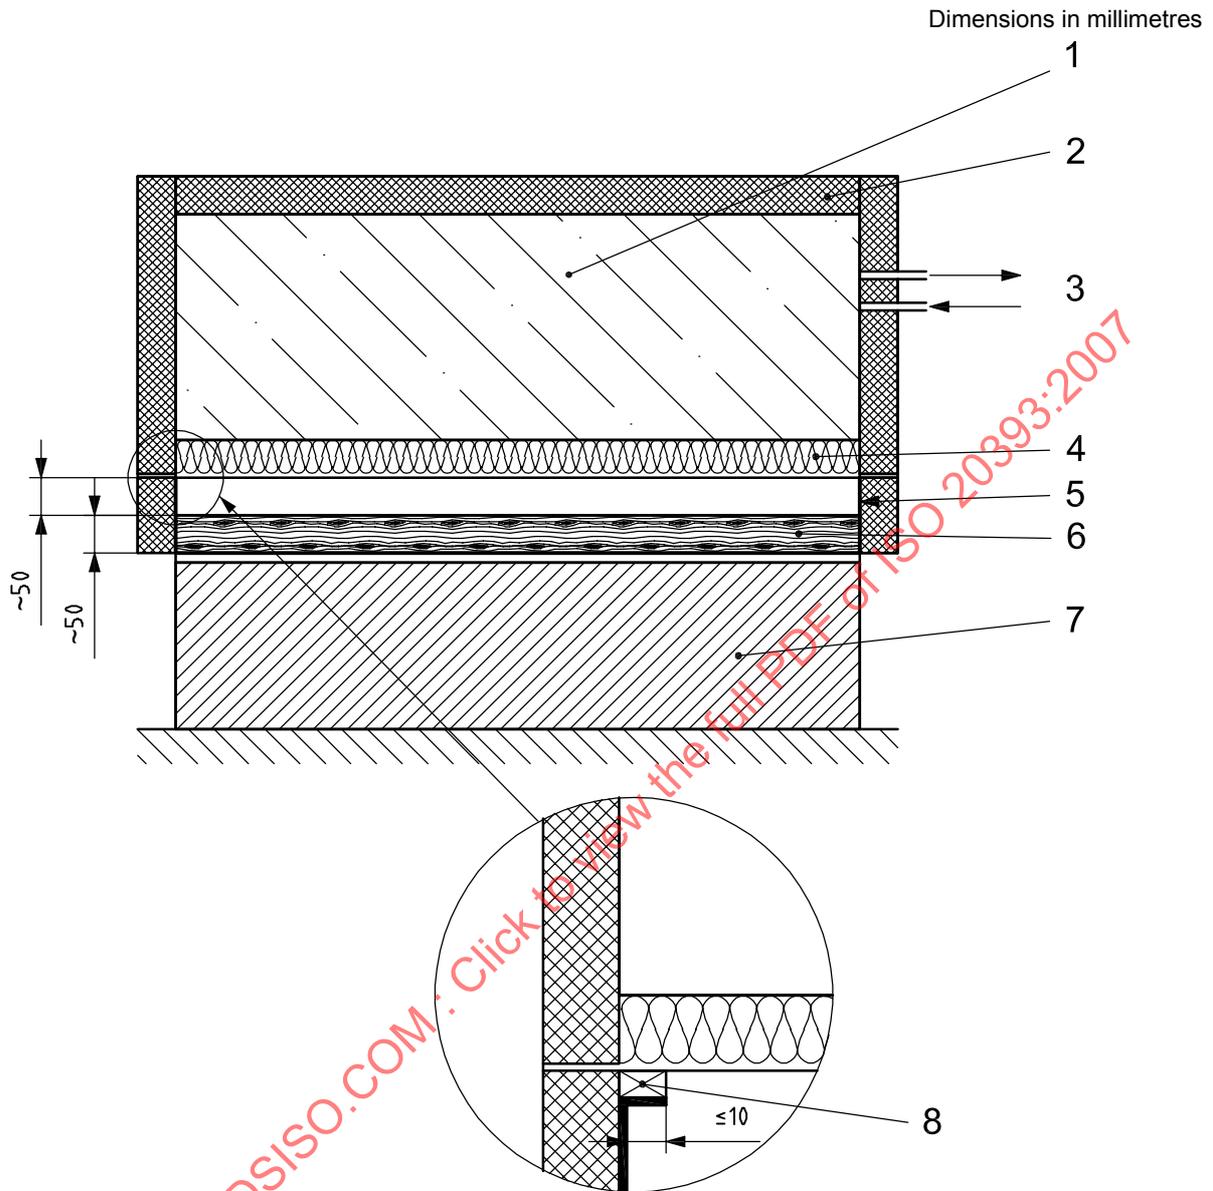

**Key**

- 1 cooling plate
- 2 thermal insulation for cooling plate and container
- 3 coolant inlet and outlet
- 4 test specimen
- 5 corrosion-resistant container with a frame supporting the test specimen
- 6 tap water
- 7 heating device with thermostat
- 8 seal

**Figure 1 — Example of apparatus for determining water absorption by diffusion**

## 6 Test specimens

### 6.1 Dimensions

The thickness of the test specimens shall be the original product thickness.

The test specimens shall be squares, with squarely cut edges, having sides of length  $(500 \pm 1)$  mm. If the product is not large enough to permit this size of test specimen, the test specimen size shall be reduced accordingly. Test specimens shall contain no joints.

### 6.2 Number

The number of test specimens shall be at least two.

### 6.3 Preparation

The test specimens shall be cut so that they do not include original product edges.

Test specimens shall be prepared by methods that do not substantially change the original structure of the product. Any facings, skins and/or coatings shall be retained.

NOTE Special methods of preparation, when needed, are given in the relevant product standard.

### 6.4 Conditioning

The test specimens shall be conditioned for at least 6 h at

$(23 \pm 2)$  °C and  $(50 \pm 10)$  % relative humidity

or

$(23 \pm 5)$  °C and  $50_{-10}^{+20}$  % relative humidity

or

$(27 \pm 5)$  °C and  $65_{-10}^{+20}$  % relative humidity.

In cases of dispute, they shall be conditioned at  $(23 \pm 2)$  °C and  $(50 \pm 5)$  % relative humidity for the time stated in the relevant product standard, but in any case for a minimum of 6 h.

## 7 Procedure

Measure the dimensions of the test specimens in accordance with ISO 1923.

Weigh the test specimen to the nearest 0,1 g to determine its initial mass,  $m_0$ .

Place the test specimen on the frame of the container. If the product is faced on one side, begin the test with the facing uppermost. Seal the bottom edge of the test specimen to the container. The width of the seal shall be  $\leq 10$  mm (see Figure 1). Place the insulated cooling plate on top of the test specimen.

Subject the test specimen to a temperature and water vapour pressure difference for 28 days, maintaining the tap water at a temperature of  $(50 \pm 1)$  °C and the cooling plate on the other side at a temperature of  $(1 \pm 0,5)$  °C.

Turn the test specimen over every 7 days.

After 28 days, remove the test specimen and wipe off any surface water. Weigh the test specimen again to determine its mass,  $m_D$ .

## 8 Calculation and expression of results

For each test specimen, calculate the long-term water absorption by diffusion,  $W_{dP}$  or  $W_{dV}$ , in kilograms per square metre or in percent by volume, using Equation (1) or (2), respectively:

$$W_{dP} = \frac{m_D - m_0}{A_p} \quad (1)$$

$$W_{dV} = \frac{m_D - m_0}{A_p \times d} \times \frac{100}{\rho_W} \quad (2)$$

where

- $m_0$  is the initial mass of the test specimen, in kilograms;
- $m_D$  is the mass of the test specimen after being subjected to a temperature and water vapour pressure difference for 28 days, in kilograms;
- $A_p$  is the area of the lower surface of the test specimen, in square metres;
- $d$  is the thickness of the test specimen, in metres;
- $\rho_W$  is the density of water, assumed to be 1 000 kg/m<sup>3</sup>.

The test result shall be taken as the mean value of the individual values, rounded to the nearest 0,01 kg/m<sup>2</sup> in the case of  $W_{dP}$  and to the nearest 0,1 % by volume in the case of  $W_{dV}$ .

Results shall not be extrapolated to other thicknesses.

## 9 Precision

It has not been possible to include a statement on the precision of the measurements in this edition of this International Standard, but it is intended to include such a statement when the standard is next revised.

## 10 Test report

The test report shall include the following information:

- a) a reference to this International Standard;
- b) product identification:
  - 1) the name of the product, the factory where it was manufactured and the manufacturer or supplier,
  - 2) the production code number,
  - 3) the type of product,
  - 4) the type of packaging,
  - 5) the form in which the product arrived at the laboratory,
  - 6) any other information as appropriate, e.g. nominal thickness, nominal density;