
**Hot-rolled steel sheet in coils of higher
yield strength with improved formability
and heavy thickness for cold forming**

*Tôles fortes en acier laminées à chaud à limite d'élasticité et aptitude au
formage accues, en bobines, pour formage à froid*

STANDARDSISO.COM : Click to view the full PDF of ISO 20805:2005



PDF disclaimer

This PDF file may contain embedded typefaces. In accordance with Adobe's licensing policy, this file may be printed or viewed but shall not be edited unless the typefaces which are embedded are licensed to and installed on the computer performing the editing. In downloading this file, parties accept therein the responsibility of not infringing Adobe's licensing policy. The ISO Central Secretariat accepts no liability in this area.

Adobe is a trademark of Adobe Systems Incorporated.

Details of the software products used to create this PDF file can be found in the General Info relative to the file; the PDF-creation parameters were optimized for printing. Every care has been taken to ensure that the file is suitable for use by ISO member bodies. In the unlikely event that a problem relating to it is found, please inform the Central Secretariat at the address given below.

STANDARDSISO.COM : Click to view the full PDF of ISO 20805:2005

© ISO 2005

All rights reserved. Unless otherwise specified, no part of this publication may be reproduced or utilized in any form or by any means, electronic or mechanical, including photocopying and microfilm, without permission in writing from either ISO at the address below or ISO's member body in the country of the requester.

ISO copyright office
Case postale 56 • CH-1211 Geneva 20
Tel. + 41 22 749 01 11
Fax + 41 22 749 09 47
E-mail copyright@iso.org
Web www.iso.org

Published in Switzerland

Foreword

ISO (the International Organization for Standardization) is a worldwide federation of national standards bodies (ISO member bodies). The work of preparing International Standards is normally carried out through ISO technical committees. Each member body interested in a subject for which a technical committee has been established has the right to be represented on that committee. International organizations, governmental and non-governmental, in liaison with ISO, also take part in the work. ISO collaborates closely with the International Electrotechnical Commission (IEC) on all matters of electrotechnical standardization.

International Standards are drafted in accordance with the rules given in the ISO/IEC Directives, Part 2.

The main task of technical committees is to prepare International Standards. Draft International Standards adopted by the technical committees are circulated to the member bodies for voting. Publication as an International Standard requires approval by at least 75 % of the member bodies casting a vote.

Attention is drawn to the possibility that some of the elements of this document may be the subject of patent rights. ISO shall not be held responsible for identifying any or all such patent rights.

ISO 20805 was prepared by Technical Committee ISO/TC 17, *Steel*, Subcommittee SC 12, *Continuous mill flat rolled products*.

STANDARDSISO.COM : Click to view the full PDF of ISO 20805:2005

Hot-rolled steel sheet in coils of higher yield strength with improved formability and heavy thickness for cold forming

1 Scope

1.1 This International Standard applies to continuous hot-rolled steel sheet of higher yield strength with improved formability. The steel is killed, made according to a fine-grain practice and has a suitable chemical composition, which shall include microalloying elements, to provide improved formability. The steel may be treated to achieve inclusion control. The product is intended for applications where parts are to be fabricated requiring better formability than is provided by normal high-yield-strength steel sheet. It is generally used in the as-delivered condition. This product is commonly produced on a wide strip mill.

Because of the combination of higher strength and improved formability, it is possible to obtain savings in mass along with better weldability (see 4.4).

1.2 This product is commonly produced in the range of thicknesses greater than 6 mm to 25 mm, and widths of 600 mm and over, in coils.

1.3 This International Standard does not cover steels intended for boilers or pressure vessels, or steels designated as commercial quality, drawing quality or structural quality, or steels rolled to cold-reduced products, or steels designated as weathering steels, having increased atmospheric corrosion resistance, or those products rolled on a plate mill.

2 Normative references

The following referenced documents are indispensable for the application of this document. For dated references, only the edition cited applies. For undated references, the latest edition of the referenced document (including any amendments) applies.

ISO 148:1983, *Steel — Charpy impact test (V-notch)*

ISO 6892:1998, *Metallic materials — Tensile testing at ambient temperature*

3 Terms and definitions

For the purposes of this document, the following terms and definitions apply.

3.1

microalloying elements

elements, such as niobium, vanadium, titanium, etc., added singly or in combination to obtain higher strength levels combined with better formability, weldability and toughness as compared with non-alloyed steel produced to equivalent strength levels

3.2

hot-rolled steel sheet in coils

product obtained by rolling heated steel (billet or slab) through a continuous-type mill to the required strip thickness and tolerances

NOTE The product has a surface covered with oxide or scale resulting from the hot-rolling operation.

3.3 hot-rolled descaled steel sheet in coils

hot-rolled steel sheet from the surface of which oxide or scale has been removed, commonly by pickling in an acid solution

NOTE Descaling may also be performed by mechanical means such as grit blasting. Some increase in hardness and some loss of ductility may result from descaling.

3.4 mill edge

a normal edge produced without any definite contour produced in hot-rolling.

NOTE Mill edges may contain some irregularities such as cracked or torn edges or thin (feathered) edges.

3.5 sheared edge

a normal edge obtained by shearing, slitting or trimming a mill edge product

NOTE Normal processing does not necessarily provide a definite positioning of the slitting burr.

4 Conditions of manufacture

4.1 Steelmaking

Unless otherwise agreed upon by the interested parties, the processes used in making the steel and in manufacturing hot-rolled sheet are left to the discretion of the manufacturer. On request, the purchaser shall be informed of the steelmaking process being used.

4.2 Chemical composition

4.2.1 The chemical composition (heat analysis) shall conform to the requirements in Tables 1 and 2.

4.2.2 The steel covered by this International Standard shall contain microalloying elements. The chemical composition may be agreed between the interested parties at the time of enquiry and ordering.

Table 1 — Chemical analysis (heat analysis)

| All grades | Carbon | Manganese | Phosphorus | Sulfur |
|------------|--------------|--------------|---------------|---------------|
| | 0,15 max., % | 1,65 max., % | 0,025 max., % | 0,030 max., % |

NOTE 1 As the form of sulfide inclusions may have a certain influence on the cold forming properties of the products, the manufacturers may, at their discretion, influence the form of inclusions by adding certain elements, such as Ce or Ca, or may choose a very low sulfur content for these steels.

NOTE 2 These steels shall also contain one or more of the following elements: vanadium, titanium or niobium. Other alloying elements may be present, but are not required.

Table 2 — Limits on additional chemical elements

| | | |
|----------------------------|------------------|------|
| Copper , max. % | Heat analysis | 0,20 |
| | Product analysis | 0,23 |
| Nickel , max. % | Heat analysis | 0,20 |
| | Product analysis | 0,23 |
| Chromium , max. % | Heat analysis | 0,15 |
| | Product analysis | 0,19 |
| Molybdenum , max. % | Heat analysis | 0,06 |
| | Product analysis | 0,07 |

4.3 Chemical analysis

4.3.1 Heat analysis

A heat analysis of each heat of steel shall be made by the manufacturer to determine the percentage of carbon, manganese, phosphorus and sulphur, and the contents of other elements giving the specified mechanical strength and formability. On request, this analysis shall be reported to the purchaser or his representative.

4.3.2 Product analysis

A product analysis may be made by the purchaser to verify the specified analysis of the product and shall take into consideration any normal heterogeneity. Non-killed steels (such as rimmed or capped) are not technologically suited to product analysis. For killed steels, the sampling method shall be agreed upon between the interested parties at the time of ordering. The product analysis tolerances shall be in accordance with Table 3.

Table 3 — Product analysis tolerances

| Element | Maximum of specified element, % | Tolerance over maximum specified, % |
|------------|------------------------------------|--|
| Carbon | $\leq 0,15$ | 0,03 |
| Manganese | $> 1,15$ to $\leq 1,65$ | 0,05 |
| Phosphorus | $\leq 0,04$ | 0,010 |
| Sulfur | $\leq 0,06$ | 0,010 |

NOTE The above maximum tolerance is the allowable excess over the specified requirement and not the heat analysis. For example: for all grades in this standard the following product analysis values are within these tolerances: C 0,18 %, Mn 1,70 %, P 0,035 %, S 0,040 %.

4.4 Weldability

This product is normally suitable for welding if appropriate welding conditions are selected. For underscaled steel, it may be necessary to remove the scale or oxide depending upon the welding method. As the carbon content increases above 0,15 %, spot welding becomes increasingly difficult.

4.5 Application

It is desirable that hot-rolled steel sheet be identified for fabrication by the name of the part or by the intended application. Proper identification of the part may include visual examination, prints or description, or a combination of these.

4.6 Mechanical properties

At the time that the steel is made available for shipment, the mechanical properties shall be as stated in Table 4, when they are determined on test pieces in accordance with the requirements of Clause 6. Any additional property requirements specified or required are subject to agreement between the interested parties at the time of enquiry and ordering. Such additional requirements may include characterization or prescribed values for properties such as impact for sheet over 6 mm in thickness (see 7.2).

Table 4 — Mechanical properties

| Grade | R_e min. ^a N/mm ² | R_m min. N/mm ² | A^b min., % | | | |
|-------|---|------------------------------------|------------------------|--------------------------------------|--------------|--------------|
| | | | $L_o = 5,65\sqrt{S_o}$ | $L_o = 50$ mm for sheet thickness | | |
| | | | | 6 – 12 mm | > 12 – 19 mm | > 19 – 25 mm |
| 325 | 325 | 410 | 19 | 21 | 24 | 26 |
| 355 | 355 | 420 | 18 | 20 | 23 | 25 |
| 420 | 420 | 480 | 15 | 17 | 19 | 21 |
| 490 | 490 | 540 | 12 | 13 | 16 | 17 |
| 560 | 560 | 610 | 9 | 10 | 12 | 13 |

R_e is the yield strength;
 R_{eH} is the upper yield stress;
 R_{eL} is the lower yield stress;
 R_m is the tensile strength;
 A is the percentage elongation after fracture;
 L_o is the gauge length on test piece;
 S_o is the original cross-sectional area of gauge length;
 1 N/mm² = 1 MPa.

^a Either R_{eH} or R_{eL} shall be measured and either value shall meet the minimum requirement. The yield strength values can be measured by 0,5 % total elongation proof stress (proof stress under load) or by 0,2 % offset when a definite yield phenomenon is not present.
^b In case of dispute, only the results obtained on a 50 mm test piece will be valid.

4.7 Surface condition

Designation AR describes the as-rolled condition.

Oxide or scale on hot-rolled steel sheet is subject to variations in thickness, adherence and colour. Removal of the oxide or scale by pickling or blast cleaning may disclose surface imperfections not readily visible prior to this operation.

The steel shall be supplied as-rolled or pickled and oiled, as requested by the purchaser at the time of enquiry and ordering (see 3.3). If neither condition is specified, the delivery will be as-rolled.

4.8 Oiling

Designation DO describes the descaled and oiled condition. As a deterrent to rusting, a coating of oil is usually applied to hot-rolled descaled steel sheet. The oil is not intended as a drawing or forming lubricant and shall be easily removable with degreasing chemicals. On request, the manufacturer shall advise the purchaser which type of oil has been used. Hot-rolled descaled steel sheet may be ordered not oiled, if required, in which case the supplier has limited responsibility if oxidation occurs.

5 Dimensional tolerances

5.1 Dimensional tolerances applicable to hot-rolled steel sheet in coils of structural quality and heavy thickness shall be in accordance with Tables 5 and 6. These tolerances also apply to descaled material.

5.2 Camber shall not exceed 25 mm in any 5 000 mm of length (see Figure 1).

NOTE Camber is the greatest deviation of a side from a straight line, the measurement being taken on the concave side with a straight edge.

Table 5 — Thickness tolerances for heavy thickness hot-rolled sheet (including descaled) in coils

Dimensions and tolerances in millimetres

| Specified widths | Thickness tolerances for specified thicknesses ^a | | | | |
|------------------|--|----------------|-----------------|-----------------|-----------------|
| | > 6,00 ≤ 8,00 | > 8,00 ≤ 10,00 | > 10,00 ≤ 12,50 | > 12,50 ≤ 16,00 | > 16,00 ≤ 25,00 |
| 600 ≤ 1 200 | ± 0,29 | ± 0,32 | ± 0,35 | ± 0,38 | ± 0,40 |
| > 1 200 ≤ 1 500 | ± 0,30 | ± 0,33 | ± 0,36 | ± 0,39 | ± 0,42 |
| > 1 500 ≤ 1 800 | ± 0,31 | ± 0,34 | ± 0,37 | ± 0,40 | ± 0,44 |
| > 1 800 | ± 0,35 | ± 0,40 | ± 0,43 | ± 0,48 | ± 0,50 |

The values specified do not apply to the uncropped ends for a length, *l*, of a mill edge coil. The length, *l*, would be calculated using the following formula:

$$\text{length, } l, \text{ in metres} = \frac{90}{\text{thickness in millimetres}}$$


provided that the result was not greater than 20 m inclusive of both ends.

^a Thickness is measured at any point on the sheet not less than 40 mm from a side edge for mill edge material and not less than 25 mm from the edge for sheared material.

Table 6 — Width tolerances for heavy thickness hot-rolled sheet in coils

Dimensions and tolerances in millimetres

| Specified widths | Mill edges | | Sheared edges | |
|------------------|------------|---|---------------|---|
| | + | 0 | + | 0 |
| < 600 ≤ 1 200 | + 28 | 0 | + 5 | 0 |
| > 1 200 ≤ 1 500 | + 38 | 0 | + 6 | 0 |
| > 1 800 | + 50 | 0 | + 10 | 0 |
| > 1 500 ≤ 1 800 | + 45 | 0 | + 8 | 0 |

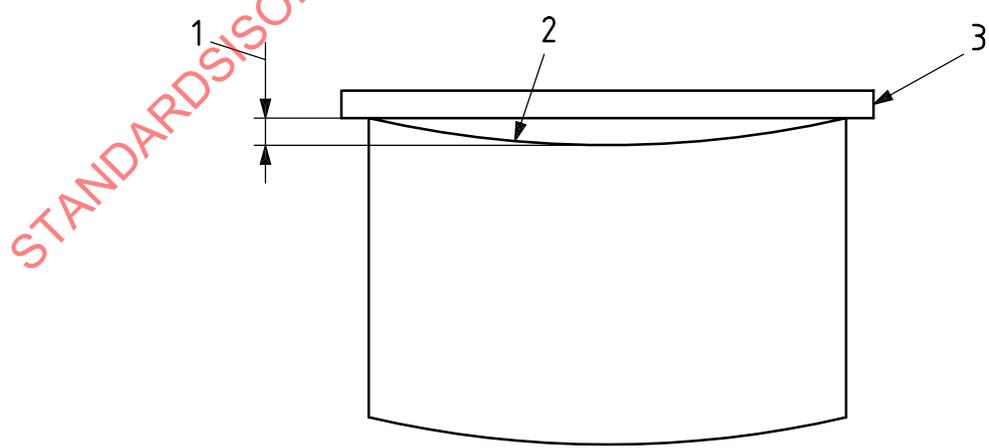

Key

- 1 edge camber
- 2 side edge (concave side)
- 3 straight edge

Figure 1 — Measurement of camber

6 Sampling – tensile test

One representative sample for the tensile test required in Table 4 shall be taken from each lot of sheet for shipment. A lot consists of 50 tonnes or less of sheet of the same designation rolled to the same thickness and condition.

7 Mechanical property tests

7.1 Tensile test

The tensile test shall be carried out in accordance with ISO 6892. Transverse test pieces shall be taken mid-way between the centre and edge of the sheet as-rolled.

7.2 Impact test

While not usually specified, if so agreed at the time of ordering, impact tests may be specified for material over 12,5 mm in thickness. The test piece shall be in the longitudinal direction and the test shall be carried out in accordance with ISO 148.

8 Retests

8.1 Machining and flaws

If any test piece shows defective machining or develops flaws, it shall be discarded and another piece substituted.

8.2 Elongation

If the percentage of elongation of any test piece is less than that specified in Table 4 and if any part of the fracture is outside the middle half of the gauge length as scribed before the test, the test shall be discarded and a retest shall be carried out.

8.3 Additional tests

If a test does not give the specified results, two more tests shall be carried out at random on the same lot. Both retests shall conform to the requirements of this International Standard; otherwise, the lot may be rejected.

9 Resubmission

The manufacturer may resubmit for acceptance the products that have been rejected during earlier inspection because of unsatisfactory properties, after he has subjected them to a suitable treatment (selection, heat treatment), which, on request, will be indicated to the purchaser.

In this case, the tests should be carried out as if they applied to a new batch.

The manufacturer has the right to present the rejected products to a new examination for compliance with the requirements for another grade.

10 Workmanship

The surface condition shall be that normally obtained in a hot-rolled or hot-rolled descaled product.

The steel sheet in cut lengths shall be free from amounts of laminations, surface flaws and other imperfections that are detrimental to subsequent appropriate processing.

Processing for shipment in coils does not afford the manufacturer the opportunity to observe readily or to remove imperfect portions, as can be carried out on the cut length product.

11 Inspection and acceptance

While not usually required for products covered by this International Standard, when the purchaser specifies that inspection and tests for acceptance be observed prior to shipment from the manufacturer's works, the manufacturer shall afford the purchaser's inspector all reasonable facilities to determine that the steel is being furnished in accordance with this International Standard.

Steel that is reported to be defective after arrival at the user's works shall be set aside, properly and correctly identified and adequately protected. The manufacturer shall be notified in order that he may properly investigate.

12 Coil size

When hot-rolled steel sheet is ordered in coils, a minimum inside diameter (ID) or range of acceptable inside diameters shall be specified. In addition, the maximum outside diameter (OD) and the maximum acceptable coil mass shall be specified.

13 Marking

Unless otherwise stated, the following minimum requirements for identifying the steel shall be legibly stencilled on the top of each lift, or shown on a tag attached to each coil or shipping unit:

- a) manufacturer's name or identifying brand;
- b) reference to this International Standard, i.e. ISO 20805;
- c) the grade designation;
- d) the order number;
- e) the product dimensions;
- f) the lot number;
- g) the mass.

14 Information to be supplied by the purchaser

To adequately specify requirements according to this International Standard, inquiries and orders shall include the following information:

- a) reference to this International Standard, i.e. ISO 20805;
- b) the name, quality, and grade of the material (for example, hot-rolled steel sheet, higher yield strength with improved formability, grade HSF 355);
- c) the dimensions of the product and the quantity required;
- d) the application (name of part) if possible (see 4.4 and 4.5);
- e) whether pickling or descaling by grit or shot blasting is required (material so specified will be oiled unless ordered not oiled) (see 3.3);