

---

---

**Anodizing of aluminium and its alloys —  
Determination of thickness of anodic  
oxidation coatings — Non-destructive  
measurement by split-beam microscope**

*Anodisation de l'aluminium et de ses alliages — Détermination de  
l'épaisseur des couches anodiques — Méthode non destructive par  
microscope à coupe optique*



**PDF disclaimer**

This PDF file may contain embedded typefaces. In accordance with Adobe's licensing policy, this file may be printed or viewed but shall not be edited unless the typefaces which are embedded are licensed to and installed on the computer performing the editing. In downloading this file, parties accept therein the responsibility of not infringing Adobe's licensing policy. The ISO Central Secretariat accepts no liability in this area.

Adobe is a trademark of Adobe Systems Incorporated.

Details of the software products used to create this PDF file can be found in the General Info relative to the file; the PDF-creation parameters were optimized for printing. Every care has been taken to ensure that the file is suitable for use by ISO member bodies. In the unlikely event that a problem relating to it is found, please inform the Central Secretariat at the address given below.

STANDARDSISO.COM : Click to view the full PDF of ISO 2128:2010



**COPYRIGHT PROTECTED DOCUMENT**

© ISO 2010

All rights reserved. Unless otherwise specified, no part of this publication may be reproduced or utilized in any form or by any means, electronic or mechanical, including photocopying and microfilm, without permission in writing from either ISO at the address below or ISO's member body in the country of the requester.

ISO copyright office  
Case postale 56 • CH-1211 Geneva 20  
Tel. + 41 22 749 01 11  
Fax + 41 22 749 09 47  
E-mail [copyright@iso.org](mailto:copyright@iso.org)  
Web [www.iso.org](http://www.iso.org)

Published in Switzerland

## Foreword

ISO (the International Organization for Standardization) is a worldwide federation of national standards bodies (ISO member bodies). The work of preparing International Standards is normally carried out through ISO technical committees. Each member body interested in a subject for which a technical committee has been established has the right to be represented on that committee. International organizations, governmental and non-governmental, in liaison with ISO, also take part in the work. ISO collaborates closely with the International Electrotechnical Commission (IEC) on all matters of electrotechnical standardization.

International Standards are drafted in accordance with the rules given in the ISO/IEC Directives, Part 2.

The main task of technical committees is to prepare International Standards. Draft International Standards adopted by the technical committees are circulated to the member bodies for voting. Publication as an International Standard requires approval by at least 75 % of the member bodies casting a vote.

Attention is drawn to the possibility that some of the elements of this document may be the subject of patent rights. ISO shall not be held responsible for identifying any or all such patent rights.

ISO 2128 was prepared by Technical Committee ISO/TC 79, *Light metals and their alloys*, Subcommittee SC 2, *Organic and anodic oxidation coatings on aluminium*.

This second edition cancels and replaces the first edition (ISO 2128:1976), which has been technically revised.

[STANDARDSISO.COM](https://standardsiso.com) : Click to view the full PDF of ISO 2128:2010

# Anodizing of aluminium and its alloys — Determination of thickness of anodic oxidation coatings — Non-destructive measurement by split-beam microscope

## 1 Scope

This International Standard specifies a non-destructive method for determining the thickness of anodic oxidation coatings on aluminium and its alloys using a split-beam microscope.

The method is applicable, in most industrial cases, to anodic oxidation coatings above 10  $\mu\text{m}$ , or above 5  $\mu\text{m}$  when the surface is smooth.

The use of the method specified is limited by the need for the two luminous lines described in Clause 3 to be visible and distinctly separated, i.e. not in the case of opaque or dark coloured coatings.

NOTE Problems can arise as a result of the roughness of the surface.

## 2 Terms and definitions

For the purposes of this document, the following terms and definitions apply.

### 2.1

#### **thickness of an anodic oxidation coating**

arithmetic mean of the thicknesses measured at not less than 10 points of an inspection area

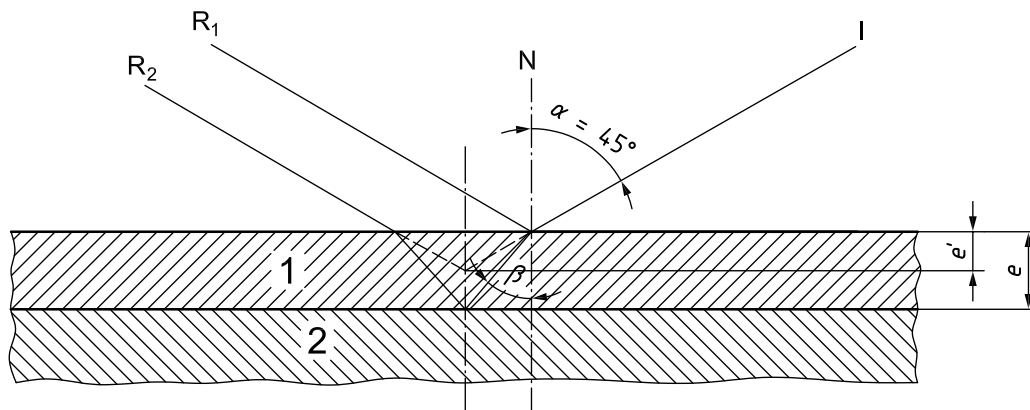
### 2.2

#### **inspection area**

part of the surface on which the specified properties are required to be measured

## 3 Principle

A parallel, lamellar beam of light ( $I$ ) in a split-beam microscope is directed obliquely, generally at an angle of incidence of  $45^\circ$ , onto the anodized surface (see Figure 1).

**Key**

- 1 oxidation coating  
2 metal

**Figure 1 — Diagram of optical path**

A part of this beam,  $R_1$ , is reflected at the outer face of the coating; another part,  $R_2$ , penetrates the coating and emerges after reflection at the metal/coating interface and two resulting refractions.

Two parallel lines are obtained at the ocular, the distance between these being proportional to the thickness of the oxidation coating and to the magnification. This distance is also dependent on the refractive index of the coating,  $n$ , which lies between 1,59 and 1,62, and on the geometry of the apparatus. When the angle of incidence and the optical axis of the objective lens of the measuring apparatus are both at  $45^\circ$ , the thickness is given by Formula (1):

$$e = e' \sqrt{2n^2 - 1}, \text{ or } e = 2,04 e', \text{ approximately} \quad (1)$$

where

$e$  is the true thickness;

$e'$  is the measured apparent thickness.

**NOTE** The use of  $e = 2e'$  provides adequate accuracy. Some instruments are calibrated in such a way that they give the actual thickness,  $e$ , rather than the apparent thickness,  $e'$ .

## 4 Apparatus

**4.1 Split-beam microscope**, specially designed for measuring the thickness of transparent coatings or surface roughness.

The calibration of the microscope shall be checked using an anodized aluminium sample, the anodic oxidation coating thickness of which has been determined by the micrographic section method.

## 5 Procedure

Proceed in accordance with the instructions provided with the apparatus.

The inspection area should be agreed between the supplier and the customer.