
**Test methods for fibre-reinforced
cementitious composites — Bending
moment — Curvature curve by four-
point bending test**

*Méthodes d'essai des composites à base de ciment renforcés par
des fibres — Moment de flexion — Courbe de courbure par essai de
flexion quatre points*

STANDARDSISO.COM : Click to view the full PDF of ISO 21914:2019



STANDARDSISO.COM : Click to view the full PDF of ISO 21914:2019



COPYRIGHT PROTECTED DOCUMENT

© ISO 2019

All rights reserved. Unless otherwise specified, or required in the context of its implementation, no part of this publication may be reproduced or utilized otherwise in any form or by any means, electronic or mechanical, including photocopying, or posting on the internet or an intranet, without prior written permission. Permission can be requested from either ISO at the address below or ISO's member body in the country of the requester.

ISO copyright office
CP 401 • Ch. de Blandonnet 8
CH-1214 Vernier, Geneva
Phone: +41 22 749 01 11
Fax: +41 22 749 09 47
Email: copyright@iso.org
Website: www.iso.org

Published in Switzerland

Contents

	Page
Foreword	iv
1 Scope	1
2 Normative references	2
3 Terms and definitions	2
4 Symbols	2
5 Test specimens	3
5.1 Geometry	3
5.2 Fabrication of specimen	3
5.3 Loading of specimen	4
6 Test equipment	4
6.1 Testing machine	4
6.2 Loading apparatus	4
6.3 Measuring device for average curvature	5
7 Test procedure	6
8 Calculations	7
9 Test report	7
Annex A (informative) Method of estimating tensile strength and average ultimate tensile strain ..	9
Bibliography	11

STANDARDSISO.COM : Click to view the full PDF of ISO 21914:2019

Foreword

ISO (the International Organization for Standardization) is a worldwide federation of national standards bodies (ISO member bodies). The work of preparing International Standards is normally carried out through ISO technical committees. Each member body interested in a subject for which a technical committee has been established has the right to be represented on that committee. International organizations, governmental and non-governmental, in liaison with ISO, also take part in the work. ISO collaborates closely with the International Electrotechnical Commission (IEC) on all matters of electrotechnical standardization.

The procedures used to develop this document and those intended for its further maintenance are described in the ISO/IEC Directives, Part 1. In particular, the different approval criteria needed for the different types of ISO documents should be noted. This document was drafted in accordance with the editorial rules of the ISO/IEC Directives, Part 2 (see www.iso.org/directives).

Attention is drawn to the possibility that some of the elements of this document may be the subject of patent rights. ISO shall not be held responsible for identifying any or all such patent rights. Details of any patent rights identified during the development of the document will be in the Introduction and/or on the ISO list of patent declarations received (see www.iso.org/patents).

Any trade name used in this document is information given for the convenience of users and does not constitute an endorsement.

For an explanation of the voluntary nature of standards, the meaning of ISO specific terms and expressions related to conformity assessment, as well as information about ISO's adherence to the World Trade Organization (WTO) principles in the Technical Barriers to Trade (TBT) see www.iso.org/iso/foreword.html.

This document was prepared by Technical Committee ISO/TC 71, *Concrete, reinforced concrete and pre-stressed concrete*, Subcommittee SC 6, *Non-traditional reinforcing materials for concrete structures*.

Any feedback or questions on this document should be directed to the user's national standards body. A complete listing of these bodies can be found at www.iso.org/members.html.


Test methods for fibre-reinforced cementitious composites — Bending moment — Curvature curve by four-point bending test

1 Scope

This document specifies the test method for obtaining bending moment-curvature curves of fibre-reinforced cementitious composites (FRCCs) through four-point bending test of prism specimens.

It is applicable to FRCCs that show separated multiple cracks under pure bending before maximum load.

NOTE Separated multiple cracks means two or more independent cracks visible to the eye occurring in the constant moment span from the bottom side over half depth of the specimen before maximum load is observed, as shown in Figure 1. For the purpose of confirmation of cracks, spraying up the specimen surface using an alcohol solution or acetone makes observations easier. The formation of multiple cracks is associated with deflection hardening behaviour. For FRCCs that do not show separated multiple cracks, see ISO 19044.

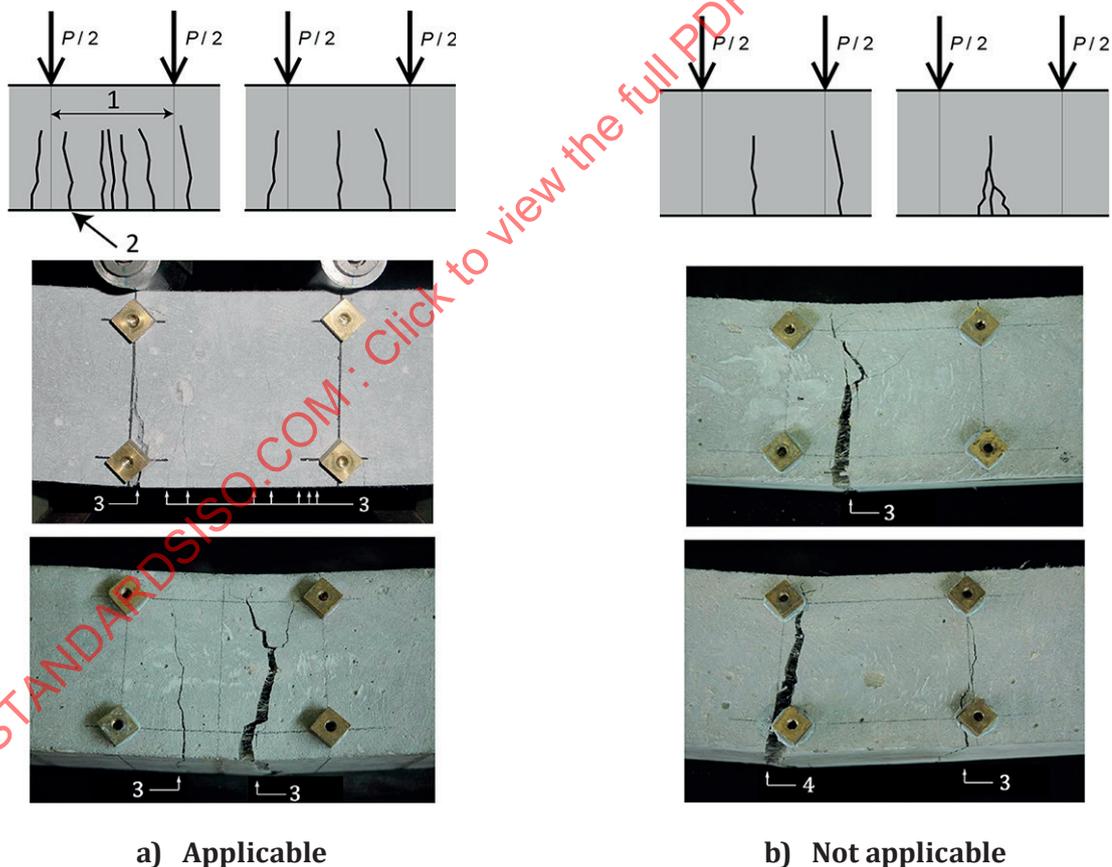

Key

- 1 constant moment span
- 2 crack visible to the eye
- 3 crack
- 4 crack (out of constant moment span)
- P applied load

Figure 1 — Cracking in FRCCs covered by this document

2 Normative references

The following documents are referred to in the text in such a way that some or all of their content constitutes requirements of this document. For dated references, only the edition cited applies. For undated references, the latest edition of the referenced document (including any amendments) applies.

ISO 1920-3:—¹⁾, *Testing of concrete — Part 3: Making and curing test specimens*

ISO 1920-4:—²⁾, *Testing of concrete — Part 4: Strength of hardened concrete*

3 Terms and definitions

For the purposes of this document, the following terms and definitions apply.

ISO and IEC maintain terminological databases for use in standardization at the following addresses:

- ISO Online browsing platform: available at <https://www.iso.org/obp>
- IEC Electropedia: available at <http://www.electropedia.org/>

3.1 fibre-reinforced cementitious composite FRCC

concrete or mortar containing short discrete fibres distributed throughout matrix

Note 1 to entry: Fibres include man-made fibres (e.g., metallic fibres, inorganic fibres, synthetic fibres) and natural fibres.

3.2 average strain

ratio of axial deformation to gauge length

3.3 average curvature

gradient of *average strains* (3.2) in constant moment span

4 Symbols

See [Table 1](#).

Table 1 — Symbols

Symbol	Unit	Description	Subclause
b	mm	width of cross-section of specimen	5.1
D	mm	depth of cross-section of specimen	5.1
d_0	mm	distance between two LVDTs	6.4
L	mm	overall length of specimen	5.1
M	N·mm	bending moment	8
P	N	applied load	8
S	mm	specimen span	6.2
ε_1	—	average strain calculated by measured displacement of upper LVDT	8
ε_2	—	average strain calculated by measured displacement of lower LVDT	8

1) Under preparation. (Stage at the time of publication: ISO/DIS 1920-3:2018.)

2) Under preparation. (Stage at the time of publication: ISO/DIS 1920-4:2018.)

Table 1 (continued)

Symbol	Unit	Description	Subclause
ϕ	mm ⁻¹	average curvature	8

5 Test specimens


5.1 Geometry

Specimens shall be prisms of square cross-section as shown in [Figure 2](#).

- a) The cross-sectional dimensions of the specimen shall be either 150 mm × 150 mm or 100 mm × 100 mm. The side length of the cross-section of the specimen shall be equal to or larger than three times the fibre length.

Specimens with different dimensions provide different test results even if the same FRCC is used. Test results from specimens of various sizes should not be compared.

- b) The overall length of the specimen shall not be less than 3,5 D .

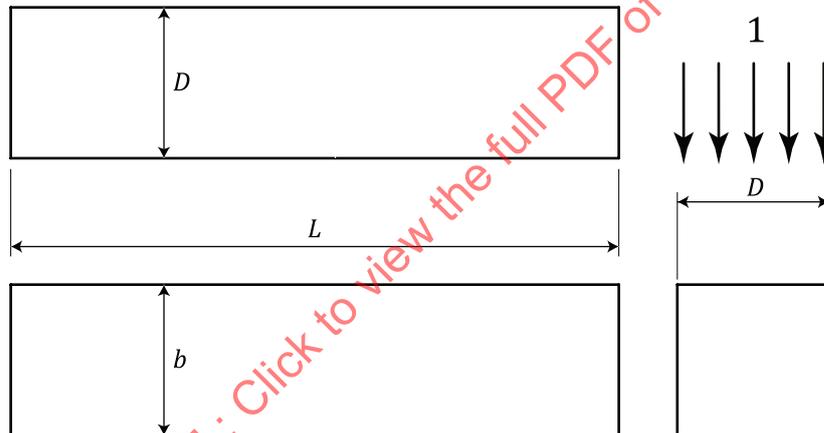

Key

- 1 direction of casting

Figure 2 — Test specimen

5.2 Fabrication of specimen

- a) The maximum aggregate size shall not be larger than 1/4 of the side length of the cross-section of the specimen.
- b) Moulds specified in ISO 1920-3:—, 5.2.1, shall be used.
- c) FRCC shall be placed continuously without joints. In case of flowable FRCC, pouring along the axial direction from one end of the mould is recommended. Internal vibrator and compacting rod/bar shall not be used.
- d) The dimension tolerance for the specimen cross-section is $\pm 0,5$ %.
- e) The mass of specimen shall be measured to the nearest 0,05 kg.
- f) The number of specimens shall not be less than six. When the number of specimens that do not show separated multiple cracks (see [Clause 1](#)) is more than one third of the total number of specimens, this document shall not be applied to that FRCC.

NOTE For FRCCs that do not show separated multiple cracks, see ISO 19044.

5.3 Loading of specimen

- a) The specimen shall be subjected to testing immediately after completion of the specified curing procedure.
- b) The specimen shall be tested in a position rotated 90° along its longitudinal axis with respect to the casting position.
- c) The specimen span shall be 3 *D* with a tolerance of ±2 %.

6 Test equipment

6.1 Testing machine


A testing machine complying with ISO 1920-4:—, 4.2.1, shall be used. A testing machine capable of operating in a controlled manner, i.e. producing a constant rate of displacement is also allowable to be used.

6.2 Loading apparatus

The device for applying loads shall consist of two upper rollers (indicated by 4 in [Figure 3](#)), two lower rollers (indicated by 6 in [Figure 3](#)), and two supports (indicated by 7 in [Figure 3](#)). Each roller, except one of the lower ones, shall be capable of being inclined in a plane normal to the longitudinal axis of the test specimen. Cup cone type of roller connections may be used instead of rollers.

NOTE [Figure 3](#) shows a typical example of the loading apparatus.

Both bottom supports should be movable, as the horizontal movement of the specimen is restrained at the loading block. Inserting multiple rods under both supports as shown in [Figure 3](#) is a simple and effective solution for a movable mechanism. In order to ensure the absence of horizontal restraint, it is advisable to press the specimen lightly by hand before applying any load to confirm smooth movement of the specimen in the horizontal direction.

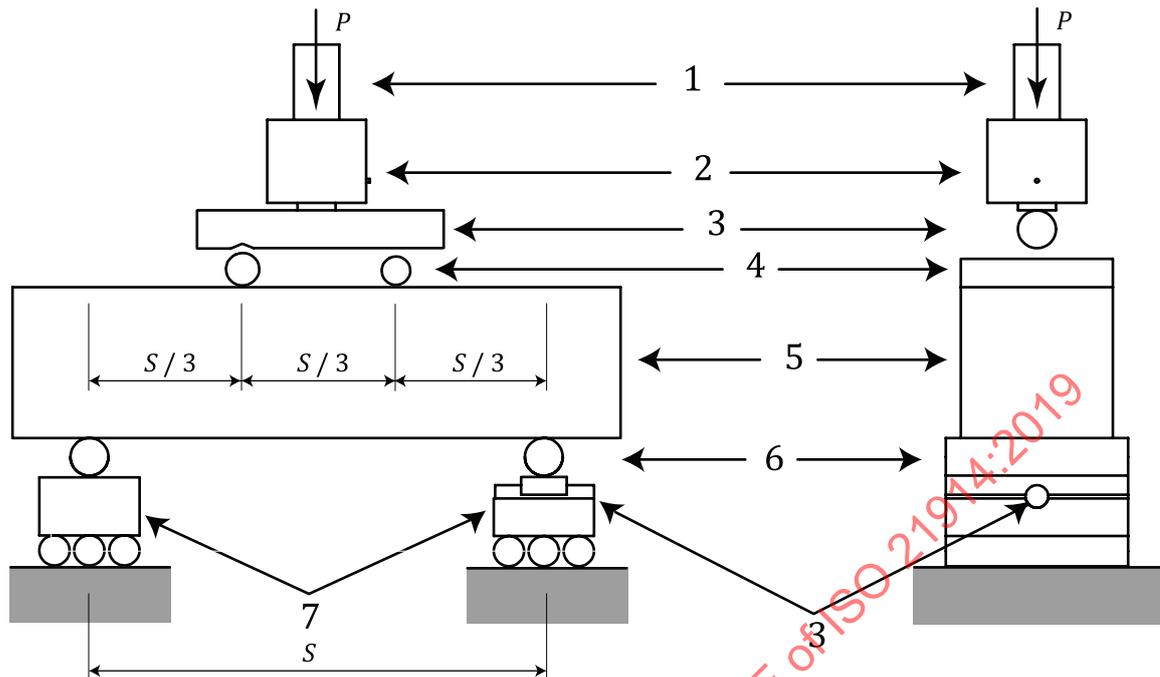

Key

- 1 machine head
- 2 load cell
- 3 round bar
- 4 upper roller
- 5 specimen
- 6 lower roller
- 7 support

Figure 3 — Example of loading apparatus


6.3 Measuring device for average curvature

The curvature measuring equipment shall consist of two linear variable displacement transducers (LVDTs) and jigs used for fixing LVDTs to the specimen. LVDTs having an accuracy of 1/500 mm or better shall be used for measuring the axial deformation of test specimen.

LVDTs shall be set to measure axial deformation in the constant moment span at positions of $0,15 D$ and $0,85 D$ from the lower surface of the test specimen as shown in [Figure 4](#). The contact length of LVDTs shall be equal to the pure bending span length ($S / 3$). The distance between two LVDTs shall be $0,7 D$. As shown in [Figure 5](#), the LVDTs shall be set via jigs to allow their rotation during testing when it is likely that such rotation is restricted.


NOTE 1 [Figure 6](#) shows typical examples of the jigs to set LVDTs. Other measuring equipment is applicable if the required accuracy is satisfied.

NOTE 2 Three or more LVDTs can be set to estimate the distribution of average strains.

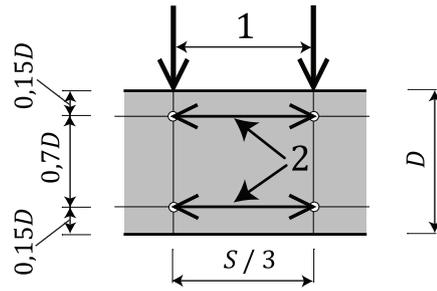

- Key**
- 1 constant moment span
 - 2 position of LVDTs

Figure 4 — Setup of LVDTs

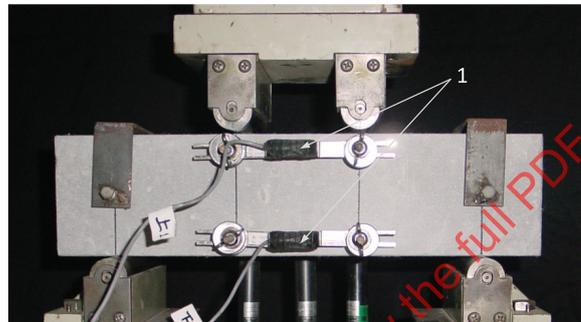


- Key**
- 1 pi-type LVDT

Figure 5 — Example of LVDT setup



Rotation bearing

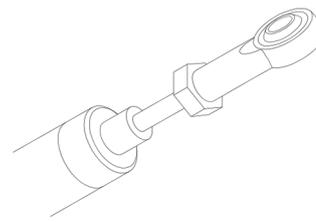

Rod end

Figure 6 — Examples of jigs

7 Test procedure

- a) Set the specimen on the loading apparatus as the casting surface shall be located on the side.
- b) Load the specimen continuously and without shock.
- c) The loading head of the testing machine shall be moved at a constant rate of $(0,3 \pm 0,2)$ mm/min.

Though it is desirable to keep the loading rate constant from the beginning through the end of testing, it can be increased within a range that does not affect substantially the bending moment-

curvature response, once the specimen is exhibiting a softening behaviour. The method of such a change in the loading rate shall be reported.

- d) Measure the load, and axial deformations by LVDTs, continuously from the beginning through the end of testing. The interval of digital measurement shall be not more than 5 seconds. A one-second intervals is recommended. Testing shall be continued until further loading leads to significant opening of one crack.
- e) When damage of the specimen concentrates outside of constant moment span, the corresponding test data should be discarded.

8 Calculations

The bending moment and average curvature shall be calculated using [Formulae \(1\)](#) and [\(2\)](#) to obtain the bending moment–curvature curve. Tensile strength and average ultimate tensile strain can be estimated following [Annex A](#).

$$M = \frac{P}{2} \cdot \frac{S}{3} \quad (1)$$

$$\varphi = \frac{\varepsilon_2 - \varepsilon_1}{d_0} \quad (2)$$

NOTE The average strain is the ratio of axial deformation to gauge length, without a unit. The location of neutral axis can be calculated from average strains.

9 Test report

The test report shall include the following items:

- a) FRCC composition;
- b) type and dimensions of fibres;
- c) volume fraction of fibres;
- d) curing conditions and history;
- e) date of mixing and loading;
- f) type of loading machine;
- g) specimen span;
- h) number of specimens;
- i) identification of test specimen;
- j) geometry of specimen;
- k) mass of specimen;
- l) loading rate;
- m) number of separated cracks in constant moment span;
- n) maximum load;
- o) maximum bending moment;
- p) average curvature at first cracking;

- q) average curvature at maximum load;
- r) bending moment-curvature curve.

NOTE Bending moment-average strain curves can be also reported.

STANDARDSISO.COM : Click to view the full PDF of ISO 21914:2019