

---

---

**Adhesives — Test methods for  
adhesives for plastic or rubber  
floor coverings or wall coverings  
— Determination of dimensional  
changes after accelerated ageing**

*Adhésifs — Méthodes d'essai des adhésifs pour revêtements de sol  
ou muraux en plastique ou en caoutchouc — Détermination des  
variations dimensionnelles après un vieillissement accéléré*

STANDARDSISO.COM : Click to view full PDF of ISO 22635:2019



STANDARDSISO.COM : Click to view the full PDF of ISO 22635:2019



**COPYRIGHT PROTECTED DOCUMENT**

© ISO 2019

All rights reserved. Unless otherwise specified, or required in the context of its implementation, no part of this publication may be reproduced or utilized otherwise in any form or by any means, electronic or mechanical, including photocopying, or posting on the internet or an intranet, without prior written permission. Permission can be requested from either ISO at the address below or ISO's member body in the country of the requester.

ISO copyright office  
CP 401 • Ch. de Blandonnet 8  
CH-1214 Vernier, Geneva  
Phone: +41 22 749 01 11  
Fax: +41 22 749 09 47  
Email: [copyright@iso.org](mailto:copyright@iso.org)  
Website: [www.iso.org](http://www.iso.org)

Published in Switzerland

# Contents

	Page
Foreword .....	iv
<b>1 Scope</b> .....	<b>1</b>
<b>2 Normative references</b> .....	<b>1</b>
<b>3 Terms and definitions</b> .....	<b>1</b>
<b>4 Principle</b> .....	<b>2</b>
<b>5 Apparatus and materials</b> .....	<b>2</b>
<b>6 Preparation of test specimens</b> .....	<b>4</b>
6.1 Conditioning of fibre cement substrate .....	4
6.2 Conditioning of test covering .....	5
6.2.1 Room temperature storage .....	5
6.2.2 Elevated temperature pre-treatment .....	5
6.3 Sampling and conditioning of adhesive .....	5
6.4 Datum points .....	5
6.4.1 Fixing of gauge positions .....	5
6.4.2 Edge to edge measurements .....	5
6.5 Initial measurements of dimensions prior to bonding .....	5
6.6 Preparation of bonded test specimens .....	6
6.6.1 Cleaning .....	6
6.6.2 Application of adhesive .....	6
6.6.3 Bonding .....	6
<b>7 Procedure</b> .....	<b>6</b>
7.1 Preconditioning .....	6
7.2 Conditioning cycle (accelerated ageing) .....	6
7.3 Subsequent cycles .....	6
<b>8 Evaluation and expression of results</b> .....	<b>7</b>
<b>9 Test report</b> .....	<b>7</b>

## Foreword

ISO (the International Organization for Standardization) is a worldwide federation of national standards bodies (ISO member bodies). The work of preparing International Standards is normally carried out through ISO technical committees. Each member body interested in a subject for which a technical committee has been established has the right to be represented on that committee. International organizations, governmental and non-governmental, in liaison with ISO, also take part in the work. ISO collaborates closely with the International Electrotechnical Commission (IEC) on all matters of electrotechnical standardization.

The procedures used to develop this document and those intended for its further maintenance are described in the ISO/IEC Directives, Part 1. In particular, the different approval criteria needed for the different types of ISO documents should be noted. This document was drafted in accordance with the editorial rules of the ISO/IEC Directives, Part 2 (see [www.iso.org/directives](http://www.iso.org/directives)).

Attention is drawn to the possibility that some of the elements of this document may be the subject of patent rights. ISO shall not be held responsible for identifying any or all such patent rights. Details of any patent rights identified during the development of the document will be in the Introduction and/or on the ISO list of patent declarations received (see [www.iso.org/patents](http://www.iso.org/patents)).

Any trade name used in this document is information given for the convenience of users and does not constitute an endorsement.

For an explanation of the voluntary nature of standards, the meaning of ISO specific terms and expressions related to conformity assessment, as well as information about ISO's adherence to the World Trade Organization (WTO) principles in the Technical Barriers to Trade (TBT) see [www.iso.org/iso/foreword.html](http://www.iso.org/iso/foreword.html).

This document was prepared by Technical Committee ISO/TC 61, *Plastics*, Subcommittee SC 11, *Products*.

Any feedback or questions on this document should be directed to the user's national standards body. A complete listing of these bodies can be found at [www.iso.org/members.html](http://www.iso.org/members.html).

# Adhesives — Test methods for adhesives for plastic or rubber floor coverings or wall coverings — Determination of dimensional changes after accelerated ageing

**SAFETY PRECAUTIONS** — Persons using this document should be familiar with the normal laboratory practice, if applicable. This document does not purport to address all of the safety problems, if any, associated with its use. It is the responsibility of the user to establish appropriate safety and health practices.

**ENVIRONMENTAL STATEMENT** — It is understood that some of the material permitted in this document may have negative environmental impact. As technological advantages lead to acceptable alternatives for these materials, they will be eliminated from this document to the extent possible. At the end of the test, it is essential that the user of this document take care to carry out an appropriate disposal of the wastes.

## 1 Scope

This document specifies a test method that measures the dimensional changes of a plastic or rubber floor or wall covering bonded to a given substrate after accelerated ageing. The term “wall covering” does not include any type of wallpaper.

## 2 Normative references

The following documents are referred to in the text in such a way that some or all of their content constitutes requirements of this document. For dated references, only the edition cited applies. For undated references, the latest edition of the referenced document (including any amendments) applies.

ISO 472, *Plastics — Vocabulary*

ISO 554, *Standard atmospheres for conditioning and/or testing — Specifications*

ISO 9142, *Adhesives — Guide to the selection of standard laboratory ageing conditions for testing bonded joints*

ISO 15605, *Adhesives — Sampling*

EN 1067, *Adhesives — Examination and preparation of samples for testing*

## 3 Terms and definitions

For the purposes of this document, the terms and definitions given in ISO 472 and the following apply.

ISO and IEC maintain terminological databases for use in standardization at the following addresses:

- ISO Online browsing platform: available at <https://www.iso.org/obp>
- IEC Electropedia: available at <http://www.electropedia.org/>

### 3.1

#### covering

flexible resilient or textile floor covering or wall covering

**3.2 adhesive for coverings**


adhesive which is intended to produce firm and durable bonds between *coverings* (3.1) and various substrates

**4 Principle**

This test method gives a measure of the suitability of a plastic or rubber floor or wall covering/adhesive combination by monitoring dimensional changes during defined conditioning sequences when bonded to a specific substrate.

**5 Apparatus and materials**

**5.1 Notched trowel** (for the shape of the notch, see [Figure 1](#)), with dimensions *a*, *b* and *c* specified by the adhesive manufacturer.

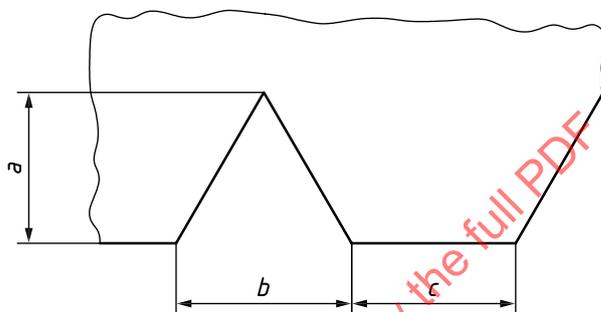

**Key**

- a* notch depth
- b* notch width
- c* notch distance

**Figure 1 — Shape of notches of notched trowels**

**5.2 Roller**, of width  $(60 \pm 5)$  mm, diameter  $(90 \pm 5)$  mm and total mass  $(3,50 \pm 0,05)$  kg with a handle at  $90^\circ$  to the axis (as an example, see [Figure 2](#)).

Dimensions in millimetres

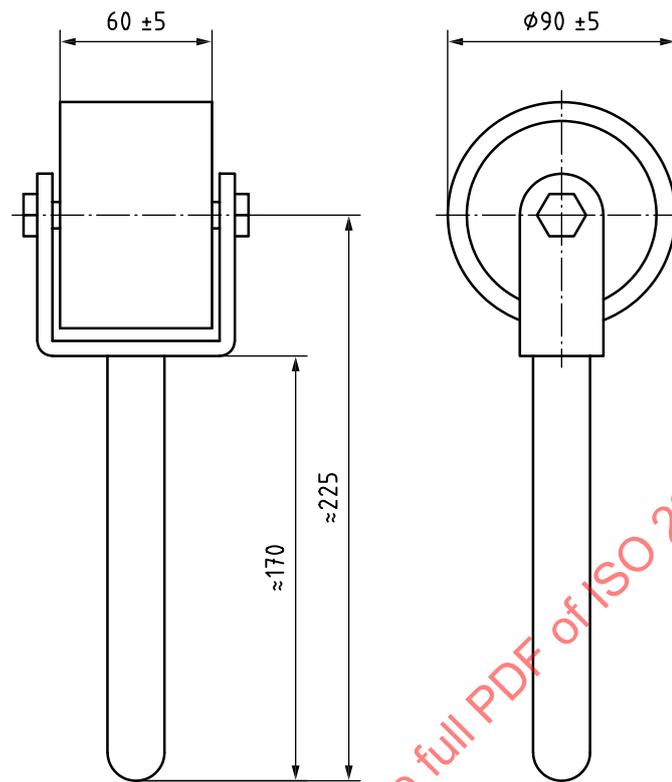


Figure 2 – Roller

NOTE The length of the handle is not critical and can be used for setting the total mass.

**5.3 Heating chamber**, ventilated and adjustable to a temperature between 20 °C and 200 °C according to ISO 9142.

**5.4 Primer**, if applicable.


**5.5 Test covering**, three test pieces for each combination with adhesive dimensions of  $(250 \pm 5)$  mm  $\times$   $(250 \pm 5)$  mm or  $(300 \pm 5)$  mm  $\times$   $(300 \pm 5)$  mm.

**5.6 Substrate**, one uncoated fibre cement panel, fully compressed and autoclaved, of a minimum thickness of approximately 8,0 mm for each test piece. Dimensions shall not be greater than 50 mm longer than the distance between the datum points, i.e. each datum point shall not be greater than  $(25 \pm 1)$  mm from the outer edge (see [Figure 3](#)).

NOTE The thickness is not critical.

Depending on the source of the fibre cement panels the surfaces can differ with respect to gloss, absorbency and strength. In this case, it is important to do some preliminary assessment (i.e. peel tests) of the panels to identify the preferred side for testing. The preferred side is referred to as the upper side of the substrate in this document.

Dimensions in millimetres

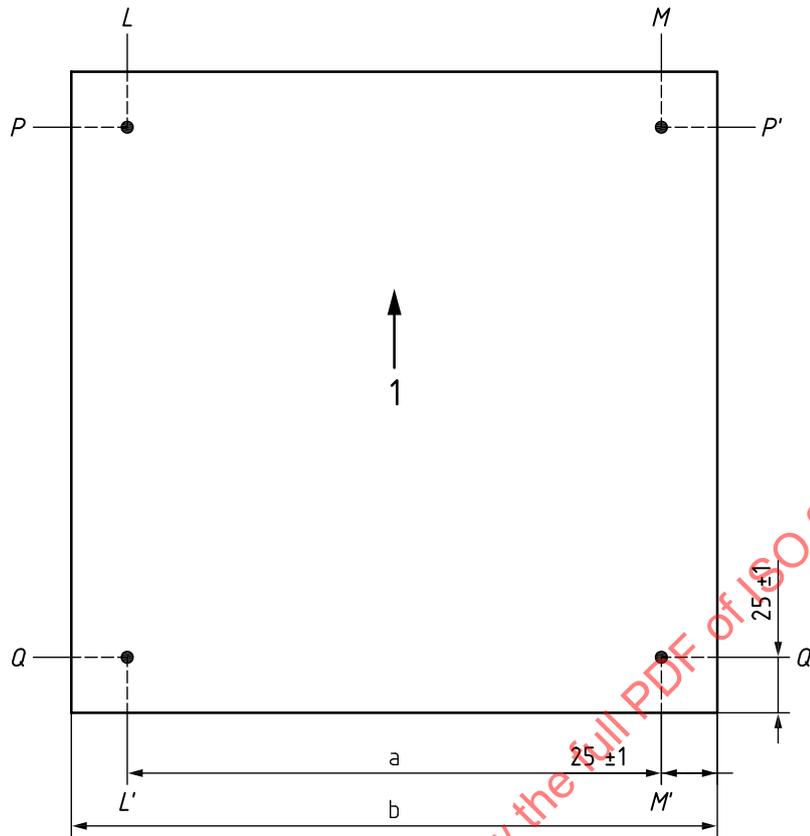

**Key**

- 1 grain direction
- L, M starting points for dimension measurement parallel to the grain
- L', M' end points for dimension measurement parallel to the grain
- P, Q starting points for dimension measurement perpendicular to the grain
- P', Q' end points for dimension measurement perpendicular to the grain
- a Measurements between studs.
- b Edge to edge measurements.

**Figure 3 — Measurements**

Where edge to edge measurements are being carried out, recommended dimensions are approximately 300 mm × 300 mm.

**5.7 Suitable measuring devices**, capable of measuring to the nearest 0,01 mm over a length of either 200 mm or 250 mm, such as an elongation meter.

**5.8 Adhesives**, for fixing gauge studs to the covering surface if required by the measuring method.

**6 Preparation of test specimens**

**6.1 Conditioning of fibre cement substrate**

Place the test panels (5.6) in a heating chamber (5.3) for 6 h at (80 ± 2) °C. Ensure that the test panels are spaced in such a way as to enable a free passage of air over them. At the end of this period, remove

the test panels from the heating chamber (5.3) and store in a standard atmosphere of  $(23 \pm 2)$  °C and  $(50 \pm 5)$  % relative humidity for at least 48 h prior to use.

## 6.2 Conditioning of test covering

### 6.2.1 Room temperature storage

Condition all test pieces (5.5) in a standard atmosphere of  $(23 \pm 2)$  °C and  $(50 \pm 5)$  % relative humidity for at least 24 h prior to use.

### 6.2.2 Elevated temperature pre-treatment

Place the test pieces (5.5) on a firm horizontal substrate (5.6) and heat for 6 h in a heating chamber (5.3) at  $(80 \pm 2)$  °C. Ensure that the test pieces and substrate are spaced in such a way as to enable a free passage of air over them. At the end of this period, remove the test pieces and supports from the heating chamber and store for 48 h in a standard atmosphere of  $(23 \pm 2)$  °C and  $(50 \pm 5)$  % relative humidity prior to use.

The pre-treatment will release any stresses in the covering so that it is in a relaxed state when the actual test is commenced. The pre-treatment of the test coverings may be run together with the conditioning of the substrate (6.1).

In most cases, a more practical assessment is required. Pre-conditioning of the floor or wall covering materials at elevated temperature may not be regarded as necessary. If knowledge of dimensional changes after this pre-treatment is required, dimensions should be measured as given in 6.5 before and after the pre-treatment.

## 6.3 Sampling and conditioning of adhesive

Take a sample in accordance with ISO 15605 of the adhesive to be tested and examine and prepare it in accordance with EN 1067.

Condition the adhesive in a standard atmosphere of  $(23 \pm 2)$  °C and  $(50 \pm 5)$  % relative humidity for at least 24 h before making the test specimens, in accordance with ISO 554.

## 6.4 Datum points

### 6.4.1 Fixing of gauge positions

Using the appropriate adhesive, fix the gauge studs in four positions, each being  $(25 \pm 1)$  mm from the outer edge of the covering (see Figure 3).

### 6.4.2 Edge to edge measurements

Test specimens shall be marked at positions  $(25 \pm 1)$  mm from each edge.

## 6.5 Initial measurements of dimensions prior to bonding

Measure the dimension of each test piece along the two datum lines LL' and MM' parallel to its grain, when this can be identified, (longitudinally) and the two datum lines PP' and QQ' at right angles to these lines (transversely). Record as measurement A.

Depending on the type of measuring device to be used, the measurements may be made from edge to edge or from scribe datum marks as described previously (see Figure 3).