

# INTERNATIONAL STANDARD

# ISO 22651

First edition  
2002-09-15

---

---

## Footwear — Test methods for insoles — Dimensional stability

*Chaussures — Méthodes d'essai relatives aux premières de montage —  
Stabilité dimensionnelle*

STANDARDSISO.COM : Click to view the full PDF of ISO 22651:2002



Reference number  
ISO 22651:2002(E)

© ISO 2002

**PDF disclaimer**

This PDF file may contain embedded typefaces. In accordance with Adobe's licensing policy, this file may be printed or viewed but shall not be edited unless the typefaces which are embedded are licensed to and installed on the computer performing the editing. In downloading this file, parties accept therein the responsibility of not infringing Adobe's licensing policy. The ISO Central Secretariat accepts no liability in this area.

Adobe is a trademark of Adobe Systems Incorporated.

Details of the software products used to create this PDF file can be found in the General Info relative to the file; the PDF-creation parameters were optimized for printing. Every care has been taken to ensure that the file is suitable for use by ISO member bodies. In the unlikely event that a problem relating to it is found, please inform the Central Secretariat at the address given below.

STANDARDSISO.COM : Click to view the full PDF of ISO 22651:2002

© ISO 2002

All rights reserved. Unless otherwise specified, no part of this publication may be reproduced or utilized in any form or by any means, electronic or mechanical, including photocopying and microfilm, without permission in writing from either ISO at the address below or ISO's member body in the country of the requester.

ISO copyright office  
Case postale 56 • CH-1211 Geneva 20  
Tel. + 41 22 749 01 11  
Fax + 41 22 749 09 47  
E-mail [copyright@iso.ch](mailto:copyright@iso.ch)  
Web [www.iso.ch](http://www.iso.ch)

Printed in Switzerland

## Foreword

ISO (the International Organization for Standardization) is a worldwide federation of national standards bodies (ISO member bodies). The work of preparing International Standards is normally carried out through ISO technical committees. Each member body interested in a subject for which a technical committee has been established has the right to be represented on that committee. International organizations, governmental and non-governmental, in liaison with ISO, also take part in the work. ISO collaborates closely with the International Electrotechnical Commission (IEC) on all matters of electrotechnical standardization.

International Standards are drafted in accordance with the rules given in the ISO/IEC Directives, Part 3.

The main task of technical committees is to prepare International Standards. Draft International Standards adopted by the technical committees are circulated to the member bodies for voting. Publication as an International Standard requires approval by at least 75 % of the member bodies casting a vote.

Attention is drawn to the possibility that some of the elements of this International Standard may be the subject of patent rights. ISO shall not be held responsible for identifying any or all such patent rights.

ISO 22651 was prepared by CEN (as EN 12800:2000) and was adopted, under a special "fast-track procedure", by Technical Committee ISO/TC 216, *Footwear*, in parallel with its approval by the ISO member bodies.

For the purposes of international standardization, a list of corresponding International and European Standards for which equivalents are not given in EN 12800 has been added as annex ZZ.

**Contents**

	<b>Page</b>
Foreword .....	3
1 Scope .....	4
2 Normative references .....	4
3 Definitions .....	4
4 Apparatus and material .....	4
5 Sampling and conditioning .....	5
6 Test method .....	5
7 Expression of results .....	6
8 Test report .....	7

STANDARDSISO.COM : Click to view the full PDF of ISO 22651:2002

## Foreword

This European Standard has been prepared by Technical Committee CEN/TC 309 "Footwear", the secretariat of which is held by AENOR.

This European Standard shall be given the status of a national standard, either by publication of an identical text or by endorsement, at the latest by August 2000, and conflicting national standards shall be withdrawn at the latest by August 2000.

According to the CEN/CENELEC Internal Regulations, the national standards organizations of the following countries are bound to implement this European Standard: Austria, Belgium, Czech Republic, Denmark, Finland, France, Germany, Greece, Iceland, Ireland, Italy, Luxembourg, Netherlands, Norway, Portugal, Spain, Sweden, Switzerland and the United Kingdom.

STANDARDSISO.COM : Click to view the full PDF of ISO 22651:2002



## 1 Scope

This European standard specifies a method for the determination of the dimensional stability of insoles, irrespective of the material, after immersion in water.

## 2 Normative references

This European Standard incorporates by dated or undated reference, provisions from other publications. These normative references are cited at the appropriate places in the text and the publications are listed hereafter. For dated references, subsequent amendments to, or revisions of, any of these publications apply to this European Standard only when incorporated into it by amendment or revision. For undated references the latest edition of the publication referred to applies.

EN 12222            *Footwear – Standard atmospheres for conditioning and testing of footwear and components for footwear.*

prEN 13400:1998   *Footwear – Sampling location of components for footwear.*

## 3 Definitions

For the purposes of this standard the following definitions apply:

### 3.1

#### **swelling**

gain in thickness, expressed as a percentage, after leaving the test piece of insole material submerged in water for 6 h

### 3.2

#### **increase in size**

increase in length and in width, expressed as a percentage, after leaving the test piece of insole material in water for 6 h

### 3.3

#### **shrinkage**

reduction in length and width, expressed as a percentage, of a test piece of insole material after leaving the test piece in an oven at 35 °C for 24 h

### 3.4

#### **dimensional stability**

the change in the distance between two reference points on a test piece before and after specified test conditions (e.g. heat, moisture) expressed as a percentage of the initial distance

## 4 Apparatus and material

The following apparatus and material shall be used:

**4.1 Dial micrometer gauge**, standing on a firm base and loaded with a dead mass such that the presser foot applies a pressure of  $50 \text{ kPa} \pm 5 \text{ kPa}$ <sup>1</sup>. The gauge has a presser foot which is flat, circular and 10,0 mm in diameter.

---

<sup>1</sup>  $1 \text{ Pa} = 1 \text{ N/m}^2$

The gauge has scale divisions of 0,01 mm.

**4.2 Measuring device - Vernier calipers or similar**, capable of measuring to an accuracy of 0,1 mm.

**4.3 Glass** or flat bottomed container of an adequate size such that the test piece can be placed in the bottom.

**4.4 Oven**, for heating the test piece to 35 °C and thermostatically controlled so that the test piece is kept within 1 °C of the required temperature during the heating period.

**4.5 Distilled water**

## 5 Sampling and conditioning

From the shoe insoles, cut insoles, or component as supplied, cut two square or rectangular test pieces of  $(60 \text{ mm} \pm 20 \text{ mm}) \times (60 \text{ mm} \pm 20 \text{ mm})$ , one to determine swelling and size growth and the other to determine shrinking. According to the given dimensions, cut the test pieces as big as the sample will allow.

If the test pieces are taken from the shoes or cut component, sampling shall be done according to prEN 13400:1998.

Condition the test pieces according to EN 12222, for a minimum of 24 h.

## 6 Test method

### 6.1 Swelling and increase in size

On one of the conditioned test pieces trace parallel lines 5 mm in from each side. Label the corners of the square or rectangle formed A, B, C and D (see figure 1). Trace diagonals AD and BC. Mark the centre E and the half way points of the diagonals AE, BE, CE and ED and label them F, G, H and I.

Measure the distances between the points A-B, C-D, A-C and B-D with a measuring device.

Measure the thickness at points E, F, G, H and I with the dial micrometer gauge.

Submerge the test piece in distilled water for 6 hours.

The test piece must be fully submerged in water being loaded with a small weight

Take the test piece out of the water and eliminate superficial drops of water.

Measure the distances AB, CD, AC and BD again and the thickness at points E, F, G, H and I.

### 6.2 Shrinkage

On the other conditioned test piece mark parallel lines in the same way as in 6.1 (see figure 1). Measure distances A-B, C-D, A-C and B-D.

Leave the test piece in the drying oven (see 4.4) for 24 h. Then measure again the distances A-B, C-D, A-C and B-D.

## 7 Expression of results

### 7.1 Swelling

Calculate the average value of the five thicknesses  $e_o$ .

Calculate the average value of the five thicknesses after removing the test piece from the water  $e_t$ .

Swelling,  $H$ , is calculated as a percentage (%) from the equation:

$$H = \frac{e_t - e_o}{e_o} \times 100$$

Where:

$e_t$  is the thickness of test piece when wet

$e_o$  is the thickness of test piece when dry

Express the result to the nearest 0,5 %.

### 7.2 Increase in size

Calculate the average value of the initial distances A-B and C-D measured in accordance with 6.1 and call it  $a_1$ . In the same way find the average of the initial distances A-C and B-D and call it  $b_1$ .

In the same way calculate the averages of the same distances measured after taking the test pieces out of the water and call it  $a_2$  for the distances A-B and C-D and  $b_2$  for distances A-C and B-D.

Calculate the increase in size,  $V$ , expressed as a percentage, from the equations:

$$V_a = \frac{a_2 - a_1}{a_1} \times 100$$

(Increase in size in direction a)

$$V_b = \frac{b_2 - b_1}{b_1} \times 100$$

(Increase in size in direction b)

Express the result to the nearest 0,5 %.

### 7.3 Shrinkage

Calculate the average of the distances A-B and C-D measured in accordance with 6.2 and call it  $a_o$ .

In the same way find the average of the distances A-C and B-D and call it  $b_o$ .

Calculate the averages of the same distances measured after leaving the test piece for 24 h in the oven at 35 °C and call them  $a_{24}$  and  $b_{24}$ .

Calculate the shrinkage  $S$ , as a percentage, from the equations:

$$S_a = \frac{a_0 - a_{24}}{a_0} \times 100$$

and

$$S_b = \frac{b_0 - b_{24}}{b_0} \times 100$$

Express the result to the nearest 0,5 %.

The result will be the average of the two values.

## 8 Test report

The test report shall include the following information:

- a) the results for swelling, increase in size and shrinkage expressed according to 7.1, 7.2 and 7.3;
- b) full description of the samples tested including commercial styles codes, colours, nature, etc.;
- c) description of sampling procedure, where relevant;
- d) reference to the method of test;
- e) details of any deviation from the standard test procedure;
- f) any deviations from the test method;
- g) date of testing.

STANDARDSISO.COM : Click to view the full PDF of ISO 22651:2002

Dimensions in millimetres

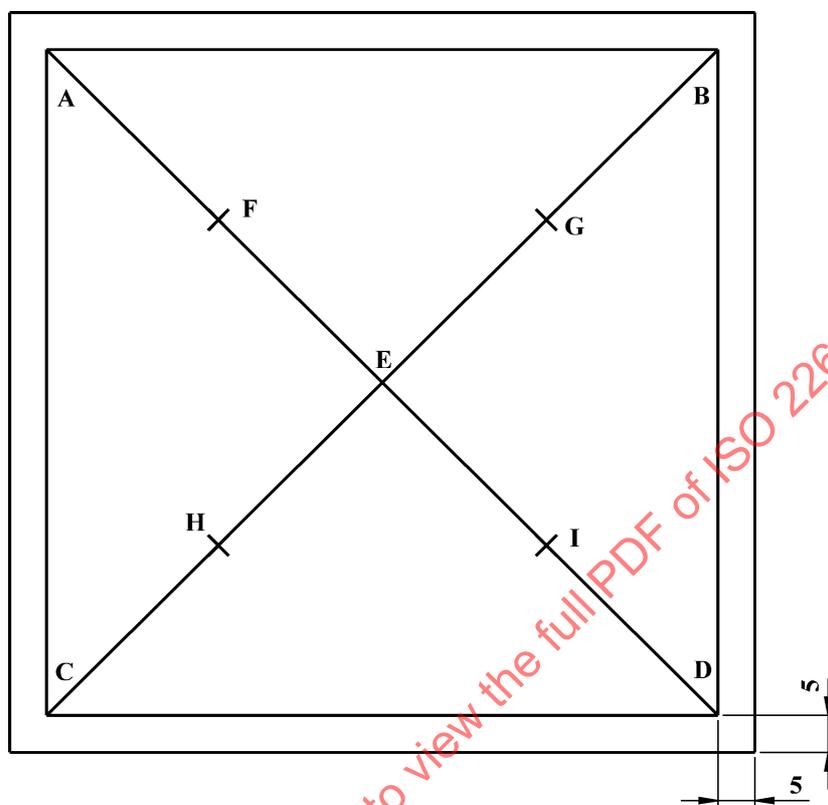


Figure 1 – Marking of the test piece

STANDARDSISO.COM : Click to view the full PDF of ISO 22651:2002