

INTERNATIONAL
STANDARD

ISO
22843

First edition
2020-08

**Rubber bands — General
requirements and test methods**

STANDARDSISO.COM : Click to view the full PDF of ISO 22843:2020



Reference number
ISO 22843:2020(E)

© ISO 2020

STANDARDSISO.COM : Click to view the full PDF of ISO 22843:2020



COPYRIGHT PROTECTED DOCUMENT

© ISO 2020

All rights reserved. Unless otherwise specified, or required in the context of its implementation, no part of this publication may be reproduced or utilized otherwise in any form or by any means, electronic or mechanical, including photocopying, or posting on the internet or an intranet, without prior written permission. Permission can be requested from either ISO at the address below or ISO's member body in the country of the requester.

ISO copyright office
CP 401 • Ch. de Blandonnet 8
CH-1214 Vernier, Geneva
Phone: +41 22 749 01 11
Email: copyright@iso.org
Website: www.iso.org

Published in Switzerland

Contents

	Page
Foreword	iv
1 Scope	1
2 Normative references	1
3 Terms and definitions	1
4 Classification	2
5 Requirements	2
5.1 General	2
5.2 Dimensions	2
5.3 Physical properties	3
6 Test methods	3
6.1 General	3
6.2 Dimensions	3
6.3 Tensile properties	4
6.3.1 Test method A: Tube sample	4
6.3.2 Test method B: Ring sample	5
6.4 Tension set	6
6.5 Density	7
6.6 Accelerated-ageing test	7
7 Packaging	7
8 Marking	7

STANDARDSISO.COM : Click to view the full PDF of ISO 22843:2020

Foreword

ISO (the International Organization for Standardization) is a worldwide federation of national standards bodies (ISO member bodies). The work of preparing International Standards is normally carried out through ISO technical committees. Each member body interested in a subject for which a technical committee has been established has the right to be represented on that committee. International organizations, governmental and non-governmental, in liaison with ISO, also take part in the work. ISO collaborates closely with the International Electrotechnical Commission (IEC) on all matters of electrotechnical standardization.

The procedures used to develop this document and those intended for its further maintenance are described in the ISO/IEC Directives, Part 1. In particular, the different approval criteria needed for the different types of ISO documents should be noted. This document was drafted in accordance with the editorial rules of the ISO/IEC Directives, Part 2 (see www.iso.org/directives).

Attention is drawn to the possibility that some of the elements of this document may be the subject of patent rights. ISO shall not be held responsible for identifying any or all such patent rights. Details of any patent rights identified during the development of the document will be in the Introduction and/or on the ISO list of patent declarations received (see www.iso.org/patents).

Any trade name used in this document is information given for the convenience of users and does not constitute an endorsement.

For an explanation of the voluntary nature of standards, the meaning of ISO specific terms and expressions related to conformity assessment, as well as information about ISO's adherence to the World Trade Organization (WTO) principles in the Technical Barriers to Trade (TBT) see www.iso.org/iso/foreword.html.

This document was prepared by Technical Committee ISO/TC 45, *Rubber and rubber products*, Subcommittee SC 4, *Products (other than hoses)*.

Any feedback or questions on this document should be directed to the user's national standards body. A complete listing of these bodies can be found at www.iso.org/members.html.

Rubber bands — General requirements and test methods

1 Scope

This document specifies general requirements and relevant test methods for rubber bands made of dry natural rubber used for general purposes such as for daily wrapping or packaging.

This document is not applicable for cover rubber bands made of blend and synthetic rubbers. This document is not applicable for rubber bands used for engineering applications, for food contact, nor for medical uses.

2 Normative references

The following documents are referred to in the text in such a way that some or all of their content constitutes requirements of this document. For dated references, only the edition cited applies. For undated references, the latest edition of the referenced document (including any amendments) applies.

ISO 37, *Rubber, vulcanized or thermoplastic — Determination of tensile stress-strain properties*

ISO 188, *Rubber, vulcanized or thermoplastic — Accelerated ageing and heat resistance tests*

ISO 2781, *Rubber, vulcanized or thermoplastic — Determination of density*

ISO 23529, *Rubber — General procedures for preparing and conditioning test pieces for physical test methods*

3 Terms and definitions

For the purposes of this document, the following terms and definitions apply.

ISO and IEC maintain terminological databases for use in standardization at the following addresses:

- ISO Online browsing platform: available at <https://www.iso.org/obp>
- IEC Electropedia: available at <http://www.electropedia.org/>

3.1

rubber band

elastic circular band used for holding things together

3.2

lay flat length

half of the inner circumference of the *rubber band* (3.1)

Note 1 to entry: See [Figure 1](#).

3.3

cut-width

distance between the two cut surfaces of the *rubber band* (3.1)


Note 1 to entry: See [Figure 1](#).

3.4

thickness

half the difference between the inside diameter and outside diameter of the *rubber band* (3.1)

Note 1 to entry: See [Figure 1](#).

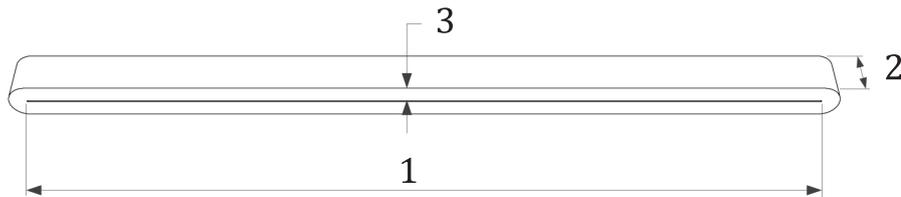

Key

- 1 lay flat length
- 2 cut-width
- 3 thickness

Figure 1 — Lay flat length, cut-width and thickness of a rubber band

4 Classification

Rubber bands are classified into three types:

- Type 1, bands with low modulus;
- Type 2, bands with moderate to high modulus;
- Type 3, bands without modulus requirement.

5 Requirements

5.1 General

Rubber bands shall have a uniform finish and free from discoloration, thin spots, air bubbles, embedded particles, tackiness, and other blemishes likely to affect its serviceability (through a visual inspection).

5.2 Dimensions

The dimensions (lay flat length, cut-width and thickness) of rubber bands shall be, unless agreed between the manufacturer and the buyer otherwise, designated as marking. The tolerances on dimensions are given in [Table 1](#).

Table 1 — Tolerances for dimensions of rubber bands

Dimensions	Tolerance
Lay flat length	
— less than 25 mm	±8,0 %
— between 25 mm and 100 mm	±5,0 %
— above 100 mm	±3,2 %
Thickness	
— less than 1 mm	±0,2 mm
— between 1 mm and 1,6 mm	±0,3 mm
— above 1,6 mm	±15 %
Cut-width	
— less than 3 mm	±10 %
— between 3 mm and 12 mm	±9 %
— above 12 mm	±7 %

5.3 Physical properties

Physical properties of rubber bands shall comply with the requirements given in [Table 2](#).

Table 2 — Required physical properties

Physical properties	Requirements			Test method
	Type 1	Type 2	Type 3	
Modulus at 300 % elongation, MPa	≤2,0	>2,0	Not required	6.3
Tensile strength, MPa, min.				
— tube sample	17,0	15,5	10,0	6.3.1
— ring sample	17,0	15,5	10,0	6.3.2
Elongation at break, %, min.				
— tube sample	700	650	500	6.3.1
— ring sample	600	550	450	6.3.2
Tension set, %, max.	7	10	13	6.4
Density, g/cm ³ , max.	1,0	1,1	1,3	6.5
After accelerated-ageing test				6.6
Change in tensile strength, %, max.	20	20	20	
Change in elongation at break, %, max.	20	20	20	

6 Test methods

6.1 General

All measurements shall be made at standard laboratory temperature after conditioning in accordance with ISO 23529 for at least 3 h.


6.2 Dimensions

Only perform the dimension measurement on the finish rubber band products, not on the uncut rubber tube.

6.2.1 For each dimension, a minimum of three pieces of rubber bands shall be measured and the average value shall be reported.

6.2.2 For lay flat length, cut a rubber band test piece to open its loop and place a strip on flat surface. The measurement shall be made on the inner side of the strip to the nearest 0,1 mm using appropriated measuring devices e.g. vernier caliper, calibrated tape and ruler. The lay flat length shall be reported as half the measured length of the strip.

Alternatively, an assisting tool may be employed to measure the lay flat length providing that its accuracy is appropriate. The example of the assisting tool is shown in [Figure 2](#).

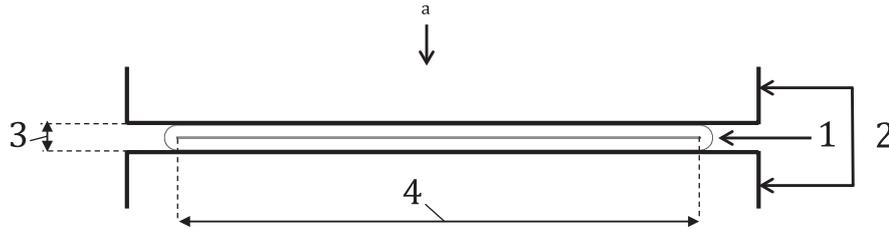

Key

- 1 rubber band
- 2 assisting tool
- 3 twice the thickness
- 4 lay flat length
- a Pressing direction.

Figure 2 — Assisting tool for the measurement of lay flat length

6.2.3 For cut-width, the measurements shall be made at four approximately equally spaced positions around the ring. Measure the cut-width to the nearest of 0,1 mm using suitable measuring devices e.g. vernier caliper, calibrated tape and magnifying microscope. The average value of each set of measurements shall be recorded.

6.2.4 For thickness, the measurements shall be made at four approximately equally spaced positions around the ring. Measure the thickness to the nearest of 0,01 mm using a thickness gauge. The average value of each set of measurements shall be recorded.

In some cases, the rubber bands can be cut or stacked before measuring the thickness. Other suitable measuring devices, e.g. magnifying microscope and force gauge, can be employed providing that their accuracy are appropriate.



6.3 Tensile properties

Where test pieces are required, they may be taken from an uncut tube shape sample (tube sample) or a finish product (ring sample). The tube sample is cut to dumb-bell-shaped type 1A or type 2 whilst the ring sample is used as it is.

Dumb-bell and ring test pieces do not necessarily give the same values for their respective tensile properties. The results obtained for a sample are likely to vary according to the type of test pieces used as well as the different formulations. Therefore, in case of dispute, the dumb-bell test piece shall be used for the referee test.

6.3.1 Test method A: Tube sample

Tensile properties shall be measured in accordance with ISO 37 using dumb-bell type 1A or type 2 test pieces. A dumb-bell test piece shall be cut across the direction of extrusion of uncut tubes (see [Figure 3](#)). A minimum of three test specimens shall be taken and the median value shall be reported. In case of dispute, dumb-bell type 2 is the preferred test method.

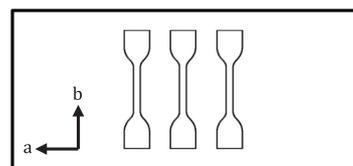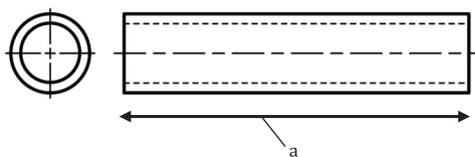

a) Uncut tube rubber band sample

b) Dumb-bell cutting direction

Key

- a Direction of extrusion.
- b Dumb-bell cutting direction.


Figure 3 — An uncut tube sample and cutting direction for dumb-bell test pieces

In case of a small tube sample, dumb-bell cutting across the direction of extrusion cannot be conducted, test method B shall be performed.

6.3.2 Test method B: Ring sample

6.3.2.1 An example of a rig for tensile property tests on ring samples is shown in [Figure 4](#). An upper and a lower roller grips shall have a flat surface with diameter (C_p) suitable to the ring sample sizes. The upper roller grip shall be free to turn with very low friction and the lower roller grip shall be driven to rotate the ring with speed between 10 rpm and 15 rpm.

6.3.2.2 Measure the cut-width and the thickness of test pieces as described in [6.2.3](#) and [6.2.4](#), respectively. The minimum value of each set of measurements shall be used for calculation.

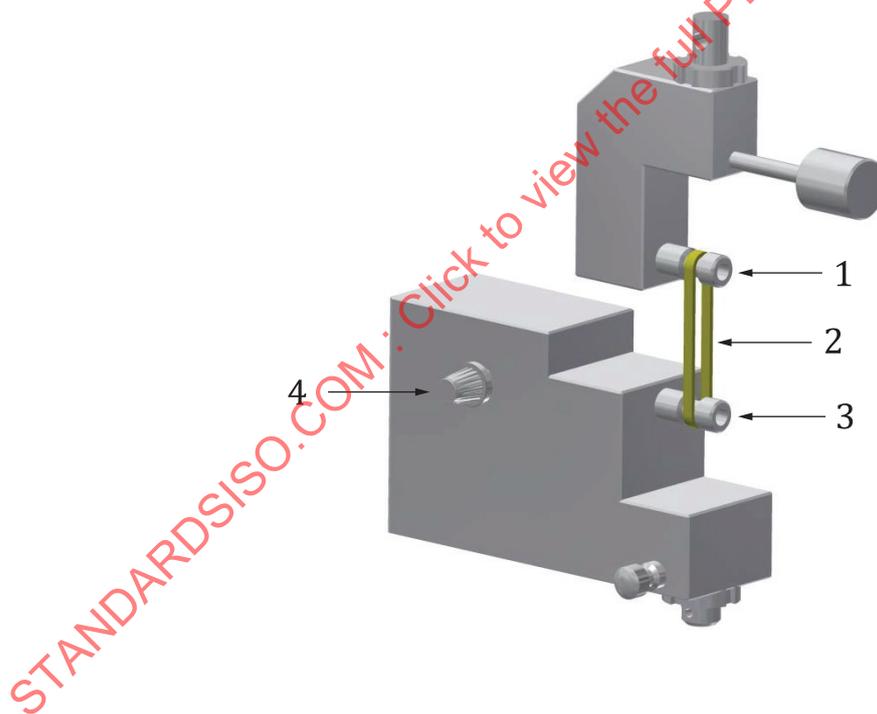**Key**

- 1 upper roller grip
- 2 rubber band
- 3 lower roller grip
- 4 rolling speed adjusting knob

Figure 4 — Example of rig for tensile property test on ring samples

6.3.2.3 Adjust the initial distance between the upper and the lower roller grips. The distance between the two rollers should be enough to hold the samples with a minimum stress. Set the load to zero before