
**Sheet materials — Determination
of water vapour transmission rate
(WVTR) — Gravimetric (dish) method**

*Matériaux en feuilles — Détermination du coefficient de transmission
de la vapeur d'eau — Méthode (de la capsule) par gravimétrie*

STANDARDSISO.COM : Click to view the full PDF of ISO 2528:2017



STANDARDSISO.COM : Click to view the full PDF of ISO 2528:2017



COPYRIGHT PROTECTED DOCUMENT

© ISO 2017, Published in Switzerland

All rights reserved. Unless otherwise specified, no part of this publication may be reproduced or utilized otherwise in any form or by any means, electronic or mechanical, including photocopying, or posting on the internet or an intranet, without prior written permission. Permission can be requested from either ISO at the address below or ISO's member body in the country of the requester.

ISO copyright office
Ch. de Blandonnet 8 • CP 401
CH-1214 Vernier, Geneva, Switzerland
Tel. +41 22 749 01 11
Fax +41 22 749 09 47
copyright@iso.org
www.iso.org

Contents

Page

Foreword.....	iv
Introduction.....	v
1 Scope.....	1
2 Normative references.....	1
3 Terms and definitions.....	1
4 Principle.....	2
5 Apparatus and material.....	2
6 Sampling.....	5
7 Conditioning.....	5
8 Preparation of test pieces.....	5
9 Preparation of dishes.....	6
9.1 General.....	6
9.2 Use of wax and a cover template [5.3 b]).....	6
9.3 Use of wax and a ring template [5.3 a]).....	6
10 Procedure.....	6
10.1 General method.....	6
10.2 Use of blank assemblies.....	7
10.3 Creased sheet.....	7
11 Expression of results.....	7
12 Precision.....	8
13 Test report.....	8
Annex A (normative) Method for determination of water vapour transmission rate of creased materials.....	9
Annex B (normative) Test conditions.....	13
Annex C (informative) Sealing waxes.....	14
Bibliography.....	15

Foreword

ISO (the International Organization for Standardization) is a worldwide federation of national standards bodies (ISO member bodies). The work of preparing International Standards is normally carried out through ISO technical committees. Each member body interested in a subject for which a technical committee has been established has the right to be represented on that committee. International organizations, governmental and non-governmental, in liaison with ISO, also take part in the work. ISO collaborates closely with the International Electrotechnical Commission (IEC) on all matters of electrotechnical standardization.

The procedures used to develop this document and those intended for its further maintenance are described in the ISO/IEC Directives, Part 1. In particular the different approval criteria needed for the different types of ISO documents should be noted. This document was drafted in accordance with the editorial rules of the ISO/IEC Directives, Part 2 (see www.iso.org/directives).

Attention is drawn to the possibility that some of the elements of this document may be the subject of patent rights. ISO shall not be held responsible for identifying any or all such patent rights. Details of any patent rights identified during the development of the document will be in the Introduction and/or on the ISO list of patent declarations received (see www.iso.org/patents).

Any trade name used in this document is information given for the convenience of users and does not constitute an endorsement.

For an explanation on the voluntary nature of standards, the meaning of ISO specific terms and expressions related to conformity assessment, as well as information about ISO's adherence to the World Trade Organization (WTO) principles in the Technical Barriers to Trade (TBT) see the following URL: www.iso.org/iso/foreword.html

This document was prepared by Technical Committee ISO/TC 6, *Paper, board and pulps*, Subcommittee SC 2, *Test methods and quality specifications for paper and board*.

This third edition cancels and replaces the second edition (ISO 2528:1995), of which it constitutes a minor revision with the following changes:

- editorial updating;
- format updating.

Introduction

This document describes a method which can in theory be applied to any sheet material. In practice its main use is for flat, usually thin, materials that can be processed to form a water vapour-resistant barrier, as used in packaging, such as paper, board, plastics films or laminates of paper with films or metal foils, and for fabrics coated with rubber or plastics.

The water vapour pressure differential is the essential part of this test and in this instance it has not been possible to adopt the conditions recommended in ISO 554. In addition, the limits of temperature and humidity control are more exacting than those required for normal testing.

This test is intended to give reliable values of water vapour transmission rate (WVTR) by means of simple apparatus. The use of the results of any particular application should, however, be based upon experience.

Transmission rate is not a linear function of temperature nor, generally, of relative humidity difference. A determination carried out under certain conditions is not, therefore, necessarily comparable with one carried out under other conditions. The conditions of test should, therefore, be chosen to be as close as possible to the conditions of use.

STANDARDSISO.COM : Click to view the full PDF of ISO 2528:2017

[STANDARDSISO.COM](https://standardsiso.com) : Click to view the full PDF of ISO 2528:2017

Sheet materials — Determination of water vapour transmission rate (WVTR) — Gravimetric (dish) method

1 Scope

This document specifies a method for the determination of the water vapour transmission rate (often erroneously called “permeability”) of sheet materials.

This method is not generally recommended for use if the transmission rate is expected to be less than 1 g/m² per day or for materials thicker than 3 mm. In such cases the method specified in ISO 9932 is preferred.

The method cannot be applied to film materials that are damaged by hot wax or that shrink to an appreciable extent under the test conditions used.

For some purposes it may be necessary to determine the transmission rate of creased material; a procedure for this is given in [Annex A](#).

2 Normative references

The following documents are referred to in the text in such a way that some or all of their content constitutes requirements of this document. For dated references, only the edition cited applies. For undated references, the latest edition of the referenced document (including any amendments) applies.

ISO 186, *Paper and board — Sampling to determine average quality*

ISO 187, *Paper, board and pulps — Standard atmosphere for conditioning and testing and procedure for monitoring the atmosphere and conditioning of samples*

ISO 209, *Aluminium and aluminium alloys — Chemical composition*

ISO 291, *Plastics — Standard atmospheres for conditioning and testing*

ISO 23529, *Rubber — General procedures for preparing and conditioning test pieces for physical test methods*

ISO 2231, *Rubber- or plastics-coated fabrics — Standard atmospheres for conditioning and testing*

3 Terms and definitions

For the purposes of this document, the following terms and definitions apply.

ISO and IEC maintain terminological databases for use in standardization at the following addresses:

- ISO Online browsing platform: available at <http://www.iso.org/obp>
- IEC Electropedia: available at <http://www.electropedia.org/>

3.1

water vapour transmission rate

WVTR

mass of water vapour transmitted through a unit area in a unit time under specified conditions of temperature and humidity

Note 1 to entry: Expressed in grams per square metre per day [g/(m² × d)].

Note 2 to entry: The WVTR depends upon the thickness, composition, homogeneity and permeability of the constituent material(s), and upon the conditions of temperature and relative humidity under which the test is carried out (see [Annex B](#)).

4 Principle

Dishes containing a desiccant and closed by the material to be tested are placed in a controlled atmosphere (see [Annex B](#)).

These dishes are weighed at suitable intervals of time and the WVTR is determined from the increase in mass when this increase has become proportional to the time interval.

5 Apparatus and material

[Figure 1](#) shows examples of equipment which has proved satisfactory in use, but other equipment may be equally satisfactory.

5.1 Test dishes, shallow, of glass, aluminium, or stainless steel and of as large a diameter as can be accommodated on the balance to be used. The dishes should be light but rigid and resistant to corrosion under the test conditions. Dishes made from aluminium, grade Al 99,5 as specified in ISO 209 and protected by chemical or anodic oxidation have been found suitable.

Each dish has a groove around the rim for sealing the test piece with wax. This groove has a profile such that the test piece can be sealed over the opening of the dish and no water vapour can enter or escape the dish through the edges of the test piece.

The internal diameter of the dish shall be equal to or very slightly larger than the diameter of the waxing templates ([5.3](#)).

The internal depth of the dish below the plane of the test piece should not be less than 15 mm (deep dish) or 8 mm (shallow dish) and there shall be no obstruction within the dish that might interfere with the flow of water vapour between the test piece and the desiccant.

The surface area of the bottom of the dish where it is filled with desiccant shall be similar to that of the exposed surface of the test piece.

Each dish shall be assigned a different number.

5.2 Lids, each numbered to correspond with a dish and made from the same material as the dish, with an outer rim designed to fit neatly over the outside of the dish so that there is negligible loss of water vapour when the dishes are removed from the test atmosphere for weighing.

5.3 Waxing templates, to place the wax sealant easily and to allow the test area to be defined exactly.

Their diameter, D , should preferably be $79,8 \text{ mm} \pm 0,4 \text{ mm}$ (corresponding to an area of 50 cm^2).

If any other diameter of template is used, this fact shall be mentioned in the test report. The diameter shall always be at least $56,1 \text{ mm}$ (corresponding to an area of 25 cm^2), and shall be known to an accuracy better than 1 %.

These templates may be either:

- a) cross-braced ring templates, which remain in place during the test. Their diameter, D , is the internal diameter of the ring. As many ring templates as dishes are required; or
- b) cover templates, which shall be taken off when the applied wax has cooled, comprising a disc with a central handle, drilled with a small hole at a suitable point (see [Figure 1](#)), and having the edge chamfered at an angle of approximately 45° . Their diameter, D , is the diameter of this smaller circle.

Small guides can be fixed to the template to centre it automatically. A few templates are sufficient.

5.4 Sealant, a wax mixture (see [Annex C](#)) which adheres strongly to both the dish and the test piece and is not brittle at ordinary temperature, not hygroscopic and not susceptible to oxidation. A surface of 50 cm² of freshly melted wax when exposed for 24 h in condition B (see [Annex B](#)) shall not change in mass by more than 1 mg.

5.5 Water bath, for melting the wax.

5.6 Device for distributing the wax, of at least 25 ml capacity and a rapid rate of discharge, such as a pipette with a discharge tube of about 3 mm inner diameter or a metal pourer with an insulated handle.

5.7 Cutting template or test-piece cutter, of a size suitable for cutting circular test pieces of a diameter suitable for the dishes in use (see [Figure 1](#)). This diameter is slightly less than the inside diameter of the top of the dish (see [Figure 2](#)).


5.8 Desiccant, silica gel or anhydrous calcium chloride (CaCl₂), in the form of granules 1,6 mm to 4 mm in size or alternatively in the form of a friable flaked product 1,5 mm to 2,0 mm in size.

NOTE The limiting saturation of 1 g of calcium chloride is 0,1 g of water. The limiting saturation of 1 g of silica gel is 0,04 g of water.


5.9 Balance, for determining the mass of each dish, lid and contents to 0,1 mg.

STANDARDSISO.COM : Click to view the full PDF of ISO 2528:2017


Dimensions in millimetres

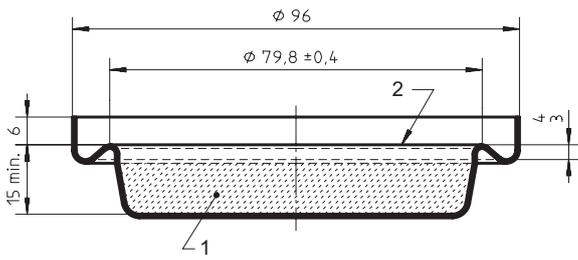


Deep dish (5.1) for materials with transmission rate greater than 100 g/(m²·d), (tapered to nest)

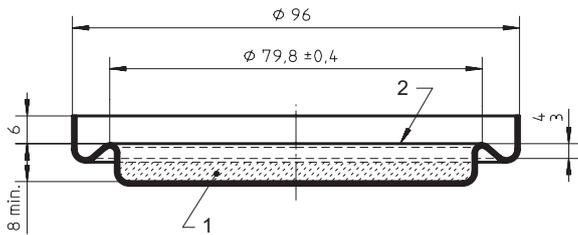


Shallow dish (5.1) for materials with normal transmission rate

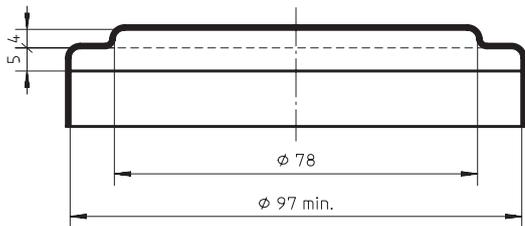


Lid (5.2) with rim to fit outside dish

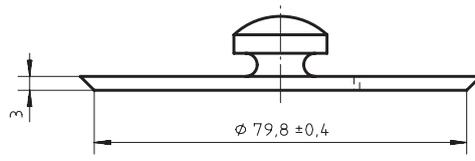

Cover template [5.3 b)]

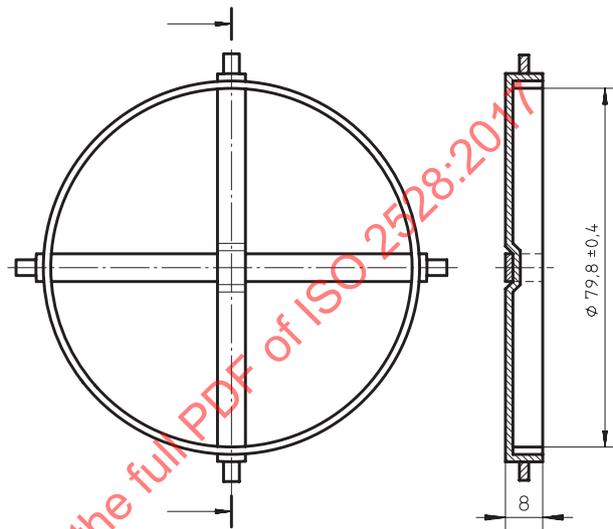

Ring template [5.3 a)]

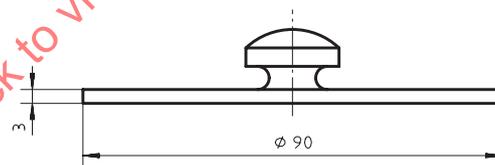

Cutting template (5.7)


Key

- 1 desiccant
- 2 test piece

NOTE 1 Dimensions are shown for test areas of 50 cm². Values for dishes and lids show inside dimensions, except the overall diameter of the dishes, which is an outside dimension.

NOTE 2 Only the dimension 79,8 mm ± 0,4 mm shall be strictly respected; the other dimensions are approximate.

Figure 1 — Examples of test dishes and templates

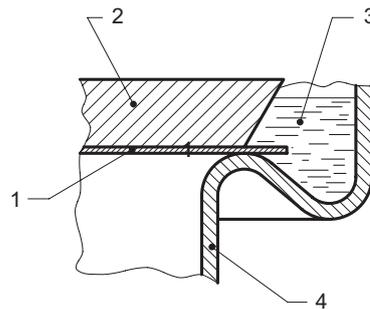**Key**

- 1 test piece
- 2 cover template
- 3 sealing material
- 4 dish

Figure 2 — Detail of sealing of test piece

5.10 Tongs, holders or other means of manipulating the dishes.

5.11 Enclosure, in which the required controlled atmosphere can be set (see [Annex B](#)) and with air continuously circulated. The control shall be such that the specified conditions are re-established not more than 15 min after the door of the enclosure has been closed.

6 Sampling

If a lot of paper is to be evaluated, select samples in accordance with ISO 186.

7 Conditioning

It is recommended that samples be conditioned in accordance with ISO 187, ISO 291, ISO 23529 or ISO 2231 depending on the material, prior to preparation of the test pieces, especially if the WVTR is known to be high.

8 Preparation of test pieces

Avoiding all damaged areas, cut from the sample, with the aid of the cutting template or test piece cutter ([5.7](#)), at least three circular test pieces of the appropriate diameter, normally 90 mm (see [Figure 1](#)), for each side to be tested. Mark the test pieces in some way so that the side to be exposed to the test atmosphere can be readily identified.

If the material is hygroscopic or if a greater accuracy is required (see [10.2](#)), prepare at least two additional test pieces for blank measurements.

If the sheet material has been prepared by a process involving solvents, the result may be affected by the residual solvent in the test pieces. If the test pieces are treated to remove the residual solvent, details of this treatment should be included in the test report.

9 Preparation of dishes

9.1 General

The method of preparation of the dishes differs slightly according to whether a cover or ring template is used. Details for the different types of template are given in 9.2 and 9.3. The work shall be done rapidly in order to keep the absorption of water vapour by the desiccant to a minimum.

Always begin by carefully cleaning and drying the dishes and the templates.

WARNING — Care should be taken when handling hot wax, as serious burns could occur if the wax is spilled or splashed. Suitable protective equipment such as glasses, gloves, etc. should be worn.

9.2 Use of wax and a cover template [5.3 b)]

Fill each dish with desiccant up to 3 mm to 4 mm below the final position of the test piece and level by tapping.

Melt the wax (5.4) on the water bath (5.5) and fill the dispensing device (5.6).

Place the test piece (Clause 8) in central position, followed by the waxing template. Run the molten wax into the groove until it reaches the level of the upper surface of the waxing template and, after cooling, complete the joint by removing air bubbles and hair cracks with a small gas flame. A warm spatula may be run over the wax to assist in this process, so that shrinkage cracks that may have developed during cooling will be closed.

Remove the waxing template and examine the assembly to make sure that the joint is satisfactory. To ensure that the waxing template comes away easily, it is advisable first to smear a thin film of petroleum jelly around the edge and to wipe away any excess which could contaminate the test piece.

Cover the assembly with a lid (5.2) numbered to correspond with the number of the dish.

9.3 Use of wax and a ring template [5.3 a)]

Fill each dish with desiccant up to a level of 3 mm to 4 mm below the final position of the test piece and level by tapping. Melt the wax (5.4) on the water bath (5.5) and fill the dispensing device (5.6). Run the molten wax into the circular groove round the dish until a slight meniscus is produced above the inner edge of the groove.

Place the test piece (Clause 8) in central position on the dish, followed by the ring template, and load it with a 1 kg weight.

Run more wax into the annular space so formed and, after cooling, complete the joint by removing any air bubbles and hair cracks with a small gas flame. A warm spatula may be run over the wax to assist in this process, so that shrinkage cracks that may have developed during cooling will be closed. Remove the weight and leave the ring in place.

Cover the assembly with a lid (5.2) numbered to correspond with the number of the dish.

10 Procedure

10.1 General method

10.1.1 Weigh all the prepared dishes, with their lids, on the balance (5.9) to the nearest 0,1 mg.

10.1.2 Place them upright in the enclosure (5.11) set to the conditions of the test (see Annex B), after removing the lids.

10.1.3 Weigh the dishes, with their lids, at suitable, regular intervals of time.

Weighing shall be carried out as follows:

- Cover the dishes with their respective lids, remove them from the controlled enclosure using the tongs or holders (5.10) and leave them for 15 min to reach ambient temperature. Weigh the assemblies to the nearest 0,1 mg and return them to the enclosure after again taking off the lids.
- Take care to work rapidly, taking the dishes in small groups always containing the same number, so that the whole weighing operation always lasts about the same time (not exceeding 30 min).
- It is also possible to work without the lids, but in this case it is advisable to use blank assemblies (see 10.2), and transport and cooling of the dishes shall be done in a closed vessel with calcium chloride desiccant.
- The interval between weighings should be adapted to the material being tested. Short time intervals (for example 3 h, 4 h or 8 h) may be necessary for materials with a high transmission rate, while longer time intervals, preferably 24 h, 48 h or 96 h, are sufficient for materials with low transmission rates. The gain in mass between two successive weighings should be at least 5 mg.
- If the first weighing shows a gain in mass too large or too small, the subsequent time intervals for weighing may be modified.

10.1.4 Continue the weighings until the increase in mass of two successive weighings per unit time of exposure to the selected atmosphere becomes constant to within 5 %.

10.1.5 The test shall be completed before the efficiency of the desiccant is appreciably reduced. In practice, the total increase in mass should not exceed 1,2 g for shallow dishes and 3,2 g for deep ones.

10.2 Use of blank assemblies

If the sample has a low transmission rate, for example rubber, plastics or polyethylene-coated board, or is appreciably hygroscopic, it is advisable to test two or more blank assemblies, prepared in the same manner but without desiccant, in addition to the three normal test assemblies. All the measured masses are then corrected at each time interval by subtracting the mean change in mass of the blank assemblies which undergo the same treatment.

10.3 Creased sheet

The WVTR of a creased sheet shall be determined using the method specified in [Annex A](#).

11 Expression of results

11.1 Express the test results by the method given in either [11.1.1](#) or [11.1.2](#).

11.1.1 For each dish, represent the total increase in mass graphically as a function of time of exposure, the test being completed when three or four points lie on a straight line (see [10.1.4](#)), showing a constant rate of passage of water vapour.

Using this straight line, the WVTR for each test piece is then calculated, in grams per square metre per day, from the formula

$$\frac{24 \times 10^4 \times m_1}{S}$$

where

m_1 is the rate of increase in mass, in grams per hour, determined from the graph;

S is the area, known to within 1 %, in square centimetres (normally 50 cm²), of the tested surface of the test piece.

11.1.2 If weighings are made at identical time intervals, it is possible to calculate the transmission rate for each test piece directly from the results, without preparing a graph, by using the formula in [11.1.1](#) but substituting m_2/t for m_1 :

$$\frac{24 \times 10^4 \times m_2}{S \times t}$$

where

t is the total duration, in hours, of the last two stable exposure periods (see [10.14](#));

m_2 is the increase in mass, in grams, of the assembly during the time t .

11.2 For several assemblies corresponding to a single sample of test material and to a single face, calculate the arithmetic mean of the results obtained in accordance with either [11.1.1](#) or [11.1.2](#).

11.3 Report the mean WVTR by rounding

- values over 100 g/(m² × d): to the nearest 10 g/(m² × d);
- values from 10 g/(m² × d) to 100 g/(m² × d): to the nearest whole number;
- values less than 10 g/(m² × d): to the first decimal place.

12 Precision

There is insufficient data available at this time to allow any statement to be made regarding repeatability and reproducibility.

13 Test report

The test report shall include the following information:

- a) a reference to this document, i.e. ISO 2528;
- b) all details necessary for complete identification of the material tested, in particular grammage, thickness (if required) and identification of the outside face during tests;
- c) the depth of the dish;
- d) the test conditions (see [Annex B](#));
- e) the type of desiccant used;
- f) the arithmetic mean and standard deviation, if the largest difference between individual WVTR results and the arithmetic mean does not exceed 10 % of this mean; otherwise, report the individual WVTR results obtained (see [Clause 11](#));
- g) whether the test has been carried out on creased test pieces in accordance with [Annex A](#);
- h) any other information which may help in interpretation of results, for example a treatment to remove residual solvent.

Annex A (normative)

Method for determination of water vapour transmission rate of creased materials

A.1 General

If the WVTR of creased material is required, the creasing should be carried out using one of the procedures recommended in this annex.

A.2 Definitions

For the purposes of this annex, the following definitions apply:

A.2.1 Transmission rate of creased sheet: Rate of transmission, expressed in grams per square metre per day, measured on a test piece cut after the sheet has been creased in a standardized manner and after the sheet has been restored to the flat condition.

A.2.2 Transmission rate of creases: Difference between the transmission rate of the creased sheet and the transmission rate of the uncreased sheet, both given in grams per square meter per day; it is expressed in grams per 100 linear meters (of creases) per day $[g/(100 \text{ m} \times d)]$.

A.3 Principle

A test piece is cut and creased to give a double series of creases in accordion fashion forming a pattern of squares, with creases at right angles.

The spacing of the pattern of squares is such that, in the final test piece, the value of the total length of the creases, in centimetres, located within the area S is the same number as the area, in square centimetres; for example, the total length of the creases is 50 cm when the test area is 50 cm².

The test piece is cut and put into the dish in such a manner that the centre of the circular dish is at the centre of one of the squares formed by the creases.

A.4 Apparatus

A.4.1 Creasing table, in the form of a flat rectangular plate, the width of which is slightly larger than the larger dimension of the test piece.

A.4.2 Cutting template, of square shape having the dimensions of the test piece before creasing. This template may have notches making it possible to mark the position of the creases (see [Figure A.1](#)).

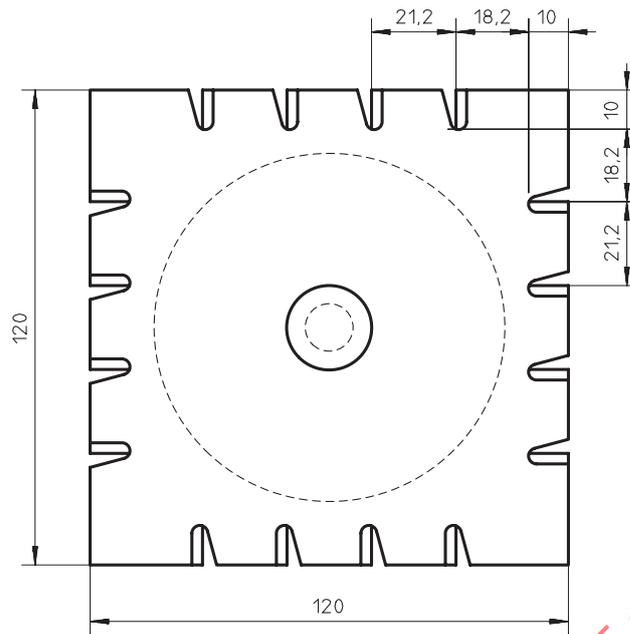


Figure A.1 — Example of cutting template (A.4.2) used for folding procedure A (A.7.2.1)

A.4.3 Pressing plate, rigid rectangular flat plate, of length about 175 mm and width either 15 mm (Procedure A) or 30 mm (Procedure B), capable of being loaded so that a load of 9,8 N per 10 mm of crease length is applied.

The creasing may also be carried out using a suitable press.

A.4.4 Ruling plate (or wooden rule), approximately 200 mm x 30 mm, with smooth straight edges.

A.5 Preparation of test pieces for creasing

The number of test pieces to be prepared for creasing is the same as that specified in [Clause 8](#) of this document.

Using the template (A.4.2), cut the test pieces in a square shape of dimensions 120 mm x 120 mm if procedure A is to be applied or 170 mm x 170 mm if procedure B is to be applied.

If a sheet with a particular direction (for example, machine direction) is used, the cutting shall be carried out in such a manner that this direction is parallel to one of the sides of the test piece (unless specified that the cutting is to be made diagonally, in which case there shall be an angle of 45° between the particular direction and the sides of the template).

If a template with notches is used, mark each crease (with a notch or pencil line, for example) on the periphery of the test piece for creasing.

A.6 Conditioning of the test pieces before creasing

Condition the test pieces in the conditions usual for the material, i.e. in accordance with the requirements of ISO 187, ISO 291, ISO 2231 or ISO 23529.

In the absence of any particular recommendation, choose one of the above International Standards.

A.7 Creasing

A.7.1 Crease spacing and loading

The spacing of the square pattern (see [A.3](#)) depends on the actual area of test, S . (Each side of a square is 21,2 mm for the recommended area of 50 cm².)

The pressing of the creases is carried out by applying a load of 9,8 N per 10 linear millimetres of crease, on a single crease or on several creases at a time.

A.7.2 Folding to make the creases

The creases may be prepared in any manner; however, the following procedures are recommended.

A.7.2.1 Procedure A (120 mm x 120 mm test piece for a test area of 50 cm²)

Make the first crease by folding the test piece at the outer pair of marks, lightly applying the ruling plate ([A.4.4](#)) to the sheet and letting it slide towards the crease.

Open the test piece and make the second, then third and fourth creases.

Take care to crease the test piece so that each two adjacent folds open in opposite directions (in such a manner as to form an “accordion”).

Make the second series of creases by carrying out exactly the same operation, but in a direction perpendicular to the first.

A.7.2.2 Procedure B (170 mm x 170 mm test piece for a test area of 50 cm²)

Make an “accordion” of eight equal rectangles in the following manner:

- a) make a centre crease by bringing together two opposite edges of the test piece, and make the crease by placing the sheet on the creasing ([A.4.1](#)) and lightly applying the ruling plate ([A.4.4](#)) close to the edges which meet and sliding it towards the crease;
- b) open the test piece, then form and make the crease of a quarter of the test piece by bringing one of the edges of the test piece to coincide with the centre crease already made;
- c) make the same crease for the opposite quarter, these two creases and the centre crease having their concavity on the same side of the sheet (see [Figure A.2](#));
- d) open the sheet and turn the upper side of the test piece downwards;
- e) form and make the other four creases of the “accordion” by successively placing one edge of the test piece to coincide with the crease of the first quarter, the crease of the first quarter with the middle crease, the middle crease with the crease of the third quarter and the crease of the third with the other edge of the test piece (see [Figure A.2](#)).

Make the second series of creases by carrying out exactly the same operation, but in a direction perpendicular to the first.

A.7.3 Pressing the creases

The creases can be pressed crease by crease, or all of the creases can be pressed simultaneously.

In either case, place the creased test piece on the creasing table, and press it for about 30 s by covering the crease or creases systematically with the pressing plate suitably loaded to press the creases with a load of 9,8 N per 10 mm of crease.