
**Sintered metal bushes — Determination
of radial crushing strength**

*Bagues en métal fritté — Détermination de la résistance à l'écrasement
radial*

STANDARDSISO.COM : Click to view the full PDF of ISO 2739:2006



PDF disclaimer

This PDF file may contain embedded typefaces. In accordance with Adobe's licensing policy, this file may be printed or viewed but shall not be edited unless the typefaces which are embedded are licensed to and installed on the computer performing the editing. In downloading this file, parties accept therein the responsibility of not infringing Adobe's licensing policy. The ISO Central Secretariat accepts no liability in this area.

Adobe is a trademark of Adobe Systems Incorporated.

Details of the software products used to create this PDF file can be found in the General Info relative to the file; the PDF-creation parameters were optimized for printing. Every care has been taken to ensure that the file is suitable for use by ISO member bodies. In the unlikely event that a problem relating to it is found, please inform the Central Secretariat at the address given below.

STANDARDSISO.COM : Click to view the full PDF of ISO 2739:2006

© ISO 2006

All rights reserved. Unless otherwise specified, no part of this publication may be reproduced or utilized in any form or by any means, electronic or mechanical, including photocopying and microfilm, without permission in writing from either ISO at the address below or ISO's member body in the country of the requester.

ISO copyright office
Case postale 56 • CH-1211 Geneva 20
Tel. + 41 22 749 01 11
Fax + 41 22 749 09 47
E-mail copyright@iso.org
Web www.iso.org

Published in Switzerland

Foreword

ISO (the International Organization for Standardization) is a worldwide federation of national standards bodies (ISO member bodies). The work of preparing International Standards is normally carried out through ISO technical committees. Each member body interested in a subject for which a technical committee has been established has the right to be represented on that committee. International organizations, governmental and non-governmental, in liaison with ISO, also take part in the work. ISO collaborates closely with the International Electrotechnical Commission (IEC) on all matters of electrotechnical standardization.

International Standards are drafted in accordance with the rules given in the ISO/IEC Directives, Part 2.

The main task of technical committees is to prepare International Standards. Draft International Standards adopted by the technical committees are circulated to the member bodies for voting. Publication as an International Standard requires approval by at least 75 % of the member bodies casting a vote.

Attention is drawn to the possibility that some of the elements of this document may be the subject of patent rights. ISO shall not be held responsible for identifying any or all such patent rights.

ISO 2739 was prepared by Technical Committee ISO/TC 119, *Powder metallurgy*, Subcommittee SC 3, *Sampling and testing methods for sintered metal materials (excluding hardmetals)*.

This second edition cancels and replaces the first edition (ISO 2739:1973), which has been technically revised by adding Clause 8, Precision statement (Statement of accuracy). Editorial changes have also been made.

STANDARDSISO.COM : Click to view the full PDF of ISO 2739:2006

Sintered metal bushes — Determination of radial crushing strength

1 Scope

This International Standard specifies a method of measuring the radial crushing strength of sintered metal parts in the form of hollow cylinders, commonly known as bushes.

This method is applicable to sintered bushes composed of pure or alloyed metal powders.

2 Principle

A hollow cylinder is submitted to a continuously increasing radial load until breakage occurs, provided that the deformation does not exceed 10 % of the diameter. The maximum load observed is used to calculate a value in relation to the dimensions of the hollow cylinder known as “radial crushing strength”.


3 Apparatus

3.1 **Pressing apparatus**, which enables a radial load to be applied to a hollow cylinder.

3.2 **Load-measuring device**, capable of giving the reading of the maximum value attained.

4 Test piece

The test piece (see Figure 1) shall be in the form of a sintered hollow cylinder (which may or may not be oil-impregnated), without flanges, notches, grooves, pronounced chamfers, drilled holes, oilways or keyways. If necessary, the cylinder may be machined but, in this case, the results obtained may differ from those obtained with a cylinder which has not been machined.

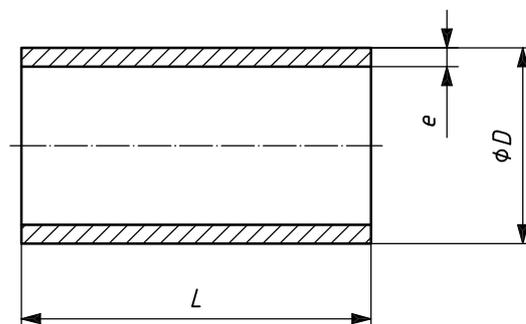


Key

- L length of the hollow cylinder
- D external diameter of the hollow cylinder
- e thickness of the cylinder wall

Figure 1 — Test piece

5 Procedure

Place the test piece between the plates of the pressing apparatus, the axis of the test piece being parallel to the planes of the plates (see Figure 2).

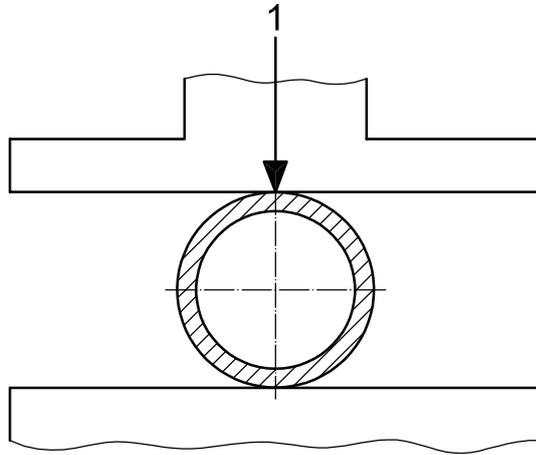

Key

1 applied load

Figure 2 — Test arrangement

Apply the load progressively, without shock, so that coefficient K (see Clause 6) increases at a rate between 2 N/mm^2 and 20 N/mm^2 per second, and that the test time is greater than 10 s.

6 Expression of results

The radial crushing strength of the bush, K , in newtons per square millimetre, is given by the following formula:

$$K = \frac{F(D - e)}{L e^2}$$

where

- F is the maximum load, in newtons, incurring fracture;
- L is the length, in millimetres, of the hollow cylinder;
- D is the external diameter, in millimetres, of the hollow cylinder;
- e is the thickness, in millimetres, of the cylinder wall.

This formula is valid only if the ratio e/D is less than $1/3$ ¹⁾.

1) In this case, the tensile strength is approximately equal to $0,5 K$.