

---

---

**Graphic technology — Colour  
and transparency of ink sets  
for four-colour-printing —**

Part 2:  
**Coldset offset lithographic printing**

*Technologie graphique — Couleur et transparence des gammes d'encre  
d'impression en quadrichromie —*

*Partie 2: Impression lithographique offset rotatif coldset*



**PDF disclaimer**

This PDF file may contain embedded typefaces. In accordance with Adobe's licensing policy, this file may be printed or viewed but shall not be edited unless the typefaces which are embedded are licensed to and installed on the computer performing the editing. In downloading this file, parties accept therein the responsibility of not infringing Adobe's licensing policy. The ISO Central Secretariat accepts no liability in this area.

Adobe is a trademark of Adobe Systems Incorporated.

Details of the software products used to create this PDF file can be found in the General Info relative to the file; the PDF-creation parameters were optimized for printing. Every care has been taken to ensure that the file is suitable for use by ISO member bodies. In the unlikely event that a problem relating to it is found, please inform the Central Secretariat at the address given below.

STANDARDSISO.COM : Click to view the full PDF of ISO 2846-2:2000

© ISO 2000

All rights reserved. Unless otherwise specified, no part of this publication may be reproduced or utilized in any form or by any means, electronic or mechanical, including photocopying and microfilm, without permission in writing from either ISO at the address below or ISO's member body in the country of the requester.

ISO copyright office  
Case postale 56 • CH-1211 Geneva 20  
Tel. + 41 22 749 01 11  
Fax + 41 22 734 10 79  
E-mail [copyright@iso.ch](mailto:copyright@iso.ch)  
Web [www.iso.ch](http://www.iso.ch)

Printed in Switzerland

## Foreword

ISO (the International Organization for Standardization) is a worldwide federation of national standards bodies (ISO member bodies). The work of preparing International Standards is normally carried out through ISO technical committees. Each member body interested in a subject for which a technical committee has been established has the right to be represented on that committee. International organizations, governmental and non-governmental, in liaison with ISO, also take part in the work. ISO collaborates closely with the International Electrotechnical Commission (IEC) on all matters of electrotechnical standardization.

International Standards are drafted in accordance with the rules given in the ISO/IEC Directives, Part 3.

Draft International Standards adopted by the technical committees are circulated to the member bodies for voting. Publication as an International Standard requires approval by at least 75 % of the member bodies casting a vote.

Attention is drawn to the possibility that some of the elements of this part of ISO 2846 may be the subject of patent rights. ISO shall not be held responsible for identifying any or all such patent rights.

International Standard ISO 2846-2 was prepared by Technical Committee ISO/TC 130, *Graphic technology*.

ISO 2846 consists of the following parts, under the general title *Graphic technology — Colour and transparency of ink sets for four-colour-printing*:

- *Part 1: Sheet-fed and heat-set web offset lithographic printing*
- *Part 2: Coldset offset lithographic printing*
- *Part 3: Gravure printing*
- *Part 4: Screen printing*
- *Part 5: Flexographic printing*

Annex A forms a normative part of this part of ISO 2846. Annexes B to D are for information only.

## Introduction

A working group consisting of TC 130/WG 4 and WG 3 experts for materials and process control examined the colorimetric properties of coldset web offset inks from around the world and found that a single set of colour coordinates could adequately represent these, within reasonable tolerances. This part of ISO 2846 is the result of that activity. It will enable printers to obtain a reasonable consistency between one another and thereby ensure that separations and digital images supplied to them can be used to best advantage.

This part of ISO 2846 will allow printers to obtain sets of process inks from various sources which will produce a similar colour when printed on the reference substrate at the appropriate film thickness. This will allow colour separations for coldset web offset printing to be based on known colour standards. The colorimetric characteristics specified in this part of ISO 2846 may only be obtained when the inks are printed on the reference substrate. However, similarity of two inks on the reference substrate will ensure similarity on another substrate.

STANDARDSISO.COM : Click to view the full PDF of ISO 2846-2:2000

# Graphic technology — Colour and transparency of ink sets for four-colour-printing —

## Part 2: Coldset offset lithographic printing

### 1 Scope

This part of ISO 2846 specifies the colour and transparency to be produced by inks intended for four-colour coldset web offset printing when printed under specified conditions on a printability tester. It also describes the test method to ensure conformance.

This part of ISO 2846 does not apply to fluorescent inks and does not specify pigments (or spectral reflectance) in order not to preclude developments which may enable different pigment combinations to be used advantageously while still achieving the colorimetric requirements specified in this part of ISO 2846.

### 2 Normative references

The following normative documents contain provisions which, through reference in this text, constitute provisions of this part of ISO 2846. For dated references, subsequent amendments to, or revisions of, any of these publications do not apply. However, parties to agreements based on this part of ISO 2846 are encouraged to investigate the possibility of applying the most recent editions of the normative documents indicated below. For undated references, the latest edition of the normative document referred to applies. Members of ISO and IEC maintain registers of currently valid International Standards.

ISO 536:1995, *Paper and board — Determination of grammage.*

ISO 2846-1:1997, *Graphic technology — Colour and transparency of ink sets for four-colour-printing — Part 1: Sheet-fed and heat-set web offset lithographic printing.*

ISO 2471:1998, *Paper and board — Determination of opacity (paper backing) — Diffuse reflectance method.*

ISO 8791-4:1992, *Paper and board — Determination of roughness/smoothness (air leak methods) — Part 4: Print-surf method.*

ISO 13655:1996, *Graphic technology — Spectral measurement and colorimetric computation for graphic arts images.*

### 3 Terms and definitions

For the purposes of this part of ISO 2846, the following terms and definitions apply.

#### 3.1

##### **coldset printing**

web offset or letterpress printing without accelerated drying; ink sets by absorption into the substrate

### 3.2

#### **standard ink**

ink, intended for four-colour printing, which, when printed on the reference substrate and within the applicable range of ink film thicknesses, complies to the colorimetric and transparency specifications of this part of ISO 2846

### 3.3

#### **primary colours**

colours of individual prints from yellow, magenta and cyan inks

NOTE If the prints are produced as specified in this part of ISO 2846 and conform to the colorimetric characteristics specified, they are standard primary colours.

### 3.4

#### **transparency**

ability of an ink film to transmit and absorb light without scattering

NOTE It is generally expressed as some measure of the unwanted scattering.

### 3.5

#### **transparency measurement value**

*T*

reciprocal of the slope of the regression line between ink film thickness and colour difference for overprints of chromatic inks over black

## 4 Test method

### 4.1 Principle

Each ink shall be printed on the reference substrate described in annex A at a range of ink film thicknesses. The colours which result shall be measured colorimetrically. If one or more samples are found which conform to the values and tolerances specified in this part of ISO 2846 that ink complies with this part of ISO 2846.

Transparency shall be evaluated by printing each of the three primary colours on a black substrate at a range of film thicknesses. The CIELAB colour difference shall be determined for each sample, between the printed and unprinted black, and the linear regression coefficient (slope of the regression line) between ink film thickness and colour difference shall be calculated for each colour. An ink conforms to this part of ISO 2846 if the reciprocal of the coefficient is negative or greater than the value specified in Table 2.

For a detailed description of procedures, together with examples, see annex D.

### 4.2 Test print preparation

#### 4.2.1 Prints for colorimetric evaluation

For each of the inks to be evaluated a number of test prints shall be made, each produced at a different ink film thickness, according to the conditions specified below.

They shall be made on the reference substrate as specified in annex A. The range of ink film thicknesses produced shall encompass that specified in 5.3.

- The print shall be made using a printability tester.
- Printing shall be directly from the printing forme to the substrate.
- The ambient temperature shall be  $(24 \pm 1)$  °C.
- Prints shall be produced with a printing line pressure of  $(225 \pm 25)$  N/cm at a speed of  $(1 \pm 0,1)$  m/s.

- The printing forme, which shall be an elastomer or rubber blanket-covered roller, shall have a Shore A hardness of between 80 and 85.
- The distribution time and the inking time shall not be greater than 60 s each. This does not include weighing time.
- The inking unit and the printing forme shall be cleaned and re-inked after each print.

NOTE Solvent used to clean the printing forme may penetrate the material. Time must be allowed to ensure full evaporation of the solvent. Using two printing formes alternately is recommended.

The amount of ink transferred to the substrate shall be determined by measuring the difference in mass of the printing forme before and after printing using an analytical balance, accurate to at least four decimal places. This amount shall be expressed in grams per square metre. Conversion to film thickness in micrometres shall be made by using the mass density of the ink and the printed area.

#### 4.2.2 Prints for transparency evaluation

Test prints for transparency evaluation shall be produced by printing the inks to be tested on a black substrate. Measurements of the CIELAB values of the black substrate shall be made prior to overprinting. The black shall have a lightness ( $L^*$ ) less than 30 when determined according to ISO 13655.

The ink to be tested shall then be printed on the black substrate<sup>1)</sup>, such that a range of samples, each with a different ink film thickness, is achieved. The range should approximate that defined in 5.3.

#### 4.2.3 Setting of test prints

Prior to colour measurement all printed samples shall be left for at least 12 h to enable setting of the ink.

#### 4.2.4 Colour measurement procedure

Test prints shall be measured in accordance with ISO 13655, except that a substrate backing consisting of at least seven sheets of the unprinted reference substrate shall be used.

NOTE The colorimetric values are related to the measurement procedure according to ISO 13655. This means that the samples shall be measured spectrally, with a 0°/45° or 45°/0° geometry instrument, and for calculation of CIELAB values and for the colour difference the CIE 1931 (2°) standard colorimetric observer data shall be used together with CIE standard illuminant D<sub>50</sub>.

## 5 Requirements for colour, transparency and ink film thickness ranges

### 5.1 Colour

For an ink to conform to this part of ISO 2846 it must meet the specifications for colour defined in Table 1, at some ink film thickness **within** the range specified in 5.3, **and** the specification for transparency defined in 5.2.

To meet the specification for colour an ink shall produce a colour that falls within the colour difference tolerances from the specified colorimetric values given in Table 1 at some ink film thickness within the range specified in Table 2 when printed as defined in 4.2.1.

---

1) Such a substrate (product code 1800399) is available at NPES The Association for Suppliers of Printing, Publishing and Converting Technologies, 1899 Preston White Drive, Reston, Virginia, 22091-4367.

Table 1 — Colorimetric values

Ink	CIELAB values			Tolerances			
	$L^*$	$a^*$	$b^*$	$\Delta E_{ab}^*$	$\Delta L^*$	$\Delta a^*$	$\Delta b^*$
Yellow	80,90	- 2,85	61,79	4,0			
Magenta	54,60	49,95	0,39	5,0			
Cyan	59,00	- 25,07	-27,41	3,0			
Black	40,00	1,60	4,52		0 <sup>a</sup> -40	± 1,0	± 2,0

<sup>a</sup> This means that for black there is no symmetrical tolerance for  $L^*$  but an upper limit.

NOTE 1 Typical spectral data for inks conforming to this part of ISO 2846 are provided in annex B. Reference spectral data for 8°/diffuse or diffuse/8° (specular included) geometry are also included.

NOTE 2 Reference data for CIELAB values calculated from the CIE 1931 (2°) standard colorimetric observer, together with CIE illuminant D<sub>65</sub>, are included in annex C for both geometries. CIELAB data for 8°/diffuse or diffuse/8° (specular included) geometry and illuminant D<sub>50</sub> are also included.

**5.2 Transparency characteristics**

To meet the specification for transparency an ink shall produce a value greater than that specified below when determined by the procedures and principles outlined in 4.1 and 4.2.2.

Table 2 — Transparency

Ink colour	Transparency measurement value $T$
Yellow	0,1
Magenta	0,2
Cyan	0,3

NOTE For highly transparent inks (usually cyan) the slope of the regression line may be zero or negative. In such a situation the transparency measurement value is considered to be approaching infinity and therefore the ink meets the specification.

For further information concerning transparency evaluation, see clause D.2

**5.3 Ink film thickness range**

The range of ink film thickness, within which a standard ink for coldset lithographic printing must conform to the colorimetric values specified in 5.1, is

0,7 µm to 1,3 µm

## Annex A (normative)

### Reference substrate

For the purposes of this part of ISO 2846, a newsprint conforming to the Newsshade 95 specification shall be used as reference substrate. The characteristics of the reference substrate as specified in IFRA Special report 1.11, Newsshade 95, shall be as follows:

#### Colour

CIELAB values  $L^* = 82,02 \pm 2,0$

$a^* = 0,28 \pm 1,0$

$b^* = 2,91 \pm 1,5$

Method: ISO 13655 (0°/45°, D<sub>50</sub>, 2°) with the exception: Reference substrate backing (4.2.4)

#### Mass per area

Specification:  $(48,8 \pm 2) \text{ g/m}^2$

Method: ISO 536

**Opacity:**  $(94 \pm 2) \%$

Method: ISO 2471

**Roughness:**  $(3,4 \pm 0,2) \mu\text{m}$  at a pressure of 1 MPa

Method: ISO 8791-4

**Annex B**  
(informative)

**Spectral data**

For some applications, such as calculating tristimulus values for a different observer or illuminant, it is useful to have recourse to spectral data. As already stated it was deliberately decided not to standardize such data since it can be very restrictive for ink manufacturing and future development of ink with improved properties. However, the following data may be taken as 'typical'. Since most inks are currently based on the same pigments any differences at the present time are likely to be small. It must be stressed that this annex is informative; inks cannot be assumed to be close to this data for standardisation purposes. It must also be remembered that these values are derived from measurements made on samples printed on the reference substrate backed by at least seven sheets of the same substrate.

Two tables of data are presented: Table B.1 is for 0°/45° geometry and Table B.2 is for 8°/diffuse (specular included). This data has been used to compute equivalent tristimulus values to those provided in Table 1 and annex A but for diffuse/8° geometry and for  $D_{65}$  (both geometries). These tristimulus values are given in annex C.

STANDARDSISO.COM : Click to view the full PDF of ISO 2846-2:2000

Table B.1 — Typical spectral reflectance data for inks conforming to this part of ISO 2846, 0°/45° geometry

Wavelength nm	Reflectance factor				
	Cyan	Magenta	Yellow	Black	Substrate <sup>a</sup>
380	0,084	0,096	0,067	0,051	0,132
390	0,131	0,119	0,078	0,058	0,187
400	0,194	0,146	0,087	0,067	0,281
410	0,263	0,176	0,095	0,076	0,370
420	0,320	0,204	0,100	0,082	0,446
430	0,379	0,227	0,104	0,088	0,507
440	0,444	0,244	0,108	0,093	0,544
450	0,494	0,249	0,115	0,096	0,571
460	0,522	0,240	0,125	0,100	0,593
470	0,540	0,222	0,135	0,102	0,610
480	0,547	0,202	0,156	0,105	0,625
490	0,546	0,182	0,209	0,107	0,636
500	0,533	0,163	0,321	0,109	0,642
510	0,505	0,144	0,472	0,110	0,644
520	0,456	0,128	0,573	0,111	0,637
530	0,394	0,121	0,605	0,111	0,622
540	0,330	0,119	0,616	0,110	0,604
550	0,266	0,114	0,617	0,110	0,588
560	0,210	0,110	0,617	0,110	0,575
570	0,172	0,117	0,615	0,110	0,568
580	0,153	0,152	0,611	0,111	0,562
590	0,142	0,240	0,604	0,112	0,557
600	0,135	0,376	0,605	0,113	0,561
610	0,133	0,511	0,624	0,117	0,586
620	0,138	0,613	0,662	0,123	0,636
630	0,144	0,683	0,704	0,130	0,693
640	0,152	0,732	0,745	0,136	0,742
650	0,162	0,767	0,777	0,141	0,776
660	0,174	0,793	0,805	0,145	0,800
670	0,182	0,813	0,825	0,148	0,814
680	0,181	0,826	0,838	0,150	0,820
690	0,177	0,837	0,849	0,152	0,825
700	0,170	0,844	0,856	0,154	0,828
710	0,168	0,848	0,861	0,156	0,830
720	0,177	0,852	0,865	0,157	0,832

<sup>a</sup> Reference substrate, see annex A.

**Table B.2 — Typical spectral reflectance data for inks conforming to this part of ISO 2846, 8°/diffuse (specular included) geometry**

Wavelength nm	Reflectance factor				
	Cyan	Magenta	Yellow	Black	Substrate <sup>a</sup>
380	0,085	0,109	0,073	0,056	0,135
390	0,133	0,137	0,087	0,064	0,190
400	0,196	0,173	0,102	0,074	0,286
410	0,266	0,211	0,116	0,083	0,377
420	0,323	0,246	0,126	0,090	0,453
430	0,382	0,275	0,134	0,096	0,514
440	0,448	0,295	0,140	0,101	0,550
450	0,499	0,303	0,149	0,104	0,576
460	0,527	0,295	0,160	0,108	0,598
470	0,545	0,277	0,171	0,110	0,617
480	0,552	0,256	0,192	0,113	0,633
490	0,550	0,234	0,244	0,116	0,647
500	0,536	0,211	0,353	0,118	0,657
510	0,506	0,186	0,498	0,119	0,663
520	0,457	0,167	0,594	0,121	0,660
530	0,395	0,158	0,624	0,121	0,648
540	0,330	0,154	0,633	0,121	0,634
550	0,267	0,149	0,633	0,122	0,621
560	0,211	0,143	0,631	0,122	0,611
570	0,174	0,150	0,629	0,123	0,607
580	0,154	0,183	0,624	0,124	0,601
590	0,143	0,270	0,614	0,125	0,594
600	0,136	0,403	0,612	0,127	0,596
610	0,135	0,535	0,628	0,131	0,621
620	0,140	0,635	0,664	0,138	0,673
630	0,146	0,702	0,706	0,145	0,734
640	0,154	0,749	0,746	0,151	0,786
650	0,165	0,780	0,778	0,157	0,822
660	0,177	0,804	0,804	0,161	0,846
670	0,185	0,821	0,824	0,164	0,860
680	0,183	0,832	0,835	0,166	0,866
690	0,180	0,840	0,845	0,169	0,872
700	0,173	0,846	0,852	0,171	0,876
710	0,171	0,850	0,856	0,173	0,879
720	0,179	0,853	0,861	0,174	0,880

<sup>a</sup> Reference substrate, see annex A

## Annex C (informative)

### Colour values for 8°/diffuse geometry and illuminant D<sub>65</sub>

For the purposes of this part of ISO 2846 the 0°/45° and 45°/0° geometries are deemed to be equivalent to each other, as are the 8°/diffuse and diffuse/8° geometries for both specular included and specular excluded conditions. The values in Tables C.1 and C.2 have been calculated from the spectral values listed in annex B.

If data is to be communicated the fact that the measurement geometry used is not normative shall be explicitly included in the report.

**Table C.1 — Colorimetric values for 8°/diffuse (specular included) geometry for illuminant D<sub>50</sub> and 2° observer**

Ink	CIELAB values		
	$L^*$	$a^*$	$b^*$
Yellow	81,72	– 3,61	55,84
Magenta	57,93	45,31	– 2,53
Cyan	59,15	– 24,75	– 27,61
Black	41,93	2,02	5,36
Substrate	83,70	0,61	5,11

**Table C.2 — Colorimetric values for 8°/diffuse (specular included) geometry for illuminant D<sub>65</sub> and 2° observer**

Ink	CIELAB values		
	$L^*$	$a^*$	$b^*$
Yellow	81,27	– 8,46	56,17
Magenta	56,98	43,60	– 4,30
Cyan	60,13	– 21,47	– 25,36
Black	41,83	1,07	5,39
Substrate	83,65	– 0,95	5,49

Table C.3 — Colorimetric values for 0°/45° geometry for illuminant D<sub>65</sub> and 2° observer

Ink	CIELAB values		
	<i>L</i> *	<i>a</i> *	<i>b</i> *
Yellow	80,40	– 7,96	62,15
Magenta	53,48	48,10	– 1,73
Cyan	59,99	– 21,80	– 25,15
Black	39,92	0,71	4,58
Substrate	82,00	– 1,10	3,35

STANDARDSISO.COM : Click to view the full PDF of ISO 2846-2:2000

## Annex D (informative)

### Detailed explanation of testing including examples

#### D.1 Colorimetric verification

In order to evaluate whether an ink is in accordance with this part of ISO 2846 it is required to print a number of samples, each of known ink film thickness, which adequately represent the range of ink film thicknesses specified in 5.3. These samples may be prepared on a printability tester by running up a small quantity of ink on the inking system, weighing the printing forme prior to printing and then printing the test sample on the reference substrate. The printing forme is then re-weighed and the difference noted. If the mass density of the ink is known (which may be determined by weighing a known volume of ink) and the printed area is measured it is possible to calculate the ink film thickness applied to the paper from the difference in mass before and after printing. This may be done using the formula:

$$s = \Delta m / (\rho \times a)$$

where

$s$  is the ink film thickness;

$m$  is the mass;

$\rho$  is the mass density;

$a$  is the printed area.

After the inking unit has been cleaned a slightly different amount of ink to that used the first time should then be applied to the inking system and the procedure repeated. The process is then repeated time and again, with differing quantities of ink each time, until a number of samples covering the range of ink film thicknesses specified in 5.3 have been prepared.

When dry, a number of the printed samples are selected and their colour is measured according to 4.3. The colour difference between each sample and the colours specified in 5.1 are then calculated and plotted as a function of ink film thickness as shown in Figure D.1. The ink is in accordance with this part of ISO 2846 if at some ink film thickness within the range specified in 5.3 the colour conforms to the values specified in Table 1 within the tolerance also specified there.

Figure D.1 shows the tolerance range for a yellow ink and curve 1 in that figure shows an ink which conforms to the standard. Curves 2 and 3 are examples of inks which deviate from this part of ISO 2846. Curve 2 shows an ink of the wrong colour, most probably of incorrect hue, whereas curve 3 shows an ink of the correct colour but with the wrong pigment concentration.

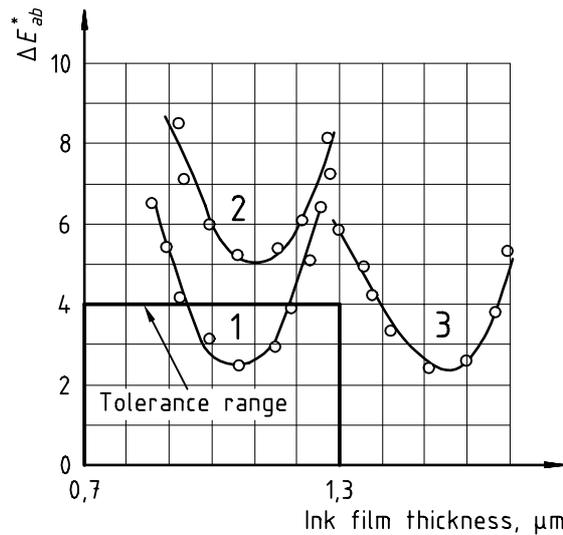


Figure D.1 — Example of how a yellow ink for cold-set lithographic printing may conform to, or deviate from this part of ISO 2846

## D.2 Determination of transparency

Using the procedure described in clause D.1 a series of prints is made covering at least the range of ink film thicknesses specified in 5.3 and preferably beyond for higher precision. For this test a black paper is used. For availability of such a substrate see footnote in 4.2.2.

For the determination of transparency each strip of black substrate should be coded and the colour of the black measured on each, in a defined area, prior to overprinting with the test inks over the range of ink film thicknesses specified.

After the samples which have been printed with the test inks are dry the colour of each sample should be measured as described earlier, in the same place as it was measured for the black.

The colour difference between the two measurements is then calculated for each sample and these are plotted as a function of ink film thickness. The 'best fit' straight line through these points is then drawn as shown in Figure D.2 and the slope of the line calculated. (Alternatively the regression coefficient may be calculated directly from the data). The reciprocal of this value is then computed and this is the transparency measurement value. Using the graphical method this value may be calculated directly as follows:

$$T = (s_1 - s_2) / (\Delta E^*_{ab1} - \Delta E^*_{ab2})$$

where

$T$  is the transparency measurement value;

$s_1$  and  $\Delta E^*_{ab1}$  are the ink film thickness and colour difference for a point on the graph at the higher level of film thickness; and

$s_2$  and  $\Delta E^*_{ab2}$  are the ink film thickness and colour difference for a point on the graph at the lower level of film thickness. These points are shown in Figure D.2.

An ink is in conformance with the transparency requirements of this part of ISO 2846 when the computed value of  $T$  is either negative or greater than the value specified in 5.3.