
**Plastics — Compression moulding
of test specimens of thermoplastic
materials**

*Plastiques — Moulage par compression des éprouvettes en matières
thermoplastiques*

STANDARDSISO.COM : Click to view the full PDF of ISO 293:2023



STANDARDSISO.COM : Click to view the full PDF of ISO 293:2023



COPYRIGHT PROTECTED DOCUMENT

© ISO 2023

All rights reserved. Unless otherwise specified, or required in the context of its implementation, no part of this publication may be reproduced or utilized otherwise in any form or by any means, electronic or mechanical, including photocopying, or posting on the internet or an intranet, without prior written permission. Permission can be requested from either ISO at the address below or ISO's member body in the country of the requester.

ISO copyright office
CP 401 • Ch. de Blandonnet 8
CH-1214 Vernier, Geneva
Phone: +41 22 749 01 11
Email: copyright@iso.org
Website: www.iso.org

Published in Switzerland

Contents

	Page
Foreword.....	iv
Introduction.....	v
1 Scope.....	1
2 Normative references.....	1
3 Terms and definitions.....	1
4 Apparatus.....	2
4.1 Moulding press.....	2
4.2 Moulds.....	2
4.2.1 General.....	2
4.2.2 Fabrication.....	3
4.2.3 Types.....	3
5 Procedure.....	4
5.1 Preparation of moulding material.....	4
5.1.1 Drying of granular material.....	4
5.1.2 Preparation of preforms.....	4
5.2 Moulding.....	5
5.3 Cooling.....	5
5.3.1 General.....	5
5.3.2 Cooling methods.....	5
6 Inspection of the moulded specimens or sheets.....	6
7 Specimen preparation report.....	6
Bibliography.....	7

STANDARDSISO.COM : Click to view the full PDF of ISO 293:2023

Foreword

ISO (the International Organization for Standardization) is a worldwide federation of national standards bodies (ISO member bodies). The work of preparing International Standards is normally carried out through ISO technical committees. Each member body interested in a subject for which a technical committee has been established has the right to be represented on that committee. International organizations, governmental and non-governmental, in liaison with ISO, also take part in the work. ISO collaborates closely with the International Electrotechnical Commission (IEC) on all matters of electrotechnical standardization.

The procedures used to develop this document and those intended for its further maintenance are described in the ISO/IEC Directives, Part 1. In particular, the different approval criteria needed for the different types of ISO documents should be noted. This document was drafted in accordance with the editorial rules of the ISO/IEC Directives, Part 2 (see www.iso.org/directives).

Attention is drawn to the possibility that some of the elements of this document may be the subject of patent rights. ISO shall not be held responsible for identifying any or all such patent rights. Details of any patent rights identified during the development of the document will be in the Introduction and/or on the ISO list of patent declarations received (see www.iso.org/patents).

Any trade name used in this document is information given for the convenience of users and does not constitute an endorsement.

For an explanation of the voluntary nature of standards, the meaning of ISO specific terms and expressions related to conformity assessment, as well as information about ISO's adherence to the World Trade Organization (WTO) principles in the Technical Barriers to Trade (TBT), see www.iso.org/iso/foreword.html.

This document was prepared by Technical Committee ISO/TC 61, *Plastics*, Subcommittee SC 9, *Thermoplastic materials*, in collaboration with the European Committee for Standardization (CEN) Technical Committee CEN/TC 249, *Plastics*, in accordance with the Agreement on technical cooperation between ISO and CEN (Vienna Agreement).

This fourth edition cancels and replaces the third edition (ISO 293:2004), which has been technically revised.

The main changes are as follows:

- the definition for “cooling rate” has been revised (see [3.6](#));
- requirements regarding the biggest clamping force and the highest platens temperature have been changed (see [4.1](#));
- the description of common specifications of positive mould has been given (see [4.2.3.3](#));
- the conditions for the use of vacuum oven while material drying have been added (see [5.1.1](#));
- the methods of cooling rate have been revised (see [Table 1](#));
- a bibliography has been added.

Any feedback or questions on this document should be directed to the user's national standards body. A complete listing of these bodies can be found at www.iso.org/members.html.

Introduction

For reproducible test results, specimens with a specified state are required. In contrast to injection moulding, the aim of compression moulding is to produce test specimens and sheets for machining or stamping of test specimens that are homogeneous and isotropic.

In the process of compression moulding, mixing of material takes place on a negligible scale. Granules and powders fuse only at their surfaces and preforms (milled sheets) are only partially softened.

Isotropic and homogeneous specimens can, therefore, only be obtained when the moulding material is itself homogeneous and isotropic. This has to be considered when processing multiphase materials, such as ABS, which retain their internal structure.

The cooling rate in the crystallization stage has a great influence on the properties of semi-crystalline or crystalline polymer (such as PB, PE, PP, etc.), so it is necessary to control the cooling rate more strictly at the cooling stage.

STANDARDSISO.COM : Click to view the full PDF of ISO 293:2023

[STANDARDSISO.COM](https://standardsiso.com) : Click to view the full PDF of ISO 293:2023

Plastics — Compression moulding of test specimens of thermoplastic materials

1 Scope

This document specifies the general principles and the procedures to be followed with thermoplastics in the preparation of compression-moulded test specimens, and sheets from which test specimens can be machined or stamped.

NOTE In order to obtain mouldings in a reproducible state, the main steps of the procedure, including eight different cooling methods, are standardized. For each material, the required moulding temperature and cooling methods are given in the appropriate International Standard for the material or as agreed between the interested parties.

This document is not applicable to reinforced thermoplastics.

2 Normative references

There are no normative references in this document.

3 Terms and definitions

For the purposes of this document, the following terms and definitions apply.

ISO and IEC maintain terminology databases for use in standardization at the following addresses:

- ISO Online browsing platform: available at <https://www.iso.org/obp>
- IEC Electropedia: available at <https://www.electropedia.org/>

3.1

moulding temperature

temperature of the mould or the press platens during the preheating and moulding time, measured in the nearest vicinity to the moulded material

Note 1 to entry: The moulding temperature is usually expressed in degrees Celsius.

3.2

demoulding temperature

temperature of the mould or the press platens at the end of the cooling time, measured in the nearest vicinity to the moulded material

Note 1 to entry: The demoulding temperature is usually expressed in degrees Celsius.

3.3

preheating time

time required to heat the material in the mould up to the *moulding temperature* (3.1) while maintaining the contact pressure

Note 1 to entry: The preheating time is usually expressed in minute.

3.4

moulding time

time during which full pressure is applied while maintaining the *moulding temperature* (3.1)

Note 1 to entry: The moulding time is usually expressed in minute.

3.5

average cooling rate

<non-linear>rate of cooling by a constant flow of the cooling fluid, calculated by dividing the difference between *moulding temperature* (3.1) and *demoulding temperature* (3.2) by the time required to cool the mould to the *demoulding temperature* (3.2)

Note 1 to entry: The average cooling rate is usually expressed in degrees Celsius per minute.

3.6

cooling rate

controlled cooling rate

<linear>constant rate of cooling in a specified temperature range obtained by controlling the flow of the cooling fluid in such a way that over each specified time interval the deviation from this specified cooling rate does not exceed the specified tolerance

Note 1 to entry: The cooling rate is usually expressed in degrees Celsius per minute.

Note 2 to entry: The specified time interval-controlled cooling rate is based on the system design of moulding press. Usually the shorter time interval used, the more accurate controlled cooling rate can be gained.

4 Apparatus

4.1 Moulding press

The press shall have a clamping force capable of applying a pressure (conventionally given as the ratio of the clamping force to the area of the mould cavity) of at least 12 MPa.

The pressure shall be maintained to within 10 % of the specified pressure during the moulding cycle.

The platens shall be capable of:

- a) being heated to at least 320 °C;
- b) being cooled at a rate given in [Table 1](#).

The difference between the temperatures of any points of the mould surfaces shall not vary by more than ± 2 °C during heating and ± 4 °C during cooling.

When the heating and cooling system is incorporated in the mould, it shall comply with the same conditions.

The platens or mould shall be heated either by high-pressure steam, by a heat-conducting fluid in an appropriate channel system, or by using electric heating elements. The platens or mould are cooled by a heat-conducting fluid (usually cold water) in a channel system.

For quench cooling (see method C in [Table 1](#)), two presses shall be used, one for heating during moulding and the other for cooling.

For a specified cooling method, the flow rate of the heat-conducting fluid shall be predetermined in a test without any material in the mould.

The temperature may be continuously controlled in the centre between the upper and lower platen of the press.

4.2 Moulds

4.2.1 General

The characteristics of the test specimens prepared by using different types of moulds are not the same. In particular, the mechanical properties depend on the pressure applied to the material during cooling.

In general, two types of moulds, “flash mould (picture frame mould)” (see [Figure 1](#)) and “positive mould” (see [Figure 2](#)), are used for compression moulding test specimens of thermoplastics.



Figure 1 — Schematic diagrams of flash mould (picture frame mould)

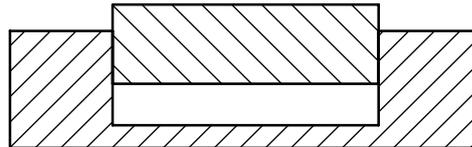


Figure 2 — Schematic diagram of positive mould

Flash mould permits excess moulding material to be squeezed out and do not exert moulding pressure on the moulding material during cooling. They are particularly convenient for preparing test specimens or panels of similar thickness or comparable levels of low internal stress.

With positive moulds, the full moulding pressure, neglecting friction, is exerted on the material during cooling. The thickness, stress and density of the resulting mouldings depend on mould construction, size of material charge and the moulding and cooling conditions. This type of mould produces consolidated test specimens with moulded surfaces and is therefore particularly suitable for obtaining flat surfaces or suppressing the formation of voids within test specimens.

4.2.2 Fabrication

The moulds shall be made of materials capable of withstanding the moulding temperature and pressure. The surfaces in contact with the material shall be polished to obtain good surface conditions on the specimens (recommended surface roughness 0,16 Ra, see ISO 21920-2). Specimen removal can be made easier by chromium plating these surfaces. For specimens of small dimensions, a 2° taper is strongly recommended.

Blind holes may be drilled in the mould so that temperature can be measured in the vicinity of the moulded material by using thermocouples.

Depending on the performance of the press (see [4.1](#)), the moulds may have built-in heating and/or cooling devices similar to those described for the press platens.

An alloy steel, resistant to mechanical shock and heat-treated to provide a tensile strength of 2 200 MPa, will generally be satisfactory for the moulds. However, in the special case of PVC moulding materials, the use of martensite stainless steel treated to provide a tensile strength of 1 050 MPa is recommended.

4.2.3 Types

4.2.3.1 General

The type of mould used shall be capable of producing test specimens of the types and states specified in the appropriate International Standard for the material or shall be agreed upon between the interested parties.

4.2.3.2 Flash moulds (picture frame moulds)

With this type of mould, the excess material is squeezed out and the moulding pressure during cooling is only exerted on the frame and not on the material. The thickness in the centre of the mouldings is slightly less than at the edges due to the shrinkage during cooling. Directly moulded test bars may also have sink marks or voids if the shrinkage is hindered by sticking of the plastic material to the mould.

To overcome these disadvantages, stamping or machining of test specimens from the central part of compression-moulded sheets is preferred.

For moulding sheets, simple and economical flash moulds can be used, consisting of a frame covered with two plates (see [Figure 1](#)). The lower and upper plates, having a thickness of about 4 mm to 5 mm, can be made from polished steel or chromium-plated brass to aid release. To avoid the plastic material sticking to the plates, they can be covered by a flexible foil, for example of aluminium or polyester.

Use of a release agent is not allowed.

The thickness of the chase shall be appropriate to the moulded sheet thickness.

The size of the moulding frame shall be such that the main test area of the specimens can be cut or machined without using the outer 20 mm perimeter of the sheet.

4.2.3.3 Positive moulds

These moulds (see [Figure 2](#)) are fitted with one or two male pistons and a female part. They allow known pressure, neglecting friction, to be applied to the material, and to be maintained during the moulding and cooling times.

NOTE 1 For positive moulds, if needed, holes are normally drilled in the mould for measuring the temperatures.

The thickness of the moulding will depend on the quantity of material, its thermal expansion, and the loss of material due to clearances in the moulds. The losses will be a function of the flow of the material at the chosen moulding temperature, the applied pressure, the time over which the pressure is applied, mould construction, etc.

Correct guidance of the male part in the female part is facilitated by use of a round cavity. A fit between these parts of H7g6 (see ISO 286-1) is recommended, i.e. between 15 µm and 90 µm for a round cavity of diameter 200 mm. The mould may be fitted with one or several ejection pins to make part removal easier.

NOTE 2 For the majority of specimen types and dimensions specified in ISO 20753, a square cavity can be used such as 170 mm × 170 mm for obtaining enough specimens for one test by each moulding and it also can make the mould weight lighter.

5 Procedure

5.1 Preparation of moulding material

5.1.1 Drying of granular material

Dry the granular material as specified in the relevant International Standard or in accordance with the material supplier's instructions. If no instructions are given, dry for 24 h ± 1 h at 70 °C ± 2 °C in an oven, or for 16 h ± 1 h at 80 °C ± 2 °C in a vacuum oven.

5.1.2 Preparation of preforms

Direct moulding of sheet from granules shall be the standard procedure, provided that a sufficiently homogeneous sheet is obtained. Normally, this means that the sheet is free from surface irregularities and internal imperfections. Direct moulding from powder or granules may sometimes require melt

homogenization using a hot melt milling or mixing procedure to achieve a satisfactory final sheet. Conditions shall be used that do not degrade the polymer. This can usually be achieved by not milling or mixing for more than 5 min after melting. The preform sheet obtained shall be thicker than the test sheet to be moulded and of sufficient size to enable the test sheet to be moulded.

Storing the preforms in a dry, airtight container is recommended.

5.2 Moulding

Adjust the mould temperature to within ± 5 °C of the moulding temperature specified in the relevant International Standard or as agreed between the interested parties.

Place a weighed quantity of the material (granules or preforms) in the preheated mould. If granular material is used, make sure that it is evenly spread over the mould surface. The mass of the material shall be sufficient to fill the cavity volume when it is melted and allow about a 10 % loss for a flash mould and about a 3 % loss for a positive mould. With flash moulds, cover the mould with a flexible foil (see 4.2.3.2) and then place the mould in the preheated press.

Close the press using contact pressure, preheat the material with preheating time, then apply full pressure with moulding time and then cool down (see 5.3) using the conditions specified in the relevant International Standard or agreed between the interested parties.

A preheating time of 5 min is the standardized time for evenly spread material charges sufficient for sheets up to 2 mm thickness. For thicker mouldings, this time shall be adjusted accordingly.

NOTE At contact pressure, the press is just closed with a pressure low enough to avoid flow of the material. Full pressure means a pressure sufficient to shape the material and squeeze out the excess material.

5.3 Cooling

5.3.1 General

With some thermoplastics, the cooling rate affects the ultimate physical properties. For this reason, the cooling methods are specified in Table 1 with different average cooling rate or cooling rate.

The method of cooling shall always be stated together with the final physical properties. The appropriate cooling method is normally given in the relevant International Standard for the material. If no method is indicated, method B shall be used.

5.3.2 Cooling methods

The appropriate cooling method shall be selected from Table 1.

Table 1 — Cooling methods

Cooling method	Average cooling rate °C/min	Cooling rate °C/min	Remarks
A	10 ± 5		
A1		10 ± 2	
B	15 ± 5		
B1		15 ± 2	
C	60 ± 30		Quench cooling
D		5 ± 0,5	Slow cooling
E	30 ± 5		
E1		30 ± 2	