
International Standard



340

INTERNATIONAL ORGANIZATION FOR STANDARDIZATION • МЕЖДУНАРОДНАЯ ОРГАНИЗАЦИЯ ПО СТАНДАРТИЗАЦИИ • ORGANISATION INTERNATIONALE DE NORMALISATION

Flame retardation of conveyor belts — Specifications and method of test

Résistance des courroies transporteuses à la flamme — Spécifications et méthodes d'essai

First edition — 1982-12-15

STANDARDSISO.COM : Click to view the full PDF of ISO 340:1982

UDC 621.867.2 : 620.1 : 536.468

Ref. No. ISO 340-1982 (E)

Descriptors : conveyor belts, fire resistance, tests, test specimens, test equipment, specifications.

Price based on 6 pages

Foreword

ISO (the International Organization for Standardization) is a worldwide federation of national standards bodies (ISO member bodies). The work of developing International Standards is carried out through ISO technical committees. Every member body interested in a subject for which a technical committee has been authorized has the right to be represented on that committee. International organizations, governmental and non-governmental, in liaison with ISO, also take part in the work.

Draft International Standards adopted by the technical committees are circulated to the member bodies for approval before their acceptance as International Standards by the ISO Council.

International Standard ISO 340 was developed by Technical Committee ISO/TC 41, *Pulleys and belts (including veebelts)*, and was circulated to the member bodies in September 1981.

It has been approved by the member bodies of the following countries:

Canada	India	Spain
Czechoslovakia	Italy	Sri Lanka
Egypt, Arab Rep. of	Korea, Rep. of	Sweden
Finland	Poland	United Kingdom
France	Romania	USSR
Germany, F.R.	South Africa, Rep. of	

The member bodies of the following countries expressed disapproval of the document on technical grounds:

Australia
Austria
Japan
USA

This International Standard cancels and replaces ISO Recommendation ISO/R 340-1963, of which it constitutes a technical revision.

Flame retardation of conveyor belts — Specifications and method of test

0 Introduction

In many countries, specifications of flame retardation of conveyor belts and the corresponding methods of test are the subject of legislation. However, it has been thought necessary to prepare an International Standard in order to give a reference if there is no particular legislation.

1 Scope and field of application

This International Standard specifies conditions for a flame retardation test for conveyor belts, and the corresponding requirements.

NOTES

- 1 To increase safety, it is important for tests to take into account, as far as possible, the circumstances which may create hazards. It is for this reason that, in this International Standard, provision is made for performing the test on test pieces without covers, as covers of belts may be ripped off accidentally in service.
- 2 It is stressed that for small scale laboratory tests of the type covered in this International Standard, the correlation of the test results with the flammability under other conditions is not in any case implied.

2 References

ISO 235, *Parallel shank twist drills, jobber and stub series, and Morse taper shank twist drills.*

ISO 426/2, *Wrought copper-zinc alloys — Chemical composition and forms of wrought products — Part 2 : Lead alloys.*

ISO 565, *Test sieves — Woven metal wire cloth and perforated plate — Nominal sizes of apertures.*

ISO 835, *Graduated pipettes (excluding blowout pipettes).*

ISO 2194, *Wire screens and plate screens for industrial purposes — Nominal sizes of apertures.*

ISO 3310/1, *Test sieves — Technical requirements and testing — Part 1 : Metal wire cloth.*

ISO 3310/2, *Test sieves — Technical requirements and testing — Part 2 : Metal perforated plate.*

3 Specifications

3.1 Duration of flame (after removal of the burner)

The duration of flame shall be less than 45 s for each group of six tests, and no individual value shall be greater than 15 s (see 4.5.1).

3.2 Non-reappearance of flame (after applying a current of air)

The flame shall not reappear (see 4.5.2).

4 Method of test

4.1 Principle

A test piece is placed in the flame of a burner, the burner is removed and the combustion time of the test piece is noted (duration of flame). A current of air is then applied to the test piece a specified time after the extinction of the flame.

4.2 Test pieces

4.2.1 Shape and dimensions

Rectangular test piece (cut out from the conveyor belt) :

- length : 200 mm
- width : 25 mm

4.2.2 Number and distribution

4.2.2.1 If the test is made with test pieces with and without covers, prepare 12 test pieces distributed as follows :

- with covers : 3 warp way and 3 weft way;
- without covers : 3 warp way and 3 weft way.

4.2.2.2 If the test is made with test pieces with covers only, prepare 6 test pieces, 3 warp way and 3 weft way.

4.2.3 Preparation

Cut out the test pieces with a knife.

For test pieces without covers, remove the covers by stripping or, if this is impossible, with a knife or by buffing. In the latter event, take care that the cover is not abnormally overheated, and cease buffing as soon as the threads of the carcass become visible.

4.3 Apparatus and materials

4.3.1 Spirit burner, the characteristics and operating conditions of which are given in the annex (see figure 1).

4.3.2 Tank and flexible supply tube of approximately 1,50 m length (see the annex).

4.3.3 Fuel (see the annex).

4.4 Procedure

Operate in an open atmosphere, sheltered from draughts.

Arrange the test piece in a vertical plane (with its major axis vertical) so that its lower edge is 50 mm away from the top of the burner. The burner shall be inclined at an angle of 45° and the vertical plane through its axis should coincide with the mid-plane of the test piece parallel to the covers (see figure 2).

The fuel consumption of the burner shall be 2,55 ± 0,15 ml/min. In this case the burner should have a flame length of approximately 150 to 180 mm. Check that the burner is operating properly by measuring the fuel flow according to the method described in the annex (see A.3.3).

Hold the test piece in the flame for 45 s and then remove the burner without extinguishing it. (Keep the burner sheltered from the current of air, if further tests are to be performed.)

Note the duration of flame, starting from this moment.

One minute (with a tolerance of ± 10 s) after the removal of the burner, apply a current of air with a velocity of about 1,5 m/s (see figure 2).

4.5 Expression of results

4.5.1 Duration of flame (after removal of the burner)

4.5.1.1 Express the results by :

a) total of results of 6 tests with covers, i.e. :

3 warp way, 3 weft way;

b) whenever relevant, total of results of 6 tests without covers, i.e. :

3 warp way, 3 weft way.

4.5.1.2 Note, in each of cases 4.5.1.1 a) and b), the maximum value of the individual results obtained.

4.5.2 Non-reappearance of flame

Note whether or not the flame reappears.

5 Test report

The test report shall refer to this International Standard and contain the following information :

- a) the identification of the belt tested;
- b) the results of the test, as described in 4.5;
- c) the date of the test.

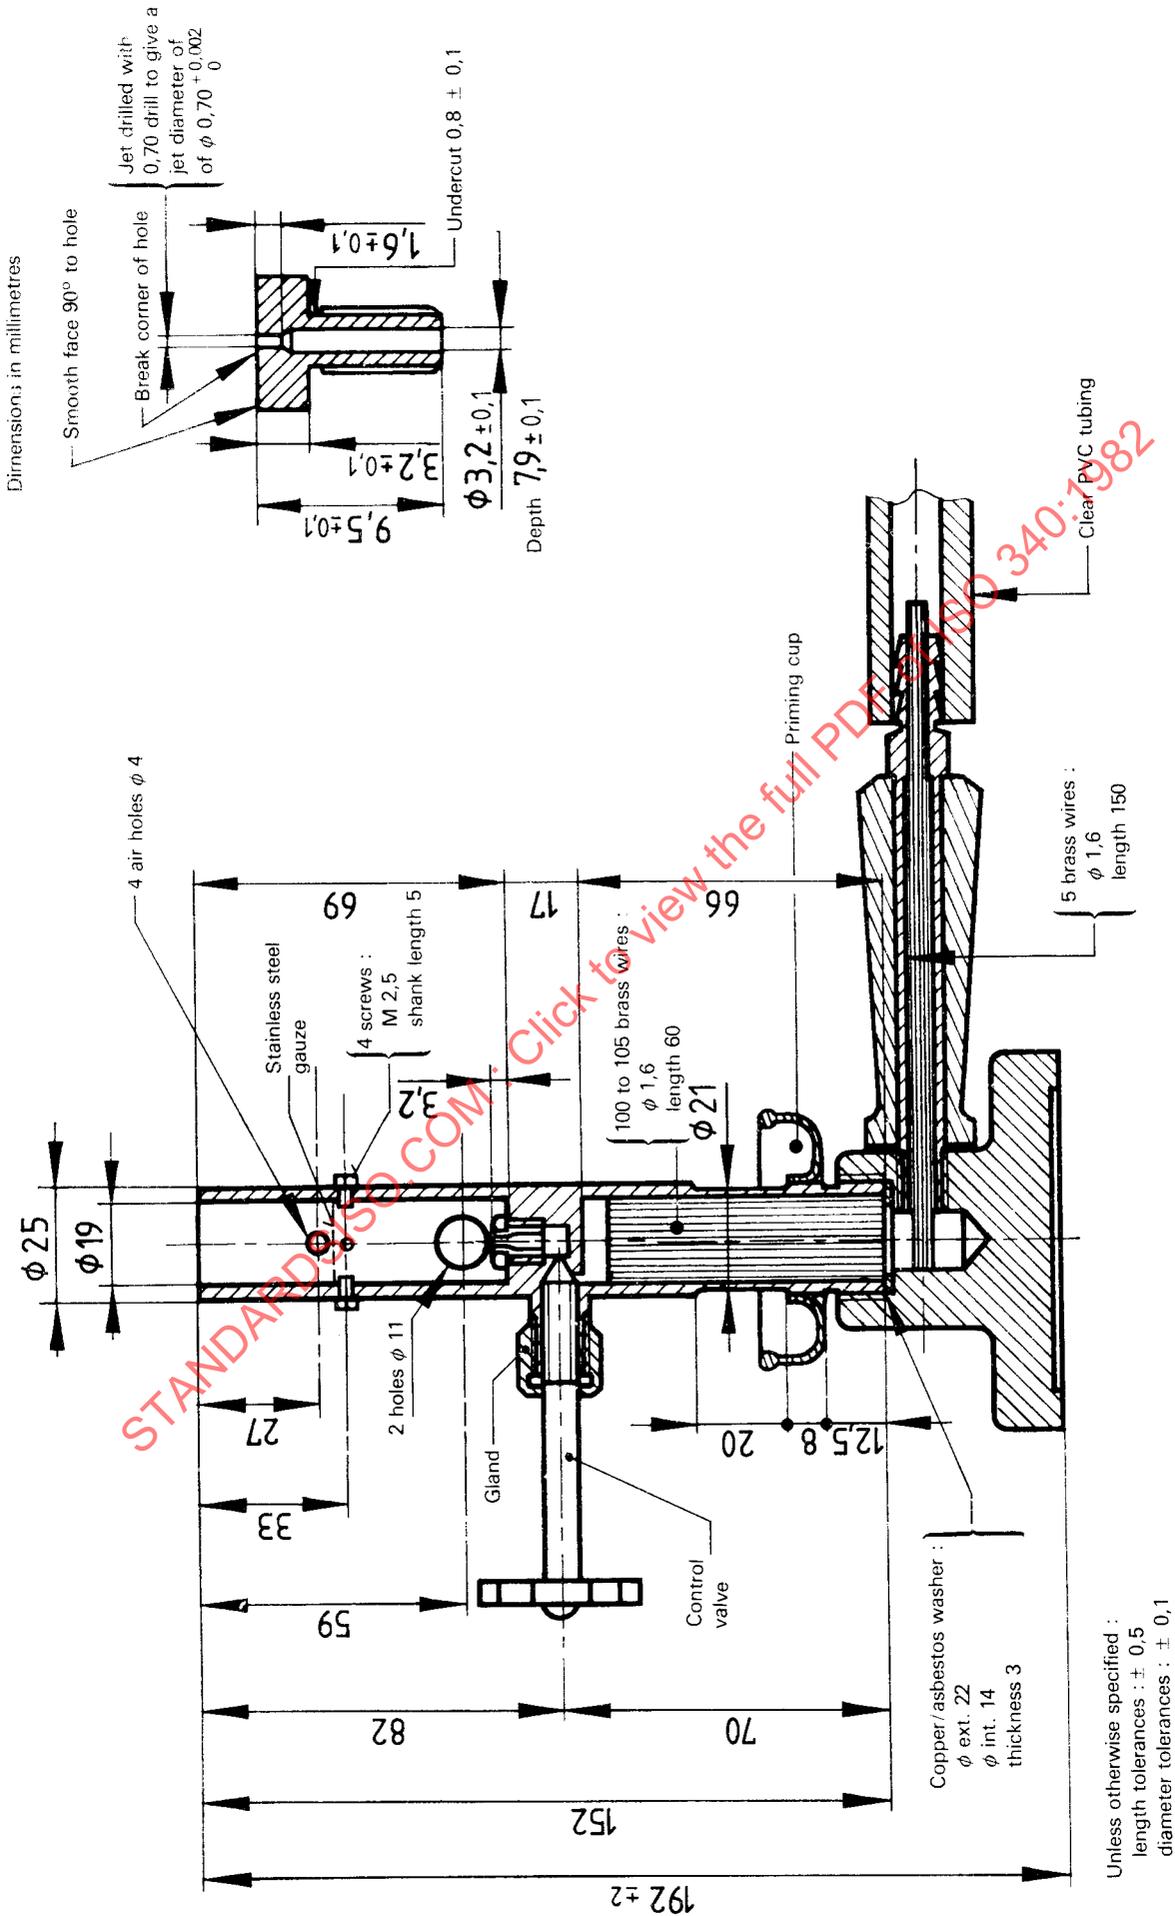


Figure 1 — Spirit burner

Unless otherwise specified:
 length tolerances: $\pm 0,5$
 diameter tolerances: $\pm 0,1$

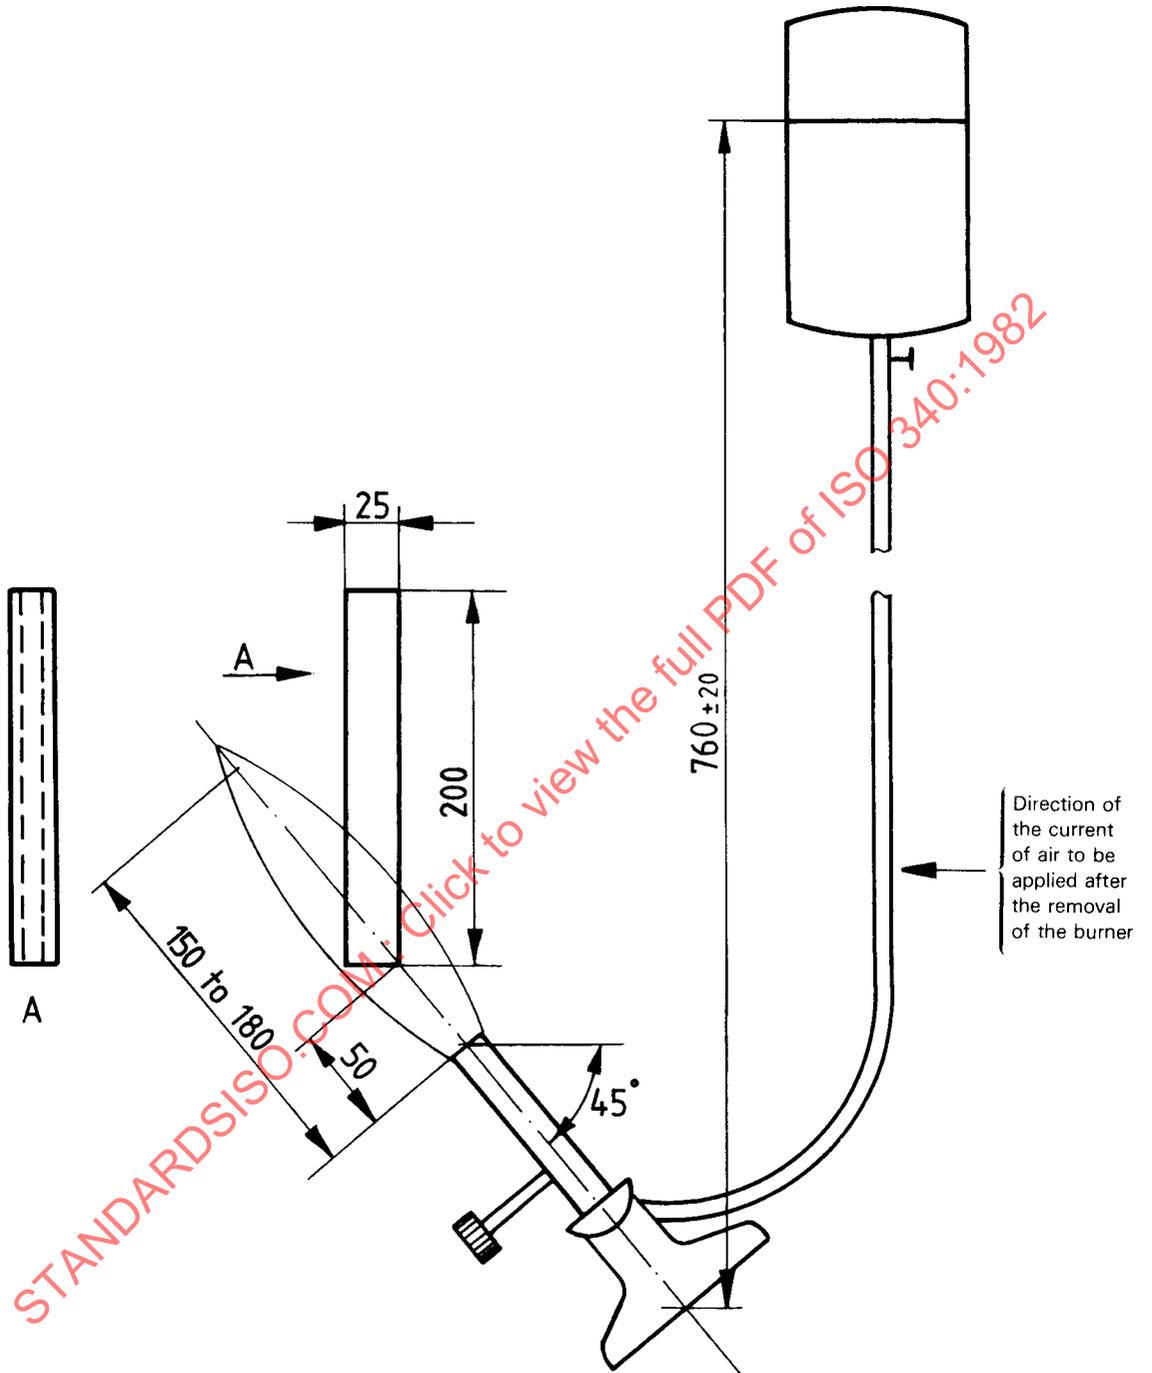


Figure 2 – Air current direction