
**Gas welding equipment — Rubber
hoses for welding, cutting and allied
processes**

*Matériel de soudage aux gaz — Tuyaux souples en caoutchouc pour le
soudage, le coupage et les techniques connexes*

STANDARDSISO.COM : Click to view the full PDF of ISO 3821:2019



STANDARDSISO.COM : Click to view the full PDF of ISO 3821:2019



COPYRIGHT PROTECTED DOCUMENT

© ISO 2018

All rights reserved. Unless otherwise specified, or required in the context of its implementation, no part of this publication may be reproduced or utilized otherwise in any form or by any means, electronic or mechanical, including photocopying, or posting on the internet or an intranet, without prior written permission. Permission can be requested from either ISO at the address below or ISO's member body in the country of the requester.

ISO copyright office
CP 401 • Ch. de Blandonnet 8
CH-1214 Vernier, Geneva
Phone: +41 22 749 01 11
Fax: +41 22 749 09 47
Email: copyright@iso.org
Website: www.iso.org

Published in Switzerland

Contents

	Page
Foreword	v
1 Scope	1
2 Normative references	1
3 Terms and definitions	2
4 Abbreviated terms	2
5 Application	2
6 Hose designation	2
7 Materials	3
7.1 Construction	3
7.1.1 Light and normal duty hoses	3
7.1.2 Flux fuel gas hose	3
7.1.3 Twin hose	3
7.2 Manufacture	3
8 Dimensions and tolerances	3
8.1 Inside diameters	3
8.2 Outside diameters	4
8.3 Wall thickness	4
8.4 Concentricity (total indicator reading)	5
8.5 Cut lengths and tolerances	5
8.6 Disclosure of inside diameter and outside diameter	5
9 Requirements and type tests	5
9.1 General	5
9.2 Basic requirements	5
9.2.1 Tensile strength and elongation at break	5
9.2.2 Accelerated ageing	5
9.2.3 Adhesion	5
9.2.4 Hydrostatic requirements	6
9.2.5 Flexibility at ambient temperature	6
9.2.6 Low-temperature flexibility	6
9.2.7 Protection against incandescent particles and hot surfaces	6
9.2.8 Ozone resistance	6
9.3 Special requirements	6
9.3.1 Non-ignition requirement for oxygen hoses	6
9.3.2 Resistance to acetone and dimethylformamide for acetylene hoses	7
9.3.3 Resistance to <i>n</i> -pentane for propane hoses	7
9.3.4 Resistance to azeotrope of trimethylborate with methanol for flux fuel gas hoses	7
9.3.5 Flexibility of flux fuel gas hoses	8
9.3.6 Permeability to LPG, MPS, and natural gas of methane hoses, universal fuel gas hoses, and flux fuel gas hoses	8
9.3.7 Requirements for twin hoses	8
9.3.8 Requirements for universal fuel gas hose	8
10 Hose colour and gas identification	8
10.1 General	8
10.2 Gas identification	8
10.3 Marking	9
Annex A (normative) Method of test for non-ignition	10
Annex B (normative) Method of test for resistance to <i>n</i>-pentane	12
Annex C (normative) Method of test for resistance to incandescent particles and hot surfaces	13

Annex D (normative) Summary of requirements and type tests	15
Annex E (normative) Alternative oxygen gas colour codes	16
Bibliography	17

STANDARDSISO.COM : Click to view the full PDF of ISO 3821:2019

Foreword

ISO (the International Organization for Standardization) is a worldwide federation of national standards bodies (ISO member bodies). The work of preparing International Standards is normally carried out through ISO technical committees. Each member body interested in a subject for which a technical committee has been established has the right to be represented on that committee. International organizations, governmental and non-governmental, in liaison with ISO, also take part in the work. ISO collaborates closely with the International Electrotechnical Commission (IEC) on all matters of electrotechnical standardization.

The procedures used to develop this document and those intended for its further maintenance are described in the ISO/IEC Directives, Part 1. In particular, the different approval criteria needed for the different types of ISO documents should be noted. This document was drafted in accordance with the editorial rules of the ISO/IEC Directives, Part 2 (see www.iso.org/directives).

Attention is drawn to the possibility that some of the elements of this document may be the subject of patent rights. ISO shall not be held responsible for identifying any or all such patent rights. Details of any patent rights identified during the development of the document will be in the Introduction and/or on the ISO list of patent declarations received (see www.iso.org/patents).

Any trade name used in this document is information given for the convenience of users and does not constitute an endorsement.

For an explanation of the voluntary nature of standards, the meaning of ISO specific terms and expressions related to conformity assessment, as well as information about ISO's adherence to the World Trade Organization (WTO) principles in the Technical Barriers to Trade (TBT) see www.iso.org/iso/foreword.html.

This document was prepared by Technical Committee ISO/TC 44, *Welding and allied processes*, Subcommittee SC 8, *Equipment for gas welding, cutting and allied processes*.

Any feedback or questions on this document should be directed to the user's national standards body. A complete listing of these bodies can be found at www.iso.org/members.html.

Official interpretations of TC 44 documents, where they exist, are available from this page: <https://committee.iso.org/sites/tc44/home/interpretation.html>.

This fifth edition cancels and replaces the fourth edition (ISO 3821:2008) which has been technically revised.

The main changes compared to the previous edition are as follows:

- the definition of maximum working pressure has been added;
- [Clauses 7](#) to [9](#) have been revised;
- the requirements for marking have been revised;
- editorial changes have been made.

[STANDARDSISO.COM](https://standardsiso.com) : Click to view the full PDF of ISO 3821:2019

Gas welding equipment — Rubber hoses for welding, cutting and allied processes

1 Scope

This document specifies requirements for rubber hoses (including twin hoses) for welding, cutting and allied processes.

This document specifies requirements for rubber hoses for normal duty of 2 MPa (20 bar) and light duty [limited to hoses for maximum working pressure of 1 MPa (10 bar) and with bore up to and including 6,3 mm].

This document applies to hoses operated at temperatures -20 °C to $+60\text{ °C}$ and used in:

- gas welding and cutting;
- arc welding under the protection of an inert or active gas;
- processes allied to welding and cutting, in particular, heating, brazing, and metallization.

This document does not specify requirements for hose assemblies; these are detailed in ISO 8207.

This document applies neither to thermoplastics hoses nor to hoses used for high pressure [$>0,15\text{ MPa}$ ($>1,5\text{ bar}$)] acetylene.

2 Normative references

The following documents are referred to in the text in such a way that some or all of their content constitutes requirements of this document. For dated references, only the edition cited applies. For undated references, the latest edition of the referenced document (including any amendments) applies.

ISO 37, *Rubber, vulcanized or thermoplastic — Determination of tensile stress-strain properties*

ISO 188, *Rubber, vulcanized or thermoplastic — Accelerated ageing and heat resistance tests*

ISO 1307:2006, *Rubber and plastics hoses — Hose sizes, minimum and maximum inside diameters, and tolerances on cut-to-length hoses*

ISO 1402, *Rubber and plastics hoses and hose assemblies — Hydrostatic testing*

ISO 10619-1, *Rubber and plastics hoses and tubing — Measurement of flexibility and stiffness — Part 1: Bending tests at ambient temperature*

ISO 10619-2, *Rubber and plastics hoses and tubing — Measurement of flexibility and stiffness — Part 2: Bending tests at sub-ambient temperatures*

ISO 1817, *Rubber, vulcanized or thermoplastic — Determination of the effect of liquids*

ISO 4080, *Rubber and plastics hoses and hose assemblies — Determination of permeability to gas*

ISO 4671, *Rubber and plastics hoses and hose assemblies — Methods of measurement of the dimensions of hoses and the lengths of hose assemblies*

ISO 7326, *Rubber and plastics hoses — Assessment of ozone resistance under static conditions*

ISO 8033, *Rubber and plastics hoses — Determination of adhesion between components*

ISO 8330, *Rubber and plastics hoses and hose assemblies — Vocabulary*

ISO 11114-3, *Gas cylinders — Compatibility of cylinder and valve materials with gas contents — Part 3: Autogenous ignition test for non-metallic materials in oxygen atmosphere*

ISO 15296, *Gas welding equipment — Vocabulary*

ISO 23529, *Rubber — General procedures for preparing and conditioning test pieces for physical test methods*

3 Terms and definitions

For the purposes of this document, the terms and definitions given in ISO 8330 and ISO 15296 and the following apply.

ISO and IEC maintain terminological databases for use in standardization at the following addresses:

- ISO Online browsing platform: available at <https://www.iso.org/obp>
- IEC Electropedia: available at <http://www.electropedia.org/>

3.1

twin hose

two normal rubber hoses joined together longitudinally

3.2

universal fuel gas hose

hose which can be used for all fuel gases except fluxed fuel gas

Note 1 to entry: Fuel gases are listed in [Table 5](#).

3.3

flux fuel gas hose

hose suitable for fuel gas containing a flux

3.4

maximum working pressure

maximum pressure to which the equipment may be subjected in service

4 Abbreviated terms

LPG liquefied petroleum gases

MPS methylacetylene-propadiene mixtures

5 Application

Hoses shall only be used for the gas service for which they are identified (see [10.2](#)).

6 Hose designation

The hoses covered by this document are designated using the following information:

- inside diameter, see [Table 1](#);
- light or normal duty (pressure rating), see [Table 4](#);
- colour and marking (gas service), see [Table 5](#).

EXAMPLE 1 6,3 mm, light duty. Blue (Oxygen).

EXAMPLE 2 10 mm, normal duty. Red and Orange (Universal fuel gases).

EXAMPLE 3 6,3 mm, light duty, FLUX. Red (Fluxed fuel gases).

7 Materials

7.1 Construction

7.1.1 Light and normal duty hoses

The hose shall consist of:

- a) a rubber lining of minimum thickness 1,3 mm for hoses with total wall thickness of 3,0 mm or less and 1,5 mm for hoses with total wall thickness greater than 3,0 mm;
- b) reinforcement applied by any suitable technique;
- c) a rubber cover of a minimum thickness of 1,0 mm.

7.1.2 Flux fuel gas hose

The flux fuel gas hose shall consist of the following:

- a) a rubber lining with an additional inner plastic layer, which shall be of maximum thickness 0,5 mm, to give a minimum total thickness of a rubber lining of 1,3 mm for hoses with total wall thickness of 3,0 mm or less and 1,5 mm for hoses with total wall thickness greater than 3,0 mm;
- b) reinforcement applied by any suitable technique;
- c) a rubber cover of minimum thickness 1,0 mm.

7.1.3 Twin hose

Each hose used for twin hose construction shall be as specified in [7.1.1](#) or [7.1.2](#). The two hoses shall be joined longitudinally during the extrusion and/or vulcanization process. They shall be capable of being separated free of damage to enable end fittings to be fitted (see [9.3.7](#)).

7.2 Manufacture

The lining and cover shall be of uniform thickness and free from holes, porosity and other defects.

8 Dimensions and tolerances

8.1 Inside diameters

The inside diameters of the hoses shall be in accordance with the dimensions and tolerances shown in [Table 1](#).

Table 1 — Dimensions and tolerances on inside diameter

Nominal size	Inside diameter	
	Basic dimension mm	Tolerance mm
4,0	4,0	±0,4
4,8	4,8	
5,0	5,0	
6,3	6,3	
7,1	7,1	
8,0	8,0	±0,5
9,5	9,5	
10,0	10,0	
12,5	12,5	±0,6
16,0	16,0	
20,0	20,0	
25,0	25,0	
32,0	32,0	±1,0
40,0	40,0	±1,25
50,0	50,0	

NOTE 1 Nominal sizes, basic dimensions and their tolerances on inside diameters do not comply with ISO 1307:2006, Table 1.

NOTE 2 For intermediate dimensions, numbers are chosen from the R20 series of preferred numbers (see ISO 3) with tolerances for the next larger inside diameter listed.

8.2 Outside diameters

The basic dimensions of the outside diameters of the hoses shall be determined by the manufacturer by determining the total wall thickness of the hoses (including rubber lining, rubber cover and reinforcement layer) relative to the basic dimensions of the inside diameter by the manufacturer. The tolerances on the basic dimensions of the outside diameters shall be in accordance with the values shown in [Table 2](#).

Table 2 — Outside diameter ranges and its corresponding tolerance and concentricity

OD range	Tolerance on OD	Concentricity maximum
	mm	mm
Up to and including 12,0 mm	±0,6	0,6
Greater than 12,0 mm up to and including 16,0 mm	±0,8	0,7
Greater than 16,0 mm up to and including 22,5 mm	±1,0	0,8
Greater than 22,5 mm up to and including 42,0 mm	±1,5	1,0
Greater than 42,0 mm	±1,8	1,3

8.3 Wall thickness

The wall thickness of rubber lining, rubber cover and inner plastic layer of the hoses shall be not less than the minimum thickness specified in [7.1.1](#) and [7.1.2](#).

8.4 Concentricity (total indicator reading)

The concentricity of the hose, measured in accordance with ISO 4671, shall be in accordance with the values given in [Table 2](#).

8.5 Cut lengths and tolerances

The tolerances for cut lengths shall be in accordance with ISO 1307.

8.6 Disclosure of inside diameter and outside diameter

The manufacturer shall indicate the combination of the basic dimensions of the inside diameter and the outside diameter on the hose as specified in [10.3](#). In addition, basic dimensions of the inside diameter and outside diameter of the hose and their permissible tolerances should be disclosed in the documents such as the catalogues, specifications, instruction manuals and the like.

9 Requirements and type tests

9.1 General

A summary of requirements and type tests with the corresponding number of samples is given in [Annex D](#).

9.2 Basic requirements

9.2.1 Tensile strength and elongation at break

Measurements shall be made on test pieces cut from the hoses. The materials used in the lining and cover, when tested in accordance with ISO 37, shall have a tensile strength and elongation at break not less than the values given in [Table 3](#).

Table 3 — Tensile strength and elongation at break

Rating	Tensile strength	Elongation at break
	MPa	%
Rubber lining	5	200
Cover	7	250
Inner plastic layer	5	120

9.2.2 Accelerated ageing

Measurements shall be made on test pieces cut from the hoses. After ageing for 7 days at a temperature of (70 ± 2) °C as specified in ISO 188 (air oven), the tensile strength and elongation at break respectively of the lining and cover shall not decrease from the original values obtained by more than 25 % for the tensile strength and 50 % for elongation at break.

9.2.3 Adhesion

When tested in accordance with ISO 8033 using the type 2 or type 4 test piece, the minimum adhesion between adjacent components of the hose shall be 1,5 kN/m. For flux fuel gas hoses (see [9.3.4](#)). For flux fuel gas hoses, the inner plastic layer shall be removed prior to the test.

9.2.4 Hydrostatic requirements

The hose, when tested in accordance with ISO 1402 at ambient temperature, shall meet the requirements of [Table 4](#).

Table 4 — Hydrostatic requirements

Rating	Light duty (Inside diameter ≤6,3 mm)	Normal duty (all sizes)
Maximum working pressure	1 MPa (10 bar)	2 MPa (20 bar)
Proof pressure	2 MPa (20 bar)	4 MPa (40 bar)
Minimum burst pressure	3 MPa (30 bar)	6 MPa (60 bar)
Change in length at maximum working pressure	±5 %	
Change in diameter at maximum operating pressure	±10 %	

9.2.5 Flexibility at ambient temperature

When tested in accordance with ISO 10619-1 at standard laboratory temperature as defined in ISO 23529 using a diameter of curvature, D_c , of $10 D_i$, where D_i is the inside diameter (with a minimum of 80 mm), the coefficient of deformation, K , shall not be less than 0,8. There shall be no kink in the curved portion of the hose.

9.2.6 Low-temperature flexibility

When tested in accordance with ISO 10619-2, method B, at $(-25 \pm 3) ^\circ\text{C}$, using a D_c of $10 D_i$ (with a minimum of 80 mm), the hose shall show no signs of leakage when subjected to the proof pressure (carried out at ambient temperature) stated in [Table 4](#).

9.2.7 Protection against incandescent particles and hot surfaces

The cover of the hose shall have sufficient protection against contact with incandescent particles and hot surfaces. To meet this requirement, the test piece shall resist for 60 s the test conditions given in [Annex C](#) without leaking, i.e. no loss in pressure.

If the first test fails, the two subsequent tests shall meet the requirements to pass the test.

9.2.8 Ozone resistance

Hoses up to 25 mm inside diameter shall be tested in accordance with ISO 7326, method 1, using a D_c as specified in [9.2.5](#). Hoses above 25 mm inside diameter shall be tested in accordance with ISO 7326, method 3 or method 4. For all methods the cover shall show no evidence of cracking when viewed under two times magnification.

9.3 Special requirements

9.3.1 Non-ignition requirement for oxygen hoses

The non-ignition test shall be carried out either according to ISO 11114-3 or [Annex A](#).

When tested according to ISO 11114-3, the initial conditions shall be set at 2 MPa (20 bar) (ambient temperature) and the self-ignition temperature shall be higher than 150 °C.

When tested by the method described in [Annex A](#), three samples of the lining shall remain in the apparatus at a constant temperature of 360 °C to 365 °C for 2 min without ignition.

If more than one of the samples show evidence of ignition in less than 2 min, the hose shall be considered not to comply. If only one sample shows evidence of ignition in less than 2 min, three further samples shall be prepared and tested. If any of the three samples in this second series shows evidence of ignition in less than 2 min, the hose shall be deemed not to comply.

9.3.2 Resistance to acetone and dimethylformamide for acetylene hoses

A sample of the lining, when immersed in the acetone at standard laboratory temperature as defined in ISO 23529 for 70 h, shall not increase in mass by more than 8 % when calculated in accordance with the method specified in ISO 1817.

A sample of the lining, when immersed in the dimethylformamide at standard laboratory temperature as defined in ISO 23529 for 70 h, shall not increase in mass by more than 8 % when calculated in accordance with the method specified in ISO 1817.

9.3.3 Resistance to *n*-pentane for propane hoses

A sample of the hose lining, when tested as described in [Annex B](#), shall show absorbed *n*-pentane not exceeding 15 % mass fraction (see [B.1](#)) and *n*-pentane extractable matter within 10 % mass fraction (see [B.2](#)).

9.3.4 Resistance to azeotrope of trimethylborate with methanol for flux fuel gas hoses

9.3.4.1 Adhesion after conditioning in trimethylborate-methanol azeotrope

Remove the inner plastic layer from the rubber lining.

Seal one end of the test hose and fill the hose with the test fluid and condition for (70 ± 2) h at (23 ± 2) °C. After this period empty the test fluid from the hose and leave for 24 h.

An adhesion test in accordance with ISO 8033 using the type 2 or type 4 test piece shall be carried out on three test pieces taken from the hose after the fluid has been removed.

The adhesion between the rubber lining and the reinforcement shall meet the specified requirements. The hose shall have a minimum adhesion between the rubber lining and the reinforcement of 1,5 kN/m.

9.3.4.2 Tensile strength and elongation at break after conditioning in trimethylborate-methanol azeotrope

The hose when tested in accordance with the following method shall have a variation in the tensile strength and elongation at break of less than 30 % from the original values obtained under [9.2.1](#).

Seal one end of the test hose and fill the hose with the test fluid and condition for (70 ± 2) h at (23 ± 2) °C. After this period empty the test fluid from the hose and leave for 24 h.

Tensile strength and elongation at break tests in accordance with ISO 37 shall be carried out on five test pieces of inner plastic layer of the lining cut from a hose after the fluid has been emptied. The measurement shall be carried out 24 h after the emptying of the hose.

The variation of the tensile strength and elongation at break shall meet the specified requirements.

9.3.4.3 Change in mass and volume after immersion in trimethylborate-methanol azeotrope

A mass and volume variation test in accordance with ISO 1817 shall be carried out on three test pieces of inner plastic layer of the lining, cut from a hose and immersed in the test liquid for (70 ± 2) h at (23 ± 2) °C.

The mass and volume variation of the inner plastic layer of the lining shall not exceed 8 %. The measurement shall be carried out within 30 min after taking the test pieces out of the test liquid.

9.3.5 Flexibility of flux fuel gas hoses

One sample of hose shall be filled with trimethylborate-methanol azeotrope for 70 h at (23 ± 2) °C. The flux fuel gas hoses shall then be submitted to the same test as specified in 9.2.5. The test shall be carried out within 30 min after the emptying of the hose. In addition to the requirements of 9.2.5, the hose shall show no signs of leaks when subjected to the proof pressure (carried out at ambient temperature) specified in Table 4.

9.3.6 Permeability to LPG, MPS, and natural gas of methane hoses, universal fuel gas hoses, and flux fuel gas hoses

When tested in accordance with ISO 4080 using a test gas of 95 % volume fraction propylene at cylinder pressure [approximately 0,6 MPa (6 bar)] and standard laboratory temperature of (23 ± 2) °C as defined in ISO 23529, the gas permeance shall not exceed 25 cm³/m·h, irrespective of inside diameter.

9.3.7 Requirements for twin hoses

9.3.7.1 General

Both of the hoses from the twin hose construction shall after separation by the following test method conform to this document. Each individual hose shall meet all the requirements when subjected to the relevant tests for the specific hose type.

9.3.7.2 Separation test for twin hose

It shall be possible to separate twin hose into two single hoses with a force between 25 N to 100 N. The test shall be carried out using a tensile test machine. Initially separate using a knife, a sufficient length of the twin hose to enable each individual hose to be secured in the jaws. Mark 200 mm of unseparated hose. Execute the test over a length of 300 mm with a jaw separation speed of 100 mm/min. The value of the force to be taken into account is the mean value measured during the propagation phase of the notch, excluding the first 100 mm where the tension is not yet stable.

9.3.8 Requirements for universal fuel gas hose

Hoses shall comply with the requirements of 9.3.2, 9.3.3 and 9.3.6.

10 Hose colour and gas identification

10.1 General

The hose cover material shall be coloured throughout and marked as follows.

10.2 Gas identification

In order to identify the gas for which the hose is to be used, the hose cover shall be coloured and marked as specified in Table 5. In some countries, national requirements on colour identification have been standardized. In these cases, the colour identification detailed in Annex E shall apply. For countries that have no such standards or regulations, the colour identification specified in Table 5 shall apply.

In the case of twin hoses, each of the individual hoses shall be coloured and marked in accordance with this document.

Table 5 — Hose colour and gas identification

Gas	Colour and marking of cover
Acetylene, other fuel gases ^a (except LPG, MPS, natural gas, methane)	red
Oxygen	blue
Compressed air, nitrogen, argon, helium ^b , CO ₂	black
LPG, MPS, natural gas, methane	orange
Universal fuel gases (included in this table) except fluxed fuel gases	red and orange
Fluxed fuel gases	red-FLUX
^a The manufacturer shall be consulted on the suitability of the hose for use with hydrogen.	
^b The manufacturer shall be consulted on the suitability of the hose for use with helium.	

10.3 Marking

The hose cover shall be durably marked at least every 1 000 mm with the following information:

- a) a reference to this document, i.e. ISO 3821;
- b) "FLUX" (for flux fuel gas hoses only);
- c) the maximum working pressure in megapascals and between parentheses in bar;
- d) the combination of the basic dimensions of the inside diameter and the outside diameter in millimetres;
- e) the manufacturer's and/or supplier's mark (in the examples given as XYZ);
- f) the year of manufacture.

EXAMPLE 1 ISO 3821 - 2 MPa (20 bar) - 10×17 - XYZ - 2018.

EXAMPLE 2 ISO 3821 - FLUX 2 MPa (20 bar) - 6,3×12,3 - XYZ - 2018.

Annex A (normative)

Method of test for non-ignition

A.1 Apparatus

Usual laboratory apparatus and in particular the following.

A.1.1 Apparatus shown in Figure A.1, the tubing portions of which shall be constructed from borosilicate glass of wall thickness:

- a) 0,75 mm to 1,25 mm for a diameter of 6 mm to 9 mm;
- b) 1 mm to 2 mm for a diameter of 36 mm to 46 mm.

A.1.2 Heating furnace, of 350 W, with internal dimensions: 150 mm deep by 50 mm diameter.

A.1.3 Tubular variable resistance, of 190 Ω to 200 Ω , with screw movement or an auto-transformer with continuously variable output voltage.

A.1.4 Calibrated flowmeter for oxygen, for 0 l/min to 5 l/min at atmospheric pressure and 15 °C.

A.1.5 Nitrogen-filled mercury-in-glass thermometer, suitable for use at 150 mm immersion, graduated from approximately 300 °C to 400 °C in intervals of not more than 5 °C, the graduations to start not less than 200 mm above the bulb.

A.2 Procedure

Insert the ignition test apparatus in its aluminium foil wrapping, into the electric furnace. The purpose of the aluminium foil is to minimize heat loss by radiation and to obtain a more uniform temperature distribution. Adjust the energy supply to the electric furnace with the variable resistance or auto-transformer so that a constant temperature of 360 °C to 365 °C is maintained with the oxygen flowing at $(2 \pm 0,1)$ l/min.


Cut the sample of rubber lining for test, after cleaning by buffing, into blocks of 8 mm³ to 10 mm³ of which no side shall be less than 1,3 mm nor greater than 2,5 mm.

When the furnace is at constant temperature, remove the sample holder, impale a sample block of the rubber lining under test on the tungsten point and replace the sample holder in the apparatus. It is necessary for this operation to be carried out quickly, so that cooling is reduced to a minimum. The tungsten point should be kept clean and sharp.

Retain the sample in the apparatus for at least 2 min and observe it carefully during this period for evidence of ignition. Fumes can be observed, but this shall not constitute evidence of ignition, which is normally accompanied by a flash and sometimes by a small explosion. When ignition of a sample occurs, the temperature of the apparatus can rise; time shall then be allowed to permit the temperature to return to the appropriate testing temperature.

Test three samples consecutively.

Dimensions in millimetres

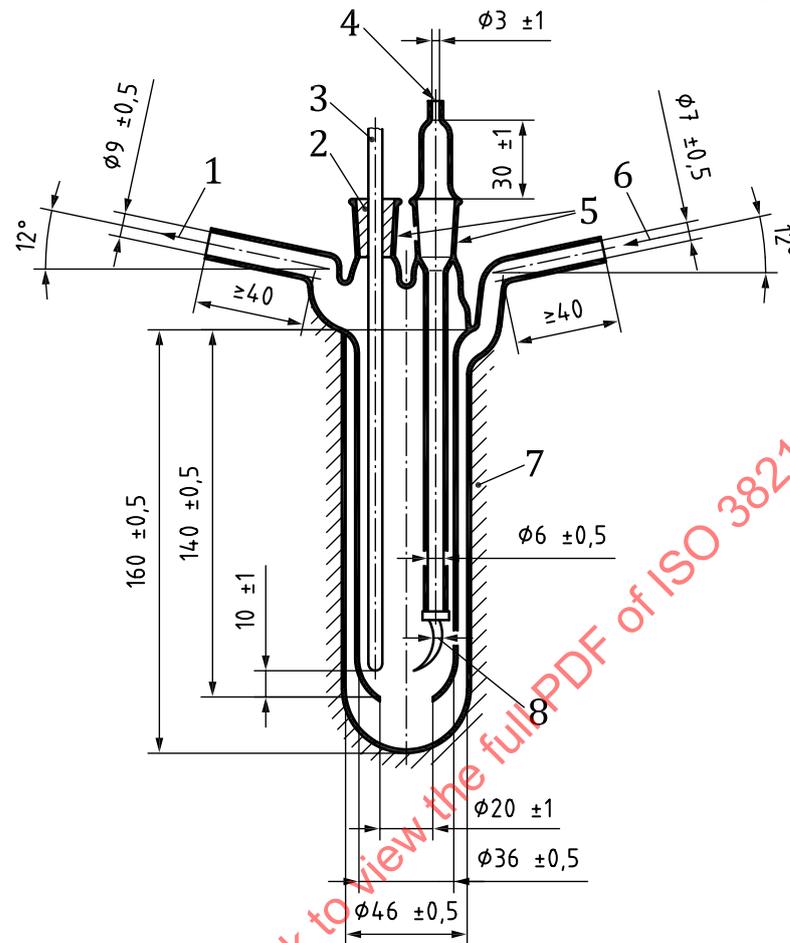**Key**

- 1 oxygen outlet
- 2 heat-resistant packing
- 3 thermometer
- 4 orifice
- 5 14/23 joints
- 6 oxygen inlet
- 7 aluminium foil
- 8 tungsten wire of diameter 0,7 mm tapered to a fine point and of length $(20 \pm 0,5)$ mm

Figure A.1 — Apparatus for ignition tests on lining samples

Annex B (normative)

Method of test for resistance to *n*-pentane

B.1 Weigh a portion of the hose lining and then immerse it in *n*-pentane at standard laboratory temperature as defined in ISO 23529 [(23±2) °C] for 72 h. The volume of the *n*-pentane shall be at least 50 times the volume of the test piece.

B.2 Following immersion, reweigh the test piece after 5 min conditioning in air at standard laboratory temperature and reweigh again after 24 h further conditioning in air at standard laboratory temperature.

B.3 Calculate the percentage mass fraction *n*-pentane absorbed from [Formula \(B.1\)](#):

$$\frac{m_1 - m_2}{m_0} \times 100 \quad (\text{B.1})$$

and the percentage mass fraction of *n*-pentane-extractable matter from [Formula \(B.2\)](#):

$$\frac{m_0 - m_2}{m_0} \times 100 \quad (\text{B.2})$$

where

m_0 is the initial mass of each test piece;

m_1 is the mass of each test piece after immersion and 5 min conditioning;

m_2 is the mass of each test piece after 24 h further conditioning.


Annex C (normative)

Method of test for resistance to incandescent particles and hot surfaces

A circuit diagram for the chromium-nickel steel heating wire is shown in [Figure C.1](#).

Clamp a sample of hose, approximately 500 mm in length, in the test apparatus (see [Figure C.2](#)). Clamp the heating wire (2,5 mm diameter) between the electrical connections, spaced 100 mm apart. The downward force of the incandescent wire, perpendicular to the hose axis, shall be 1 N during the duration of the test (see [Figure C.3](#)). At the beginning of the test, fill the hose with an inert gas, e.g. nitrogen, at a pressure of 0,1 MPa (1 bar). In the case of twin hoses, the force shall be applied straight on the separation line.

Heat the wire with a current of 50 A, at a potential of 2 V maximum, to obtain a temperature of $(800 \pm 80) ^\circ\text{C}$.

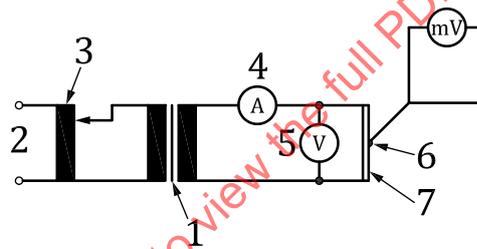

Key

- 1 isolation transformer
- 2 power supply
- 3 variable output transformer
- 4 ammeter
- 5 voltmeter
- 6 thermocouple
- 7 chromium-nickel steel wire (X10CrNi18-8 (EN steel number 1.4310)) of diameter 2,5 mm

Figure C.1 — Circuit diagram for the test apparatus