
**Plain bearings — Metallic multilayer
plain bearings —**

Part 1:

**Non-destructive ultrasonic testing
of bond of thickness greater than or
equal to 0,5 mm**

Paliers lisses — Paliers lisses métalliques multicouches —

*Partie 1: Contrôle non destructif aux ultrasons des défauts
d'adhérence d'épaisseur supérieure ou égale à 0,5 mm*

STANDARDSISO.COM : Click to view the full PDF of ISO 4386-1:2019



STANDARDSISO.COM : Click to view the full PDF of ISO 4386-1:2019



COPYRIGHT PROTECTED DOCUMENT

© ISO 2019

All rights reserved. Unless otherwise specified, or required in the context of its implementation, no part of this publication may be reproduced or utilized otherwise in any form or by any means, electronic or mechanical, including photocopying, or posting on the internet or an intranet, without prior written permission. Permission can be requested from either ISO at the address below or ISO's member body in the country of the requester.

ISO copyright office
CP 401 • Ch. de Blandonnet 8
CH-1214 Vernier, Geneva
Phone: +41 22 749 01 11
Fax: +41 22 749 09 47
Email: copyright@iso.org
Website: www.iso.org

Published in Switzerland

Contents

	Page
Foreword	iv
1 Scope	1
2 Normative references	1
3 Terms and definitions	1
4 Symbols	1
5 Test equipment	2
5.1 Ultrasonic instrument	2
5.2 Probe	2
5.3 Reference block	2
6 Preparation of test surface	2
7 Testing	2
7.1 General	2
7.2 Testing with a back-wall echo	2
7.3 Testing without a back-wall echo	3
8 Test classes	6
9 Defect groups	6
10 Evaluation	7
10.1 General	7
10.2 Marking of defective areas	8
10.3 Designation	8
Bibliography	9

STANDARDSISO.COM : Click to view the full PDF of ISO 4386-1:2019

Foreword

ISO (the International Organization for Standardization) is a worldwide federation of national standards bodies (ISO member bodies). The work of preparing International Standards is normally carried out through ISO technical committees. Each member body interested in a subject for which a technical committee has been established has the right to be represented on that committee. International organizations, governmental and non-governmental, in liaison with ISO, also take part in the work. ISO collaborates closely with the International Electrotechnical Commission (IEC) on all matters of electrotechnical standardization.

The procedures used to develop this document and those intended for its further maintenance are described in the ISO/IEC Directives, Part 1. In particular, the different approval criteria needed for the different types of ISO documents should be noted. This document was drafted in accordance with the editorial rules of the ISO/IEC Directives, Part 2 (see www.iso.org/directives).

Attention is drawn to the possibility that some of the elements of this document may be the subject of patent rights. ISO shall not be held responsible for identifying any or all such patent rights. Details of any patent rights identified during the development of the document will be in the Introduction and/or on the ISO list of patent declarations received (see www.iso.org/patents).

Any trade name used in this document is information given for the convenience of users and does not constitute an endorsement.

For an explanation of the voluntary nature of standards, the meaning of ISO specific terms and expressions related to conformity assessment, as well as information about ISO's adherence to the World Trade Organization (WTO) principles in the Technical Barriers to Trade (TBT), see www.iso.org/iso/foreword.html.

This document was prepared by Technical Committee ISO/TC 123, *Plain bearings*, Subcommittee SC 2, *Materials and lubricants, their properties, characteristics, test methods and testing conditions*.

This fourth edition cancels and replaces the third edition (ISO 4386-1:2012), of which it constitutes a minor revision. The changes compared to the previous edition are as follows:

- Adjustment to the ISO Directives, including the implementation of [Clause 3](#) *Terms and definitions*.

A list of all parts in the ISO 4386 series can be found on the ISO website.

Any feedback or questions on this document should be directed to the user's national standards body. A complete listing of these bodies can be found at www.iso.org/members.html.

Plain bearings — Metallic multilayer plain bearings —

Part 1:

Non-destructive ultrasonic testing of bond of thickness greater than or equal to 0,5 mm

1 Scope

This document specifies an ultrasonic testing method for determining bond defects between the bearing metal and the backing. The test can be performed on metallic multilayer plain bearings consisting of steel- or copper-based material backings lined with bearing metal based on lead and tin, with layer thicknesses greater than or equal to 0,5 mm. For cast iron backings, this document is applicable with restrictions.

The ultrasonic signal reflected by the bond interface between the bearing metal and the backing is used to determine bonding defects.

Ultrasonic testing is not possible on edge zones of sliding surface, flange sides, joint areas, oil holes, grooves, etc. in a range of less than half the diameter of the ultrasonic probe because of undefined reflections. The same applies to bearings with dovetail keying grooves at the bond. Ultrasonic testing of bond does not apply along the edges of the dovetails.

Evaluation of the bond on the visible transition from the backing to the bearing metal (on end faces or joint faces) is only practicable by the penetrant testing method specified in ISO 4386-3.

This document only describes in detail the pulse-echo method. Within the meaning of this document, the ultrasonic method only permits a qualitative evaluation of the bonding and not a quantitative determination of the bond strength. The ultrasonic bond test differs only between bond and bond defect.

2 Normative references

The following documents are referred to in the text in such a way that some or all of their content constitutes requirements of this document. For dated references, only the edition cited applies. For undated references, the latest edition of the referenced document (including any amendments) applies.

ISO 4386-3, *Plain bearings — Metallic multilayer plain bearings — Part 3: Non-destructive penetrant testing*

3 Terms and definitions

No terms and definitions are listed in this document.

ISO and IEC maintain terminological databases for use in standardization at the following addresses:

- ISO Online browsing platform: available at <https://www.iso.org/obp>
- IEC Electropedia: available at <http://www.electropedia.org/>

4 Symbols

The following symbol is used in this document.

Ra Surface roughness

5 Test equipment

5.1 Ultrasonic instrument

Pulse-echo ultrasonic instrument using rectified A-scope presentation shall be used for the test. The instrument shall be fitted with a calibrated attenuator, reading in decibels, and adjustable time base ranges.

5.2 Probe

For the standard procedure, normal beam probes shall be chosen with size and frequency in relation to the thickness of the bearing layer, backing thickness and backing material. The typical range of diameters is from 24 mm for 2 MHz to 6 mm for 10 MHz probes. For layer thickness < 1 mm, testing with dual-element probes may be chosen.

5.3 Reference block

The time base range shall be adjusted, using a reference block corresponding to the thicknesses of the bearing to be inspected.

6 Preparation of test surface

The test surface shall have a surface roughness of $Ra \leq 5 \mu\text{m}$. After machining, remove dirt and oil using suitable cleaning agents.

7 Testing

7.1 General

Test plain bearings using either contact scanning, with light machine oil as a couplant, or using immersion scanning. Suppression and swept-gain functions shall be switched off. The preferred test is performed from the bearing metal side under consideration of the back-wall echo. Bearings with smaller diameters can be difficult to inspect by contact scanning from the bearing metal side because of limited access of the ultrasonic probe. In such a case, contact scanning from the back surface may be used.



7.2 Testing with a back-wall echo

General preconditions are:



- a) free access with the probe to the contact surface;
- b) back-wall is always parallel to the bearing metal surface;
- c) no hollow spaces within the backing material (drilled holes, channels, etc.).

The time base range and sensitivity shall be adjusted so that at least the first back-wall echo is visible on the right-hand side of the screen at approximately 80 % of full screen height. In [Figure 1](#), the bond echo (BE) is on the left-hand side of the screen near the input signal (IS). If in doubt about having the first back-wall echo (WE1) on the screen, use a reference block for adjustment.

Bond defect is given when the back-wall echo breaks down and at the same time, the bond echo on the left-hand side of the screen increases and repeats multiple times (see [Figure 1](#)). The border of the detected defect area is on the middle of the probe diameter when the back-wall echo is reduced to its half height under the above-mentioned conditions.

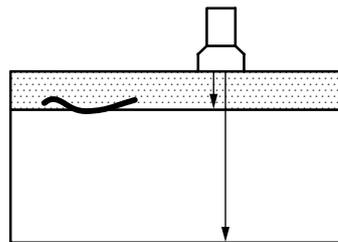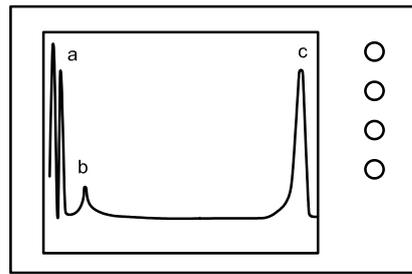

a) Bond

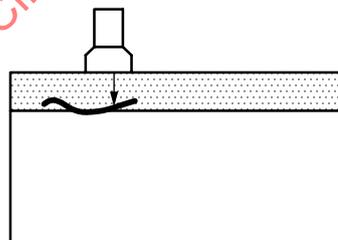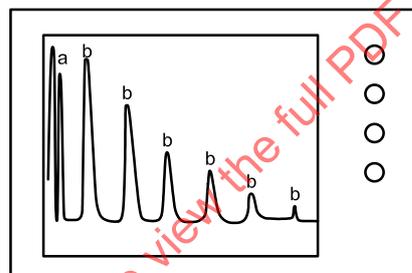

b) Defective bond

Key

- a Input signal (IS).
- b Bond echo (BE).
- c First back-wall echo (WE_1).


Figure 1 — Testing with a back-wall echo**7.3 Testing without a back-wall echo**

If the preconditions of 7.2 are not fulfilled, testing without back-wall echo becomes necessary.

Use a reference piece with good bond between similar backing material and similar bearing metal lining as the tested bearing. Adjust the reference bond echo to 20 % of full screen height; see Figure 2.

Bond is given when the echo signal of the tested plain bearing is similar to the adjusted reference bond echo; see [Figure 3](#).


Defective bond is given when the bond echo on the plain bearing is significant above the reference bond height; see [Figure 4](#).

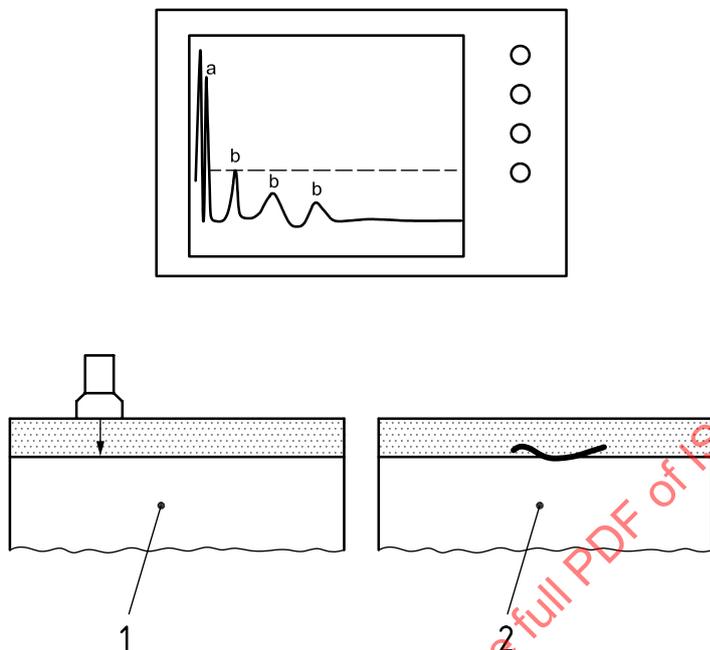

Key

- 1 reference block
- 2 test object
- a Input signal (IS).
- b Reference echo (RE).


Figure 2 — Testing without a back-wall echo: display and adjustment of reference echo

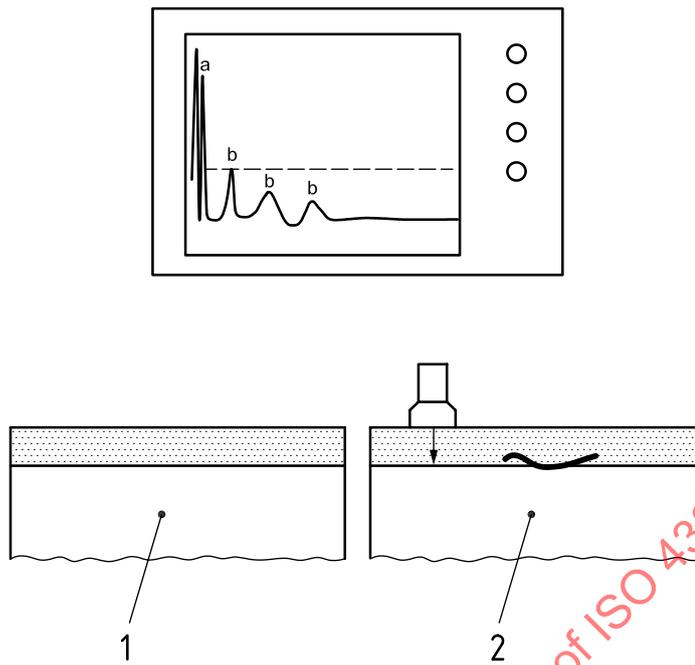

Key

- 1 reference block
- 2 test object
- a Input signal (IS).
- b Bond echo (BE).

**Figure 3 — Testing without a back-wall echo:
display of bond**

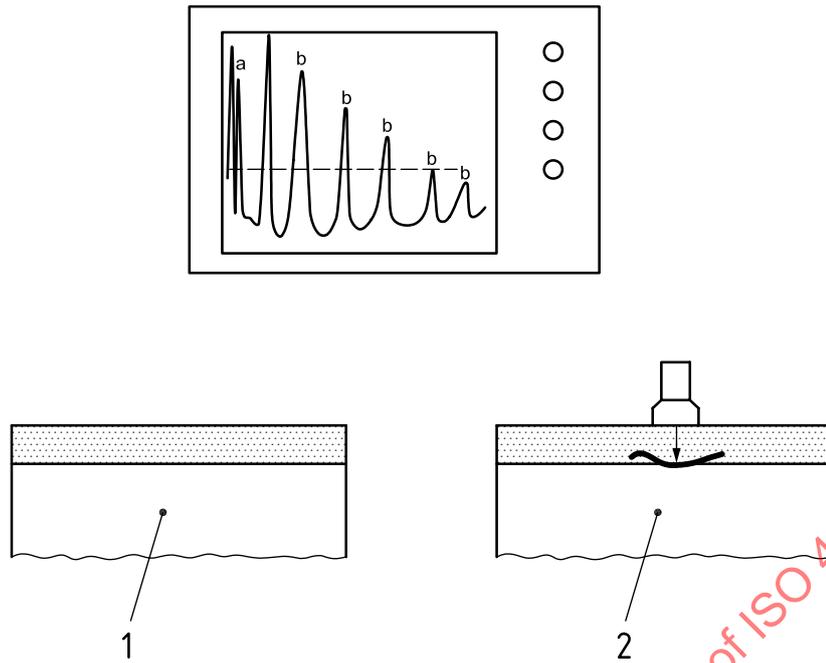

- Key**
- 1 reference block
 - 2 test object
 - a Input signal (IS).
 - b Bond echo (BE).

Figure 4 — Testing without a back-wall echo: display of bond defect

8 Test classes

The test shall be carried out in accordance with one of the following three classes, which are of increasing severity.

- Class 1: complete coverage of the testable area of the edge zones of the sliding surface at flange sides and joint areas; point-type coverage of the sliding surface.
- Class 2: complete coverage of the testable area of the edge zones of the sliding surface at flange sides and joint areas. In addition, complete coverage of the area of maximum loading (for example, in the case of a radial bearing with a bearing force acting vertically downwards, this would be in the range from 60° to 120° with respect to the sliding surface).
- Class 3: complete coverage of the testable area of the flange areas and sliding surface line-by-line. In order to cover all points, testing is carried out with an overlap of the lines of 20 % of the probe diameter.

9 Defect groups

As a guideline, [Table 1](#) shows five different defect groups. The applicable defect groups shall be agreed between the customer and the supplier in advance. Different defect groups should be defined for different regions of a bearing, depending on the kind, size and direction of the load (for example, defect group A for the high-loaded region and defect group B1 for the remaining regions of a journal bearing). Generally, defect group A should be reserved for high-loaded bearings and therefore the area of maximal loading.

Table 1 — Defect groups

Defect group	Maximum areal dimension of single defects	Maximum total defect
	mm ²	Percentage of bonding area ^a %
A	0	0
B1	0,75b ^b	1
B2	2b ^b	1
C	2b ^b	2
D	4b ^b	5

^a The bonding area is the lined area of a journal bearing or a thrust plain bearing element.

^b The width, *b*, in millimetres represents, in case of journal bearing, the functional cylindrical length and, in the case of thrust segments or rings, the distance between the inner and outer diameter. The summary of single defects may not exceed the maximum total defect size.

10 Evaluation

10.1 General

The tests should be carried out by operators educated for ultrasonic testing.

When evaluating the test results in accordance with this document, bond defects equal to or larger than half the probe diameter are normally estimated.

In case of any irregularities on bond surface of a bearing backing, the relevant area shall be collected and documented in the drawing before lining with bearing metal. This avoids misinterpretation during ultrasonic testing as a bond defect.

If the bond echo signal becomes diffuse and missing scanning contact can be excluded, this indicates porosities within the bearing metal. Such areas of porosity shall be regarded as defects due to the uncertainty of evaluation of the bond.

For inspection of the bearing, the following steps shall be considered.

- a) After local repair work by a soldering procedure, the bond test shall be repeated in the respective area.

On edge zones, the visible transition from the backing to the bearing metal shall be checked in accordance with non-destructive penetrant testing specified in ISO 4386-3.

- b) Evaluation of defect distribution: detected bond defects on new lined bearings give additional information depending on their location and distribution.

- 1) Single bond defects in the flange side edge zone or in the corner between flange side - joint side: these defects are typically based on local temperature losses during the casting procedure. Usually, these defects can be repaired by soldering procedure without any quality reduction.
- 2) Single bond defects on sliding surface: if repair work by soldering can be carried out, bond strength is sufficient and quality is not reduced.
- 3) Many bond defects distributed on sliding surface: many detected bond defects distributed on the total sliding surface and growing defects during the soldering procedure are indicators for low bond strength at all. Complete renewal of bearing metal lining is recommended.