



**International  
Standard**

**ISO 4628-3**

**Paints and varnishes — Evaluation  
of quantity and size of defects, and  
of intensity of uniform changes in  
appearance —**

**Part 3:  
Assessment of degree of rusting**

*Peintures et vernis — Évaluation de la quantité et de la  
dimension des défauts, et de l'intensité des changements  
uniformes d'aspect —*

*Partie 3: Évaluation du degré d'enrouillement*

**Fourth edition  
2024-11**

STANDARDSISO.COM : Click to view the full PDF of ISO 4628-3:2024



**COPYRIGHT PROTECTED DOCUMENT**

© ISO 2024

All rights reserved. Unless otherwise specified, or required in the context of its implementation, no part of this publication may be reproduced or utilized otherwise in any form or by any means, electronic or mechanical, including photocopying, or posting on the internet or an intranet, without prior written permission. Permission can be requested from either ISO at the address below or ISO's member body in the country of the requester.

ISO copyright office  
CP 401 • Ch. de Blandonnet 8  
CH-1214 Vernier, Geneva  
Phone: +41 22 749 01 11  
Email: [copyright@iso.org](mailto:copyright@iso.org)  
Website: [www.iso.org](http://www.iso.org)

Published in Switzerland

# Contents

	Page
<b>Foreword</b> .....	<b>iv</b>
<b>Introduction</b> .....	<b>vi</b>
<b>1 Scope</b> .....	<b>1</b>
<b>2 Normative references</b> .....	<b>1</b>
<b>3 Terms and definitions</b> .....	<b>1</b>
<b>4 Symbols and abbreviations</b> .....	<b>2</b>
<b>5 Assessment of red rust</b> .....	<b>2</b>
5.1 Method 1: Assessment of the degree of red rust by comparison with pictorial standards (R <sub>i</sub> ).....	2
5.2 Method 2: Assessment of the degree of red rust by estimating the corroded area in per cent (R%).....	8
<b>6 Assessment of white rust</b> .....	<b>8</b>
6.1 Method 1: Assessment of the degree of white rust by comparison with pictorial standards (WR <sub>i</sub> ).....	8
6.2 Method 2: Assessment of the degree of white rust by estimating the corroded area in per cent (WR%).....	13
<b>7 Expression of results</b> .....	<b>14</b>
<b>8 Test report</b> .....	<b>14</b>
<b>Annex A (normative) Calibration images</b> .....	<b>15</b>
<b>Annex B (informative) Example for degree of rusting after performing the NSS salt spray test</b> .....	<b>20</b>
<b>Annex C (informative) Correlation between the ISO rating system specified in this document and other systems</b> .....	<b>21</b>
<b>Bibliography</b> .....	<b>22</b>

STANDARDSISO.COM : Click to view the full PDF of ISO 4628-3:2024

## Foreword

ISO (the International Organization for Standardization) is a worldwide federation of national standards bodies (ISO member bodies). The work of preparing International Standards is normally carried out through ISO technical committees. Each member body interested in a subject for which a technical committee has been established has the right to be represented on that committee. International organizations, governmental and non-governmental, in liaison with ISO, also take part in the work. ISO collaborates closely with the International Electrotechnical Commission (IEC) on all matters of electrotechnical standardization.

The procedures used to develop this document and those intended for its further maintenance are described in the ISO/IEC Directives, Part 1. In particular, the different approval criteria needed for the different types of ISO documents should be noted. This document was drafted in accordance with the editorial rules of the ISO/IEC Directives, Part 2 (see [www.iso.org/directives](http://www.iso.org/directives)).

ISO draws attention to the possibility that the implementation of this document may involve the use of (a) patent(s). ISO takes no position concerning the evidence, validity or applicability of any claimed patent rights in respect thereof. As of the date of publication of this document, ISO had not received notice of (a) patent(s) which may be required to implement this document. However, implementers are cautioned that this may not represent the latest information, which may be obtained from the patent database available at [www.iso.org/patents](http://www.iso.org/patents). ISO shall not be held responsible for identifying any or all such patent rights.

Any trade name used in this document is information given for the convenience of users and does not constitute an endorsement.

For an explanation of the voluntary nature of standards, the meaning of ISO specific terms and expressions related to conformity assessment, as well as information about ISO's adherence to the World Trade Organization (WTO) principles in the Technical Barriers to Trade (TBT), see [www.iso.org/iso/foreword.html](http://www.iso.org/iso/foreword.html).

This document was prepared by Technical Committee ISO/TC 35, *Paints and varnishes*, Subcommittee SC 9, *General test methods for paints and varnishes*, in collaboration with the European Committee for Standardization (CEN) Technical Committee CEN/TC 139, *Paints and varnishes*, in accordance with the Agreement on technical cooperation between ISO and CEN (Vienna Agreement).

This fourth edition cancels and replaces the third edition (ISO 4628-3:2016), which has been technically revised.

The main changes are as follows:

- the title has been shortened;
- the normative references have been updated;
- term [3.1](#), “degree of rusting” has been deleted;
- new terms [3.1](#) “red rust”, [3.2](#) “white rust” and [3.3](#) “rust traces” have been added;
- [Clause 4](#) on symbols and abbreviations has been added;
- “rusted area” has been changed to “corroded area” in the entire text;
- a note on the original size of the figures has been added to the former [Clause 4](#), which now is [Clause 5](#);
- [Table 1](#) for designating the size of rusting has been added;
- the percentage of the corroded area in [Figure A.5](#) has been corrected;
- the assessment of white rust together with new pictorial standards has been added;
- the assessment of the degree of rusting by estimating the corroded area in per cent has been added;
- point “d) the method of assessment (method 1 or method 2) which was used;” has been added to the test report in [Clause 8](#);

## ISO 4628-3:2024(en)

- a new [Annex B](#) has been added, showing an example for a test panel after the NSS salt spray test specified in ISO 9227 with a degree of rusting Ri 4;
- the former [Annex B](#) has become [Annex C](#);
- in [Annex C](#), the correlation with the ASTM rust scale has been adjusted to ASTM D610-08.

A list of all parts in the ISO 4628 series can be found on the ISO website.

Any feedback or questions on this document should be directed to the user's national standards body. A complete listing of these bodies can be found at [www.iso.org/members.html](http://www.iso.org/members.html)

STANDARDSISO.COM : Click to view the full PDF of ISO 4628-3:2024

## Introduction

ISO 4628-1 describes the system used for designating the quantity and size of defects and the intensity of changes in appearance of coatings, and it outlines the general principles of the system. This system is intended to be used, in particular, for defects caused by ageing and weathering, and for uniform changes such as colour changes, for example yellowing.

The pictorial standards for red rust have been selected from the “European rust scale” published by the European Confederation of Paint, Printing Ink and Artists' Colours Manufacturers' Associations (CEPE), Brussels. The correlation between the ISO scale and the “European rust scale” is given in [Table C.1](#).

The correlation between the ISO scale and the rating system of ASTM D610-08 is given in [Table C.2](#).

STANDARDSISO.COM : Click to view the full PDF of ISO 4628-3:2024

# Paints and varnishes — Evaluation of quantity and size of defects, and of intensity of uniform changes in appearance —

## Part 3: Assessment of degree of rusting

### 1 Scope

This document specifies methods for assessing the degree of rusting of surfaces coated with paints and varnishes (organic coatings), and metallic coating plus an organic coating (duplex system), by comparison with pictorial standards.

The pictorial standards provided in this document show surfaces which have deteriorated to different degrees by a combination of rust broken through the coating and visible under-rusting.

The assessment of the degree of rusting in this document is only an estimation of the affected area on specimen. Edges are not included.

### 2 Normative references

The following documents are referred to in the text in such a way that some or all of their content constitutes requirements of this document. For dated references, only the edition cited applies. For undated references, the latest edition of the referenced document (including any amendments) applies.

ISO 4618, *Paints and varnishes — Vocabulary*

ISO 13076, *Paints and varnishes — Lighting and procedure for visual assessments of coatings*

### 3 Terms and definitions

For the purposes of this document, the terms and definitions in ISO 4618 and the following apply.

ISO and IEC maintain terminology databases for use in standardization at the following addresses:

- ISO Online browsing platform: available at <https://www.iso.org/obp>
- IEC Electropedia: available at <https://www.electropedia.org/>

#### 3.1 red rust

corrosion products formed on ferrous substrates, such as iron or steel

Note 1 to entry: The red rust layer is generally porous, brittle and/or powdery.

#### 3.2 white rust

corrosion products formed on non-ferrous substrates, such as zinc or aluminium

Note 1 to entry: White rust results from the formation of metal hydroxides and oxides when exposed to moist or humid conditions.

Note 2 to entry: The white/grey products are generally porous, brittle and/or powdery.

### 3.3

#### rust traces

contamination due to bleeding of the corrosion products formed

## 4 Symbols and abbreviations

NSS	neutral salt spray
R	red rust
Ri	degree of red rust by comparison with pictorial standards
R%	degree of red rust by estimating the corroded area in per cent
WR	white rust
WRi	degree of white rust by comparison with pictorial standards
WR%	degree of white rust by estimating the corroded area in per cent

## 5 Assessment of red rust

### 5.1 Method 1: Assessment of the degree of red rust by comparison with pictorial standards (Ri)

Assess the degree of red rust by means of the pictorial standards (Ri) given in [Figures 1](#) to [5](#). The original pictures are only examples of organic coated steel surfaces after natural weathering and do not show the rust reactions of surfaces after short time corrosion tests. [Annex B](#) shows an example for a test panel after the NSS salt spray test specified in ISO 9227 with a degree of rusting Ri 4. Rust traces shall not be assessed.

NOTE 1 When viewed in A4 format, the photographs in this document are in the original size for comparison.



Figure 1 — Degree of rusting Ri 1



Figure 2 — Degree of rusting Ri 2

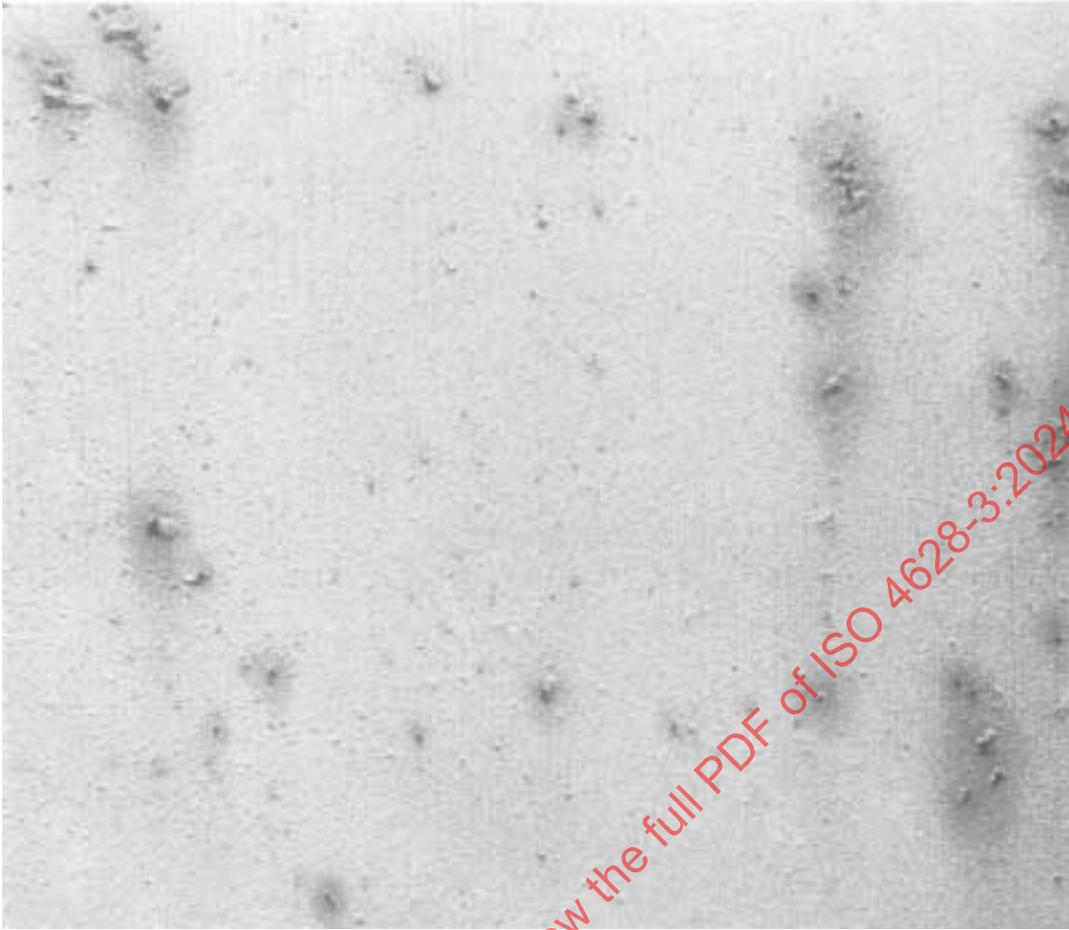


Figure 3 — Degree of rusting Ri 3

STANDARDSISO.COM : Click to view the full PDF of ISO 4628-3:2024

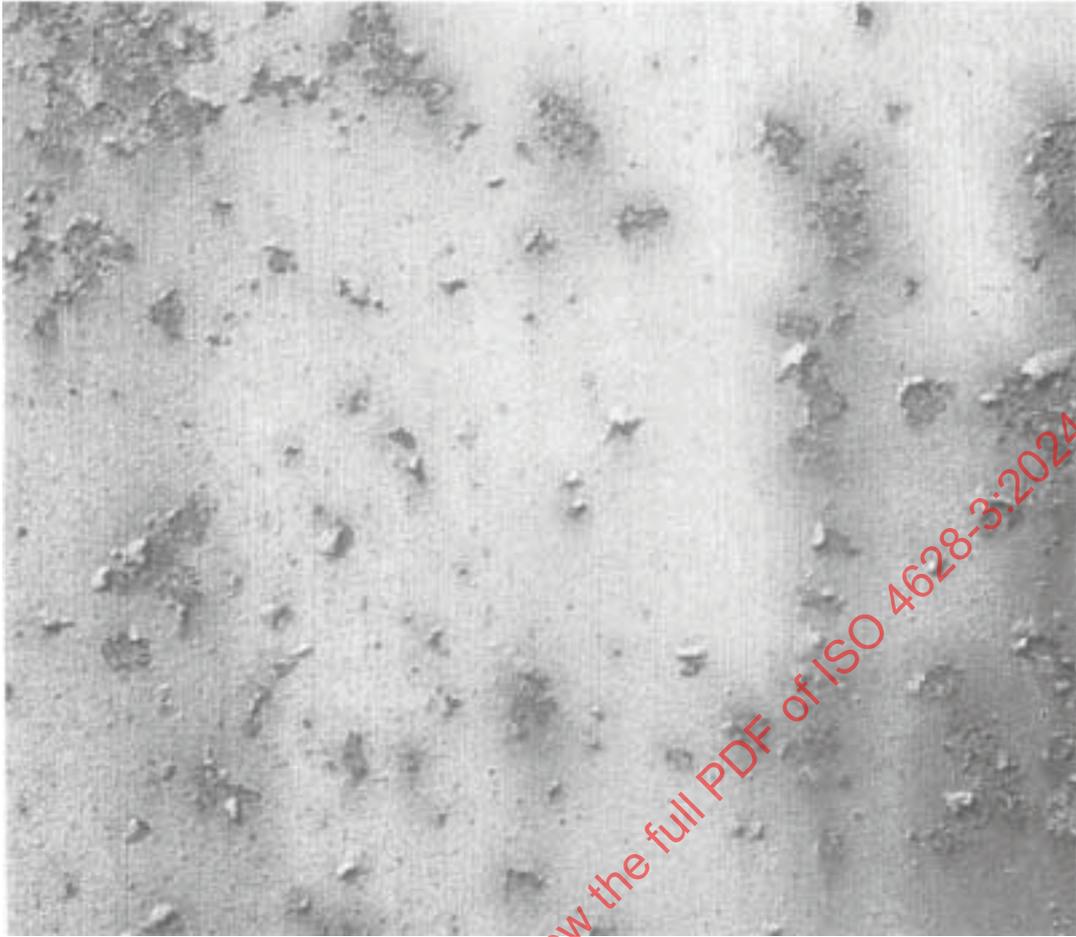
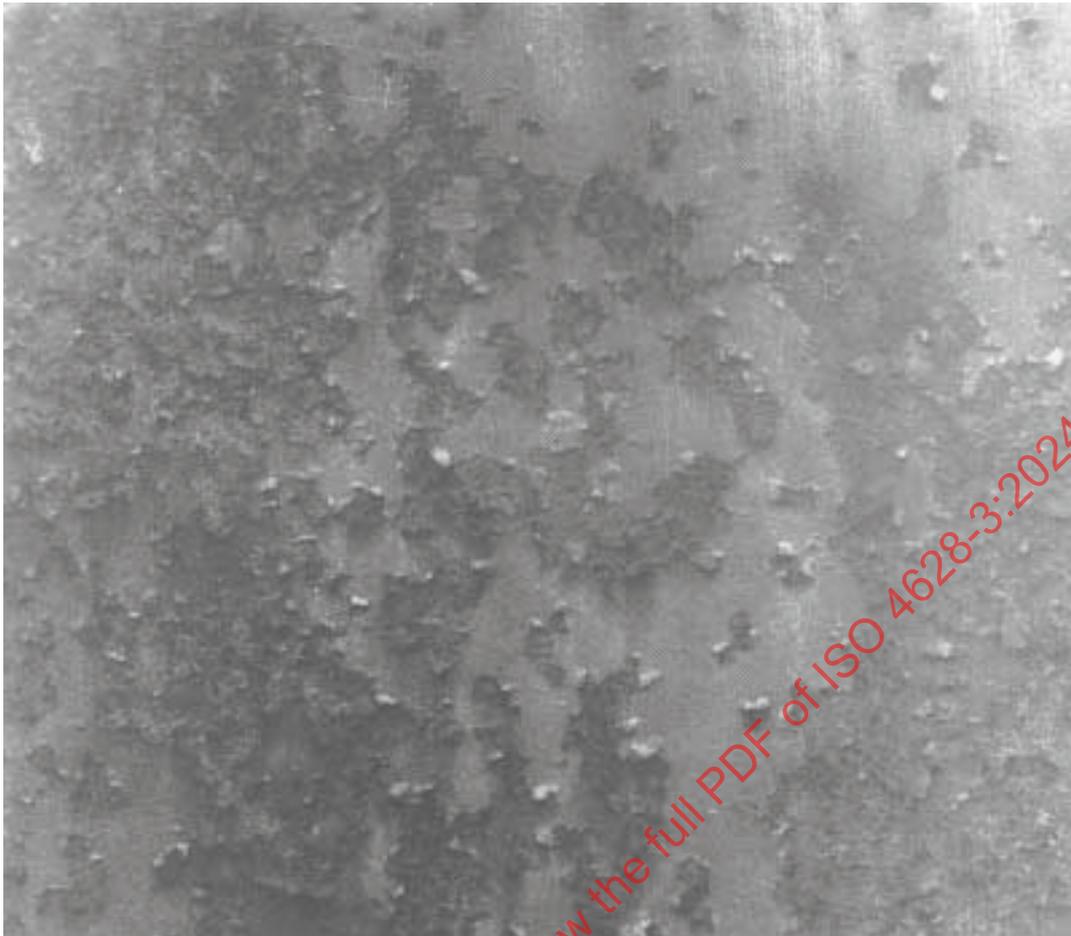


Figure 4 — Degree of rusting Ri 4



**Figure 5 — Degree of rusting Ri 5**

A better visibility is shown in the pictorial black-white calibration images in [Figures A.1 to A.5](#). These figures shall be used to calibrate optical imaging systems.

Removing procedures to make possible under-rusting visible for assessing, if required, shall be agreed between the interested parties.

Where different degrees of rusting occur in different parts of the area being assessed, indicate these degrees of rusting together with the approximate dimensions of the area concerned, or its portion of the total area, expressed in per cent.

Carry out the assessment under good illumination, as specified in ISO 13076.

If the average size of the rust spots on the test area differs considerably from those shown in the pictorial standards, an indication of their size may be given as indicated in [Table 1](#).

NOTE 2 The pictorial standards are intended for assessing the degree of rusting of organic coated iron/steel substrates. They can be used for designating the degree of corrosion of coated non-ferrous metals if the form of breakdown is comparable with that shown in the standards. In most cases, non-ferrous metals or zinc coated steel substrates show different reactions.

**Table 1 — Size of rusting and corroded area for red rust**

Rating	Size of rusting
S 0	not visible under ×10 magnification
S 1	only visible under magnification up to ×10
S 2	just visible with normal corrected vision (up to 0,2 mm) <sup>a</sup>
S 3	clearly visible with normal corrected vision (larger than 0,2 mm up to 0,5 mm)
S 4	larger than 0,5 mm up to 5 mm
S 5	larger than 5 mm

NOTE Reproduced from ISO 4628-1:2016, Table 2.

<sup>a</sup> Typically, defects larger than 0,2 mm are visible with normal corrected vision.

**5.2 Method 2: Assessment of the degree of red rust by estimating the corroded area in per cent (R%)**

If method 1 is not applicable, use method 2. [Table 2](#) shows an alternative ranking of the rust grade as percentage estimation (R%) with broader percentage ranges for uncoated and coated substrates.

**Table 2 — Degree of rusting and corroded area for red rust**

Degree of rusting in per cent	Corroded area <sup>a</sup> %
R% 0	0
R% 1	up to 5 %
R% 2	more than 5 % up to 10 %
R% 3	more than 10 % up to 25 %
R% 4	more than 25 % up to 50 %
R% 5	more than 50 %

<sup>a</sup> This is a real estimation of the affected area in per cent.

**6 Assessment of white rust**

**6.1 Method 1: Assessment of the degree of white rust by comparison with pictorial standards (WRi)**

Assess the degree of white rust by means of the pictorial standards (WRi) based on NSS testing given in [Figures 6](#) to [10](#).

The pictorial standards in [Figures 6](#) to [10](#) show examples of a hot-dip galvanized coating plus an organic coating (duplex system) after a neutral salt spray test.



NOTE The original panel size is 150 mm × 100 mm. When viewed in A4 format, the photographs in this document are in the original size for comparison.

**Figure 6 — Degree of rusting WRI 1**



Figure 7 — Degree of rusting WRi 2

STANDARDSISO.COM : Click to view the full PDF of ISO 4628-3:2024



Figure 8 — Degree of rusting WRi 3

STANDARDSISO.COM : Click to view the full PDF of ISO 4628-3:2024



Figure 9 — Degree of rusting WRi 4

STANDARDSISO.COM : Click to view the full PDF of ISO 4628-3:2024



**Figure 10 — Degree of rusting WRi 5**

Rinse the test panel with fresh tap water immediately after exposure, i.e. before the surface dries out. Blow off residues of water from the surface using compressed air if necessary, and inspect for visible changes.

Carry out the assessment under good illumination, as specified in ISO 13076.

If the average size of the area of white rust on the test area differs considerably from those shown in the pictorial standards, an indication of their size may be given as indicated in [Table 1](#).

## **6.2 Method 2: Assessment of the degree of white rust by estimating the corroded area in per cent (WR%)**

If method 1 is not applicable, use method 2. [Table 3](#) shows an alternative ranking of the rust grade as percentage estimation (WR%) with broader percentage ranges.

Table 3 — Degree of rusting and corroded area for white rust

Degree of rusting in per cent	Corroded area <sup>a</sup> %
WR% 0	0
WR% 1	up to 5 %
WR% 2	more than 5 % up to 10 %
WR% 3	more than 10 % up to 25 %
WR% 4	more than 25 % up to 50 %
WR% 5	more than 50 %

<sup>a</sup> This is a real estimation of the affected area in per cent.

## 7 Expression of results

Express the degree of rusting as Ri class or WRi class (method 1) or R% class or WR% class (method 2).

If applicable, indicate the different degrees of rusting obtained, together with the parts of the test area concerned.

If applicable, indicate the degree of rusting Ri or WRi, together with the numerical rating of the size of the rust spots (see [Table 1](#)).

EXAMPLE 1 Method 1, if the corroded area corresponds to [Figure 3](#), Ri 3, and the sizes of the individual rust spots are between 0,5 mm and 5 mm (size 4), report the result as:

— rusting; degree of rusting Ri 3 (S 4).

EXAMPLE 2 Method 2, if the corroded area is about 20 %, R% 3 report the result as:

— rusting; degree of rusting R% 3.

## 8 Test report

The test report shall contain at least the following information:

- all details necessary to identify the coating examined;
- a reference to this document, i.e. ISO 4628-3:2024;
- the type of surface examined, its size and, if appropriate, its location;
- the method of assessment (method 1 or method 2) which was used;
- results of the assessment in accordance with [Clause 7](#);
- an indication of the illumination under which the assessment was carried out;
- any deviations from the procedure;
- any unusual features (anomalies) observed during the assessment;
- the date of the examination.

**Annex A**  
(normative)

**Calibration images**

If the assessment is done using an optical imaging system, use the images given in [Figure A.1](#) to [Figure A.5](#) to calibrate the imaging system.

NOTE If viewed in A4 format, the photographs in this document are in the original size for comparison.




NOTE Corroded area, detected by optical imaging: 0,05 %.

**Figure A.1 — Degree of rusting Ri 1**




NOTE Corroded area, detected by optical imaging: 0,5 %.

Figure A.2 — Degree of rusting Ri 2

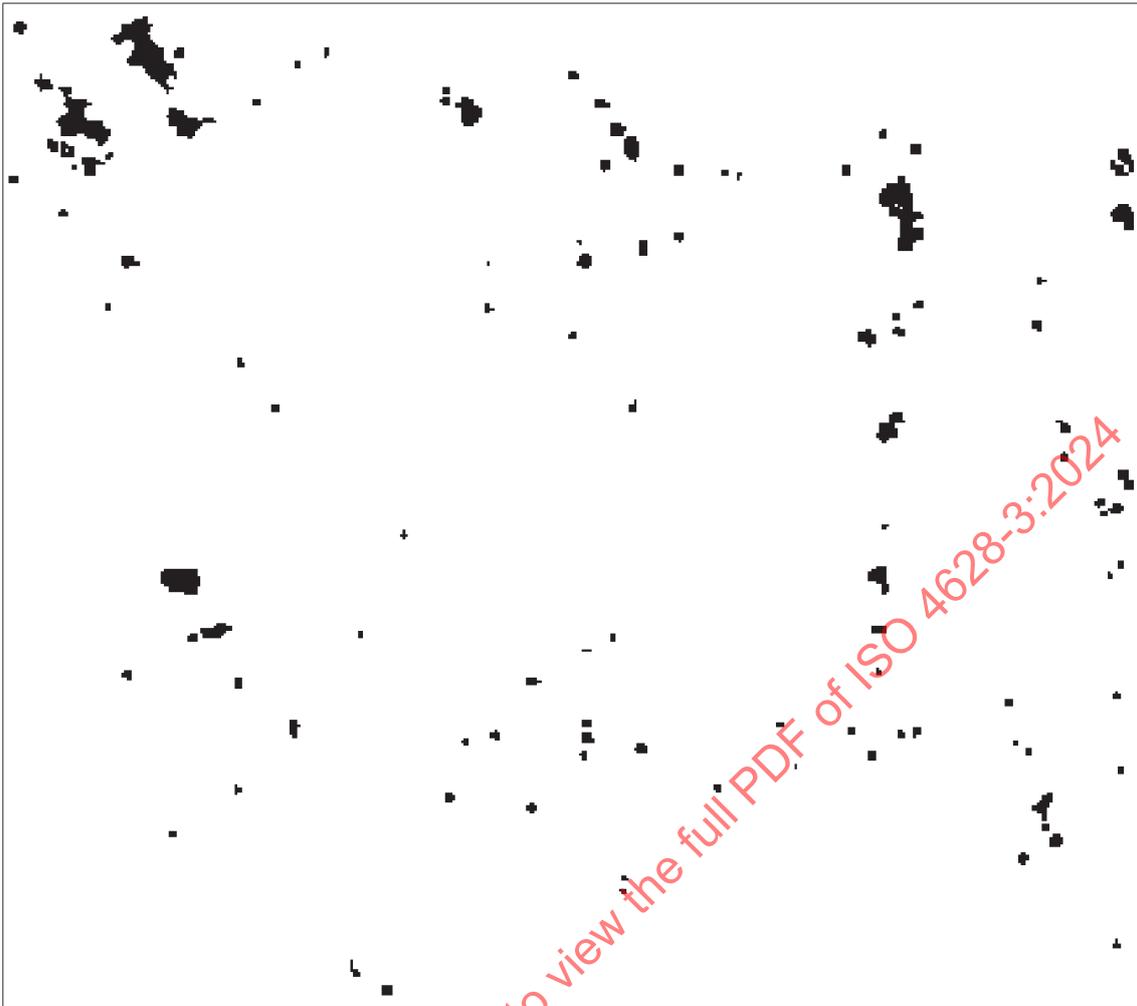

NOTE Corroded area, detected by optical imaging: 1 %.

Figure A.3 — Degree of rusting Ri 3

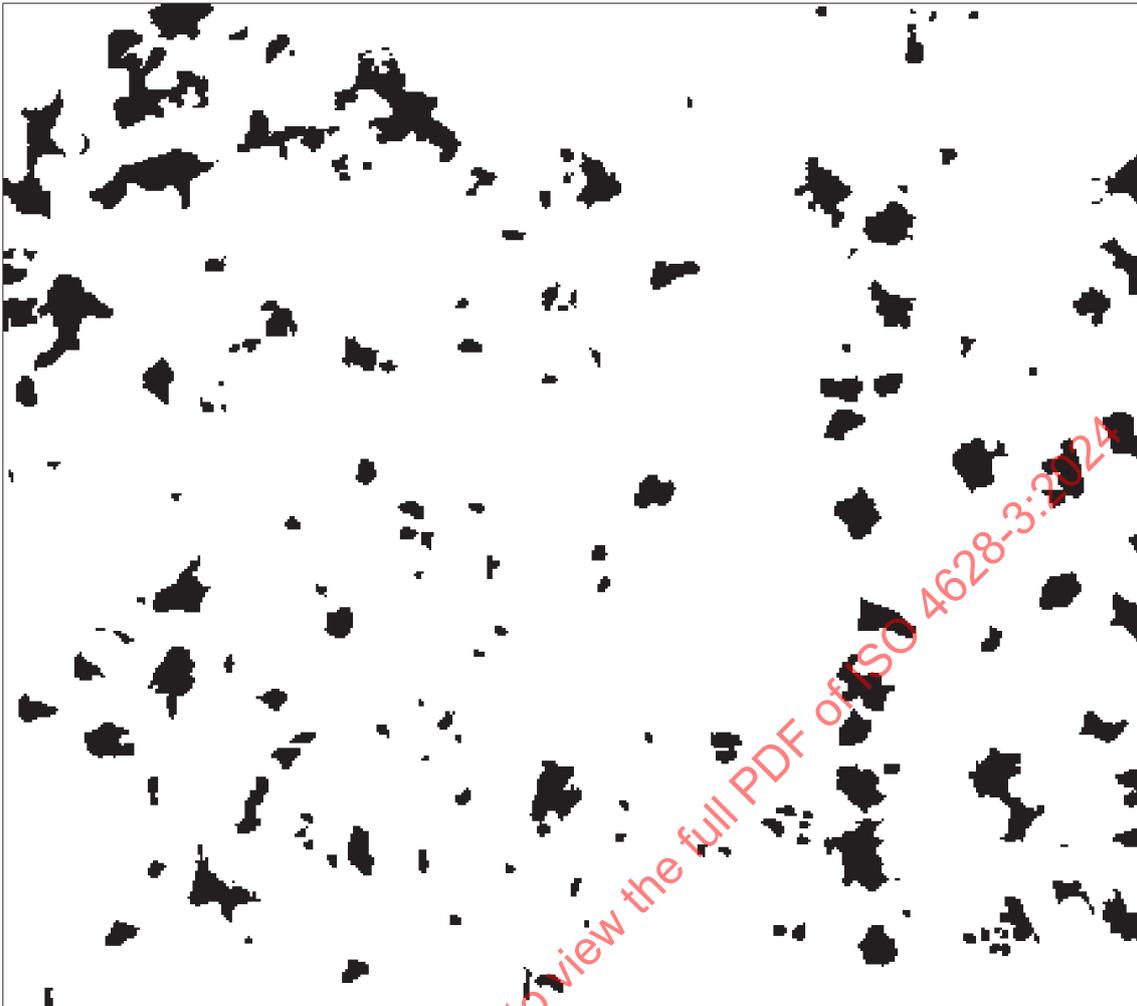

NOTE Corroded area, detected by optical imaging: 8 %.

Figure A.4 — Degree of rusting Ri 4