

INTERNATIONAL STANDARD

ISO 4957

Second edition
1999-12-15

Tool steels

Aciers à outils

STANDARDSISO.COM : Click to view the full PDF of ISO 4957:1999



Reference number
ISO 4957:1999(E)

© ISO 1999

PDF disclaimer

This PDF file may contain embedded typefaces. In accordance with Adobe's licensing policy, this file may be printed or viewed but shall not be edited unless the typefaces which are embedded are licensed to and installed on the computer performing the editing. In downloading this file, parties accept therein the responsibility of not infringing Adobe's licensing policy. The ISO Central Secretariat accepts no liability in this area.

Adobe is a trademark of Adobe Systems Incorporated.

Details of the software products used to create this PDF file can be found in the General Info relative to the file; the PDF-creation parameters were optimized for printing. Every care has been taken to ensure that the file is suitable for use by ISO member bodies. In the unlikely event that a problem relating to it is found, please inform the Central Secretariat at the address given below.

STANDARDSISO.COM : Click to view the full PDF of ISO 4957:1999

© ISO 1999

All rights reserved. Unless otherwise specified, no part of this publication may be reproduced or utilized in any form or by any means, electronic or mechanical, including photocopying and microfilm, without permission in writing from either ISO at the address below or ISO's member body in the country of the requester.

ISO copyright office
Case postale 56 • CH-1211 Geneva 20
Tel. + 41 22 749 01 11
Fax + 41 22 734 10 79
E-mail copyright@iso.ch
Web www.iso.ch

Printed in Switzerland

Contents

1	Scope	1
2	Normative references	1
3	Terms and definitions	2
4	Requirements	3
5	Inspection, testing and conformance of products	4
6	Marking	5
7	Ordering and designation	5
	Annex A (informative) Hardness-tempering temperature-curves	18
	Annex B (normative) Supplementary or special requirements	28
	Annex C (informative) Designations of comparable steels.....	30
	Bibliography	32

STANDARDSISO.COM : Click to view the full PDF of ISO 4957:1999

Foreword

ISO (the International Organization for Standardization) is a worldwide federation of national standards bodies (ISO member bodies). The work of preparing International Standards is normally carried out through ISO technical committees. Each member body interested in a subject for which a technical committee has been established has the right to be represented on that committee. International organizations, governmental and non-governmental, in liaison with ISO, also take part in the work. ISO collaborates closely with the International Electrotechnical Commission (IEC) on all matters of electrotechnical standardization.

International Standards are drafted in accordance with the rules given in the ISO/IEC Directives, Part 3.

Draft International Standards adopted by the technical committees are circulated to the member bodies for voting. Publication as an International Standard requires approval by at least 75 % of the member bodies casting a vote.

Attention is drawn to the possibility that some of the elements of this International Standard may be the subject of patent rights. ISO shall not be held responsible for identifying any or all such patent rights.

International Standard ISO 4957 was prepared by Technical Committee ISO/TC 17, *Steel*, Subcommittee SC 4, *Heat treatable and alloy steels*.

This second edition cancels and replaces the first edition (ISO 4957:1980) which has been technically revised.

Annex B forms a normative part of this International Standard, annexes A and C are for information only.

STANDARDSISO.COM : Click to view the full PDF of ISO 4957:1999

Tool steels

1 Scope

1.1 This International Standard covers the following grades of wrought tool steels:

- a) non-alloy cold-work tool steels;
- b) alloy cold-work tool steels;
- c) alloy hot-work tool steels;
- d) high-speed tool steels.

If not stated otherwise, this International Standard applies to all types of hot-rolled, forged, cold-drawn or cold-rolled products which are supplied in one of the surface and heat-treatment conditions given in 4.1.2 and Table 1.

Products according to this International Standard may be produced by powder metallurgy.

NOTE 1 The Tables 2, 4, 6 and 8 cover only those steels which have gained certain international importance, which does not mean however, that they are available in all industrial countries. In addition, a number of other steels for tools are specified in regional, national or company standards.

NOTE 2 Where the heat resistance of the tools is of particular importance, as for example in the case of tools for hot forming glass, the material selection should be based on ISO 4955 or ISO 9722.

1.2 In addition to this International Standard, the general technical delivery requirements of ISO 404 are applicable.

2 Normative references

The following normative documents contain provisions which, through reference in this text, constitute provisions of this International Standard. For dated references, subsequent amendments to, or revisions of, any of these publications do not apply. However, parties to agreements based on this International Standard are encouraged to investigate the possibility of applying the most recent editions of the normative documents indicated below. For undated references, the latest edition of the normative document referred to applies. Members of ISO and IEC maintain registers of currently valid International Standards.

ISO 377:1997, *Steel and steel products — Location and preparation of samples and test pieces for mechanical testing*.

ISO 404:1992, *Steel and steel products — General technical delivery requirements*.

ISO 1035-1:1980, *Hot-rolled steel bars — Part 1: Dimensions of round bars*.

ISO 1035-3:1980, *Hot-rolled steel bars — Part 3: Dimensions of flat bars*.

ISO 1035-4:1982, *Hot-rolled steel bars — Part 4: Tolerances*.

ISO 4957:1999(E)

ISO 4948-1:1982, *Steels — Classification — Part 1: Classification of steels into unalloyed and alloy steels based on chemical composition.*

ISO 6506:1981¹⁾, *Metallic materials — Hardness test — Brinell test.*

ISO 6508:1986²⁾, *Metallic materials — Hardness test — Rockwell test (scales A - B - C - D - E - F - G - H - K).*

ISO 6929:1987, *Steel products — Definitions and classification.*

ISO/TR 9769:1991, *Steel and iron — Review of available methods of analysis.*

ISO 10474:1991, *Steel and steel products — Inspection documents.*

ISO 14284:1996, *Steel and iron — Sampling and preparation of samples for the determination of chemical composition.*

3 Terms and definitions

For the purposes of this International Standard, the terms and definitions given in ISO 4948-1 and ISO 6829 as well as the following apply.

**3.1
product forms**
[ISO 6929]

**3.2
unalloyed and alloyed steel**
[ISO 4948-1]

**3.3
tool steels**

special steels suitable for working or processing of materials, for handling and measuring workpieces and, for this purpose, exhibiting high hardness and wear resistance and/or toughness

**3.3.1
cold-work tool steels**

non-alloy or alloy tool steels for applications in which the surface temperature is generally below 200 °C

**3.3.2
hot-work tool steels**

alloy tool steels for applications in which the surface temperature is generally over 200 °C

**3.3.3
high-speed tool steels**

steels used mainly for machining and for forming processes and which, because of their chemical composition, have the highest high-temperature hardness and temper resistance up to about 600 °C

1) To be replaced by ISO 6506-1, ISO 6506-2 and ISO 6506-3.

2) To be replaced by ISO 6508-1, ISO 6508-2 and ISO 6508-3.

4 Requirements

4.1 Manufacturing process

4.1.1 General

The manufacturing process of the steel and the products is left to the discretion of the manufacturer, with the restrictions given in 4.1.2.

When he so requests, the purchaser shall be informed what steel making process is being used.

4.1.2 Heat-treatment condition and surface condition on delivery

The heat-treatment and surface conditions of the products shall comply with the agreements when ordering.

4.1.2.1 Heat-treatment condition

The heat-treatment conditions are given in Table 1.

Unless otherwise specified in the order, the tool steels (except C45U, Table 2, 35CrMo7, X38CrMo16 and 40CrMnNiMo8-6-4, Table 4, 55NiCrMoV7, Table 6) are delivered in the annealed condition.

4.1.2.2 Surface condition

Usual surface conditions are:

- a) the hot-rolled or forged condition (= as hot worked);
- b) the machined (ground, polished, turned, peeled or milled) condition;
- c) the cold-reduced condition.

4.2 Chemical composition and mechanical properties

4.2.1 Table 1 gives a survey of combinations of usual heat-treatment conditions at delivery and requirements according to Tables 2 to 9 (chemical composition, hardness).

4.2.2 For hardness-tempering temperature-curves of the steels see annex A.

4.2.3 For hardness penetration depth of non-alloy cold-work tool steels, see Table 2, footnote d.

4.3 Surface quality

4.3.1 All products shall have a workmanlike finish and shall be clean and free from surface imperfections likely to have an adverse effect on their processing or designated application.

4.3.2 Ground, polished or finished-machined products shall be free from surface imperfections and surface decarburization.

4.3.3 Hot-rolled, forged, cold-drawn or rough-machined products shall be ordered with sufficient material to be removed from all surfaces by machining or grinding to allow for

- a) surface decarburization and
- b) surface imperfections.

As long as no International Standard for the machining allowances of tool steels is available, the allowances shall be agreed at the time of enquiry and order.

4.4 Shape, dimensions and tolerances

The shape, dimensions and tolerances of the products shall comply with the requirements agreed upon at the time of enquiry and order. The agreements shall, as far as possible, be based on corresponding International Standards or otherwise, on suitable national standards.

For rolled flat and round bars, the following International Standards cover dimensions and/or tolerances for products included in this International Standard: ISO 1035-1, ISO 1035-3 and ISO 1035-4.

NOTE By agreement, the tolerances can be all plus or other disposition than equal plus/minus.

5 Inspection, testing and conformance of products

5.1 Inspection and testing procedures and types of inspection documents

5.1.1 For each delivery, the issue of any inspection document in accordance with ISO 10474 may be agreed upon at the time of enquiry and order.

5.1.2 If, in accordance with the agreements made at the time of enquiry and order, a test report is to be provided, this shall cover:

- a) the statement that the material complies with the requirements of the order;
- b) the results of the cast analysis for all elements specified for the type of steel supplied.

5.1.3 If, in accordance with the agreements in the order, an inspection certificate 3.1.A, 3.1.B or 3.1.C or an inspection report 3.2 (see ISO 10474) is to be provided, the specific inspections and tests described in 5.2 shall be carried out and their results shall be certified in the document.

In addition the document shall cover

- a) the results of the cast analysis provided by the manufacturer for all elements specified for the steel type concerned;
- b) the results of all inspections and tests ordered by supplementary requirements (see annex B);
- c) the symbol letters or numbers connecting the inspection documents, the test pieces and products to each other.

5.2 Specific inspection and testing

5.2.1 Number of sample products

5.2.1.1 Chemical composition

The cast analysis is given by the manufacturer. For product analysis see B.2 in annex B.

5.2.1.2 Mechanical properties

One sample product per test unit shall be tested.

5.2.1.2.1 For material delivered in the annealed or annealed and cold rolled or annealed and cold drawn condition, the test unit shall consist of products from the same cast and the same heat-treatment batch.

In the case of material heat treated in a continuous furnace, a heat-treatment batch is regarded as that quantity of products (of the same cast and dimensions) which without any interruptions, was under constant treatment conditions (same furnace temperature, atmosphere and transportation speed) through the furnace.

5.2.1.2.2 For material delivered in the quenched and tempered condition, the test unit shall consist of products from the same cast, heat-treatment and thickness.

However, if the manufacturer verifies that the thickness has no significant effect on the hardness in the quenched and tempered condition, then different thicknesses may be covered in a test unit.

5.2.1.3 Inspection of the surface quality

Unless otherwise agreed when ordering (see B.5), the number of products to be inspected for surface quality is left to the discretion of the inspector.

5.2.1.4 Dimensional inspection

Unless otherwise agreed when ordering (see B.6) the number of products to be inspected for their shape and dimensions is left to the discretion of the inspector.

5.2.2 Sampling

5.2.2.1 The general conditions for selection and preparation of samples and test pieces shall be in accordance with ISO 377 and ISO 14284.

5.2.2.2 For the Brinell hardness test the surface of the sample product or of a test piece taken from the sample product in the delivery condition shall be prepared in accordance with the requirements of ISO 6506.

5.2.3 Test methods

5.2.3.1 The Brinell hardness test shall be made in accordance with ISO 6506.

5.2.3.2 Unless otherwise agreed (see B.5), the surface quality shall be inspected visually.

5.2.4 Retests

For retests, ISO 404 shall apply.

6 Marking

The manufacturer shall mark the products or the bundles or boxes containing the products in a suitable way, so that the identification of the cast, the steel type and the origin of the delivery is possible (see B.8).

7 Ordering and designation

The designation of the product in an order shall cover the following:

- a) The quantity to be delivered.
- b) The designation of the product form (e.g. bar) followed by
 - 1) either the designation of the dimensional standard and the dimensions and tolerances selected from it (see 4.4) or
 - 2) the designation of any other document covering the dimensions and tolerances required for the product.

ISO 4957:1999(E)

- c) If a surface condition other than "hot worked" or a special surface quality is required
- 1) the surface condition (see 4.1.2.2);
 - 2) the surface quality (see 4.3).
- d) A description of the steel comprising
- 1) the reference to this International Standard;
 - 2) the designation of the steel type (see Tables 2, 4, 6 and 8);
 - 3) the symbol for the heat-treatment condition on delivery (see Table 1) and, if the products are to be delivered in the quenched and tempered condition, the hardness values required;
 - 4) the standard designation for the required type of inspection document (see ISO 10474);
 - 5) the symbol and, where necessary, the details of this supplementary requirement (see annex B), if any supplementary requirement shall be complied with.

EXAMPLE

The following are to be ordered.

- a) 2 t Hot-rolled round bars
- 1) in accordance with ISO 1035-1;
 - 2) with a nominal diameter of 30,0 mm;
 - 3) with a nominal length of 4 000 mm;
 - 4) with a tolerance on diameter of $\pm 0,30$ mm (class S of ISO 1035-4:1982);
 - 5) with a tolerance on length of $^{+100}_0$ mm (class L2 of ISO 1035-4:1982);
 - 6) all other tolerances as given in ISO 1035-4, for normal cases.
- b) Surface
- 1) as hot worked.
- c) Steel
- 1) in accordance with this International Standard, type X153CrMoV12 (see Table 4);
 - 2) heat-treatment condition: annealed (soft annealed) (symbol +A, see Table 1);
 - 3) with an inspection certificate 3.1.B (see ISO 10474).

- d) Designation

2 t rounds ISO 1035-1-30,0 S x 4 000 L2

Steel ISO 4957-X153CrMoV12+A-3.1.B

Table 1 — Combinations of heat-treatment conditions at delivery and requirements in accordance with Tables 2 to 9

		4																
		Applicable requirements for																
1	2	3	4.1 non-alloy cold-work tool steels				4.2 alloy cold-work tool steels				4.3 hot-work tool steels				4.4 high-speed tool steels			
	Heat-treatment condition at delivery	Symbol ^a	Chemical composition acc. to Tables 2 and 3		Hardness acc. to Table 2		Chemical composition acc. to Tables 4 and 5		Hardness acc. to Table 4		Chemical composition acc. to Tables 6 and 7		Hardness acc. to Table 6		Chemical composition acc. to Tables 8 and 9		Hardness acc. to Table 8	
2	Untreated	+U	— ^c	+A ^c	— ^c	+A ^c	— ^c	+A ^c	— ^c	+A ^c	— ^c	+A ^c	— ^c	+A ^c	— ^c	+A ^c	— ^c	+A ^c
3	Annealed (soft annealed) ^b	+A ^b	+A and footnote b to Table 2 ^c															
4	Annealed and cold drawn	+A+C																
	Annealed and cold-rolled ^d	+A+CR ^d																+A and footnote d to Table 8 ^c
5	Quenched and tempered ^e	+QT ^e	—															—

^a In cases where no heat-treatment condition is specified at the time of ordering, the product will be delivered in the usual heat-treatment condition given in 4.1.2.1.

^b Most common heat-treatment condition at delivery.

^c In addition, the requirements for minimum hardness in the hardening test apply. For verification see B.3.

^d Only for steels of Table 8.

^e Mainly for individually manufactured blocks for moulds and dies.

^f The hardness requirements are to be agreed at the time of enquiry and order.

Table 2 — Chemical composition (cast analysis), annealed hardness, temperature for hardening and hardness in the hardened and tempered condition for non-alloy cold-work tool steels

Steel name	Chemical composition, (% m/m) ^a						Hardness (annealed) ^b +A HB max.	Hardening test			
	C	Si	Mn	P max.	S max.	Hardening temperature °C (± 10 °C)		Quenching medium	Tempering temperature °C (± 10 °C)	Hardness HRC min.	
C45U	0,42 to 0,50	0,15 to 0,40	0,60 to 0,80	0,030	0,030	0,030	207 ^c	W	810	180	54
C70U ^d	0,65 to 0,75	0,10 to 0,30	0,10 to 0,40	0,030	0,030	0,030	183	W	800	180	57
C80U ^d	0,75 to 0,85	0,10 to 0,30	0,10 to 0,40	0,030	0,030	0,030	192	W	790	180	58
C90U ^d	0,85 to 0,95	0,10 to 0,30	0,10 to 0,40	0,030	0,030	0,030	207	W	780	180	60
C105U ^d	1,00 to 1,10	0,10 to 0,30	0,10 to 0,40	0,030	0,030	0,030	212	W	780	180	61
C120U ^d	1,15 to 1,25	0,10 to 0,30	0,10 to 0,40	0,030	0,030	0,030	217	W	770	180	62

^a Elements not quoted in this table shall not be intentionally added to the steel without the agreement of the purchaser, other than for the purpose of finishing the heat. All reasonable precautions shall be taken to prevent the addition from scrap or other materials used in manufacture, of such elements which affect the hardenability, mechanical properties and applicability.

^b Hardness in the cold drawn condition (+A+C) may be 20 HB higher than in the annealed (+A) condition.

^c This grade is used in the non-heat treated condition.

^d Steel grades C70U to C120U are due to their chemical composition shallow hardening steels. For diameters of 30 mm, the hardness penetration depth will be approximately 3 mm. Through-hardening may only be achieved in diameters up to 10 mm.

Table 3 — Permissible deviations between specified analysis and product analysis for non-alloy cold-work tool steels (see Table 2)

Permissible deviations, (% <i>m/m</i>)				
C	Si	Mn	P	S
± 0,03	± 0,03	± 0,04	+ 0,005	+ 0,005
<p>NOTE The deviations, other than when maxima only are specified, apply either above or below the specified limits of the range but not both above and below for the same element from different sample products from the same cast. When maxima only are specified, the deviations are positive only. The values are valid only if the samples are selected in accordance with ISO 14284, so that they represent the average composition of the cross-section of the product.</p>				

STANDARDSISO.COM : Click to view the full PDF of ISO 4957:1999

Table 4 —Chemical composition (cast analysis), annealed hardness, temperature for hardening and hardness in the hardened and tempered condition for alloy cold-work tool steels

Steel name	Chemical composition ^{a, b} (% m/m)										Hardness (annealed) ^c			Hardening test			Hardness HRC min.
	C	Si	Mn	Cr	Mo	Ni	V	W	+A HB max.	Hardening temperature °C (± 10°C)	Quenching medium ^d	Tempering temperature °C (± 10°C)					
105V	1,00 to 1,10	0,10 to 0,30	0,10 to 0,40	-	-	-	0,10 to 0,20	-	212	790	W	180	61				
50WCrV8	0,45 to 0,55	0,70 to 1,00	0,15 to 0,45	0,90 to 1,20	-	-	0,10 to 0,20	1,70 to 2,20	229	920	O	180	56				
60WCrV8	0,55 to 0,65	0,70 to 1,00	0,15 to 0,45	0,90 to 1,20	-	-	0,10 to 0,20	1,70 to 2,20	229	910	O	180	58				
102Cr6	0,95 to 1,10	0,15 to 0,35	0,25 to 0,45	1,35 to 1,65	-	-	-	-	223	840	O	180	60				
21MnCr5	0,18 to 0,24	0,15 to 0,35	1,10 to 1,40	1,00 to 1,30	-	-	-	-	217	e	e	e	e				
70MnMoCr8	0,65 to 0,75	0,10 to 0,50	1,80 to 2,50	0,90 to 1,20	0,90 to 1,40	-	-	-	248	835	A	180	58				
90MnCrV8	0,85 to 0,95	0,10 to 0,40	1,80 to 2,20	0,20 to 0,50	-	-	0,05 to 0,20	-	229	790	O	180	60				
95MnWCr5	0,90 to 1,00	0,10 to 0,40	1,05 to 1,35	0,40 to 0,65	-	-	0,05 to 0,20	0,40 to 0,70	229	800	O	180	60				
X100CrMoV5	0,95 to 1,05	0,10 to 0,40	0,40 to 0,80	4,80 to 5,50	0,90 to 1,20	-	0,15 to 0,35	-	241	970	A	180	60				
X153CrMoV12	1,45 to 1,60	0,10 to 0,60	0,20 to 0,60	11,00 to 13,00	0,70 to 1,00	-	0,70 to 1,00	-	255	1020	A	180	61				
X210Cr12	1,90 to 2,20	0,10 to 0,60	0,20 to 0,60	11,00 to 13,00	-	-	-	-	248	970	O	180	62				
X210CrW12	2,00 to 2,30	0,10 to 0,40	0,30 to 0,60	11,00 to 13,00	-	-	-	0,60 to 0,80	255	970	O	180	62				
35CrMo7	0,30 to 0,40	0,30 to 0,70	0,60 to 1,00	1,50 to 2,00	0,35 to 0,55	-	-	-	f	-	-	-	f				
40CrMnNiMo8-6-49	0,35 to 0,45	0,20 to 0,40	1,30 to 1,60	1,80 to 2,10	0,15 to 0,25	0,90 to 1,209	-	-	f	-	-	-	f				
45NiCrMo16	0,40 to 0,50	0,10 to 0,40	0,20 to 0,50	1,20 to 1,50	0,15 to 0,35	3,80 to 4,30	-	-	285	850	O	180	52				
X40Cr14 ^h	0,36 to 0,42	≤ 1,00	≤ 1,00	12,50 to 14,50	-	-	-	-	241	1010	O	180	52				
X38CrMo16 ⁹	0,33 to 0,45	≤ 1,00	≤ 1,50	15,50 to 17,50	0,80 to 1,30	≤ 1,00	-	-	f	-	-	-	f				

a Elements not quoted in this table shall not be intentionally added to the steel without the agreement of the purchaser, other than for the purpose of finishing the heat. All reasonable precautions shall be taken to prevent the addition from scrap or other materials used in manufacture, of such elements which affect the hardenability, mechanical properties and applicability.

b For all steels: phosphorus ≤ 0,030 % and sulfur ≤ 0,030 % (see, however, footnote g).

c Hardness in the cold drawn condition (+A +C) may be 20 HB higher than in the annealed condition (+A).

d Quenching medium: A = Air, O = Oil, W = Water.

e This material when carburized, quenched and tempered should achieve a surface hardness of 60 HRC.

f This steel is normally supplied in the quenched and tempered condition with a hardness of approximately 300 HB.

g By agreement, sulfur may be increased to between 0,050 % and 0,100 % and Ni may be omitted.

h This steel may also be supplied in the pre-heated condition with a hardness of approximately 300 HB.

Table 5 — Permissible deviations between specified analysis and product analysis for alloy cold-work tool steels (see Table 4)

Steel name	Permissible deviations ^a , (% m/m)										
	C	Si	Mn	P	S	Cr	Mo	Ni	V	W	
105V	± 0,03	± 0,03	± 0,04	+ 0,005	+ 0,005	—	—	—	± 0,02	—	—
50WCrV8	± 0,03	± 0,05	± 0,04	+ 0,005	+ 0,005	± 0,05	—	—	± 0,02	± 0,07	—
60WCrV8	± 0,03	± 0,05	± 0,04	+ 0,005	+ 0,005	± 0,05	—	—	± 0,02	± 0,07	—
102Cr6	± 0,03	± 0,03	± 0,04	+ 0,005	+ 0,005	± 0,07	—	—	—	—	—
21MnCr5	± 0,03	± 0,03	± 0,08	+ 0,005	+ 0,005	± 0,05	—	—	—	—	—
70MnMoCr8	± 0,03	± 0,03	± 0,08	+ 0,005	+ 0,005	± 0,05	± 0,05	—	—	—	—
90MnCrV8	± 0,03	± 0,03	± 0,08	+ 0,005	+ 0,005	± 0,05	—	—	± 0,02	—	—
95MnCrW5	± 0,03	± 0,03	± 0,06	+ 0,005	+ 0,005	± 0,05	—	—	± 0,02	± 0,04	—
X100CrMoV5	± 0,03	± 0,03	± 0,04	+ 0,005	+ 0,005	± 0,10	± 0,05	—	± 0,03	—	—
X153CrMoV12	± 0,04	± 0,03	± 0,04	+ 0,005	+ 0,005	± 0,15	± 0,05	—	± 0,04	—	—
X210Cr12	± 0,05	± 0,03	± 0,04	+ 0,005	+ 0,005	± 0,15	—	—	—	—	—
X210CrW12	± 0,05	± 0,03	± 0,04	+ 0,005	+ 0,005	± 0,15	—	—	—	± 0,04	—
35CrMo7	± 0,03	± 0,03	± 0,04	+ 0,005	+ 0,005	± 0,07	± 0,05	—	—	—	—
40CrMnNiMo8-6-4 ^b	± 0,03	± 0,03	± 0,08	+ 0,005	+ 0,005	± 0,07	± 0,03	± 0,07	—	—	—
45NiCrMo16	± 0,03	± 0,03	± 0,04	+ 0,005	+ 0,005	± 0,07	± 0,03	± 0,07	—	—	—
X40Cr14	± 0,03	+ 0,05	± 0,04	+ 0,005	+ 0,005	± 0,15	—	—	—	—	—
X38CrMo16	± 0,03	+ 0,05	± 0,04	+ 0,005	+ 0,005	± 0,15	± 0,05	+ 0,07	—	—	—

^a The deviations, other than maxima only are specified, apply either above or below the specified limits of the range but not both above and below for the same element from different sample products from the same cast. When maxima only are specified the deviations are positive only. The values are valid only if the samples are selected in accordance with ISO 14284, so that they represent the average composition of the cross-section of the product.

^b If a range for the sulfur content of this grade is agreed, the permissible deviation shall be ± 0,010 %.

Table 6 — Chemical composition (cast analysis), annealed hardness, temperature for hardening, and hardness in the quenched and tempered condition for hot-work tool steels

Steel name	Chemical composition ^{a, b, 1} (% m/m)										Hardness (annealed) ^c			Hardening test		
	C	Si	Mn	Cr	Mo	V	W	Others	HB max.	Hardening temperature °C (± 10°C)	Quenching medium ^d	Tempering temperature °C (± 10°C)	Hardness HRC min.			
55NiCrMoV7 ^e	0,50 to 0,60	0,10 to 0,40	0,60 to 0,90	0,80 to 1,20	0,35 to 0,55	0,05 to 0,15		Ni: 1,50 to 1,80	248 ^f	850	O	500	429			
32CrMoV12-28	0,28 to 0,35	0,10 to 0,40	0,15 to 0,45	2,70 to 3,20	2,50 to 3,00	0,40 to 0,70		-	229	1040	O	550	46			
X37CrMoV5-1	0,33 to 0,41	0,80 to 1,20	0,25 to 0,50	4,80 to 5,50	1,10 to 1,50	0,30 to 0,50		-	229	1020	O	550	48			
X38CrMoV5-3	0,35 to 0,40	0,30 to 0,50	0,30 to 0,50	4,80 to 5,20	2,70 to 3,20	0,40 to 0,60		-	229	1040	O	550	50			
X40CrMoV5-1	0,35 to 0,42	0,80 to 1,20	0,25 to 0,50	4,80 to 5,50	1,20 to 1,50	0,85 to 1,15		-	229	1020	O	550	50			
50CrMoV13-15	0,45 to 0,55	0,20 to 0,80	0,50 to 0,90	3,00 to 3,50	1,30 to 1,70	0,15 to 0,35		-	248	1010	O	510	56			
X30WCrV9-3	0,25 to 0,35	0,10 to 0,40	0,15 to 0,45	2,50 to 3,20	-	0,30 to 0,50	8,50 to 9,50	-	241	1150	O	600	48			
X35CrWMoV5	0,32 to 0,40	0,80 to 1,20	0,20 to 0,50	4,75 to 5,50	1,25 to 1,60	0,20 to 0,50	1,10 to 1,60	-	229	1020	O	550	48			
38CrCoWV18-17	0,35 to 0,45	0,15 to 0,50	0,20 to 0,50	4,00 to 4,70	0,30 to 0,50	1,70 to 2,10	3,80 to 4,50	Co 4,00 to 4,50	260	1120	O	600	48			

^a Elements not quoted in this table shall not be intentionally added to the steel without the agreement of the purchaser, other than for the purpose of finishing the heat. All reasonable precautions shall be taken to prevent the addition from scrap or other materials used in manufacture, of such elements which affect the hardenability, mechanical properties and applicability.

^b For all steels (unless otherwise specified), phosphorus ≤ 0,030 % and sulfur ≤ 0,020 %.

^c Hardness in the cold drawn condition (+A +C) may be 20 HB higher than in the annealed condition (+A).

^d Quenching medium: O = Oil. Usual quenching media for tools are air, gas or salt bath.

^e The sulfur content for this grade is ≤ 0,030 %.

^f For greater dimensions, this steel is normally supplied in the quenched and tempered condition with a hardness of approximately 380 HB.

^g This value applies for smaller dimensions only.

Table 7 — Permissible deviations between specified analysis and product analysis for hot-work tool steels (see Table 6)

Steel name	Permissible deviations, (% m/m)										
	C	Si	Mn	P	S	Cr	Mo	Ni	Co	V	W
55NiCrMoV7	± 0,02	± 0,03	± 0,04	+ 0,005	+ 0,005	± 0,05	± 0,04	± 0,07	-	± 0,02	-
32CrMoV12-28	± 0,02	± 0,03	± 0,04	+ 0,005	+ 0,005	± 0,10	± 0,10	-	-	± 0,04	-
X37CrMoV5-1	± 0,02	± 0,05	± 0,04	+ 0,005	+ 0,005	± 0,10	± 0,05	-	-	± 0,04	-
X38CrMoV5-3	± 0,02	± 0,03	± 0,04	+ 0,005	+ 0,005	± 0,10	± 0,10	-	-	± 0,04	-
X40CrMoV5-1	± 0,02	± 0,05	± 0,04	+ 0,005	+ 0,005	± 0,10	± 0,05	-	-	± 0,05	-
50CrMoV13-15	± 0,02	± 0,05	± 0,04	+ 0,005	+ 0,005	± 0,10	± 0,05	-	-	± 0,04	-
X30WCrV9-3	± 0,02	± 0,03	± 0,04	+ 0,005	+ 0,005	± 0,10	-	-	-	± 0,04	± 0,10
X35CrWMoV5	± 0,02	± 0,05	± 0,04	+ 0,005	+ 0,005	± 0,10	± 0,05	-	-	± 0,04	± 0,07
38CrCoWV18-17-17	± 0,02	± 0,03	± 0,04	+ 0,005	+ 0,005	± 0,10	± 0,04	-	± 0,10	± 0,10	± 0,10

NOTE The deviations, other than when maxima only are specified, apply either above or below the specified limits of the range but not both above and below for the same element from different sample products from the same cast. When maxima only are specified the deviations are positive only. The values are valid only if the samples are selected in accordance with ISO 14284, so that they represent the average composition of the cross-section of the product.

Table 8 — Chemical composition (cast analysis), annealed hardness, temperature for hardening and hardness in the hardened and tempered condition for high-speed tool steels

Steel name	Chemical composition ^{a, b, c} (% ml/m)							Hardness (annealed) ^d +A HB max.	Hardening temperature °C (±10°C)	Quenching medium ^e	Hardening test ^f	
	C	Co	Cr	Mo	V	W	Si				Hardening temperature °C (±10°C)	Tempering temperature °C (±10°C)
HS0-4-1	0,77 to 0,85	—	3,90 to 4,40	4,00 to 4,50	0,90 to 1,10	—	≤ 0,65	262	1120		560	60
HS1-4-2	0,85 to 0,95	—	3,60 to 4,30	4,10 to 4,80	1,70 to 2,20	0,80 to 1,40	≤ 0,65	262	1180		560	63
HS18-0-1	0,73 to 0,83	—	3,80 to 4,50	—	1,00 to 1,20	17,20 to 18,70	≤ 0,45	269	1260		560	63
HS2-9-2	0,95 to 1,05	—	3,50 to 4,50	8,20 to 9,20	1,70 to 2,20	1,50 to 2,10	≤ 0,70	269	1200		560	64
HS1-8-1	0,77 to 0,87	—	3,50 to 4,50	8,00 to 9,00	1,00 to 1,40	1,40 to 2,00	≤ 0,70	262	1190		560	63
HS3-3-2	0,95 to 1,03	—	3,80 to 4,50	2,50 to 2,90	2,20 to 2,50	2,70 to 3,00	≤ 0,45	255	1190		560	62
HS6-5-2	0,80 to 0,88	—	3,80 to 4,50	4,70 to 5,20	1,70 to 2,10	5,90 to 6,70	≤ 0,45	262	1220		560	64
HS6-5-2C ^g	0,86 to 0,94	—	3,80 to 4,50	4,70 to 5,20	1,70 to 2,10	5,90 to 6,70	≤ 0,45	269	1210		560	64
HS6-5-3	1,15 to 1,25	—	3,80 to 4,50	4,70 to 5,20	2,70 to 3,20	5,90 to 6,70	≤ 0,45	269	1200		560	64
HS6-5-3C	1,25 to 1,32	—	3,80 to 4,50	4,70 to 5,20	2,70 to 3,20	5,90 to 6,70	≤ 0,70	269	1180		560	64
HS6-6-2	1,00 to 1,10	—	3,80 to 4,50	5,50 to 6,50	2,30 to 2,60	5,90 to 6,70	≤ 0,45	262	1200		560	64
HS6-5-4	1,25 to 1,40	—	3,80 to 4,50	4,20 to 5,00	3,70 to 4,20	5,20 to 6,00	≤ 0,45	269	1210		560	64
HS6-5-2-5 ^g	0,87 to 0,95	4,50 to 5,00	3,80 to 4,50	4,70 to 5,20	1,70 to 2,10	5,90 to 6,70	≤ 0,45	269	1210		560	64
HS6-5-3-8	1,23 to 1,33	8,00 to 8,80	3,80 to 4,50	4,70 to 5,30	2,70 to 3,20	5,90 to 6,70	≤ 0,70	302	1180		560	65
HS10-4-3-10	1,20 to 1,35	9,50 to 10,50	3,80 to 4,50	3,20 to 3,90	3,00 to 3,50	9,00 to 10,00	≤ 0,45	302	1230		560	66
HS2-9-1-8	1,05 to 1,15	7,50 to 8,50	3,50 to 4,50	9,00 to 10,00	0,90 to 1,30	1,20 to 1,90	≤ 0,70	277	1190		550	66

a Elements not quoted in this table shall not be intentionally added to the steel without the agreement of the purchaser, other than for the purpose of finishing the heat. All reasonable precautions shall be taken to prevent the addition from scrap or other materials used in manufacture, of such elements which affect the hardenability, mechanical properties and applicability.

b Maximum 0,40 % Mn unless otherwise specified (see footnote g).

c Maximum 0,030 % P and S each.

d Hardness in the annealed plus cold drawn condition (+A+C) may be 50 HB and hardness in the annealed plus cold rolled condition (+A+CR) may be 70 HB higher than in the annealed condition (+A).

e For the reference hardening test either oil or salt bath: in cases of dispute, however, only oil. Usual quenching media in practice are air, gas or salt bath.

f See B.3.

g A sulfur range of 0,060 % to 0,150 % may be agreed at the time of enquiry and order for this grade. In this case a max. of 0,80 % Mn applies.


Table 9 — Permissible deviations between specified analysis and product analysis for high-speed tool steels (see Table 8)

Steel name	Permissible deviations a, b, (% m/m)										
	C	Si	Mn	P	S	Co	Cr	Mo	V	W	
HS0-4-1	± 0,03	+ 0,03	+ 0,04	+ 0,005	+ 0,005	-	± 0,10	± 0,10	± 0,05	-	
HS1-4-2	± 0,03	+ 0,03	+ 0,04	+ 0,005	+ 0,005	-	± 0,10	± 0,10	± 0,07	± 0,10	
HS18-0-1	± 0,03	+ 0,03	+ 0,04	+ 0,005	+ 0,005	-	± 0,10	-	± 0,05	± 0,20	
HS2-9-2	± 0,03	+ 0,03	+ 0,04	+ 0,005	+ 0,005	-	± 0,10	± 0,10	± 0,07	± 0,10	
HS1-8-1	± 0,03	+ 0,03	+ 0,04	+ 0,005	+ 0,005	-	± 0,10	± 0,10	± 0,05	± 0,10	
HS3-3-2	± 0,03	+ 0,03	+ 0,04	+ 0,005	+ 0,005	-	± 0,10	± 0,10	± 0,10	± 0,10	
HS6-5-2	± 0,03	+ 0,03	+ 0,04	+ 0,005	+ 0,005	-	± 0,10	± 0,10	± 0,07	± 0,10	
HS6-5-2C	± 0,03	+ 0,03	+ 0,04	+ 0,005	+ 0,005	-	± 0,10	± 0,10	± 0,07	± 0,10	
HS6-5-3	± 0,03	+ 0,03	+ 0,04	+ 0,005	+ 0,005	-	± 0,10	± 0,10	± 0,10	± 0,10	
HS6-5-3C	± 0,04	+ 0,03	+ 0,04	+ 0,005	+ 0,005	-	± 0,10	± 0,10	± 0,10	± 0,10	
HS6-6-2	± 0,03	+ 0,03	+ 0,04	+ 0,005	+ 0,005	-	± 0,10	± 0,10	± 0,10	± 0,10	
HS6-5-4	± 0,04	+ 0,03	+ 0,04	+ 0,005	+ 0,005	-	± 0,10	± 0,10	± 0,10	± 0,10	
HS6-5-2-5	± 0,03	+ 0,03	+ 0,04	+ 0,005	+ 0,005	± 0,10	± 0,10	± 0,10	± 0,07	± 0,10	
HS6-5-3-8	± 0,04	+ 0,03	+ 0,04	+ 0,005	+ 0,005	± 0,10	± 0,10	± 0,10	± 0,10	± 0,10	
HS10-4-3-10	± 0,03	+ 0,03	+ 0,04	+ 0,005	+ 0,005	± 0,15	± 0,10	± 0,10	± 0,10	± 0,10	
HS2-9-1-8	± 0,03	+ 0,03	+ 0,04	+ 0,005	+ 0,005	± 0,10	± 0,10	± 0,10	± 0,05	± 0,10	

a The deviations, other than when maxima only are specified, apply either above or below the specified limits of the range but not both above and below for the same element from different sample products from the same cast. When maxima only are specified the deviations are positive only. The values are valid only if the samples are selected in accordance with ISO 14284, so that they represent the average composition of the cross-section of the product.


b If a range for the sulfur content is agreed, the permissible deviation shall be ± 0,010 %.

Dimensions in millimetres

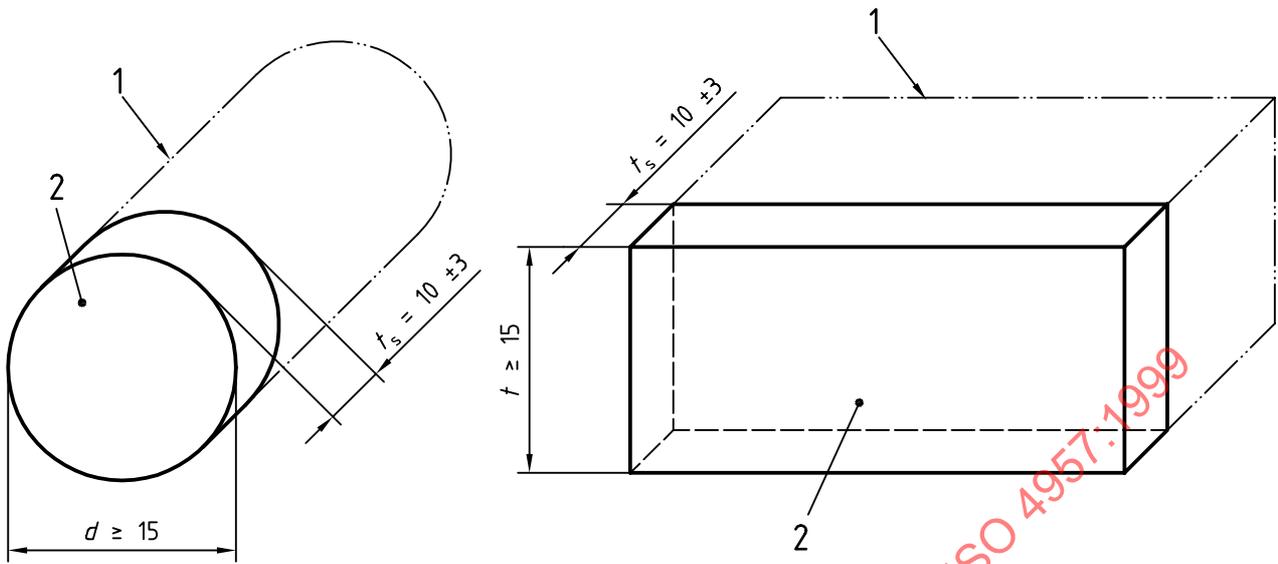


The test piece shall, according to the choice of the manufacturer:


- a) be identical with the test sample, or
- b) be taken from the sample by one cut as demonstrated below, or

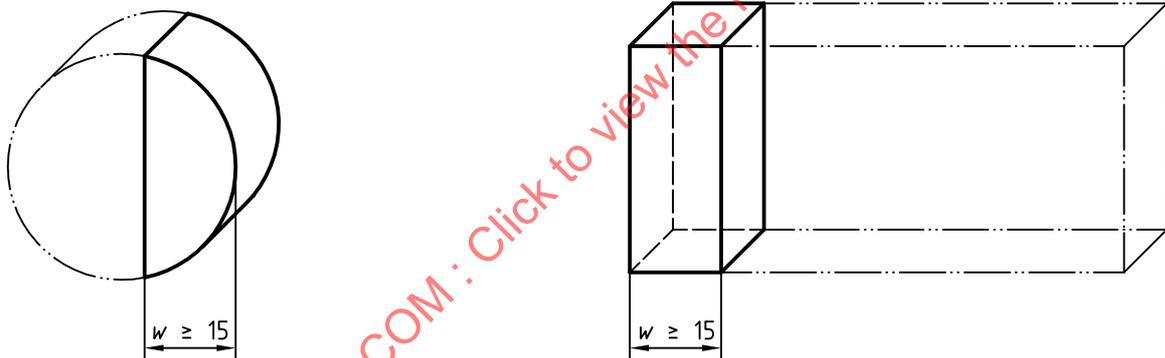

- c) be taken from the sample by two cuts as demonstrated below.

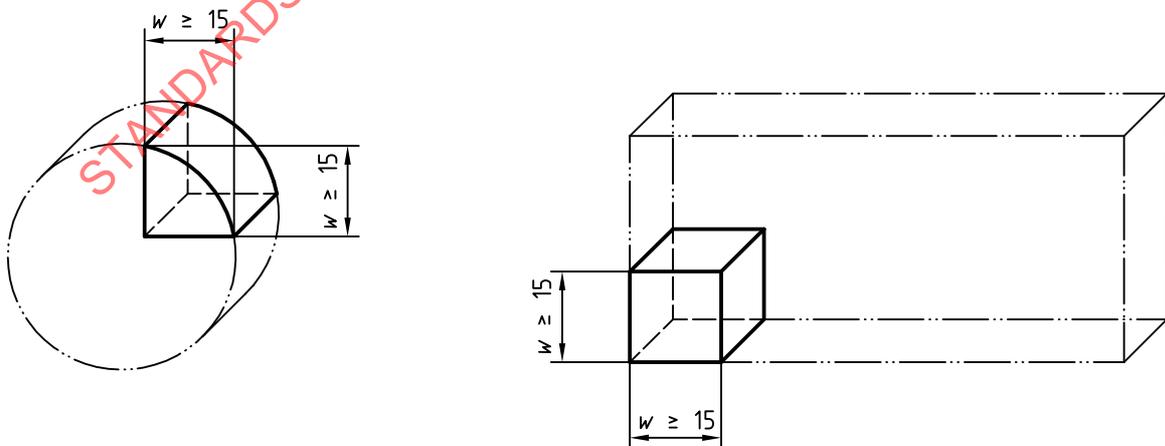

a) Product diameter or thickness ≥ 15 mm

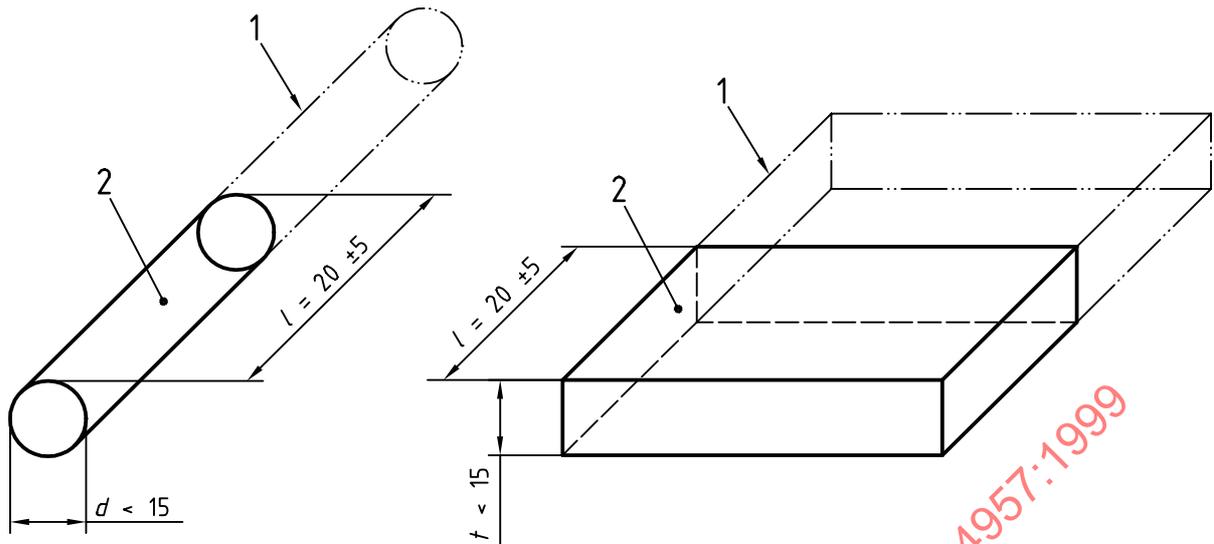


The test piece shall, according to the choice of the manufacturer, either

- a) be identical with the sample, or
- b) be taken from rectangular samples by one cut as demonstrated below.

Key

- 1 Product
- 2 Sample

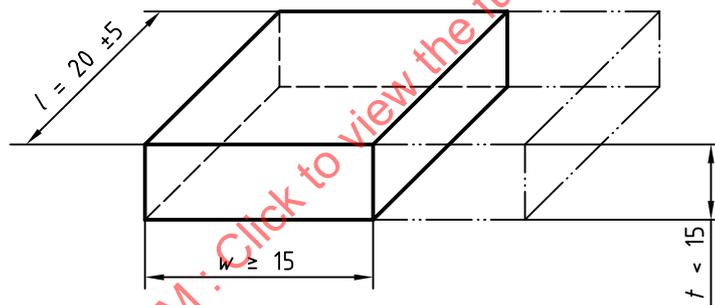

b) Product diameter or thickness < 15 mm

Figure 1 — Location of test pieces in the hardening test

Annex A (informative)

Hardness-tempering temperature-curves

In Figures A.1 to A.4 the hardness-tempering temperature-curves of the steels are given for guidance. In these figures, the austenitizing temperature and the quenching medium (W = water, O = oil, A = air) are mentioned.

NOTE The hardness-tempering temperature-curve for a certain steel type can vary to a considerable extent depending on the chemical composition of the cast, the hardening conditions and the tempering conditions. Consequently the curves in Figures A.1 to A.4 which originate from data from different sources can for the time being give only a rough guide to the tempering behaviour of the steels. They are assumed to apply with the above reservations for test pieces which have been tempered at the relevant tempering temperature but which in all other respects have been prepared according to the conditions for the hardening test (see B.3). When applying the curves for an estimation of the hardness which can be expected in quenched and tempered tools, it should be taken into account that the optimum heat-treatment conditions for the tools are not necessarily identical with those specified for the test pieces and that especially the times for heating given in B.3 are not valid for thicker tools.

STANDARDSISO.COM : Click to view the full PDF of ISO 4957:1999

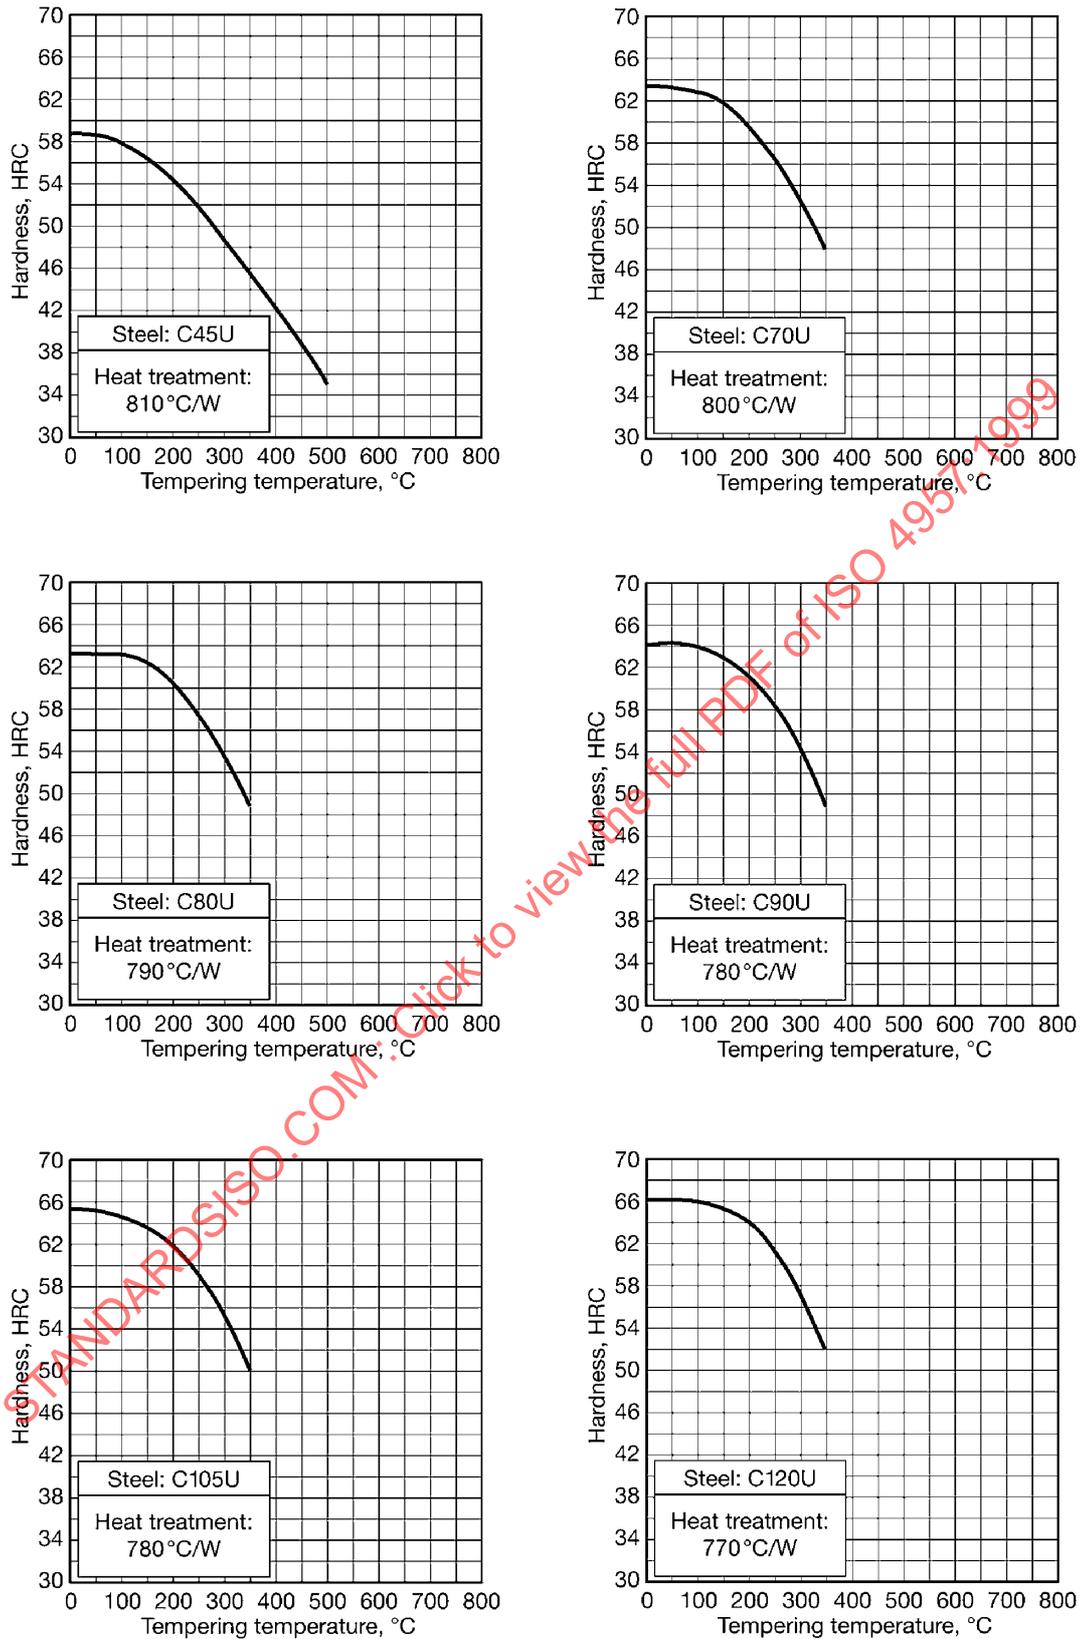


Figure A.1 — Hardness-tempering temperature-curves for unalloyed cold-work tool steels (see Table2)

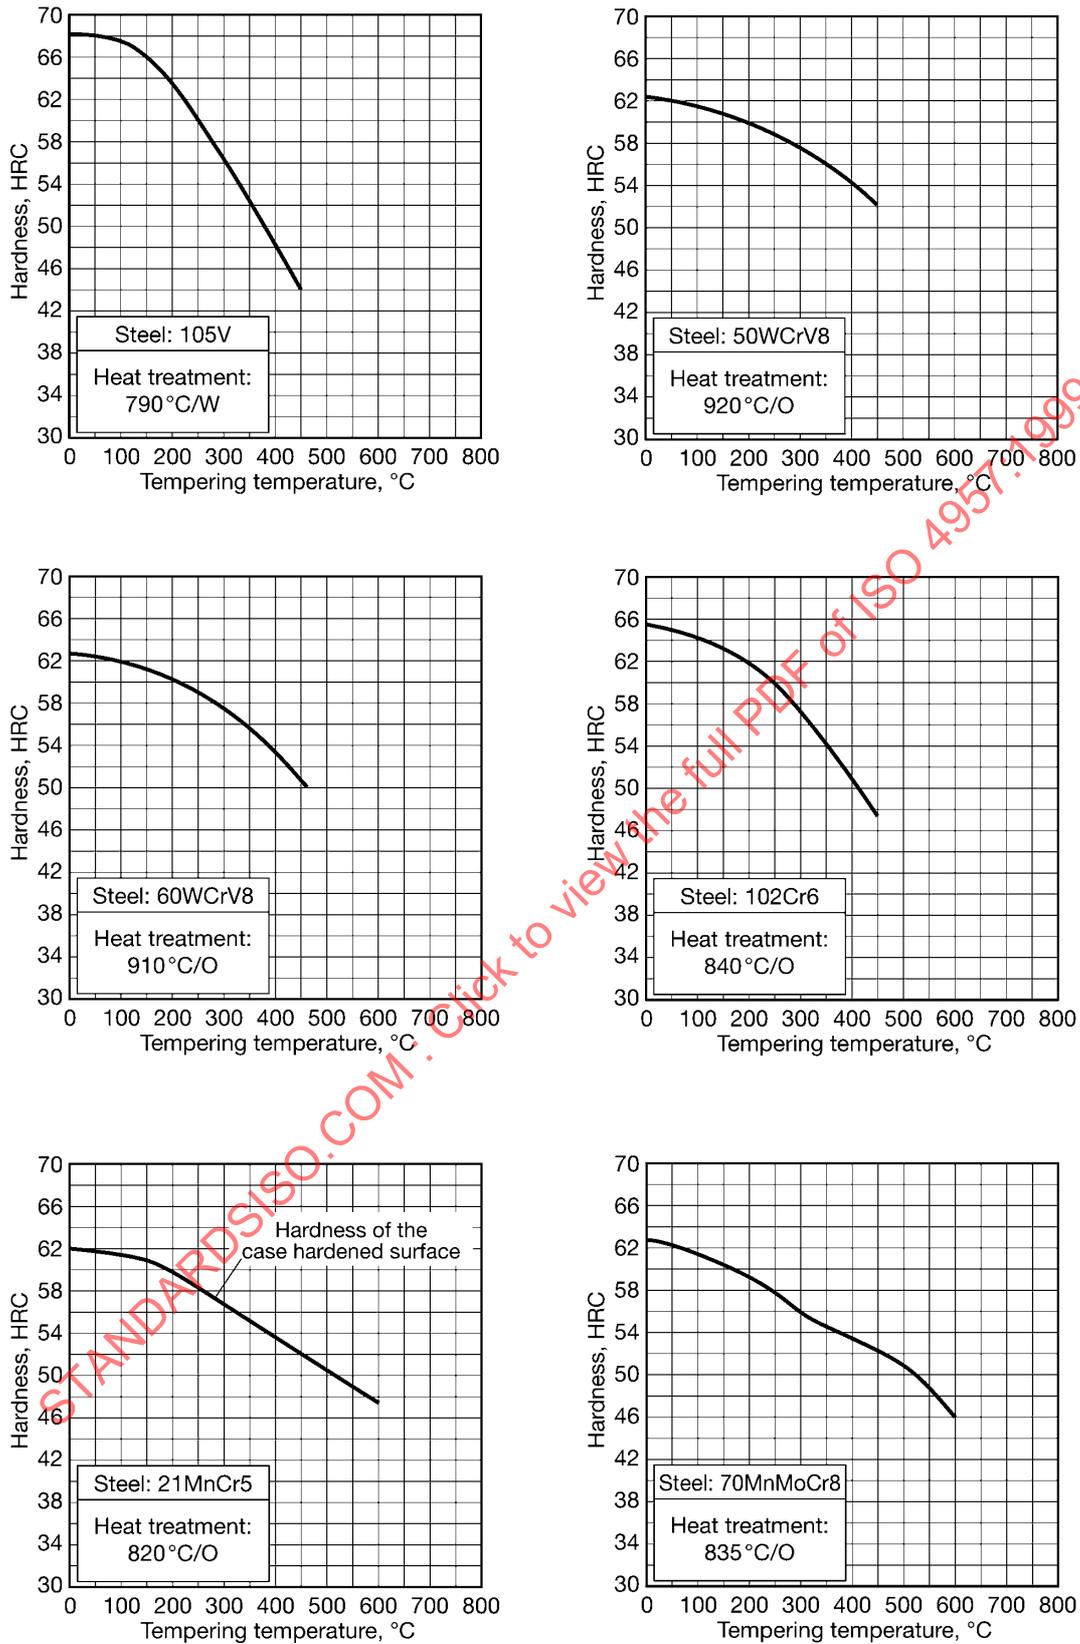


Figure A.2 — Hardness-tempering temperature-curves for alloyed cold-work tool steels (see Table 4)

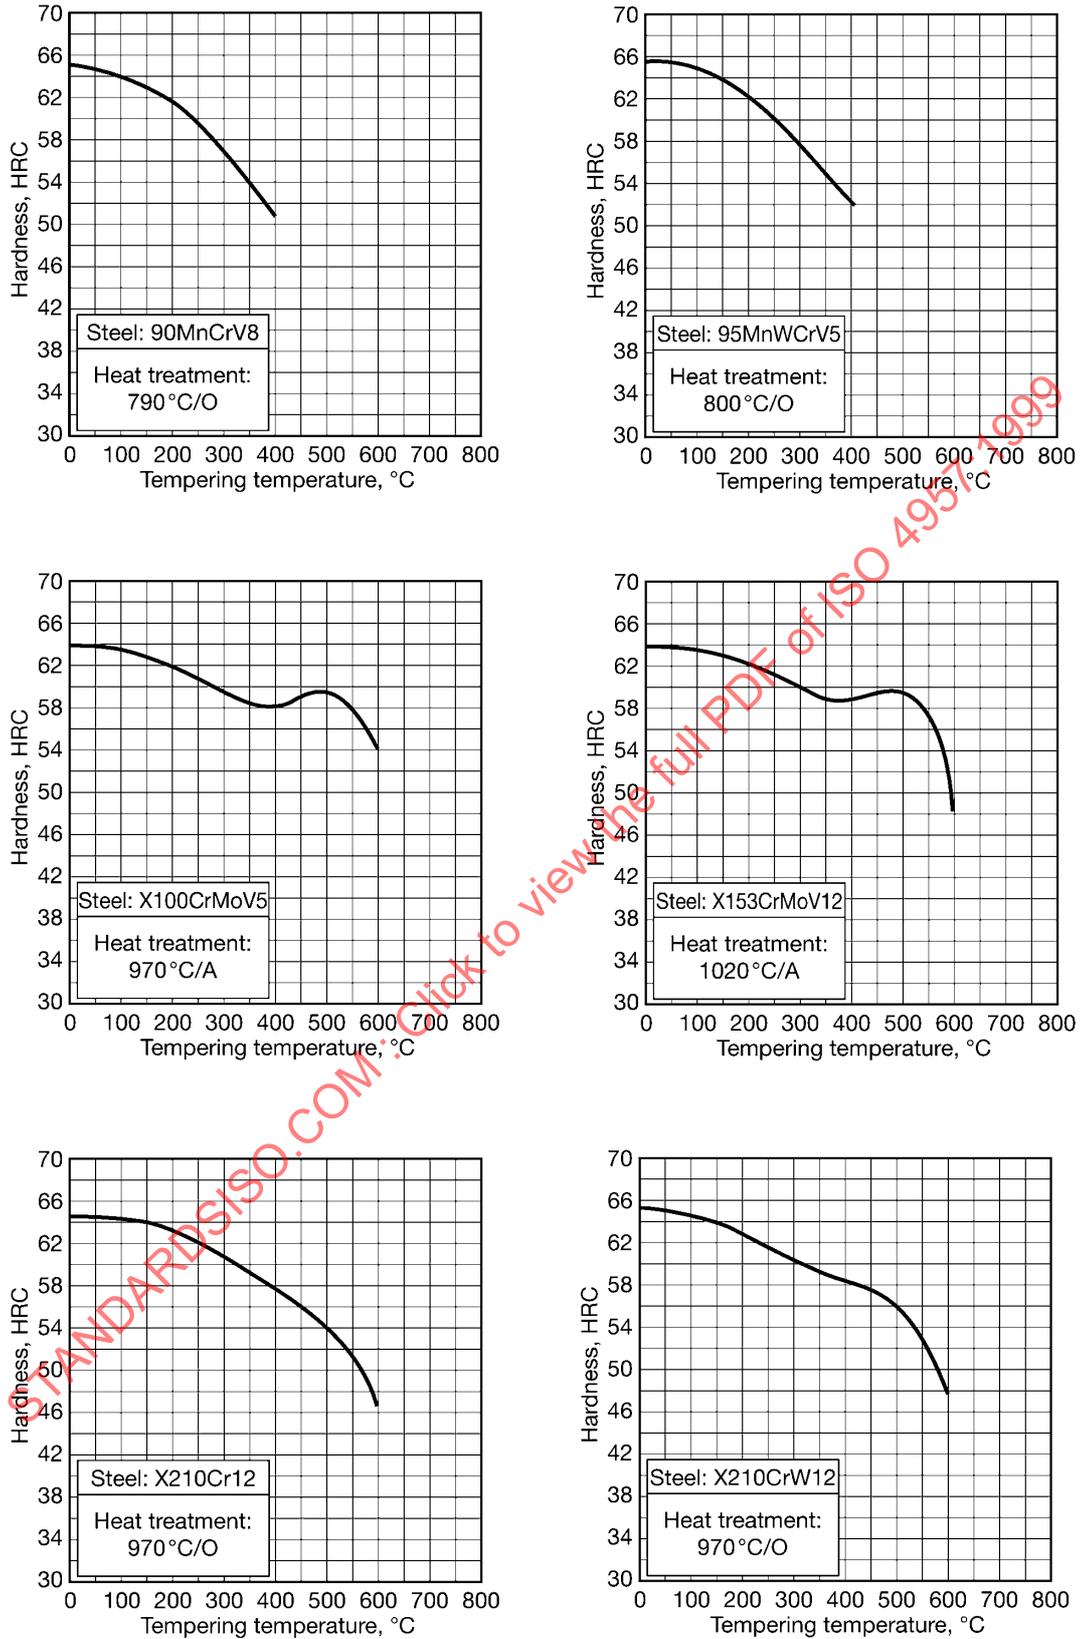


Figure A.2 (continued)

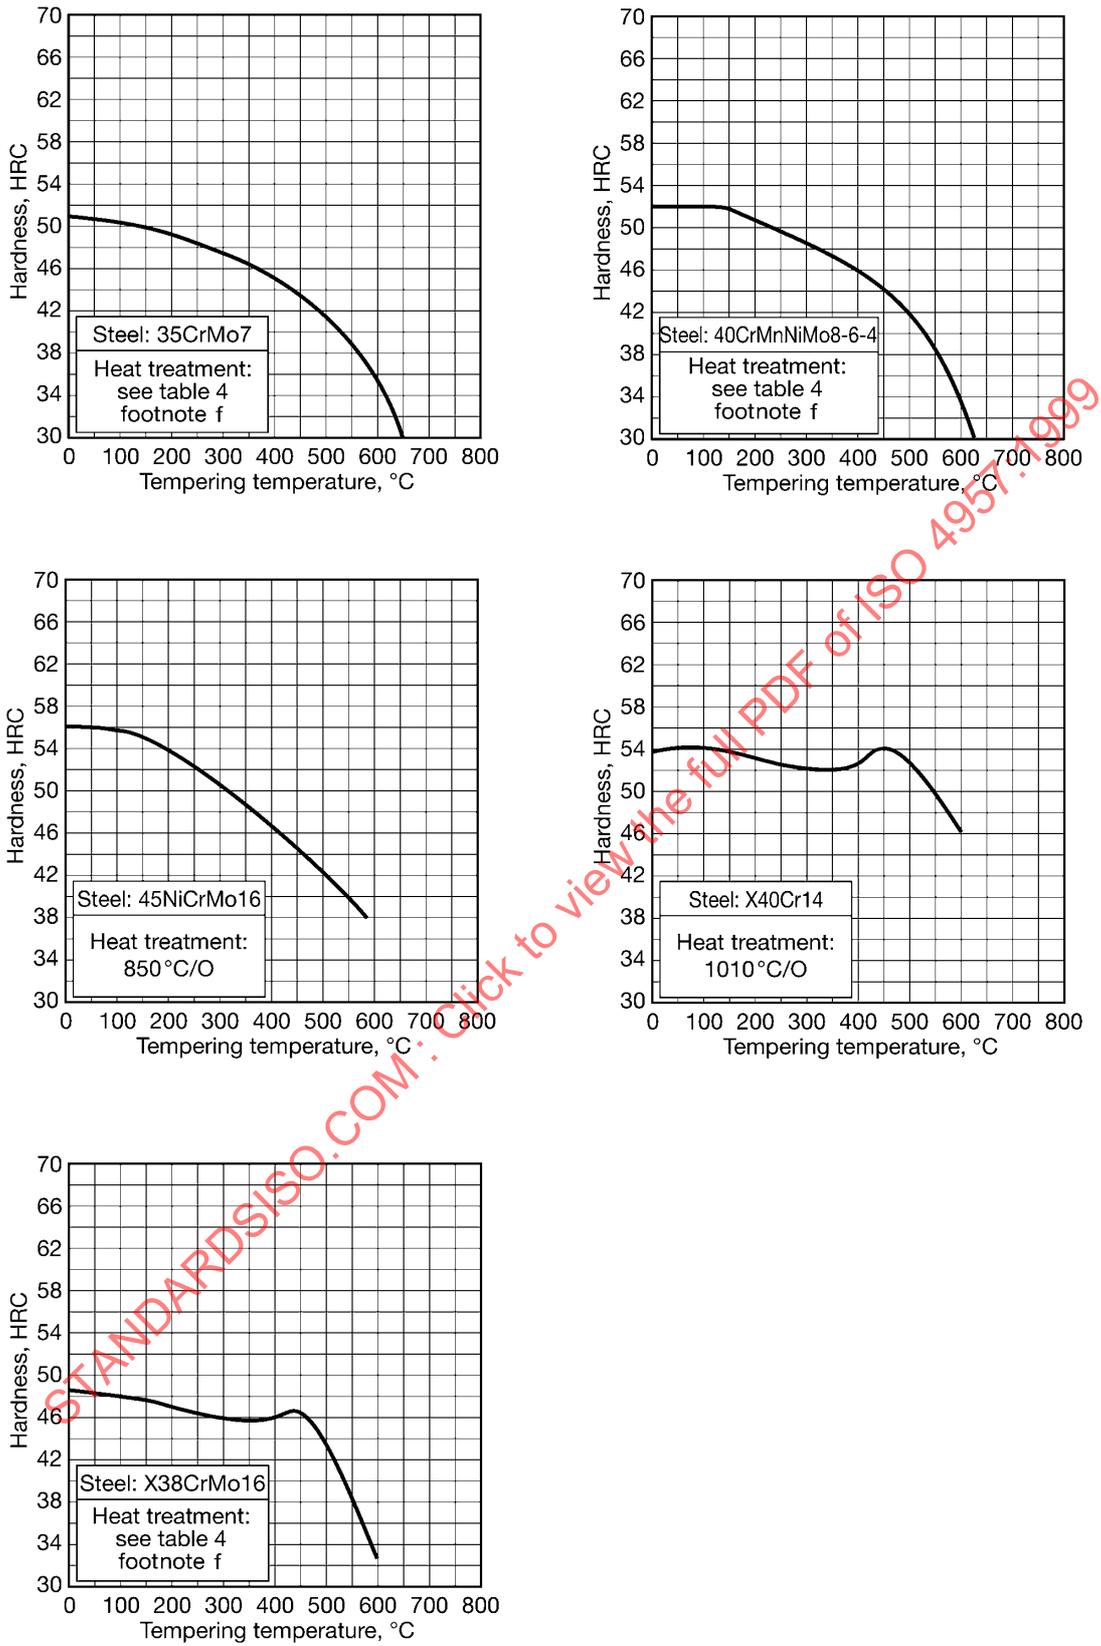


Figure A.2 (continued)

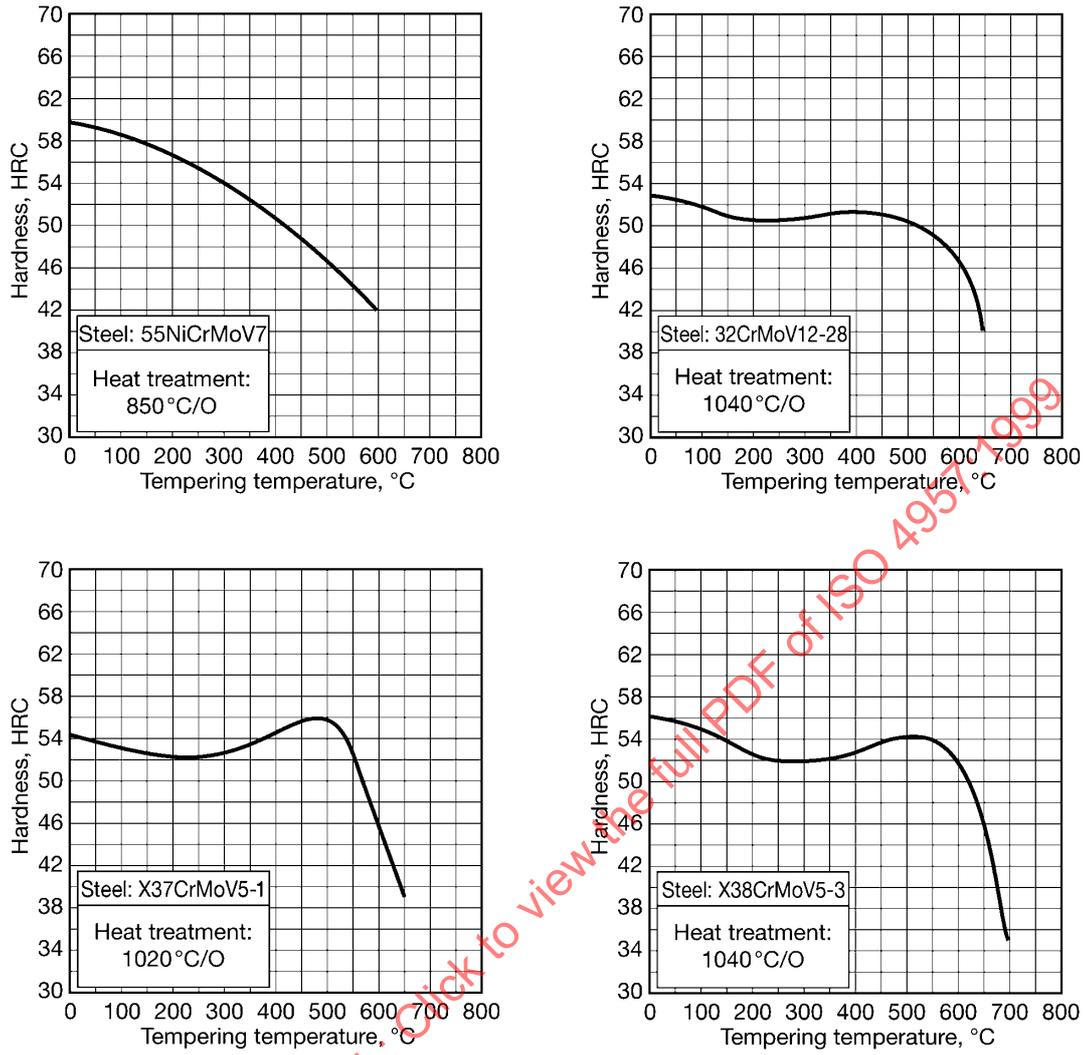


Figure A.3 — Hardness-tempering temperature-curves for hot-work tool steels (see Table 6)

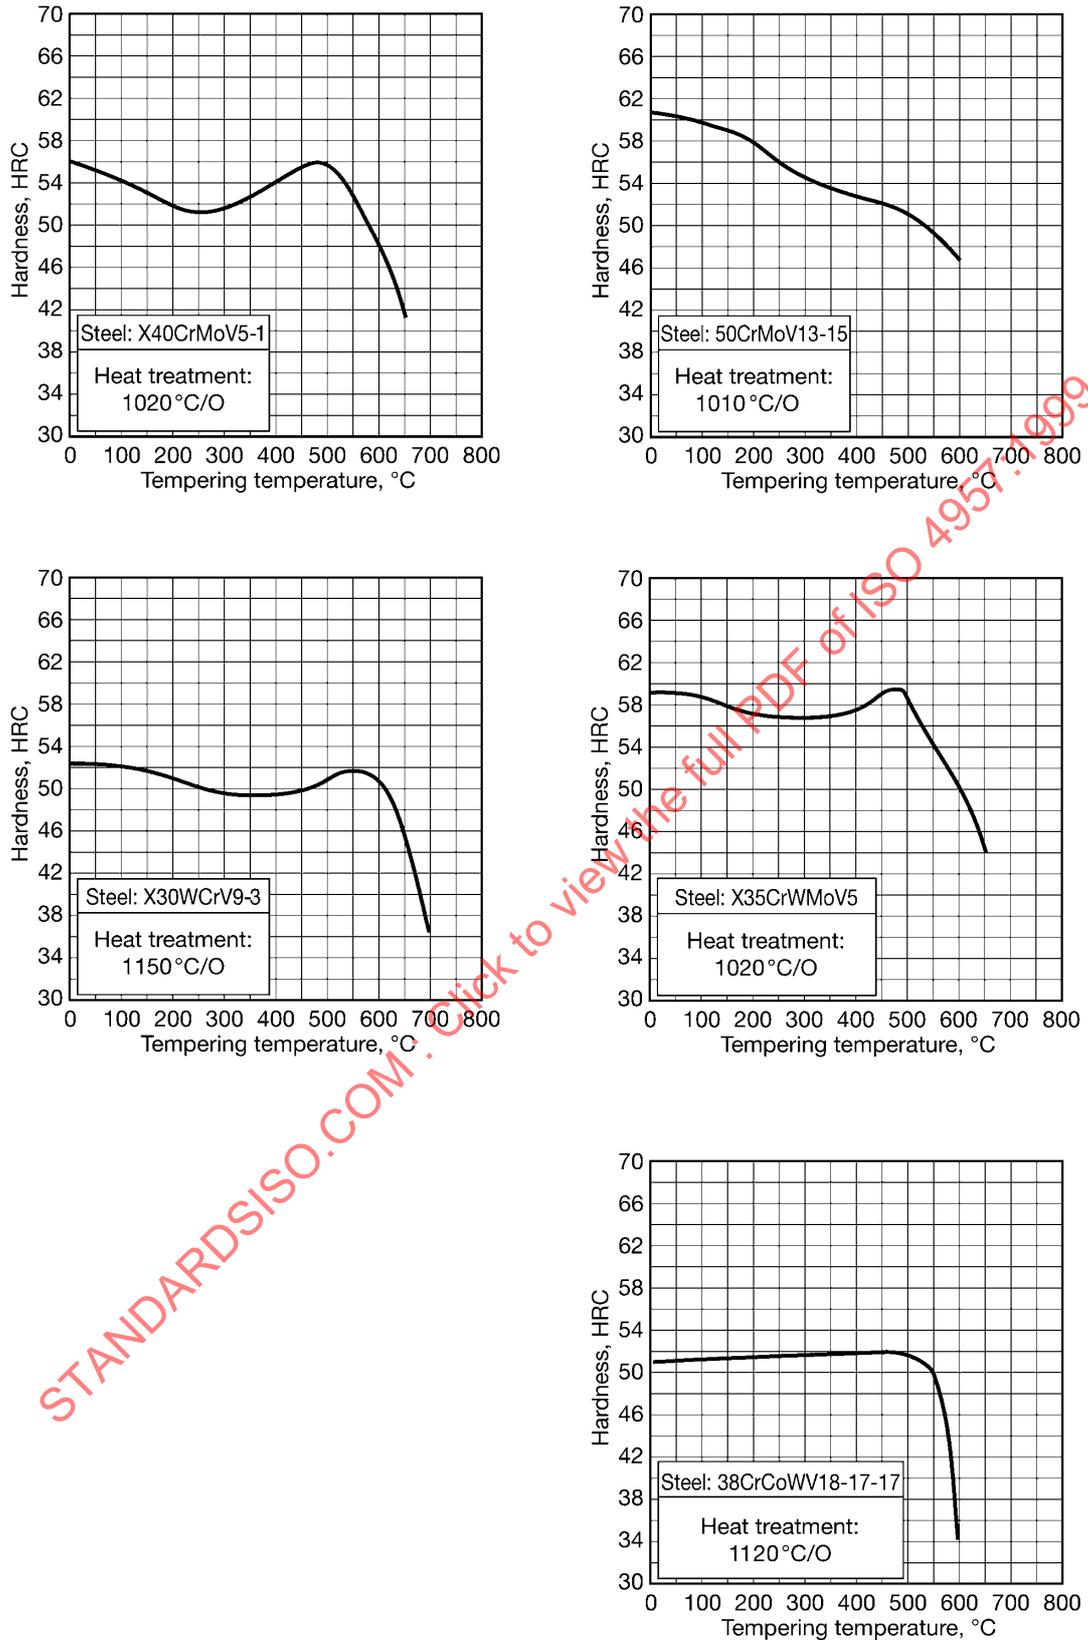


Figure A.3 (continued)

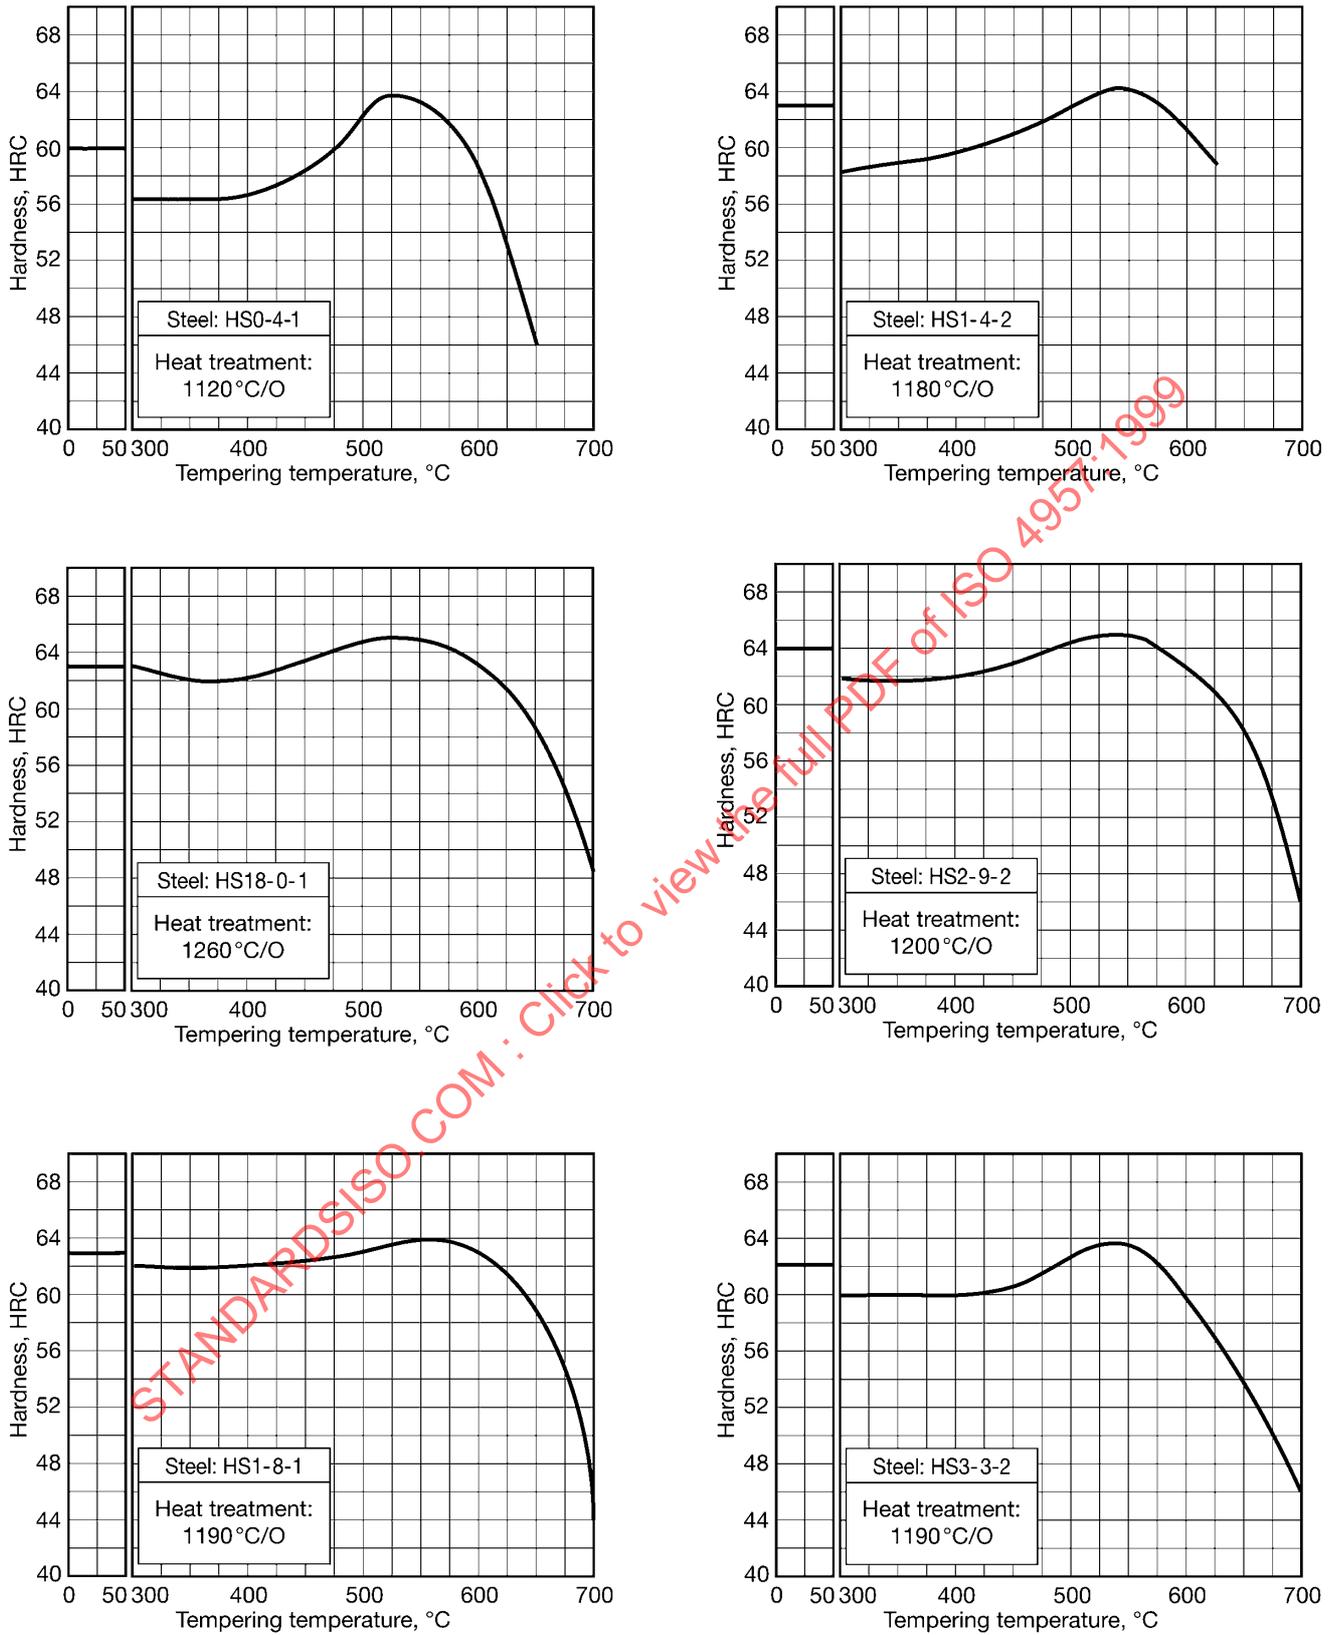


Figure A.4 — Hardness-tempering temperature-curves for high-speed tool steels (see Table 8)

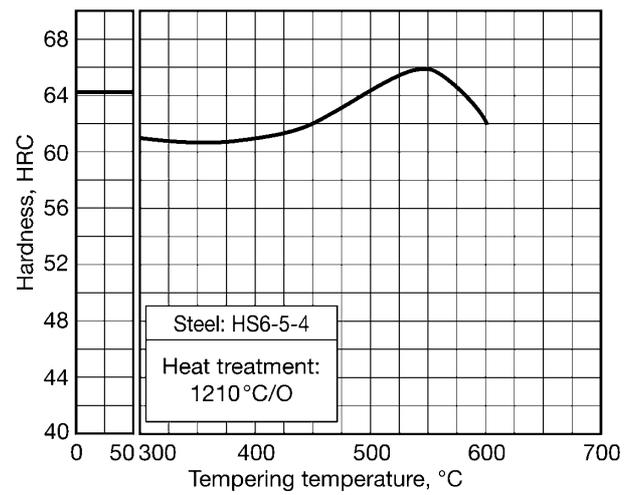
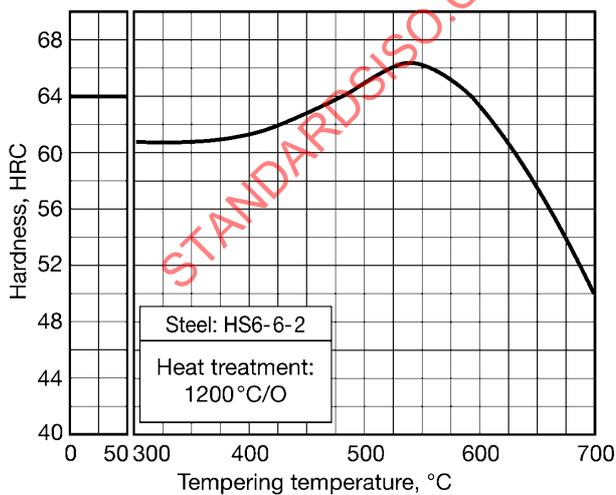
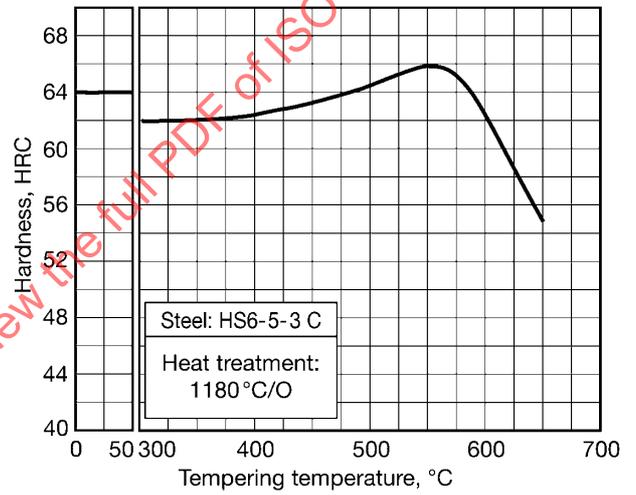
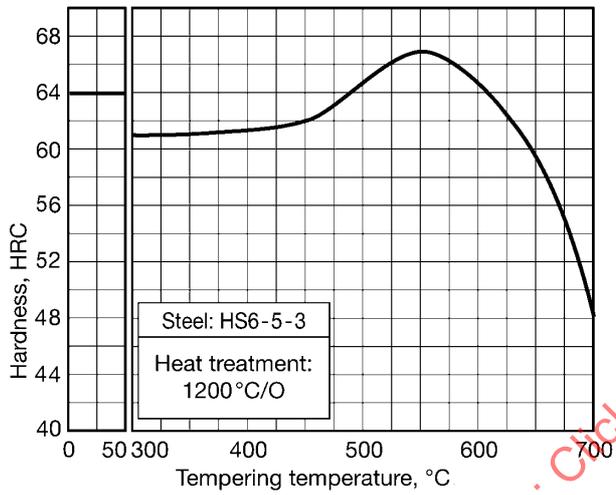
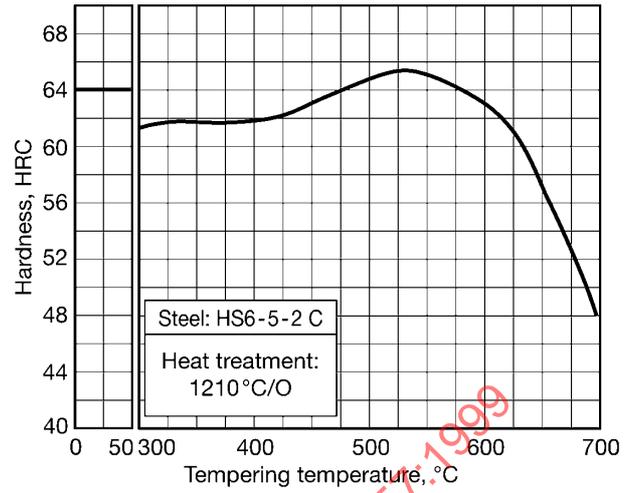
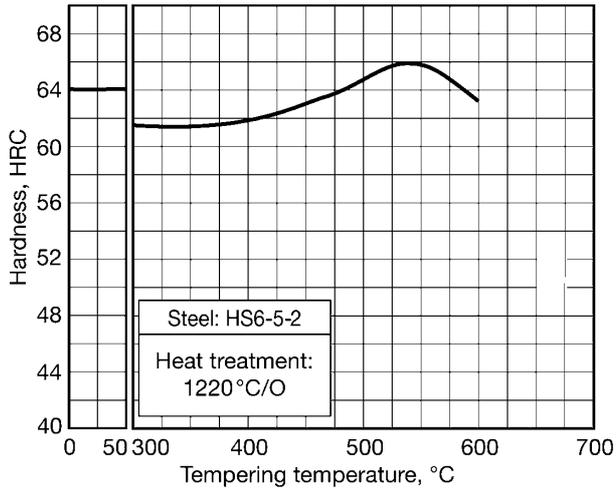


Figure A.4 (continued)