
**Calculation of load capacity of spur
and helical gears —**

**Part 5:
Strength and quality of materials**

*Calcul de la capacité de charge des engrenages cylindriques à
dentures droite et hélicoïdale —*

Partie 5: Résistance et qualité des matériaux

STANDARDSISO.COM : Click to view the full PDF of ISO 6336-5:2016



STANDARDSISO.COM : Click to view the full PDF of ISO 6336-5:2016



COPYRIGHT PROTECTED DOCUMENT

© ISO 2016, Published in Switzerland

All rights reserved. Unless otherwise specified, no part of this publication may be reproduced or utilized otherwise in any form or by any means, electronic or mechanical, including photocopying, or posting on the internet or an intranet, without prior written permission. Permission can be requested from either ISO at the address below or ISO's member body in the country of the requester.

ISO copyright office
Ch. de Blandonnet 8 • CP 401
CH-1214 Vernier, Geneva, Switzerland
Tel. +41 22 749 01 11
Fax +41 22 749 09 47
copyright@iso.org
www.iso.org

Contents

	Page
Foreword	iv
Introduction	v
1 Scope	1
2 Normative references	1
3 Terms, definitions and symbols	2
4 Methods for the determination of allowable stress numbers	2
4.1 General	2
4.2 Method A	3
4.3 Method B	3
4.4 Method B _R	3
4.5 Method B _k	3
4.6 Method B _p	3
5 Standard allowable stress numbers — Method B	3
5.1 Application	3
5.2 Allowable stress number (contact), $\sigma_{H \text{ lim}}$	4
5.3 Bending stress number values for $\sigma_{F \text{ lim}}$ and σ_{FE}	5
5.3.1 Nominal stress numbers (bending), $\sigma_{F \text{ lim}}$	5
5.3.2 Allowable stress number (bending), σ_{FE}	5
5.3.3 Reversed bending	5
5.4 Graphs for $\sigma_{H \text{ lim}}$ and $\sigma_{F \text{ lim}}$ and σ_{FE}	6
5.5 Calculation of $\sigma_{H \text{ lim}}$ and $\sigma_{F \text{ lim}}$	6
5.6 Hardening depth of surface hardened gears in finished condition	23
5.6.1 General	23
5.6.2 Case depth of carburized and hardened gears	23
5.6.3 Nitriding hardening depth of nitrided gears	25
6 Requirements for material quality and heat treatment	26
6.1 General aspects	26
6.2 Normalized low carbon or cast steel, plain carbon, unalloyed steels (see Figures 1 and 2)	27
6.3 Black malleable cast iron [see Figures 3 a) and 4 a)]	27
6.4 Other materials [see Figures 3 b), 3 c), 4 b), 4 c), 5 to 16]	27
6.5 Coupon	40
6.6 Mechanical cleaning by shot blasting	41
6.7 Shot peening	41
6.7.1 General	41
6.7.2 Strength enhancement	41
6.7.3 Salvage	41
Annex A (informative) Considerations of size of controlling section for through hardened gearing	43
Annex B (informative) Core hardness coefficients	46
Bibliography	47

Foreword

ISO (the International Organization for Standardization) is a worldwide federation of national standards bodies (ISO member bodies). The work of preparing International Standards is normally carried out through ISO technical committees. Each member body interested in a subject for which a technical committee has been established has the right to be represented on that committee. International organizations, governmental and non-governmental, in liaison with ISO, also take part in the work. ISO collaborates closely with the International Electrotechnical Commission (IEC) on all matters of electrotechnical standardization.

The procedures used to develop this document and those intended for its further maintenance are described in the ISO/IEC Directives, Part 1. In particular the different approval criteria needed for the different types of ISO documents should be noted. This document was drafted in accordance with the editorial rules of the ISO/IEC Directives, Part 2 (see www.iso.org/directives).

Attention is drawn to the possibility that some of the elements of this document may be the subject of patent rights. ISO shall not be held responsible for identifying any or all such patent rights. Details of any patent rights identified during the development of the document will be in the Introduction and/or on the ISO list of patent declarations received (see www.iso.org/patents).

Any trade name used in this document is information given for the convenience of users and does not constitute an endorsement.

For an explanation on the meaning of ISO specific terms and expressions related to conformity assessment, as well as information about ISO's adherence to the World Trade Organization (WTO) principles in the Technical Barriers to Trade (TBT) see the following URL: www.iso.org/iso/foreword.html.

The committee responsible for this document is ISO/TC 60, *Gears*, Subcommittee SC 2, *Gear capacity calculation*.

This third edition cancels and replaces the second edition (ISO 6336-5:2003), which has been technically revised to reflect current practices throughout the industry.

A list of all parts in the ISO 6336 series can be found on the ISO website.

Introduction

This document, together with ISO 6336-1, ISO 6336-2, ISO 6336-3 and ISO 6336-6, provides the principles for a coherent system of procedures for the calculation of the load capacity of cylindrical involute gears with external or internal teeth. ISO 6336 is designed to facilitate the application of future knowledge and developments, as well as the exchange of information gained from experience.

Allowable stress numbers, as covered by this document, may vary widely. Such variation is attributable to defects and variations of chemical composition (charge), structure, the type and extent of hot working (e.g. bar stock, forging, reduction ratio), heat treatment, residual stress levels, etc.

Tables summarize the most important influencing variables and the requirements for the different materials and quality grades. The effects of these influences on surface durability and tooth bending strength are illustrated by graphs.

This document covers the most widely used ferrous gear materials and related heat treatment processes. Recommendations on the choice of specific materials, heat treatment processes or manufacturing processes are not included. Furthermore, no comments are made concerning the suitability or otherwise of any materials for specific manufacturing or heat treatment processes.

STANDARDSISO.COM : Click to view the full PDF of ISO 6336-5:2016

[STANDARDSISO.COM](https://standardsiso.com) : Click to view the full PDF of ISO 6336-5:2016

Calculation of load capacity of spur and helical gears —

Part 5: Strength and quality of materials

1 Scope

This document describes contact and tooth-root stresses and gives numerical values for both limit stress numbers. It specifies requirements for material quality and heat treatment and comments on their influences on both limit stress numbers.

Values in accordance with this document are suitable for use with the calculation procedures provided in ISO 6336-2, ISO 6336-3 and ISO 6336-6 and in the application standards for industrial, high-speed and marine gears. They are applicable to the calculation procedures given in ISO 10300 for rating the load capacity of bevel gears. This document is applicable to all gearing, basic rack profiles, profile dimensions, design, etc., covered by those standards. The results are in good agreement with other methods for the range indicated in the scope of ISO 6336-1 and ISO 10300-1.

2 Normative references

The following documents are referred to in the text in such a way that some or all of their content constitutes requirements of this document. For dated references, only the edition cited applies. For undated references, the latest edition of the referenced document (including any amendments) applies.

ISO 53, *Cylindrical gears for general and heavy engineering — Standard basic rack tooth profile*

ISO 642, *Steel — Hardenability test by end quenching (Jominy test)*

ISO 643:2012, *Steels — Micrographic determination of the apparent grain size*

ISO 683-1, *Heat-treatable steels, alloy steels and free-cutting steels — Part 1: Non-alloy steels for quenching and tempering*

ISO 683-2, *Heat-treatable steels, alloy steels and free-cutting steels — Part 2: Alloy steels for quenching and tempering*

ISO 683-3, *Heat-treatable steels, alloy steels and free-cutting steels — Part 3: Case-hardening steels*

ISO 683-4, *Heat-treatable steels, alloy steels and free-cutting steels — Part 4: Free-cutting steels*

ISO 683-5, *Heat-treatable steels, alloy steels and free-cutting steels — Part 5: Nitriding steels*

ISO 1328-1, *Cylindrical gears — ISO system of flank tolerance classification — Part 1: Definitions and allowable values of deviations relevant to flanks of gear teeth*

ISO 2639, *Steels — Determination and verification of the depth of carburized and hardened cases*

ISO 3754, *Steel — Determination of effective depth of hardening after flame or induction hardening*

ISO 4948-2, *Steels — Classification — Part 2: Classification of unalloyed and alloy steels according to main quality classes and main property or application characteristics*

ISO 4967, *Steel — Determination of content of non-metallic inclusions — Micrographic method using standard diagrams*

ISO 6336-5:2016(E)

ISO 6336-1, *Calculation of load capacity of spur and helical gears — Part 1: Basic principles, introduction and general influence factors*

ISO 6336-2, *Calculation of load capacity of spur and helical gears — Part 2: Calculation of surface durability (pitting)*

ISO 6336-3:2006, *Calculation of load capacity of spur and helical gears — Part 3: Calculation of tooth bending strength*

ISO 9443, *Heat-treatable and alloy steels — Surface quality classes for hot-rolled round bars and wire rods — Technical delivery conditions*

ISO 10474, *Steel and steel products — Inspection documents*

ISO 14104, *Gears — Surface temper etch inspection after grinding, chemical method*

ISO 18265, *Metallic materials — Conversion of hardness values*

EN 10204, *Metallic products — Types of inspection documents*

EN 10228-1, *Non-destructive testing of steel forgings — Magnetic particle inspection*

EN 10228-3, *Non-destructive testing of steel forgings — Ultrasonic testing of ferritic or martensitic steel forgings*

EN 10308, *Non-destructive testing — Ultrasonic testing of steel bars*

ASTM¹⁾ A388-01, *Standard practice for ultrasonic examination of heavy steel forgings*

ASTM A609-91, *Standard practice for castings, carbon, low alloy and martensitic stainless steel, ultrasonic examination thereof*

ASTM E428-00, *Standard Practice for Fabrication and Control of Steel Reference Blocks Used in Ultrasonic Examination*

ASTM E1444-01, *Standard practice for magnetic particle examination*

3 Terms, definitions and symbols

For the purposes of this document, the terms and definitions given in ISO 1122-1 and the symbols and units given in ISO 6336-1 apply.

ISO and IEC maintain terminological databases for use in standardization at the following addresses:

- IEC Electropedia: available at <http://www.electropedia.org/>
- ISO Online browsing platform: available at <http://www.iso.org/obp>

4 Methods for the determination of allowable stress numbers

4.1 General

Allowable stress numbers should be determined for each material and material condition, preferably by means of gear running tests. Test conditions and component dimensions should equate, as nearly as is practicable, to the operating conditions and dimensions of the gears to be rated.

When evaluating test results or data derived from field service, it is always necessary to ascertain whether or not specific influences on permissible stresses are already included with the evaluated data, e.g. in the case of surface durability, the effects of lubricants, surface roughness and gear geometry; in

1) American Society for Testing and Materials

the case of tooth bending strength, the fillet radius, surface roughness and gear geometry. If a specific influence is included in the permissible stress derived from tests or from field service data, then the relevant influence factor should be set equal to 1,0 in the calculation procedure of ISO 6336-2 and ISO 6336-3.

4.2 Method A

The allowable stress numbers for contact and bending are derived from endurance tests of gears having dimensions closely similar to those of the gears to be rated, under test conditions which are closely similar to the intended operating conditions.

4.3 Method B

The allowable stress numbers for contact and bending were derived from endurance tests of reference test gears under reference test conditions. Tooth-root allowable stress numbers were also derived from pulsator tests. Practical experience should be taken into account. The standard allowable stress numbers specified in [5.2](#) and [5.3](#) are based on such tests and experience.

Three different classes, ME, MQ and ML, are given for the allowable stress numbers. The appropriate choice of class will depend, as described in [Clause 6](#), on the type of production and quality control exercised.

4.4 Method B_r

Contact stress numbers derived from rolling contact fatigue testing have to be used with caution since they tend to overestimate allowable contact stress numbers for gear teeth.

4.5 Method B_k

Allowable stress numbers for bending are derived from the results of testing notched test pieces. Preferably, the ratio of the test piece notch radius to thickness should be similar to that of the fillet radius to the tooth-root chord in the critical section and the surface condition should be similar to that of the tooth root. When evaluating test data, it should be understood that test pieces are usually subjected to repeating bending stress, whereas in the case of a gear tooth, the fillets of the teeth are subjected to combined bending, shear and compressive stresses. Data on the various materials can be obtained from in-house testing, experience or from literature.

4.6 Method B_p

Allowable stress numbers for bending are derived from the results of testing un-notched test pieces. See [4.5](#) for comments on evaluation of test results. In order to take into account the effect of notch sensitivity, it is necessary that actual notch form and notch factors be included in calculations; thus, their results will be influenced by the extreme unreliability of these factors. Data on the various materials can be obtained from known test facilities or from literature.

5 Standard allowable stress numbers — Method B

5.1 Application

The allowable stress numbers shall be derived from [Figures 1](#) to [16](#) or calculated by [Formula 2](#) and [Table 1](#).

The allowable stress numbers shown in [Figures 1](#) to [16](#) are based on the assumption that material composition, heat treatment and inspection methods are appropriately chosen for the size of the gear.

If test values for specific materials are available, they can be used in replacement of the values in [Figures 1](#) to [16](#).

The data furnished in this document are well substantiated by tests and practical experience.

The values are chosen for 1 % probability of damage. Statistical analysis enables adjustment of these values in order to correspond to other probabilities of damage but such adjustments need to be considered very carefully and may require additional specific tests or detailed documentation of the source of the information used to derive the confidence level of the failure probabilities.

When other probabilities of damage (reliability) are desired, the values of $\sigma_{H \text{ lim}}$, $\sigma_{F \text{ lim}}$ and σ_{FE} are adjusted by an appropriate “reliability factor.” When this adjustment is made, a subscript shall be added to indicate the relevant percentage (e.g. $\sigma_{H \text{ lim}10}$ for 10 % probability of damage). For statistical analysis of fatigue testing results, see also Reference [6].

The allowable stress numbers indicated in [Figures 9](#) and [10](#) were derived for effective case depths of about $0,15m_n$ to $0,2m_n$ on finish-machined gears.

The extent to which the level of surface hardness influences the strength of contour-hardened, nitrided, carbo-nitrided and nitro-carburized gears cannot be reliably specified. Other surface-related factors of the material and heat treatment have a much more pronounced influence.

In some cases, the full hardness range is not covered. The ranges covered are indicated by the length of the lines in [Figures 1](#) to [16](#).

For surface hardened steels ([Figures 9](#) to [16](#)), the HV scale was chosen as the reference axis. The HRC scale is included for comparison. To define the relationship between Vickers and Rockwell hardness numbers conversion tables, see ISO 18265.

5.2 Allowable stress number (contact), $\sigma_{H \text{ lim}}$

The allowable stress number, $\sigma_{H \text{ lim}}$, is derived from a contact pressure that may be sustained for a specified number of cycles without the occurrence of progressive pitting. For the beginning of the long-life area refer to the life factor Z_{NT} for the different materials in ISO 6336-2 (for example case carburized, through hardened, and induction-hardened material 5×10^7 , stress cycles are considered to be the beginning for the long life area).

Values of $\sigma_{H \text{ lim}}$ indicated in [Figures 1, 3, 5, 7, 9, 11, 13](#) and [15](#) are appropriate for the reference operating conditions and dimensions of the reference test gears, as follows:²⁾

— Centre distance	$a = 100 \text{ mm}$
— Helix angle	$\beta = 0$ ($Z_\beta = 1$)
— Module	$m = 3 \text{ mm to } 5 \text{ mm}$ ($Z_x = 1$)
— Mean peak-to-valley roughness of the tooth flanks	$Rz = 3 \text{ }\mu\text{m}$ ($Z_R = 1$)
— Tangential velocity	$v = 10 \text{ m/s}$ ($Z_v = 1$)
— Lubricant viscosity	$\nu_{50} = 100 \text{ mm}^2/\text{s}$ ($Z_L = 1$)
— Mating gears of the same material	($Z_W = 1$)
— Gearing accuracy grades	4 to 6 according to ISO 1328-1
— Face width	$b = 10 \text{ mm to } 20 \text{ mm}$
— Load influence factors	$K_A = K_v = K_{H\beta} = K_{H\alpha} = 1$

2) Data obtained under different conditions of testing were adjusted to be consistent with reference conditions. It is important to note $\sigma_{H \text{ lim}}$ is not the contact pressure under continuous load, but rather the upper limit of the contact pressure derived in accordance with ISO 6336-2, which can be sustained without progressive pitting damage, for a specified number of load cycles.

Test gears were deemed to have failed by pitting when the following conditions were met: when 2 % of the total working flank area of through hardened gears, or when 0,5 % of the total working flank area of surface hardened gears, or 4 % of the working flank area of a single tooth, is damaged by pitting. The percentages refer to test evaluations; they are not intended as limits for product gears.

5.3 Bending stress number values for $\sigma_{F \text{ lim}}$ and σ_{FE}

5.3.1 Nominal stress numbers (bending), $\sigma_{F \text{ lim}}$

The nominal stress number (bending), $\sigma_{F \text{ lim}}$, was determined by testing reference test gears (see ISO 6336-3). It is the bending stress limit value relevant to the influences of the material, the heat treatment and the surface roughness of the test gear root fillets.

5.3.2 Allowable stress number (bending), σ_{FE}

The allowable stress number for bending, σ_{FE} (for the definition of σ_{FE} , see ISO 6336-3), is the basic bending strength of the un-notched test piece, under the assumption that the material condition (including heat treatment) is fully elastic:

$$\sigma_{FE} = \sigma_{F \text{ lim}} \cdot Y_{ST} \quad (1)$$

For the reference test gear, the stress correction factor $Y_{ST} = 2,0$. For all materials covered in this document, 3×10^6 stress cycles are considered to be the beginning of the long-life strength range (see life factor Y_{NT} in ISO 6336-3).

Values of $\sigma_{F \text{ lim}}$ and σ_{FE} indicated in [Figures 2, 4, 6, 8, 10, 12, 14](#) and [16](#) are appropriate for the reference operating conditions and dimensions of the reference test gears, as shown below (see [5.2](#)):

— Helix angle	$\beta = 0$ ($Y_{\beta} = 1$)
— Module	$m = 3 \text{ mm to } 5 \text{ mm}$ ($Y_X = 1$)
— Stress correction factor	$Y_{ST} = 2,0$
— Notch parameter	$q_{ST} = 2,5$ ($Y_{\delta \text{ rel-T}} = 1$)
— Mean peak-to-valley roughness of the tooth fillets	$Rz = 10 \text{ }\mu\text{m}$ ($Y_{R \text{ rel-T}} = 1$)
— Gearing accuracy grades	4 to 7 according to ISO 1328-1
— Basic rack	according to ISO 53
— Face width	$b = 10 \text{ mm to } 50 \text{ mm}$
— Load factors	$K_A = K_V = K_{F\beta} = K_{F\alpha} = 1$

5.3.3 Reversed bending

The allowable stress numbers indicated in [Figures 2, 4, 6, 8, 10, 12, 14](#) and [16](#) are appropriate for repeated, unidirectional, tooth loading. When reversals of full load occur, a reduced value of σ_{FE} is required. In the most severe case (e.g. an idler gear where full load reversal occurs each load cycle), the values $\sigma_{F \text{ lim}}$ and σ_{FE} should be reduced to 0,7 times the unidirectional value. If the number of load reversals is less frequent than this, a different factor, depending on the number of reversals expected during the gear lifetime, can be chosen. For guidance on this, see ISO 6336-3:2006, Annex B.

5.4 Graphs for $\sigma_{H \text{ lim}}$ and $\sigma_{F \text{ lim}}$ and σ_{FE}

Allowable stress numbers for hardness values which exceed the minimum and maximum hardness values in [Figures 1 to 16](#) are subject to agreement between manufacturer and purchaser on the basis of previous experience.

5.5 Calculation of $\sigma_{H \text{ lim}}$ and $\sigma_{F \text{ lim}}$

The allowable stress numbers, $\sigma_{H \text{ lim}}$, and the nominal stress numbers, $\sigma_{F \text{ lim}}$, based on [Figures 1 to 16](#), can be calculated by the following equation:

$$\left. \begin{matrix} \sigma_{H \text{ lim}} \\ \sigma_{F \text{ lim}} \end{matrix} \right\} = A \cdot x + B \quad (2)$$

where

x is the surface hardness HBW or HV on the finished functional surface;

A, B are constants (see [Table 1](#)).

The hardness ranges are restricted by the minimum and maximum hardness values given in [Table 1](#). It shall be used together with [Figures 1 to 16](#).

Table 1 — Calculation of $\sigma_{H \text{ lim}}$ and $\sigma_{F \text{ lim}}$

No.	Material	Stress	Type	Abbreviation	Fig.	Quality	A	B	Hardness	Min. hardness	Max. hardness				
1	Normal-ized low carbon steels/cast steels ^a	Contact	Wrought normal-ized low carbon steels	St	1 a)	ML/MQ	1,000	190	HBW	110	210				
2						ME	1,520	250		110	210				
3			Cast steels	St. (cast)	1 b)	ML/MQ	0,986	131	HBW	140	210				
4							ME	1,143	237		140	210			
5		Bending	Wrought normal-ized low carbon steels	St	2 a)	ML/MQ	0,455	69	HBW	110	210				
6						ME	0,386	147		110	210				
7						Cast steels	St (cast)	2 b)		ML/MQ	0,313	62	HBW	140	210
8											ME	0,254	137		140

Table 1 (continued)

No.	Material	Stress	Type	Abbrevia- tion	Fig.	Quality	A	B	Hard- ness	Min. hard- ness	Max. hard- ness				
9	Cast iron materials	Contact	Black malleable cast iron	GTS (perl.)	3 a)	ML/MQ	1,371	143	HBW	135	250				
10						ME	1,333	267		175	250				
11				GGG	3 b)	ML/MQ	1,434	211	HBW	175	300				
12		ME	1,500			250	200	300							
13		GG	3 c)			ML/MQ	1,033	132		HBW	150	240			
14				ME	1,465	122	175	275							
15		Bending	Black malleable cast iron	GTS (perl.)	4 a)	ML/MQ	0,345	77	HBW	135	250				
16						ME	0,403	128		175	250				
17						GGG	4 b)	ML/MQ		0,350	119	HBW	175	300	
18								ME		0,380	134		200	300	
19	GG					4 c)	ML/MQ	0,256		8	HBW	150	240		
20		ME	0,200	53	175		275								
21	Through hardened wrought steels ^b	Contact	Carbon steels	V	5	ML	0,963	283	HV	135	210				
22						MQ	0,925	360		135	210				
23						ME	0,838	432		135	210				
24						Alloy steels	V	5		ML	1,313	188	HV	200	360
25										MQ	1,313	373		200	360
26										ME	2,213	260		200	390
27		Bending	Carbon steels	V	6	ML	0,250	108	HV	115	215				
28						MQ	0,240	163		115	215				
29						ME	0,283	202		115	215				
30			Alloy steels	V	6	ML	0,423	104	HV	200	360				
31						MQ	0,425	187		200	360				
32						ME	0,358	231		200	390				
33	Through hardened cast steels	Contact	Carbon steels	V	7	ML/MQ	0,831	300	HV	130	215				
34						(cast)	ME	0,951		345	130	215			
35						Alloy steels	V	7		ML/MQ	1,276	298	HV	200	360
36		(cast)	ME	1,350	356				200	360					
37		Bending	Carbon steels	V	8	ML/MQ	0,224	117	HV	130	215				
38						(cast)	ME	0,286		167	130	215			
39						Alloy steels	V	8		ML/MQ	0,364	161	HV	200	360
40		(cast)	ME	0,356	186				200	360					

Table 1 — (continued)

No.	Material	Stress	Type	Abbreviation	Fig.	Quality	A	B	Hardness	Min. hardness	Max. hardness
41	Case hardened wrought steels ^c	Contact		Eh	9	ML	0,000	1 300	HV	600	800
42						MQ	0,000	1 500		660	800
43						ME	0,000	1 650		660	800
44		Bending	Core hardness: ≥25 HRC, lower	Eh	10	ML	0,000	312	HV	600	800
45						MQ	0,000	425		660	800
46							0,000	461		660	800
47							0,000	500		660	800
48						ME	0,000	525		660	800
49	Flame- or induction-hardened wrought and cast steels	Contact		IF	11	ML	0,740	602	HV	485	615
50						MQ	0,541	882		500	615
51						ME	0,505	1 013		500	615
52		Bending		IF	12	ML	0,305	76	HV	485	615
53						MQ	0,138	290		500	570
54							0,000	369		570	615
55						ME	0,271	237		500	615
56	Nitrided wrought steels/nitriding steels ^d / through hardening steels ^b nitride	Contact	Nitriding steels	NT (nitr.)	13 a)	ML	0,000	1 125	HV	650	900
57						MQ	0,000	1 250		650	900
58						ME	0,000	1 450		650	900
59			Through hardening steels	NV (nitr.)	13 b)	ML	0,000	788	HV	450	650
60						MQ	0,000	998		450	650
61						ME	0,000	1 217		450	650
62		Bending	Nitriding steels	NT (nitr.)	14 a)	ML	0,000	270	HV	650	900
63						MQ	0,000	420		650	900
64						ME	0,000	468		650	900
65			Through hardening steels	NV (nitr.)	14 b)	ML	0,000	258	HV	450	650
66						MQ	0,000	363		450	650
67	ME					0,000	432	450		650	
68	Wrought steels nitro-carburized ^e	Contact	Through hardening steels	NV (nitro-car.)	15	ML	0,000	650	HV	300	650
69						MQ/ME	1,167	425		300	450
70							0,000	950		450	650
71		Bending	Through hardening steels	NV (nitro-car.)	16	ML	0,000	224	HV	300	650
72						MQ/ME	0,653	94		300	450
73							0,000	388		450	650

NOTE Table 1 shall be used together with footnotes from the corresponding Figures 1 to 16.


a In accordance with ISO 4948-2.

b In accordance with ISO 683-1 and ISO 683-2.


c In accordance with ISO 683-3.

d In accordance with ISO 683-5.

e In accordance with ISO 683-1, ISO 683-2, ISO 683-3 or ISO 683-5.

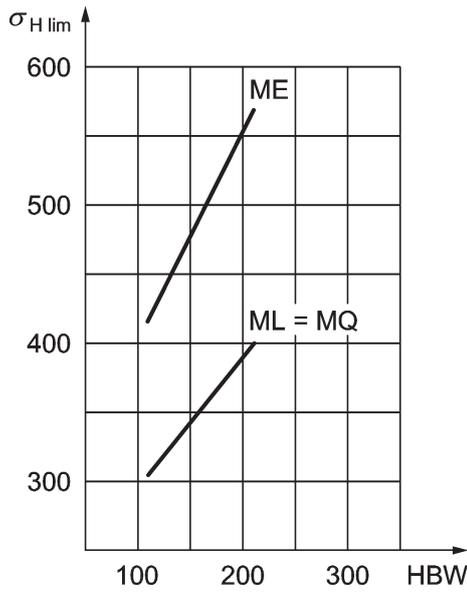

a) Wrought normalized low carbon steels

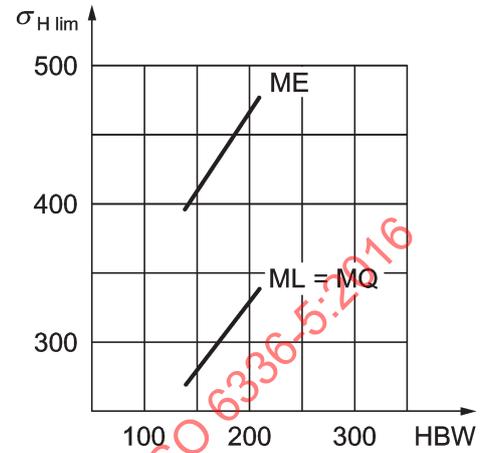


b) Cast steels


Key

$\sigma_{H \text{ lim}}$ allowable stress number (contact), N/mm²
 HBW surface hardness

Figure 1 — Allowable stress numbers (contact) for wrought normalized low carbon steels and cast steels (attention is drawn to the quality requirements of 6.2)

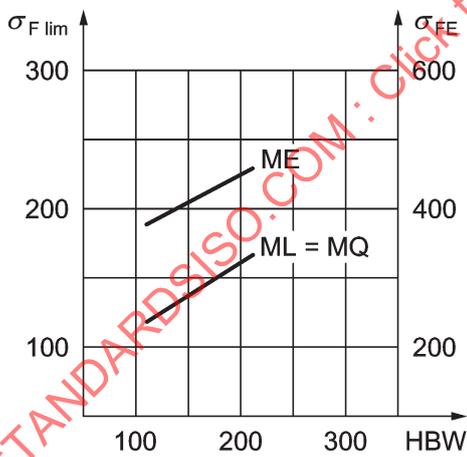

a) Wrought normalized low carbon steels

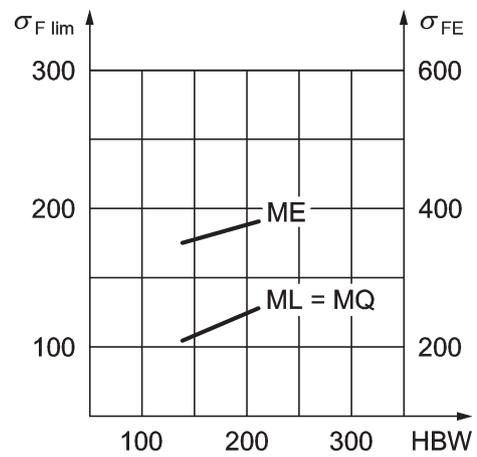


b) Cast steels


Key

$\sigma_{F \text{ lim}}$ nominal stress number (bending), N/mm²
 σ_{FE} allowable stress number (bending), N/mm²
 HBW surface hardness


Figure 2 — Nominal and allowable stress numbers (bending) for wrought normalized low carbon steels and cast steels (attention is drawn to the quality requirements of 6.2)

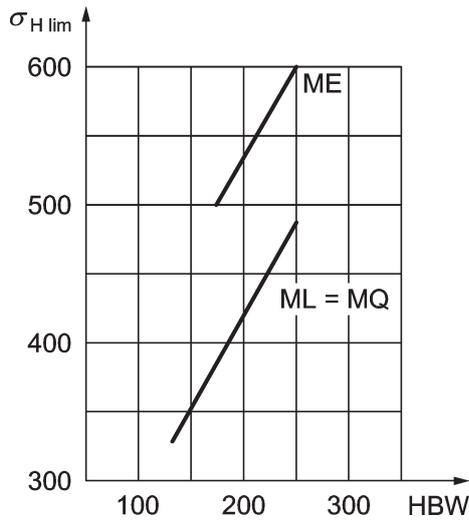

a) Black malleable cast iron (see 6.3)

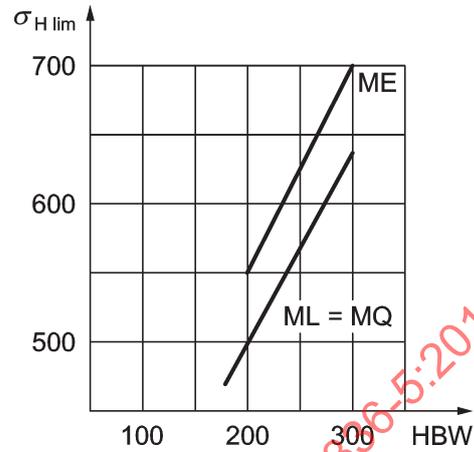

b) Nodular cast iron (see Table 2)

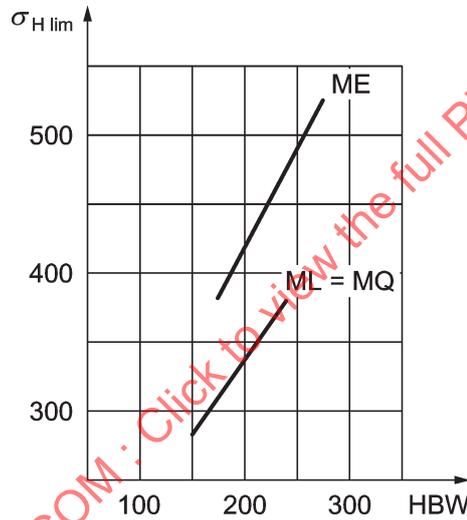

c) Grey cast iron (see Table 2)



Key

$\sigma_{H \text{ lim}}$ allowable stress number (contact), N/mm²

HBW surface hardness

NOTE Brinell hardness < 180 HBW indicates the presence of a high proportion of ferrite in the structure. For gears, this condition is not recommended.

Figure 3 — Cast iron materials — Allowable stress numbers (contact) for cast iron materials
(attention is drawn to the quality requirements of 6.3 and Table 2)

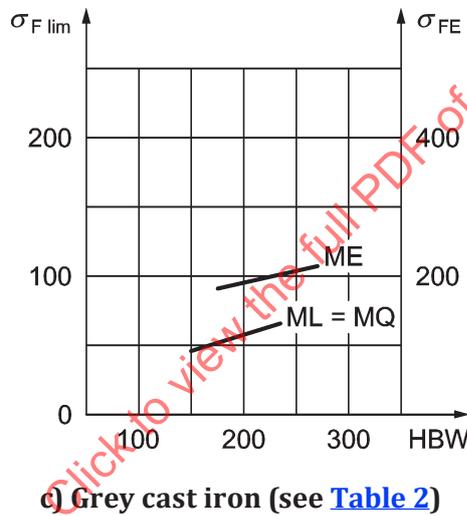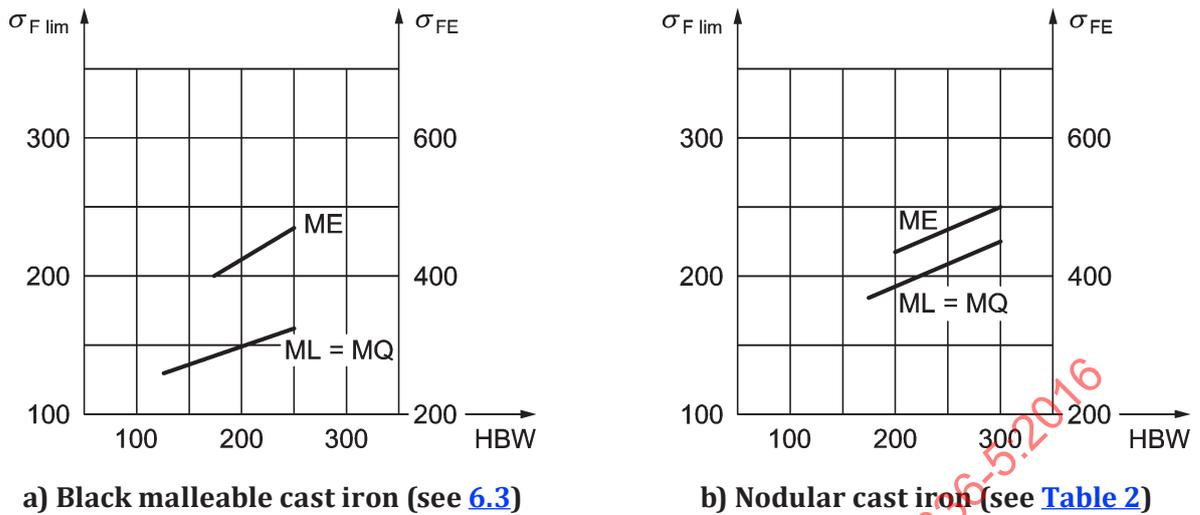


Key

- $\sigma_{F\ lim}$ nominal stress number (bending), N/mm²
- σ_{FE} allowable stress number (bending), N/mm²
- HBW surface hardness

NOTE Brinell hardness < 180 HBW indicates the presence of a high proportion of ferrite in the structure. For gears, this condition is not recommended.

Figure 4 — Cast iron materials — Nominal and allowable stress numbers (bending) for cast iron materials (attention is drawn to the quality requirements of 6.3 and Table 2)

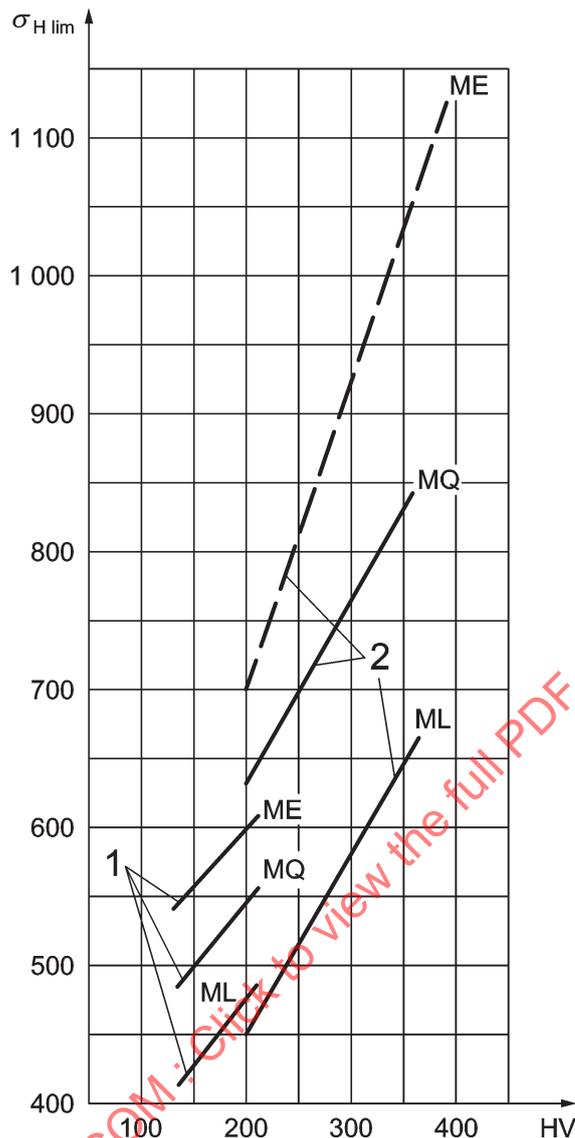

Key

$\sigma_{H \text{ lim}}$ allowable stress number (contact), N/mm²

HV surface hardness

1 carbon steels


2 alloy steels

NOTE 1 Nominal carbon content $\geq 0,20 \%$.

NOTE 2 The alloy steel MX line from the first edition of ISO 6336-5 was replaced (in 2003 edition) by the ME line.

NOTE 3 The use of the ME line stress numbers for alloy steels relies heavily on the experience of the manufacturer. This line is not supported by recently made (2011) standardized test. Results obtained without pitting stabilization.

Figure 5 — Allowable stress numbers (contact) for through hardened wrought steels (attention is drawn to the quality requirements of [Table 3](#))

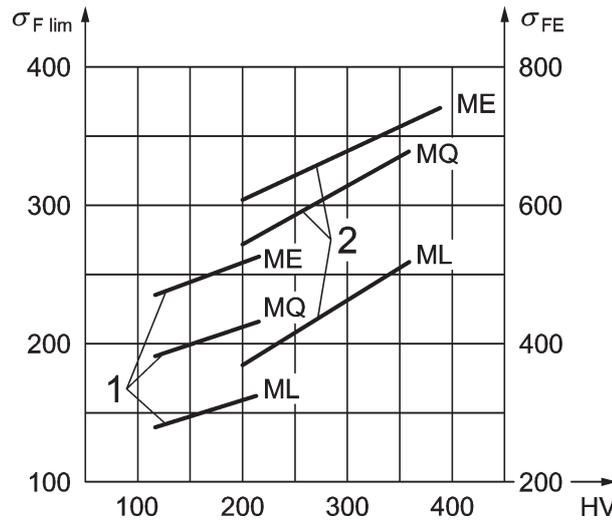


Key

- $\sigma_{F \text{ lim}}$ nominal stress number (bending), N/mm²
- σ_{FE} allowable stress number (bending), N/mm²
- HV surface hardness
- 1 carbon steels
- 2 alloy steels

NOTE Nominal carbon content $\geq 0,20$ %.

Figure 6 — Nominal and allowable stress numbers (bending) for through hardened wrought steels (attention is drawn to the quality requirements of [Table 3](#))

STANDARDSISO.COM : Click to view the full PDF of ISO 6336-5:2016

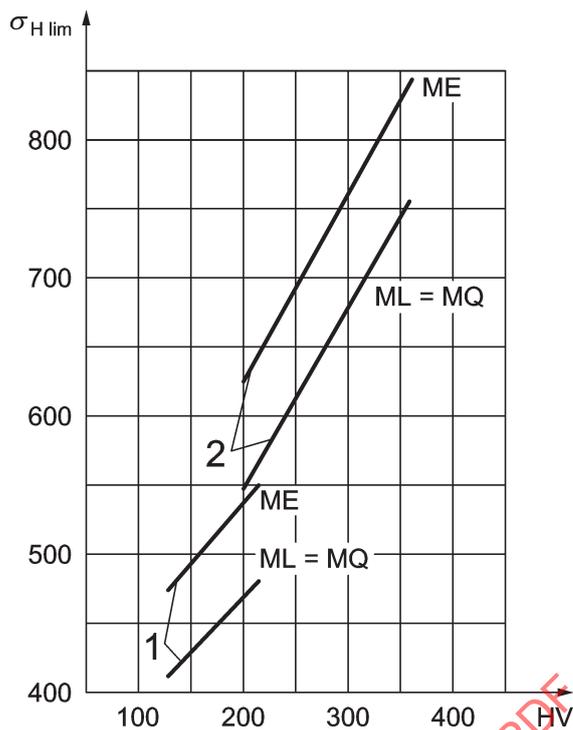

Key


$\sigma_{H \text{ lim}}$ allowable stress number (contact), N/mm²

HV surface hardness

1 carbon steels


2 alloy steels

Figure 7 — Allowable stress numbers (contact) for through hardened cast steels (attention is drawn to the quality requirements of [Table 4](#))

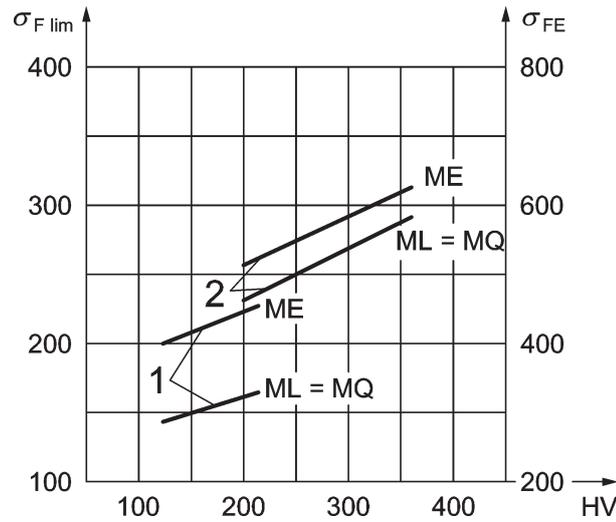**Key**

- $\sigma_{F \text{ lim}}$ nominal stress number (bending), N/mm²
 σ_{FE} allowable stress number (bending), N/mm²
 HV surface hardness
 1 carbon steels
 2 alloy steels

Figure 8 — Nominal and allowable stress numbers (bending) for through hardened cast steels
 (attention is drawn to the quality requirements of [Table 4](#))

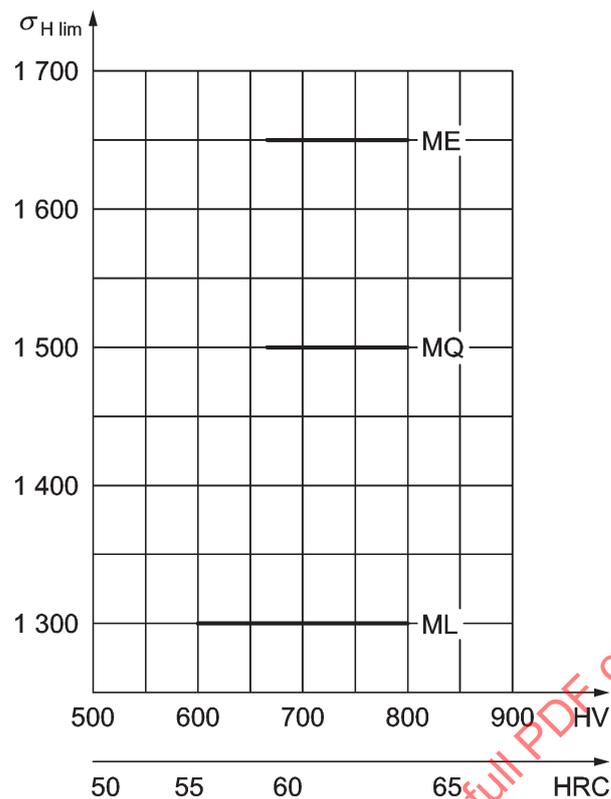

Key


$\sigma_{H \text{ lim}}$ allowable stress number (contact), N/mm²

HRC surface hardness

HV surface hardness

NOTE Adequate case depth required (see 5.6.1).

Figure 9 — Allowable stress numbers (contact) for case hardened wrought steels (attention is drawn to the quality requirements of Table 5)

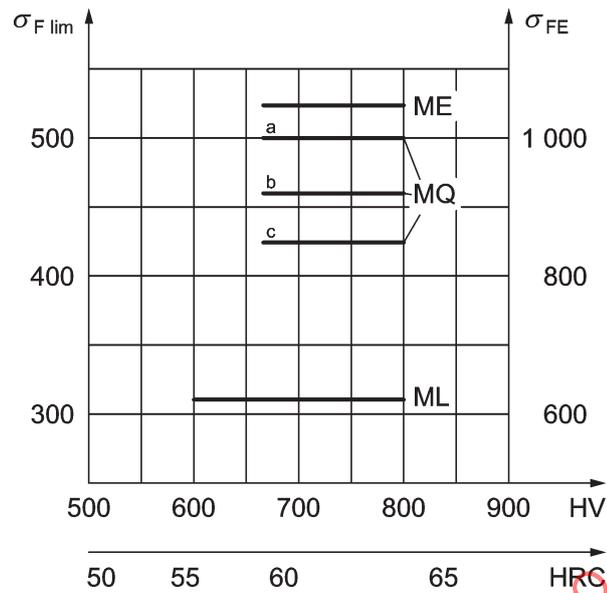

Key

$\sigma_{F \text{ lim}}$ nominal stress number (bending), N/mm²

σ_{FE} allowable stress number (bending), N/mm²

HRC surface hardness

HV surface hardness

a Core hardness ≥ 30 HRC.


b Core hardness ≥ 25 HRC Jominy hardenability at $J = 12$ mm ≥ 28 HRC.

c Core hardness ≥ 25 HRC Jominy hardenability at $J = 12$ mm < 28 HRC.

NOTE 1 Adequate case depth required (see 5.6.2).

NOTE 2 See 6.6.

Figure 10 — Nominal and allowable stress numbers (bending) for case hardened wrought steels (attention is drawn to the quality requirements of Table 5)

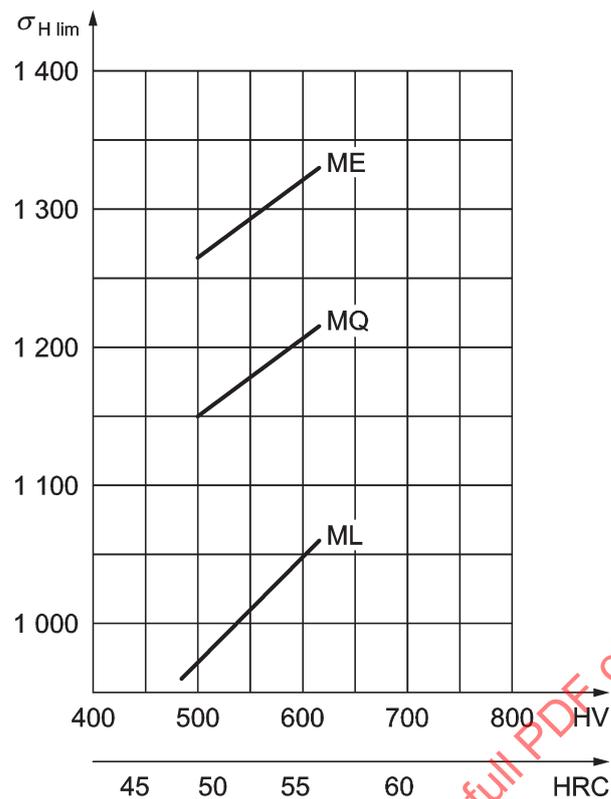

Key


$\sigma_{H \text{ lim}}$ allowable stress number (contact), N/mm²

HRC surface hardness

HV surface hardness

NOTE Adequate surface hardening depth required. Case depth to be determined for each part by experience.

Figure 11 — Allowable stress numbers (contact) for flame- or induction-hardened wrought and cast steels (attention is drawn to the quality requirements of [Table 6](#))

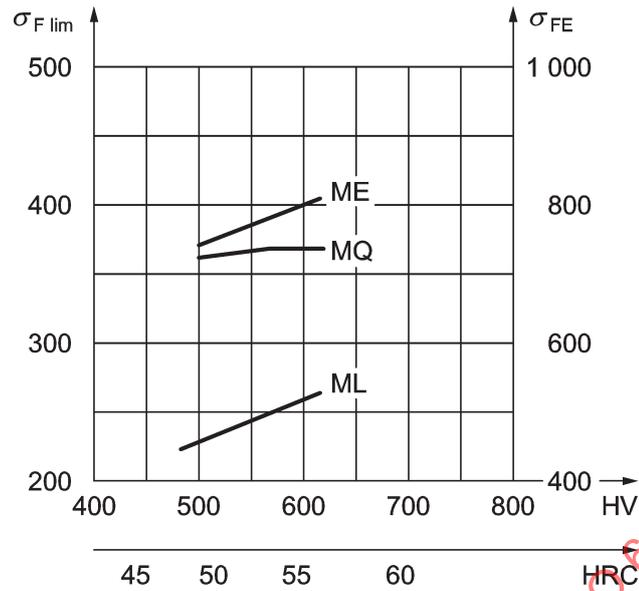


Key


- $\sigma_{F\ lim}$ nominal stress number (bending), N/mm²
- σ_{FE} allowable stress number (bending), N/mm²
- HRC surface hardness
- HV surface hardness

NOTE Hardened fillets only. Values for unhardened fillets are not provided. Adequate surface hardening depth required.

Figure 12 — Nominal and allowable stress numbers (bending) for flame- or induction-hardened wrought and cast steels (attention is drawn to the quality requirements of [Table 6](#))

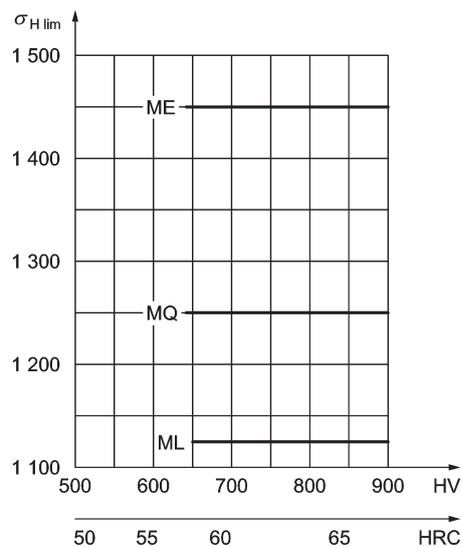

a) Nitriding steels: hardened, tempered and gas nitrided

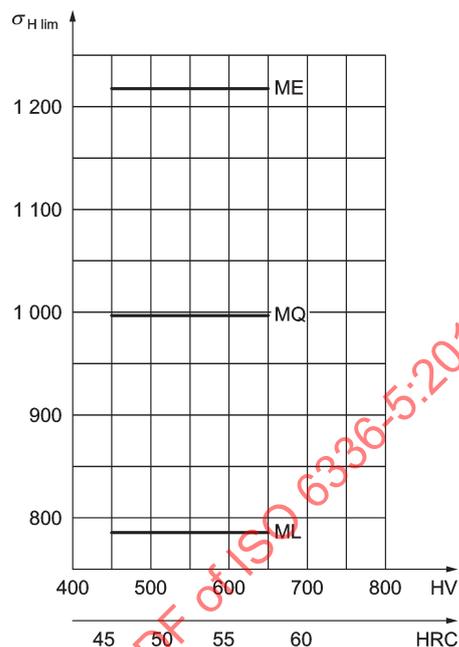

b) Through hardening steels: hardened, tempered and gas nitrided

Key


σ_{H lim} allowable stress number (contact), N/mm²

HRC surface hardness


HV surface hardness

NOTE Adequate nitriding hardening depth required (see 5.6.3).

Figure 13 — Allowable stress numbers (contact) for nitrided wrought steels/nitriding steels/through hardening steels nitrided (attention is drawn to the quality requirements of [Table 7](#))

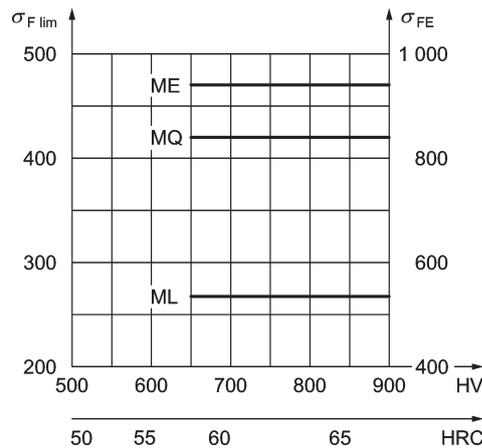

a) Nitriding steels: hardened, tempered and gas nitrided

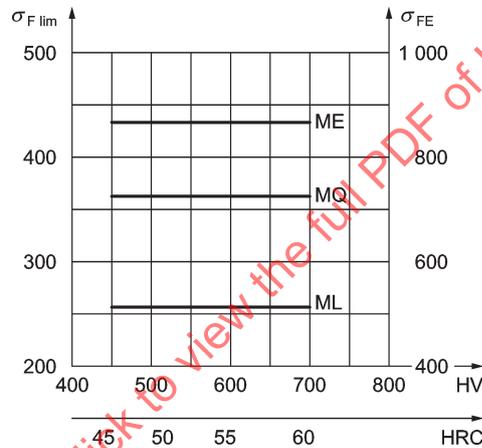

b) Through hardening steels: hardened, tempered and gas nitrided

Key


- σ_{F lim} nominal stress number (bending), N/mm²
 σ_{FE} allowable stress number (bending), N/mm²
 HRC surface hardness
 HV surface hardness

NOTE 1 Only applicable for Figure a): for flank hardness > 750 HV₁, the allowable stress numbers can be reduced by embrittlement when the white layer thickness exceeds 10 μm. Adequate nitriding hardening depth required, see 5.6.3.

NOTE 2 Only applicable for Figure a): aluminium containing nitriding steels Nitralloy N, Nitralloy 135 and similar are limited to grades ML and MQ. Tooth root stress numbers σ_{F lim} for these materials are limited to 250 N/mm² for ML and 340 N/mm² for MQ.

NOTE 3 Only applicable for Figure b): adequate nitriding hardening depth required, see 5.6.3.

Figure 14 — Nominal and allowable stress numbers (bending) for nitrided wrought steels/nitriding steels/through hardening steels nitrided (attention is drawn to the quality requirements of Table 7)

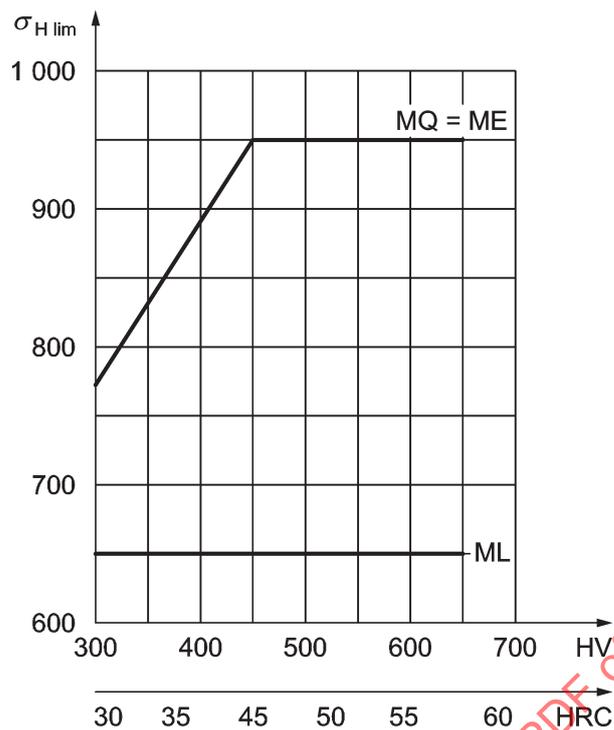

Key


$\sigma_{H \text{ lim}}$ allowable stress number (contact), N/mm²

HRC surface hardness

HV surface hardness

NOTE Adequate nitriding hardening depth required (see 5.6.3).

Figure 15 — Allowable stress numbers (contact) for wrought steels nitrocarburized (attention is drawn to the quality requirements of [Table 8](#))

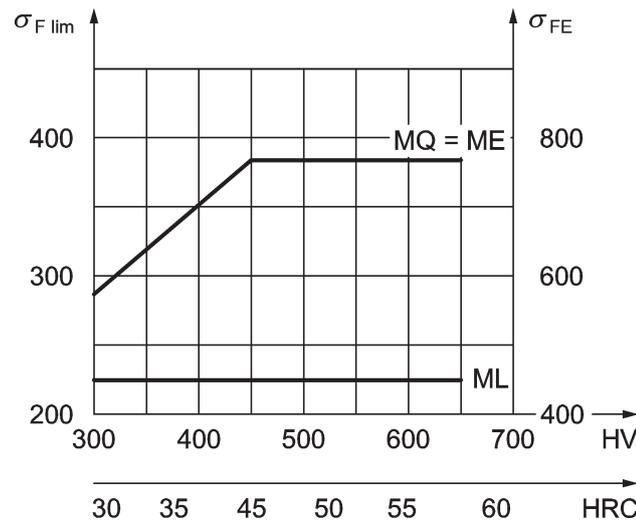**Key**

- $\sigma_{F \text{ lim}}$ nominal stress number (bending), N/mm²
 σ_{FE} allowable stress number (bending), N/mm²
 HRC surface hardness
 HV surface hardness

NOTE Adequate nitriding hardening depth required, see 5.6.3.

Figure 16 — Nominal and allowable stress numbers (bending) for wrought steels nitrocarburized (attention is drawn to the quality requirements of Table 8)

5.6 Hardening depth of surface hardened gears in finished condition

5.6.1 General


Surface hardened gear teeth require adequate hardening depth to resist the stress condition in the loaded tooth. Minimum and maximum values of hardening depth shall be shown on the drawing. When specifying minimum hardening depth, note that the “optimum” values for bending and surface load capacity are calculated separately and are not necessarily the same. The specified maximum hardening depths should not be exceeded, because to do so would increase risk of embrittlement of the tooth tips and lower allowable stress numbers.³⁾

5.6.2 Case depth of carburized and hardened gears⁴⁾

- a) **Recommended values of case depth to achieve the specified strength values for pitting** ($CHD_{H \text{ opt}}$) are shown in Figure 17. $CHD_{H \text{ opt}}$ is the optimum effective case depth relating to permissible contact stress for long life at the reference circle after tooth finishing:

3) The data of 5.6 may not apply to bevel gears.

4) Definition of case depth according to Table 5, item 9.

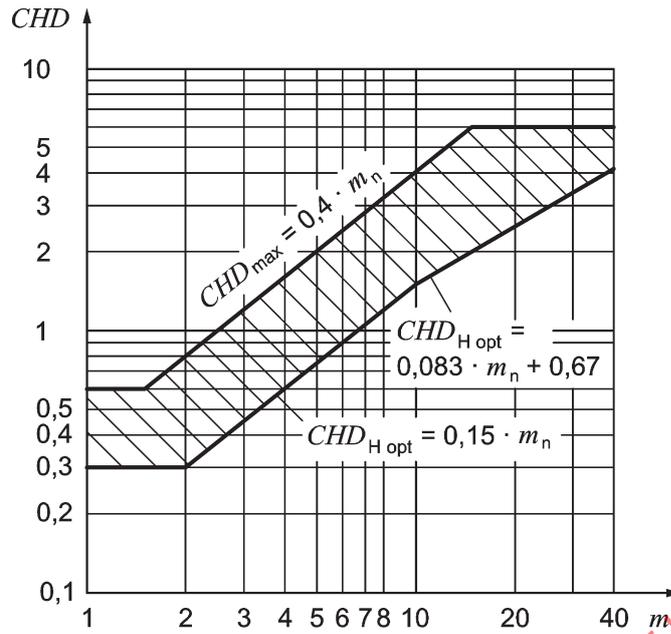

Key

CHD case hardening depth, mm
 m_n Normal module, mm

Figure 17 — Recommended values of optimum case depth $CHD_{H\ opt}$ regarding surface load capacity and maximum case depth CHD_{max} regarding bending and surface load capacity

b) **Recommended values of case depth to achieve the specified strength values regarding tooth root bending ($CHD_{F\ opt}$):** $CHD_{F\ opt}$ is the optimum effective case depth relating to permissible bending stress for long life at the root fillet on a normal to the 30° tangent (external gears), 60° tangent (internal gears) after tooth finishing:

$$0,1m_n \leq CHD_{F\ opt} \leq 0,2m_n \tag{3}$$

c) **Recommended values of case depth regarding case-crushing (CHD_c):** CHD_c is the minimum effective case depth at the reference circle after tooth finishing based on the depth of maximum shear stress from contact load.

NOTE Regarding case-crushing, at present there is no standardized calculation method available.

A guide to avoid case crushing the CHD_c is given by the following formula. Note that this equation has not been validated for contact stress numbers $\sigma_H > 1400\ N/mm^2$.

$$CHD_c = \frac{\sigma_H \cdot d_{w1} \cdot \sin\alpha_{wt}}{U_H \cdot \cos\beta_b} \cdot \frac{z_2}{z_1 + z_2} \tag{4}$$

with


$U_H = 66\ 000\ N/mm^2$ for quality grades MQ/ME;

$U_H = 44\ 000\ N/mm^2$ for quality grades ML.

d) **Recommended limits of minimum and maximum effective case depth:** $CHD_{min/max}$ is the effective case depth at the reference circle after tooth finishing (values also shown in [Figure 17](#)): $CHD_{min} \geq 0,3\ mm$ and $CHD_{max} \leq 0,4 \cdot m_n (\leq 6\ mm)$.

5.6.3 Nitriding hardening depth of nitrided gears⁵⁾

a) **Recommended values of effective nitriding hardening depth (NHD):** See [Figure 18](#).

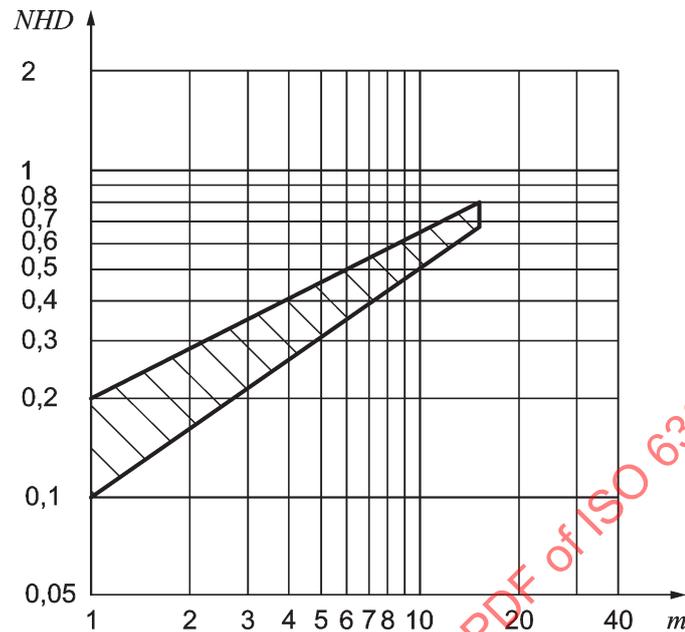

Key

NHD nitriding hardening depth, mm

m module, mm

NOTE Steel grade should be suitable for the recommended NHD which should not exceed a maximum value of 0,8 mm.

Figure 18 — Recommended values of nitriding hardening depth, NHD

b) **Recommended values of nitriding hardening depth regarding case-crushing (NHD_c):** NHD_c is the minimum effective nitriding hardening depth for nitrided gears, and is based on the depth of maximum shear stress from contact load. If the value of NHD_c is less than the value for nitriding hardening depth NHD from [Figure 18](#), then the minimum value from [Figure 18](#) should be used.

NOTE Regarding case-crushing, at present, there is no standardized calculation method available.


$$NHD_c = \frac{U_c \cdot \sigma_H \cdot d_{w1} \cdot \sin \alpha_{wt}}{1,14 \cdot 10^5 \cdot \cos \beta_b} \cdot \frac{z_2}{z_1 + z_2} \quad (5)$$

where U_c is the core hardness coefficient:

$$U_c = a + b \cdot \sigma_H + c \cdot \sigma_H^2 + d \cdot \sigma_H^3, \quad (6)$$

see [Figure 19](#).

5) Definition of nitriding hardening depth according to [Table 7](#), item 7.

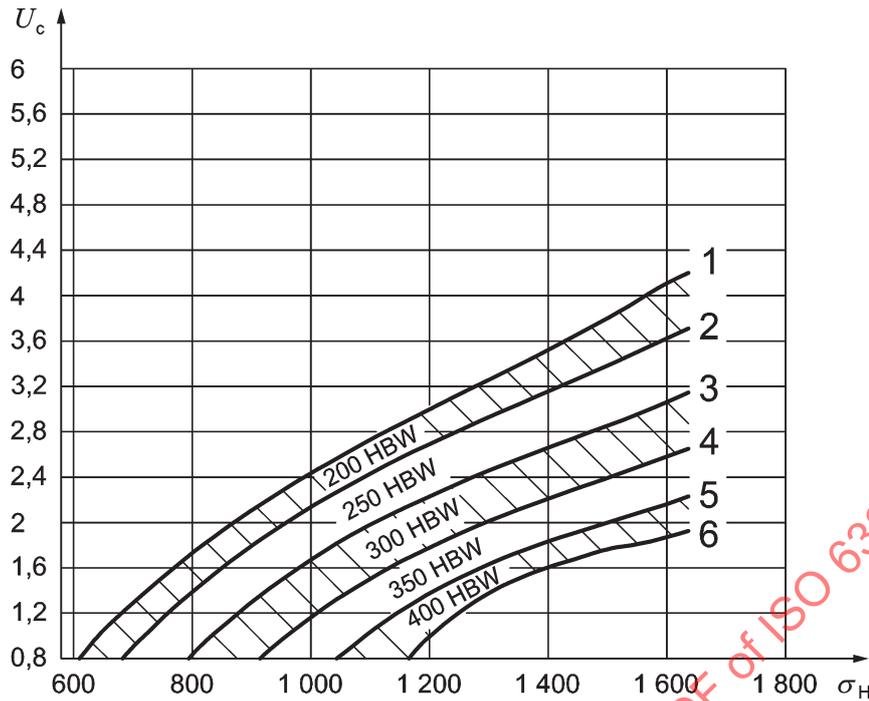

Key

- U_c core hardness coefficient
- σ_H contact stress, N/mm²
- 1 to 6 curve numbers, see [Table B.1](#) for values of coefficients a, b, c and d

NOTE Use upper portion of core hardness band (which yields heavier case depths) for general design purpose and lower portion for high-quality material.

Figure 19 — Core hardness coefficient for nitrided gearing, U_c

6 Requirements for material quality and heat treatment

6.1 General aspects

The three material quality grades ML, MQ and ME stand in relationship to [Figures 1 to 16](#), which means that they refer to the allowable stress numbers determined using Method B.⁶⁾ See [4.3](#), [5.2](#) and [5.3](#).

- ML stands for modest demands on the material quality and on the material heat treatment process during gear manufacture.
- MQ stands for requirements that can be met by experienced manufacturers at moderate cost.
- ME represents requirements that must be realized when a high degree of operating reliability is required.

NOTE This document does not allow extrapolation of the allowable stress lines.

Frequently, special quality material such as Vacuum Induction Melted/Vacuum Arc Remelted (VIM/VAR) is used to achieve high reliability or load-bearing capability.

Gear wheels which are manufactured by fabricating rims to centers using conventional welding procedures should be stress relieved following the fabrication process.

6) The material quality grade MX, which existed in the first edition (1995) of this document, was replaced with the ME line in 2003.

The provisions given in 6.2 to 6.4 have been confirmed by practical experience and may be used as guidelines. All requirements for a material grade shall be met when the allowable stress numbers are to be applied.⁷⁾ Where not specified in the tables, this can be accomplished by specifically certifying each requirement where necessary, or by establishing practices and procedures to obtain the requirements on a production basis. It is not the intent of this document that all requirements for quality grades are to be certified, but that practices and procedures are to be established for their compliance on a production basis. Intermediate values are not classified since the effect of deviations from the quality standards cannot be evaluated easily. These requirements refer to those portions of the gear material where the teeth will be located and at a distance below the finished tip diameter as defined in the applicable Tables 2 to 7. However, depending on their experience, manufacturers may adopt methods or values other than those listed here. The manufacturer and the customer should agree on the details, particularly for large gears. Also, the gear manufacturer and purchaser shall mutually agree on acceptance or corrections of non-confirming parts which do not fulfil all the requirements.

6.2 Normalized low carbon or cast steel, plain carbon, unalloyed steels (see Figures 1 and 2)

Since the composition of these is not specified and the melting method is often unknown, the MQ line was positioned at the lower limit (ML). Normalized low carbon steels are used only for lightly loaded gears and secondary applications. If high quality of steel production is achieved and when justified by experience, the levels of ME may be used.

6.3 Black malleable cast iron [see Figures 3 a) and 4 a)]

High quality can be achieved through controlled heat treatment. However, since it is ordinarily used for small, lightly loaded gears, the MQ line was positioned at the lower limit (ML) to be on the safe side. When justified by experience, the levels of ME may be used.

6.4 Other materials [see Figures 3 b), 3 c), 4 b), 4 c), 5 to 16]

Material quality and heat treatment for other materials shall be in accordance with Tables 2 to 8.

7) The material chosen is either that quoted in the relevant grade according to ISO 683-1, ISO 683-2, ISO 683-3, ISO 683-4 or ISO 683-5 (recommended) or an appropriate National or International Standard.

Table 2 — Cast iron materials (grey and nodular — spheroidal — graphite cast iron)

Item	Requirement	Grey cast iron (see Figures 3 and 4)		Nodular cast iron (see Figures 3 and 4)	
		ML MQ	ME	ML MQ	ME
1	Chemical analysis	Not verified	100 % verified Foundry certificate	Not verified	100 % verified Foundry certificate
2	Melting practice	No specification	Electric furnace or equivalent	No specification	Electric furnace or equivalent
3	Mechanical properties evaluation	Only HBW	R_m Specific test report on a separate test piece from the same cast	Only HBW	$\sigma_s (\sigma_{0,2}) \sigma_b \delta_s \psi$ Specific test report per ISO 10474 of physical testing on a representative sample which is an integral part on each test piece, heat treated with the parts before being cut. Verification of HBW on gear teeth or as near as practicable.
4	Structure: graphite form	Specified but not verified	Limited	Not verified	Limited
	Basic structure ^a	No specification (alloyed grey cast iron, maximum ferrite: 5 %)	Maximum ferrite: 5 %	No specification	
5	Tests for inner separations (cracks). Acceptability agreed between customer and supplier.	Not tested	Tested (pores, cracks, blow-holes), limited defects	Not tested	Tested (pores, cracks, blow-holes), limited defects
6	Stress relief	Not required	Recommended: 2 h at 500 °C to 530 °C. Alloyed, grey cast iron 2 h at 530 °C to 560 °C	Not required	Recommended: 2 h at 500 °C to 560 °C
7	Repair welding	Not permitted near tooth region; elsewhere, permissible only with approved processes		Not permitted near tooth region; elsewhere, permissible only with approved processes	
8	Surface crack detection	Not tested	Visual inspection required, dye penetrant test by agreement between purchaser and manufacturer.	Not tested	Cracks not permitted. 100 % magnetic particle, fluorescent magnetic particle penetrant or dye penetrant inspection. Statistical sampling permitted for large production lots.

^a Can be checked on a representative sample from the same cast.

Table 3 (continued)

Item	Requirement	ML	MQ	ME ^a
5.2	Surface cracks detection (in finished condition, before any shot peening treatment)	Cracks are not permitted. Ground gears should be inspected for surface cracks. Inspection by ASTM E1444 including fluorescent, magnetic particle or by ASTM E1417 for dye penetrant inspection.		Cracks are not permitted. Ground gears shall be inspected for surface cracks. Inspection by ASTM E1444, including fluorescent, magnetic particle or by ASTM E1417 for dye penetrant inspection. Preferred method of inspection is fluorescent, magnetic particle inspection.
6	Extent of forging reduction	No specification	Area reduction ratio ^d : At least 3:1 for ingot cast and at least 5:1 for continuous cast. The minimum reduction ratio shall be achieved by hot working processes which ensure through-section working.	
7	Microstructure	No specification	No specification. For material strengths greater than 800 N/mm ² (240 HBW) the gear should be quenched and tempered.	Minimum temper temperature 480 °C. Root hardness shall meet drawing requirements. Microstructure in gear rim predominantly tempered martensite. ^e
<p>NOTE To use the values in Table 1, a hardness difference of 40 HV minimum is recommended between the pinion and the wheel.</p> <p>^a The material quality grade MX, which existed in the first edition (1995) of this document, was replaced by the ME line in 2003.</p> <p>^b CAUTION: For cold service, below 0 °C:</p> <ul style="list-style-type: none"> — consider low temperature charpy specification; — consider fracture appearance transition or nil ductility temperature specification; — consider using higher nickel alloy steels; — consider reduced carbon content to less than 0,4 % carbon; — consider using heating elements to increase lubricant temperature. <p>^c The grade cleanliness and UT requirements apply only to those portions of the gear material where the teeth will be located at a distance below the finished tip diameter of at least two times the tooth depth. The gear manufacturer shall specify the inspection zone to the steel supplier or forge house.</p> <p>^d The area reduction is a total reduction irrespective of the method. Applies to forgings from ingot cast material. The reduction ratio can be less than 5:1 but not less than 3:1 when</p> <ol style="list-style-type: none"> 1) the rolled bar is subject to further hot working, 2) the central portion of the billet is removed, and 3) the 5:1 minimum reduction ratio is physically unobtainable due to the final size of the gear. <p>^e The microstructure of the gear section to a depth of 1,2 times the tooth height to consist primarily of tempered martensite with limited upper transformation products (proeutectoid ferrite, upper bainite and fine pearlite). No blocky ferrite, due to incomplete austenitization, is permitted. The maximum limit for upper transformation products is 10 % for gear controlling sections ≤250 mm, and 20 % for gear controlling sections >250 mm.</p> <p>^f Grain size should be determined at the position most relevant to the anticipated failure mechanism of the part. Tests can be determined on a sample from the same cast with similar reduction ratio and heat treatment. Reference surface area is 3,0 mm².</p>				

Table 4 — Through hardened cast steels, not surface hardened (see [Figures 7](#) and [8](#))

Item	Requirement	ML-MQ	ME
1	Chemical analysis	Not verified	Specific test report in accordance with ISO 10474 with 100 % traceability to the original cast.
2	Mechanical properties after heat treatment	HBW	$\sigma_s (\sigma_{0,2}) \sigma_B \delta_s \psi$ HBW Specific test report in accordance with ISO 10474 with 100 % traceability to the original cast. Verification of HBW. Statistical inspection required.
3	Grain size in accordance with ISO 643 ^a	No specification	Fine grain, with 90% of the area having grain size 5 and finer, and no grain coarser than size 3. Test report in accordance with ISO 10474.
4	Non-destructive testing		
4.1	Ultrasonic test (in rough machined condition) in accordance with ISO 9443	No specification	Check tooth and tooth root areas only. Specific test report in accordance with ISO 10474. Recommended but not required. Suggested for large diameter parts to detect flaws before the expense of tooth cutting. Acceptance criteria per ASTM A609 level 1 in Zone 1 (Outside diameter to 25 mm below roots) and level 2 in Zone 2 (remainder of rim) using 3,2 mm flat bottom hole; or approved equivalent using the back reflection technique.
4.2	Surface cracks detection (in finished condition but before any shot peening treatment)	Cracks not permitted. 100 % inspection by ASTM E1444 including fluorescent, magnetic particle or dye penetrant inspection. Statistical sampling permitted for large production lots.	
5	Repair welding	Allowed with approved procedure agreed upon by customer	Allowed only in rough condition if performed before heat treatment with approved procedure agreed upon by customer. Not allowed after tooth cutting.
<p>NOTE When the casting quality meets the quality criteria for wrought (forged or rolled) steels, wrought steel allowable stress numbers may be used in gear rating calculations for cast steel gears operating with wrought steel pinions. Suitability of using wrought steel allowable stress numbers for casting rating calculations shall be supported by test and operating experience.</p> <p>For castings, wrought steel cleanliness and forging reduction ratio criteria are excluded. Inclusion content and shape control are required to produce predominantly round manganese sulfide inclusions (Type I). No grain boundary (Type II) manganese sulfide inclusions permitted.</p> <p>^a Grain size should be determined at the position most relevant to the anticipated failure mechanism of the part. Reference surface area is 3,0 mm². Tests can be determined on a sample from the same cast with similar reduction ratio and heat treatment.</p>			

Table 5 (continued)

Item	Requirement	ML	MQ	ME
7	Surface hardness			
7.1	Surface hardness on a representative surface of workpiece ^d (see Vickers-Rockwell hardness conversion table in ISO 18265)	600 HV or 55 HRC minimum. Statistical sample testing.	660 HV to 800 HV or 58 HRC to 64 HRC. Statistical sample testing.	660 HV to 800 HV or 58 HRC to 64 HRC. 100 % testing if heat treatment lot size ≤ 5, else statistical samples permitted. Test method as appropriate for the size of the part.
7.2	Surface hardness in root space, mid-face width, for modules ≥12 ^d .	No specification	Meets drawing specification. Statistical sampling or on representative test piece.	Meets drawing specification. 100 % testing of every pinion and gear wheel or on representative test piece.
8	Core hardness at mid-face width on a normal to the 30° tangent at distance 5 × case depth but not less than 1 × module or measured on a representative test bar in accordance with 6.5.	21 HRC or more. Specified but not verified.	25 HRC or more, measured on a representative test bar per 6.5 b) or calculated based on knowledge of quench rate and hardenability curve.	30 HRC or more, measured on sample part or representative test bar in accordance with 6.5.
9	Case depth in finished condition in accordance with ISO 2639. Measured on representative test bar per 6.5 or measured at mid-face width and mid-height of the tooth.	Case depth is defined as the distance from the surface to a point at which the hardness number is 550 HV or 52 HRC. Minimum and maximum limits shall be shown on the drawing. When specifying case depth, note that the “optimum” values for bending and surface load capacity are not the same. Recommended values of case depth are shown in 5.6 ^e .		
10	Inspection of the microstructure requirements can be made on a test bar according to 6.5 in a depth corresponding to the finished condition. This inspection is optional for MQ but required for ME. (Not required for ML.)			
10.1	Limits on surface carbon content.	No specification	Low nominal alloy steels with total alloy content ≤ 1,5 %: 0,65 % to 1,0 %. High nominal alloy steels with total alloy content > 1,5 %: 0,60 % to 0,90 %. Recommended.	

Table 5 (continued)

Item	Requirement	ML	MQ	ME		
10.2	Surface structure: The desired structure has less than 10 % bainite determined by metallographic inspection	No specification	Recommended. Martensite, essentially fine acicular, as shown by a representative test bar.	Required. Martensite, fine acicular, as shown by a representative test bar.		
10.3	Carbide precipitation	Semi-continuous carbide network permitted in accordance with Figure 20 a). On representative test bar.	Discontinuous carbides permitted in accordance with Figure 20 b). Discontinuous carbides differ from semicontinuous carbide network in such a way that they do not delineate the grain structure. Maximum length of any carbide is 0,02 mm. (On representative test bar, if used.)	Dispersed carbides permitted in accordance with Figure 20 c). Maximum size of any carbide is 0,01 mm. Inspection of representative test bar in accordance with 6.5.		
10.4	Residual austenite. Determined by metallographic inspection. ^h	No specification	Up to 30 % on inspection of companion heat treatment batch test piece. If outside specification, salvage may be possible by controlled shot-peening in accordance with 6.7, or other appropriate procedures.	Up to 30 %, finely dispersed. Inspection of representative test bar in accordance with 6.5.		
10.5	Intergranular oxidation (IGO), applicable to unground surface. Determined by metallographic inspection of unetched coupon, if used. Limits in micrometers shall be based on actual achieved case depth <i>e</i> . No IGO or non-martensitic product on ground surface visible ^l	No specification	Case depth <i>e</i>	IGO	Case depth <i>e</i>	IGO
			mm	µm	mm	µm
			$e < 0,75$	17	$e < 0,75$	12
			$0,75 \leq e < 1,50$	25	$0,75 \leq e < 1,50$	20
			$1,50 \leq e < 2,25$	35	$1,50 \leq e < 2,25$	20
			$2,25 \leq e < 3,00$	45	$2,25 \leq e < 3,00$	25
			$3,00 \leq e < 5,00$	50	$3,00 \leq e < 5,00$	30
			$e \geq 5,00$	60	$e \geq 5,00$	35
			If outside specification, salvage may be possible by controlled shot-peening in accordance with 6.7, or other appropriate procedures, with the agreement of the customer.			
10.6	Grain size in final heat treated condition in accordance with ISO 643 ^k	No specification	Fine grain, with 90% of the area having grain size 5 and finer, and no grain coarser than size 3. Test report in accordance with ISO 10474 recommended.	Fine grain, with 90% of the area having grain size 5 and finer, and no grain coarser than size 3. Test report in accordance with ISO 10474 required.		
11	Core structure at the same location as item 8	No specification	Martensite, acicular ferrite and bainite. No blocky ferrite (see item 8)	Martensite, acicular ferrite and bainite. No blocky ferrite. Applies to representative test bar in accordance with 6.5		

Table 5 (continued)

Item	Requirement	ML	MQ	ME
12	Surface cracks ⁱ	Cracks not permissible. Statistical sample inspection by magnetic particle inspection, fluorescent magnetic particle penetrant or dye penetrant method.	Cracks not permissible. 50 % inspection by ASTM E1444 or EN 10228-1 (magnetic particle inspection method). Statistical inspection depending on lot size permitted.	Cracks not permissible. 100 % inspection by ASTM E1444 or EN 10228-1 (magnetic particle inspection method).
13	Grinding temper control using nital etch in accordance with ISO 14104 ^j	Grade B temper permitted on 100 % of functional area (FB3), statistical inspection recommended but not required.	Grade B temper permitted on 10 % of functional area (FB1), statistical inspection required. If outside specification, salvage may be possible by controlled shot-peening as described in item 6.7. Refinishing may be required in order to achieve specific surface finish and geometry.	No temper permitted on functional area (FA), 100 % inspection by ISO 14104.

NOTE See also 6.6 and 6.7. Requirements for carbonitrided steels are presently not given in the document.

^a The material chosen is either that quoted in the relevant grade according to ISO 683-1, ISO 683-2, ISO 683-3, ISO 683-4 or ISO 683-5 (recommended) or an appropriate National or International Standard.

^b The grade cleanliness requirements apply only to those portions of the gear material where the teeth will be located at a distance below the finished tip diameter of at least two times the tooth depth. On external gears, this portion of the gear blank normally will be less than 25 % of the radius of the gear blank.

^c The total reduction ratio may be achieved as a result of a number of hot working operations. The reduction ratio can be less than 5:1 but not less than 3:1 when

- 1) the rolled bar is subject to further hot working,
- 2) the central portion of the billet or strand is removed, and
- 3) the 5:1 minimum reduction ratio is physically unobtainable due to the final size of the gear.

^d Root hardness may be somewhat less than flank hardness, depending on the size of the gear and the process. Allowable values may be agreed between the manufacturer and the purchaser, but a minimum value of 55 HRC is required.

^e For other values of case depth, see, for example, Reference [10].


^h X-ray analysis can be used as an alternative method. Limiting values should be agreed between the gear manufacturer and the purchaser.

ⁱ No cracks, bursts, seams or laps are permitted in the tooth areas of finished gears, regardless of grade. Limits: maximum of one indication per 25 mm of face width and maximum of five in one tooth flank. No indications allowed below 1/2 of working depth of tooth. Removal of defects which exceed the stated limits is acceptable, with customer approval, provided the integrity of the gear is not compromised.


^j Other methods are available for grinding temper control and can be used by agreement between purchaser and manufacturer.

^k Grain size should be determined at the positions most relevant to the anticipated failure mechanism for the part. Reference surface area is 3,0 mm².


^l As IGO depth correlates strongly with the depth of non-martensitic transformation product and possible decarburization, the measurement of the depth of IGO in combination with the specified requirements for surface hardness (item 7.2) and microstructure (item 10.2) is sufficient.

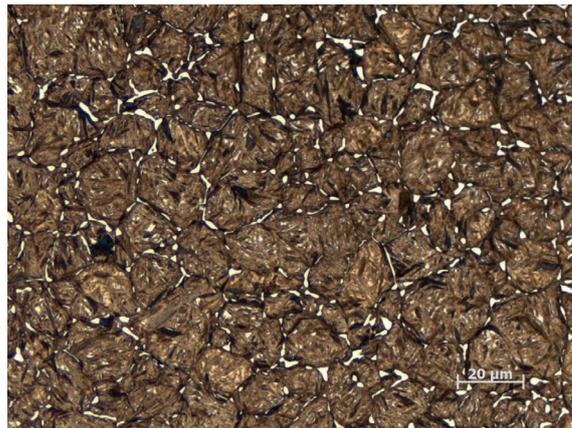

**a) Semi-continuous carbide network:
Permissible for Grade ML**

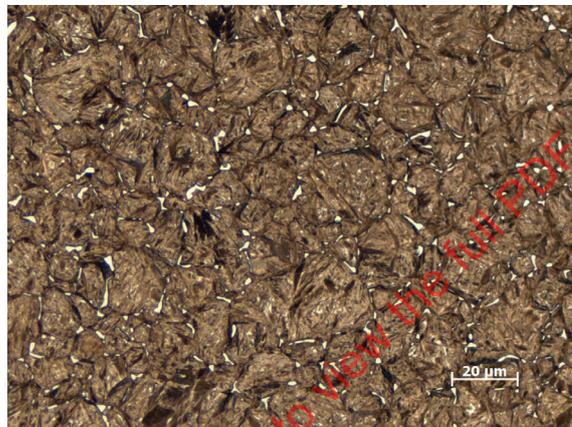

**b) Discontinuous carbides:
Permissible for ML and MQ**

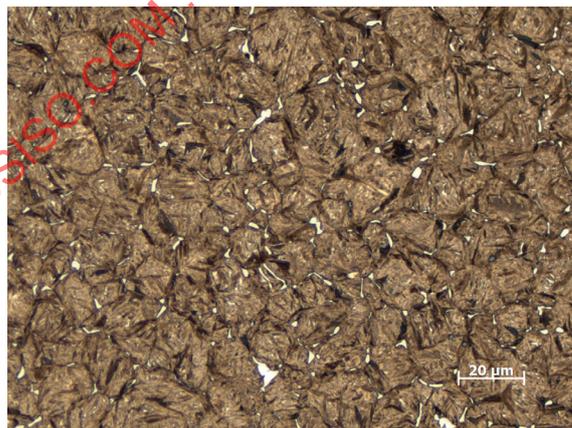

**c) Dispersed carbides:
Permissible for ML, MQ and ME**

**Figure 20 — Photo micrographs of permissible carbide structures for case carburized gears
(5 % nital etch. × 400 magnification)**

Table 6 — Induction or flame hardened wrought and cast steels (see [Figures 11](#) and [12](#))

Item	Requirement	ML	MQ	ME	
1	Chemical analysis	No specification	As in Table 3 (through hardened wrought steels: items 1 to 6) or as in Table 4 (through hardened cast steels: items 1 to 3)		
2	Mechanical properties — after heat treatment				
3	Cleanliness				
4	Grain size				
5	Ultrasonic test				
6	Extent of forging reduction				
7	Surface hardness	All induction-hardened gears should be furnace tempered. ^a 485 HV to 615 HV or 48 HRC to 56 HRC	All induction-hardened gears should be furnace tempered. ^a 500 HV to 615 HV or 50 HRC to 56 HRC	All induction-hardened gears shall be furnace tempered. 500 HV to 615 HV or 50 HRC to 56 HRC	
8	Hardening depth ^b , in accordance with ISO 3754	The hardening depth is defined as the distance to the surface from a point where the hardness is equal to 80 % of the required surface hardness. Depth of case to be determined for each part by experience. Location of SHD measurement to be determined on the drawing			
9	Surface structure	No specification	Inspection of statistical samples, mainly fine acicular martensite.	Stricter inspection of statistical samples, fine acicular martensite, ≤10 % non-martensitic structure; no free ferrite permitted.	
10	Non-destructive testing				
10.1	Surface cracks — not permitted (ASTM E1444)	Inspection of first batch (magnetic particle, fluorescent magnetic particle penetrant or dye penetrant method).	Inspection of first batch (magnetic particle, fluorescent magnetic particle penetrant or dye penetrant method).	100 % inspection (magnetic particle, fluorescent magnetic particle penetrant or dye penetrant method).	
10.2	Magnetic particle inspection (teeth area only) ASTM E1444c	No specification		Module	Max. indication mm
				≤2,5	1,6
				>2,5 to 8	2,4
				>8	3,0
11	Prior structure	Quenched and tempered			