

---

---

**Methods for the petrographic analysis  
of coals —**

Part 4:  
**Method of determining  
microlithotype, carbominerite and  
minerite composition**

*Méthodes d'analyse pétrographique des charbons —*

*Partie 4: Détermination de la composition en microlithotypes,  
carbominérîtes et minérîtes*

STANDARDSISO.COM : Click to view the full PDF of ISO 7404-4:2017



STANDARDSISO.COM : Click to view the full PDF of ISO 7404-4:2017



**COPYRIGHT PROTECTED DOCUMENT**

© ISO 2017, Published in Switzerland

All rights reserved. Unless otherwise specified, no part of this publication may be reproduced or utilized otherwise in any form or by any means, electronic or mechanical, including photocopying, or posting on the internet or an intranet, without prior written permission. Permission can be requested from either ISO at the address below or ISO's member body in the country of the requester.

ISO copyright office  
Ch. de Blandonnet 8 • CP 401  
CH-1214 Vernier, Geneva, Switzerland  
Tel. +41 22 749 01 11  
Fax +41 22 749 09 47  
copyright@iso.org  
www.iso.org

# Contents

	Page
Foreword.....	iv
Introduction.....	v
1 Scope.....	1
2 Normative references.....	1
3 Terms and definitions.....	1
4 Principle.....	1
5 Material.....	2
6 Apparatus.....	2
7 Procedure.....	3
8 Expressions of results.....	5
9 Precision.....	7
9.1 Repeatability limit.....	7
9.2 Reproducibility limit.....	7
10 Test report.....	8
Bibliography.....	9

STANDARDSISO.COM : Click to view the full PDF of ISO 7404-4:2017

## Foreword

ISO (the International Organization for Standardization) is a worldwide federation of national standards bodies (ISO member bodies). The work of preparing International Standards is normally carried out through ISO technical committees. Each member body interested in a subject for which a technical committee has been established has the right to be represented on that committee. International organizations, governmental and non-governmental, in liaison with ISO, also take part in the work. ISO collaborates closely with the International Electrotechnical Commission (IEC) on all matters of electrotechnical standardization.

The procedures used to develop this document and those intended for its further maintenance are described in the ISO/IEC Directives, Part 1. In particular the different approval criteria needed for the different types of ISO documents should be noted. This document was drafted in accordance with the editorial rules of the ISO/IEC Directives, Part 2 (see [www.iso.org/directives](http://www.iso.org/directives)).

Attention is drawn to the possibility that some of the elements of this document may be the subject of patent rights. ISO shall not be held responsible for identifying any or all such patent rights. Details of any patent rights identified during the development of the document will be in the Introduction and/or on the ISO list of patent declarations received (see [www.iso.org/patents](http://www.iso.org/patents)).

Any trade name used in this document is information given for the convenience of users and does not constitute an endorsement.

For an explanation on the voluntary nature of standards, the meaning of ISO specific terms and expressions related to conformity assessment, as well as information about ISO's adherence to the World Trade Organization (WTO) principles in the Technical Barriers to Trade (TBT) see the following URL: [www.iso.org/iso/foreword.html](http://www.iso.org/iso/foreword.html).

This document was prepared by Technical Committee TC 27, *Solid mineral fuels*, Subcommittee SC 5, *Methods of analysis*.

This second edition cancels and replaces the first edition (ISO 7404-4:1988), which has been technically revised.

A list of all the parts in the ISO 7404 series can be found on the ISO website.

## Introduction

Petrographic analyses have been recognized internationally as important in the context of the genesis, vertical and lateral variation, continuity, metamorphism and usage of coal. The International Committee for Coal Petrology (ICCP) has made recommendations concerning nomenclature and analytical methods and has published and described in detail the characteristics of a wide range of coals. This document agrees substantially with the text of relevant ICCP publications and incorporates many useful comments made by members of the ICCP and by member bodies of ISO/TC 27.

Petrographic analyses of a single coal provide information about the rank, the maceral and microlithotype compositions and the distribution of mineral matter in the coal. The reflectance of vitrinite is a useful measure of coal rank and the distribution of the reflectance of vitrinite in a coal blend, together with a maceral group analysis, can provide information about some important chemical and technological properties of the blend.

The ISO 7404 series is concerned with the methods of petrographic analysis currently employed in characterizing coal in the context of its technological and/or geological use. It establishes a system for petrographic analysis and comprises five parts, see ISO website:

Microlithotypes are the naturally occurring associations of macerals which characterize the microscopically visible different types of coal. By convention, the identity of a microlithotype is determined by the maceral group or groups occurring within an area of at least  $50\ \mu\text{m} \times 50\ \mu\text{m}$  and which are present in amounts equal to or exceeding 5 % by volume. Hence, they can comprise a single maceral or maceral group if it exceeds these dimensions. Microlithotypes may include up to 20 % by volume of minerals such as clay, quartz and carbonates or up to 5 % by volume of sulfide minerals. If the content of mineral matter exceeds these amounts, the material is designated as minerite or carbominerite depending on the proportions of coal and mineral matter.

Carbominerites can be subdivided according to the type of mineral matter.

Microlithotypes contribute information on the genesis of coal seams and can assist in solving problems of seam correlation. Because they determine, together with rank and mineral matter, the hardness and density of the bulk coal substance, microlithotypes affect the behaviour of coal in mining and coal preparation processes. The different microlithotypes determine, under given geological conditions, the distribution of micro-cracks and to some extent the cleat in the coal. The results of maceral analyses can be interpreted more meaningfully from a knowledge of microlithotype composition. Such information can assist in explaining the behaviour of coal in commercial and experimental utilization processes where the association of macerals is known to be important.

**NOTE** The percentage volume of carbonate, clay and quartz minerals on the one hand and sulfide minerals on the other, which define the carbominerites and minerites, correspond to the densities which separate acceptable coal from middlings ( $1,5\ \text{g/cm}^3$ ) and from rejects in coal preparation.

STANDARDSISO.COM : Click to view the full PDF of ISO 7404-4:2017

# Methods for the petrographic analysis of coals —

## Part 4:

# Method of determining microlithotype, carbominerite and minerite composition

## 1 Scope

This document specifies a method, using a graticule with 20 crossline intersections, for determining the proportions of microlithotypes, carbominerite and minerite in coals. It applies only to determinations made on polished particulate blocks using reflected white light (about 400 nm to 700 nm). Additional blue, blue-violet or UV light excitation (365 nm to 440 nm) for better identification of liptinite in fluorescence may be used especially at low rank coals.

## 2 Normative references

The following documents are referred to in the text in such a way that some or all of their content constitutes requirements of this document. For dated references, only the edition cited applies. For undated references, the latest edition of the referenced document (including any amendments) applies.

ISO 7404-1, *Methods for the petrographic analysis of coals — Part 1: Vocabulary*

ISO 7404-2, *Methods for the petrographic analysis of coals — Part 2: Methods of preparing coal samples*

## 3 Terms and definitions

For the purposes of this document, the terms and definitions given in ISO 7404-1 and the following apply.

ISO and IEC maintain terminological databases for use in standardization at the following addresses:

- ISO Online browsing platform: available at <http://www.iso.org/obp>
- IEC Electropedia: available at <http://www.electropedia.org/>

### 3.1

#### point

observation of a portion of the particulate block through the eyepiece graticule made during the analysis

Note 1 to entry: The allocation of a point to a particular microlithotype, or to carbominerite or minerite, is determined by the macerals and/or mineral matter present at the 20 intersections of the graticule. A point is only counted if at least 10 intersections fall on a particle.

## 4 Principle

Examination by using a reflected light microscope and point count procedure of a representative sample of coal prepared as a particulate block as described in ISO 7404-2. Identification under an immersion medium of the microlithotypes from their maceral composition. The proportions of the macerals are determined using a graticule having a grid with 20 points of intersection spaced to define a distance of 50 µm on the specimen between extreme intersections in the x (abscissa) and y (ordinate) directions, respectively. The use of such a graticule allows the analyst to comply with the 5 % minimum content and 50 µm minimum size stipulation.

## 5 Material


Immersion medium, having a suitable refractive index and compatible with the microscope objective.

NOTE If reflectance measurements are required on the same particulate block, an immersion oil as specified in ISO 7404-5 is used.

## 6 Apparatus

**6.1 Reflected light microscope**, having an immersion objective of magnification between  $\times 25$  and  $\times 60$  and eyepiece of magnification between  $\times 8$  and  $\times 12$ . The eyepiece shall have the facility for inserting a graticule.

**6.2 Graticule**, inscribed with a grid having 20 crossline intersections according to the pattern shown in [Figure 1](#). The effective distance between extreme intersections in the x- and y-directions, respectively, is 50  $\mu\text{m}$ .

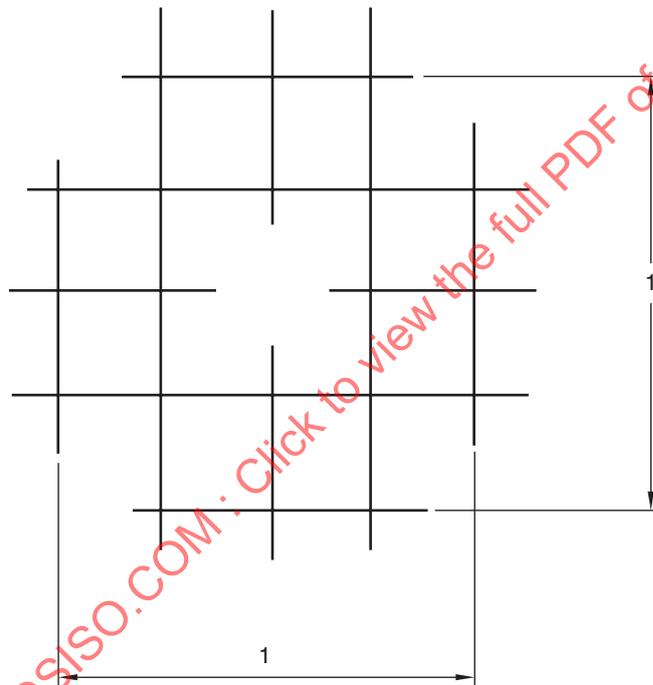

### Key

1 50  $\mu\text{m}$  on the specimen

**Figure 1 — Design of grid for microlithotype analysis**

NOTE 1 With a total number of 20 cross line intersections, a maceral appearing beneath a single intersection can be assumed to occupy 5 % by volume of the area covered by the grid.

NOTE 2 The graticule is designed for use with a particular combination of objective and eyepiece. Change in either objective or eyepiece will necessitate the use of a grid of different dimensions.

**6.3 Mechanical or scanning stage**, capable of advancing the specimen in the x-direction by equal steps of such length that only a negligibly small proportion of the particles examined receives more than one count on the same particle. The step-length is equal to half the maximum particle diameter, i.e. 0,5 mm to 0,6 mm for samples with a standard top particle size of 1 mm. The stage also permits a similar stepped advance in the y-direction. The stage movement may be actuated manually, by the counter mechanism or a computer attached to the stage.

**6.4 Counter/computer**, capable of registering the points in each category and preferably the grand total of points counted.

**6.5 Sample mounting equipment**, comprising slides, modelling clay and levelling press.

## 7 Procedure

Insert the graticule (6.2) into the eyepiece of the adjusted microscope (6.1).

Place the levelled particulate block, prepared in accordance with ISO 7404-2, on the stage. Add the immersion medium to the surface of the block, focus and observe the image in the microscope.

Assess the number of crossline intersections lying on the particle in order to decide whether the point should be recorded in the counting procedure and, if so, whether it should be assigned to the category of a microlithotype, carbominerite or minerite. If the number of intersections on one particle is 10 or more the point shall be accepted for analysis. If there are no intersections on coal or mineral matter, the point is ignored (i.e. it is not recorded). If the number is less than 10 it shall be recorded as a rejected category and the stage shall be advanced by one step. The number of such rejected points shall not exceed 10 % of the total accepted and rejected points. If the proportion exceeds 10 %, excessive fines may have been produced during preparation and a fresh sample should be prepared if material is available. If this is not possible the fact shall be recorded in the test report. For identifying the material under the individual crosslines, apply the procedure described in ISO 7404-3. The criteria for determining accepted and rejected points are shown in [Figure 2](#).

If the particle is accepted for analysis, assess the number of intersections lying on mineral matter. If the number of crossline intersections on mineral matter exceeds the number shown in [Table 1](#) for a given number of intersections lying within the particle, the material is either carbominerite or minerite.

**Table 1 — Maximum permissible number of intersections falling on mineral matter for the point to be classified as a microlithotype**

No. of intersections lying within the particle	Number of intersections on	
	carbonate, clay, quartz	sulfide
16 to 20	3	0
11 to 15	2	0
10	1	0

If the particle is a microlithotype, it is identified according to the criteria shown in [Table 2](#) ignoring any intersections on carbonate, clay or quartz.

**Table 2 — Delimitation of microlithotypes**

Microlithotype	Location of the crossline intersections lying in the coal
Vitrite	All intersections in the vitrinite
Liptite	All intersections in the liptinite
Inertite	All intersections in the inertinite
Clarite	All intersections in the vitrinite and liptinite, at least one intersection in each of the two maceral groups
Durite	All intersections in the inertinite and liptinite, at least one intersection in each of the two maceral groups
Vitrinertite	All intersections in the vitrinite and inertinite, at least one intersection in each of the two maceral groups
Trimacerite	At least one intersection in each of the three maceral groups

These criteria are applicable to microlithotypes containing mineral matter not exceeding the limits given in [Table 1](#).

If the intersections on mineral matter exceed the limits given in [Table 1](#), determine whether the particle is minerite or a carbominerite according to the criteria given in [Table 3](#) and [Table 4](#), if necessary. In using [Table 3](#) to identify carbominerite or minerite, the minerals appearing under the intersections shall be either sulfide or other minerals, but not both. The carbominerite may be named carbankerite, carbargilite, carbosilicite, carbopyrite or carbopolyminerite, according to the mineral matter appearing under the intersections.

**Table 3 — Delimitation of carbominerite (excluding carbopolyminerite with sulfide) and minerite**

No. of intersections lying within particle	Intersections falling on specified minerals			
	Carbominerite		Minerite	
	Carbonate, clay, quartz	Sulfide	Carbonate, clay, quartz	Sulfide
19 or 20	4 to 11	1 to 3	>11	>3
17 or 18	4 to 10	1 to 3	>10	>3
16	4 to 9	1 to 3	>9	>3
14 or 15	3 to 8	1 or 2	>8	>2
12 or 13	3 to 7	1 or 2	>7	>2
11	3 to 6	1 or 2	>6	>2
10	2 to 5	1	>5	>1

If both sulfide and other minerals occur under intersections of the grid, within the limits given in [Table 4](#), the carbominerite is named carbopolyminerite, otherwise the particle is again assigned to minerite.

**Table 4 — Delimitation of carbopolyminerite with sulfide**

No. of intersections lying within the particle	Carbopolyminerite	
	Intersection falling on specified minerals	
	Carbonate, clay, quartz	Sulfide
16 to 20	1 to 3	1 to 3
11 to 15	1 or 2	1 or 2
10	1	1

The maceral group or groups associated with the mineral matter and appearing under the residual intersections of the grid may be recorded to further characterize the carbominerite.

Having identified the point, advance the particulate block by one step along the x-axis, and continue counting and traversing the specimen. At the end of a traverse, advance the block by a step of at least equal length along the y-axis to start the next parallel traverse. The step length shall be chosen to ensure a uniform counting of points over the surface of the particulate block.

The total number of accepted points shall be at least 500.

**NOTE** For the assignment of a microlithotype, only the maceral group or groups appearing under the crossline intersections are considered. If a natural boundary between the two different microlithotypes lies under the grid, the assessment is made as if there were no boundary. The analysis, as described in this document, is traditionally applied to hard coals; there is, however, no reason, why it cannot be applied to lignite.

## 8 Expressions of results

Report the number of accepted points per microlithotype, per carbominerite and per minerite as the percentage of total number of accepted points. Express the values obtained as percentages by volume to the nearest integer.

The number of accepted points and the percentage of rejected points shall be indicated in the test report. An example of a suitable method of expressing results is shown in [Table 5](#).

The nature of coal associated with carbominerite and minerite, if determined, expressed as

- a) general qualitative observations, or
- b) quantitative record of maceral groups under residual intersections

may be recorded as shown in [Table 6](#).

**Table 5 — An example of a method of expressing the results**

Sample No.		Date:	
Microlithotype	Number of accepted points	Volume %	
Vitrite	101	20	
Liptite			
Inertite	64	13	
Clarite	57	11	
Durite	115	23	
Vitrinertite			
Trimacerite	141	28	
Total microlithotypes		95	
Carbominerite	Number of accepted points	Volume %	
Carbargilite	13	3	
Carbankerite			
Carbosilicite			
Carbopyrite	5	1	
Carbopolyminerite			
Total carbominerite		4	
Minerite	Number of accepted points	Volume %	
	4	1	
Grand total		100	

Total number of accepted points 500

Percentage of rejected points 7

**Table 6 — Nature of coal associated with carbominerite and minerite (example)**

Carbominerite/minerite (specify)	Associated maceral group(s) observed <sup>a</sup>	Number of accepted points	Accepted points as a percentage of carbominerite/minerite
Carbargilite	V	3	20
	V + L	12	80
Carbopyrite	V	1	20
	V + L	3	60
	V + L + I	1	20
Minerite	V + I	5	100

<sup>a</sup> L = liptinite  
I = inertinite  
V = vitrinite