
**Textiles — Test method for assessing the
appearance of creases in fabrics after
cleansing**

*Textiles — Méthode d'essai pour l'évaluation de l'aspect des plis des
étoffes après nettoyage*

STANDARDSISO.COM : Click to view the full PDF of ISO 7769:2009



PDF disclaimer

This PDF file may contain embedded typefaces. In accordance with Adobe's licensing policy, this file may be printed or viewed but shall not be edited unless the typefaces which are embedded are licensed to and installed on the computer performing the editing. In downloading this file, parties accept therein the responsibility of not infringing Adobe's licensing policy. The ISO Central Secretariat accepts no liability in this area.

Adobe is a trademark of Adobe Systems Incorporated.

Details of the software products used to create this PDF file can be found in the General Info relative to the file; the PDF-creation parameters were optimized for printing. Every care has been taken to ensure that the file is suitable for use by ISO member bodies. In the unlikely event that a problem relating to it is found, please inform the Central Secretariat at the address given below.

STANDARDSISO.COM : Click to view the full PDF of ISO 7769:2009



COPYRIGHT PROTECTED DOCUMENT

© ISO 2009

All rights reserved. Unless otherwise specified, no part of this publication may be reproduced or utilized in any form or by any means, electronic or mechanical, including photocopying and microfilm, without permission in writing from either ISO at the address below or ISO's member body in the country of the requester.

ISO copyright office
Case postale 56 • CH-1211 Geneva 20
Tel. + 41 22 749 01 11
Fax + 41 22 749 09 47
E-mail copyright@iso.org
Web www.iso.org

Published in Switzerland

Contents

Page

Foreword.....	iv
1 Scope	1
2 Normative references	1
3 Principle	1
4 Apparatus	1
5 Test specimens	4
6 Procedure	4
7 Expression of results	5
8 Test report	5
Annex A (informative) Precision and bias statement	7
Annex B (informative) Digital description of the ISO crease replicas	9

STANDARDSISO.COM : Click to view the full PDF of ISO 7769:2009

Foreword

ISO (the International Organization for Standardization) is a worldwide federation of national standards bodies (ISO member bodies). The work of preparing International Standards is normally carried out through ISO technical committees. Each member body interested in a subject for which a technical committee has been established has the right to be represented on that committee. International organizations, governmental and non-governmental, in liaison with ISO, also take part in the work. ISO collaborates closely with the International Electrotechnical Commission (IEC) on all matters of electrotechnical standardization.

International Standards are drafted in accordance with the rules given in the ISO/IEC Directives, Part 2.

The main task of technical committees is to prepare International Standards. Draft International Standards adopted by the technical committees are circulated to the member bodies for voting. Publication as an International Standard requires approval by at least 75 % of the member bodies casting a vote.

Attention is drawn to the possibility that some of the elements of this document may be the subject of patent rights. ISO shall not be held responsible for identifying any or all such patent rights.

ISO 7769 was prepared by Technical Committee ISO/TC 38, *Textiles*, Subcommittee SC 2, *Cleansing, finishing and water resistance tests*.

This fourth edition cancels and replaces the third edition (ISO 7769:2006), of which it constitutes a minor revision. It incorporates ISO 7769:2006/DAmD.1:2008 to add Annex B (informative).

STANDARDSISO.COM : Click to view the full PDF of ISO 7769:2009

Textiles — Test method for assessing the appearance of creases in fabrics after cleansing

1 Scope

This International Standard specifies a test method for evaluating the retention of pressed-in creases in fabrics after one or several cleansing treatments. A technique for inserting creases is not included as this is controlled by fabric properties.

This method has been developed for use primarily with type B domestic washing machines, as defined in ISO 6330, in the cleansing process. However, it may be possible to use it with type A machines, as defined in the same International Standard.

2 Normative references

The following referenced documents are indispensable for the application of this document. For dated references, only the edition cited applies. For undated references, the latest edition of the referenced document (including any amendments) applies.

ISO 105-A03, *Textiles — Tests for colour fastness — Part A03: Grey scale for assessing staining*

ISO 139, *Textiles — Standard atmospheres for conditioning and testing*

ISO 3175 (all parts), *Textiles — Professional care, drycleaning and wetcleaning of fabrics and garments*

ISO 6330, *Textiles — Domestic washing and drying procedures for textile testing*

3 Principle

3.1 Creased fabric specimens are subjected to procedures simulating cleansing practices. One of the domestic washing and drying procedures specified in ISO 6330 or one of the professional procedures specified in the series of ISO 3175 is used, as agreed between the interested parties.

3.2 Evaluation is performed by supplementing the overhead lighting arrangement with a spotlight suitably placed to highlight the creased area. The specimens are compared visually with plastic crease replicas under specified illumination.

4 Apparatus

4.1 **Washing and drying apparatus**, as specified in ISO 6330, or **professional care apparatus**, as specified in ISO 3175.

4.2 **Steam or dry iron**, with appropriate fabric temperature settings.

4.3 Lighting.

The evaluation area shall be a darkened room, using the lighting arrangement shown in Figures 1 and 2 and comprising the following items. Lamp dimensions should be chosen to extend beyond the overall surface of a test specimen and replicas, when used for the assessment.

4.3.1 Two CW (cool white) fluorescent lamps, without baffle or glass, a minimum of 2 m in length each, placed side by side.


4.3.2 One white enamel reflector, without baffle or glass.

4.3.3 One thick plywood viewing board, painted grey to the match No. 2 rating on the grey scale for assessing staining specified in ISO 105-A03.

4.3.4 One 500 W reflector flood lamp and lightshield (for the purpose of protecting the viewer's eyes from direct light as illustrated in Figure 2).

4.4 Plastic crease replicas, prepared for evaluating creases, as shown in Figure 3 ¹⁾

NOTE A digital description of the ISO crease replicas is given in Annex B.

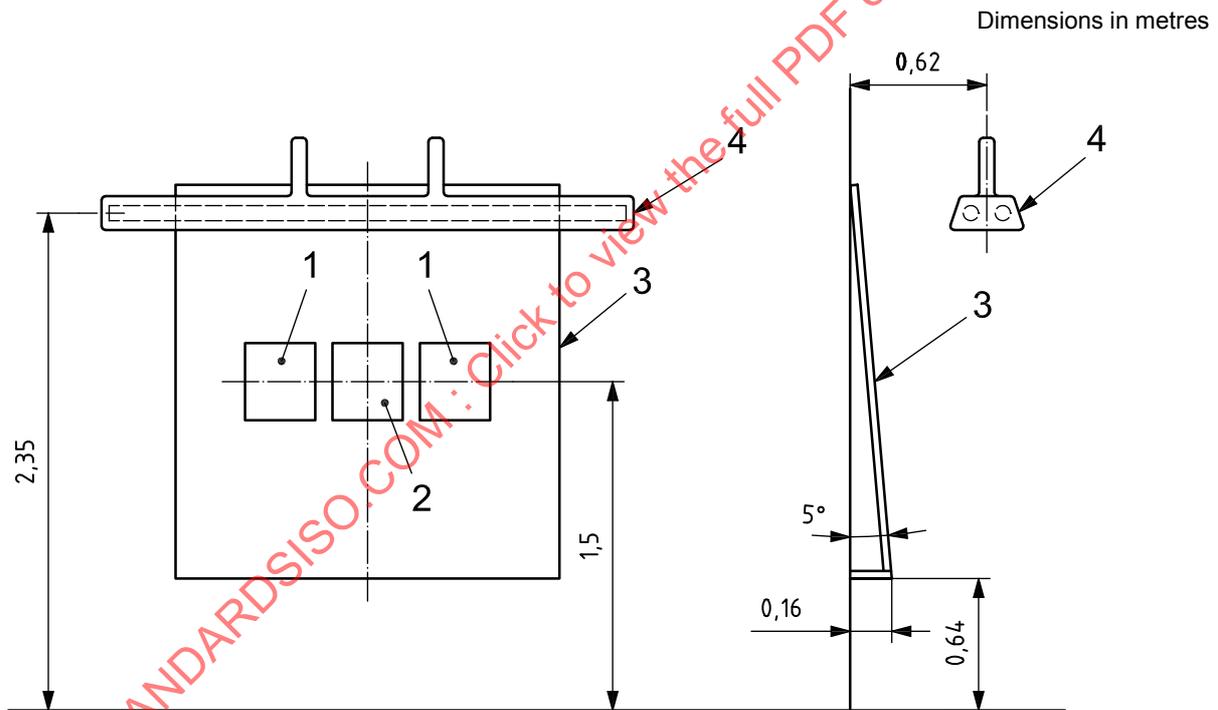



Key

- 1 replica
- 2 test specimen
- 3 board for viewing
- 4 example of fluorescent lamp placement

Figure 1 — Lighting equipment for viewing test specimens

1) The replicas shown in Figure 3 are for illustration purposes only. These replicas may be obtained from AATCC Technical Center, One Davis Drive, P.O. Box 12215, Research Triangle Park, North Carolina 27709-2215, USA; Tel: +1 919-549-8141; Fax: +1 919-549-8933; <http://www.aatcc.org>. This information is given for the convenience of users of this document and does not constitute an endorsement by ISO of the product named. Equivalent products may be used if they can be shown to lead to the same results.

Dimensions in metres

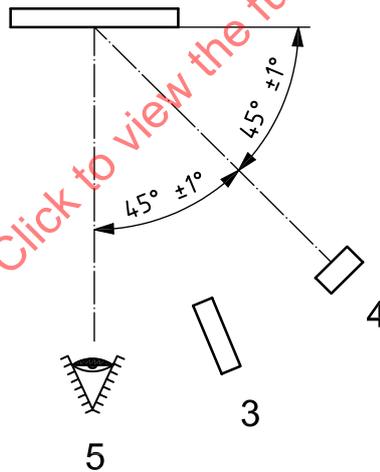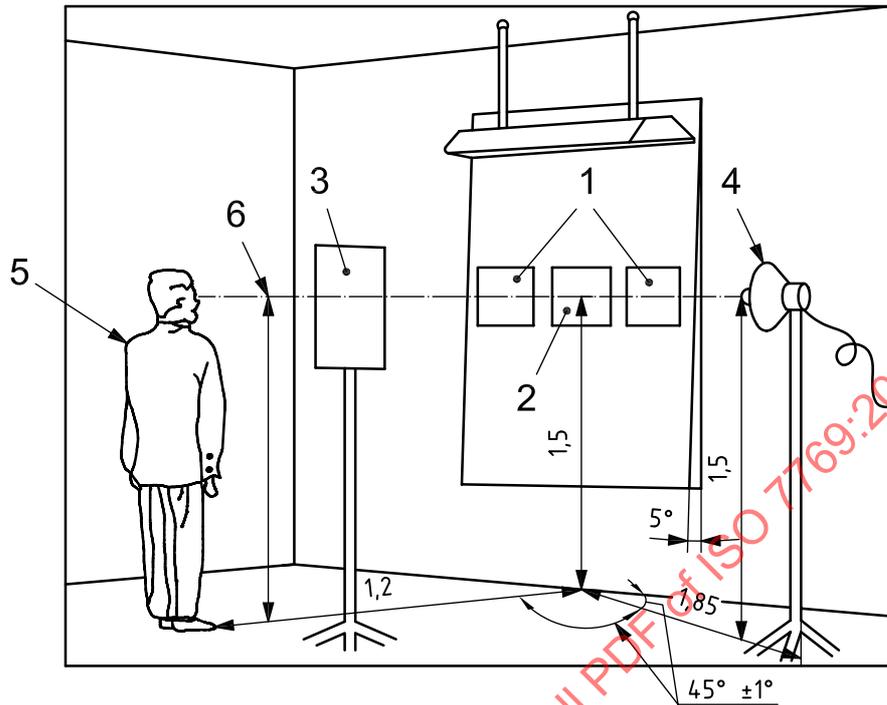

Key

- 1 replica
- 2 test specimen
- 3 light shield
- 4 500 W reflector flood lamp
- 5 observer
- 6 arbitrary eye level

Figure 2 — Lighting and viewing arrangement

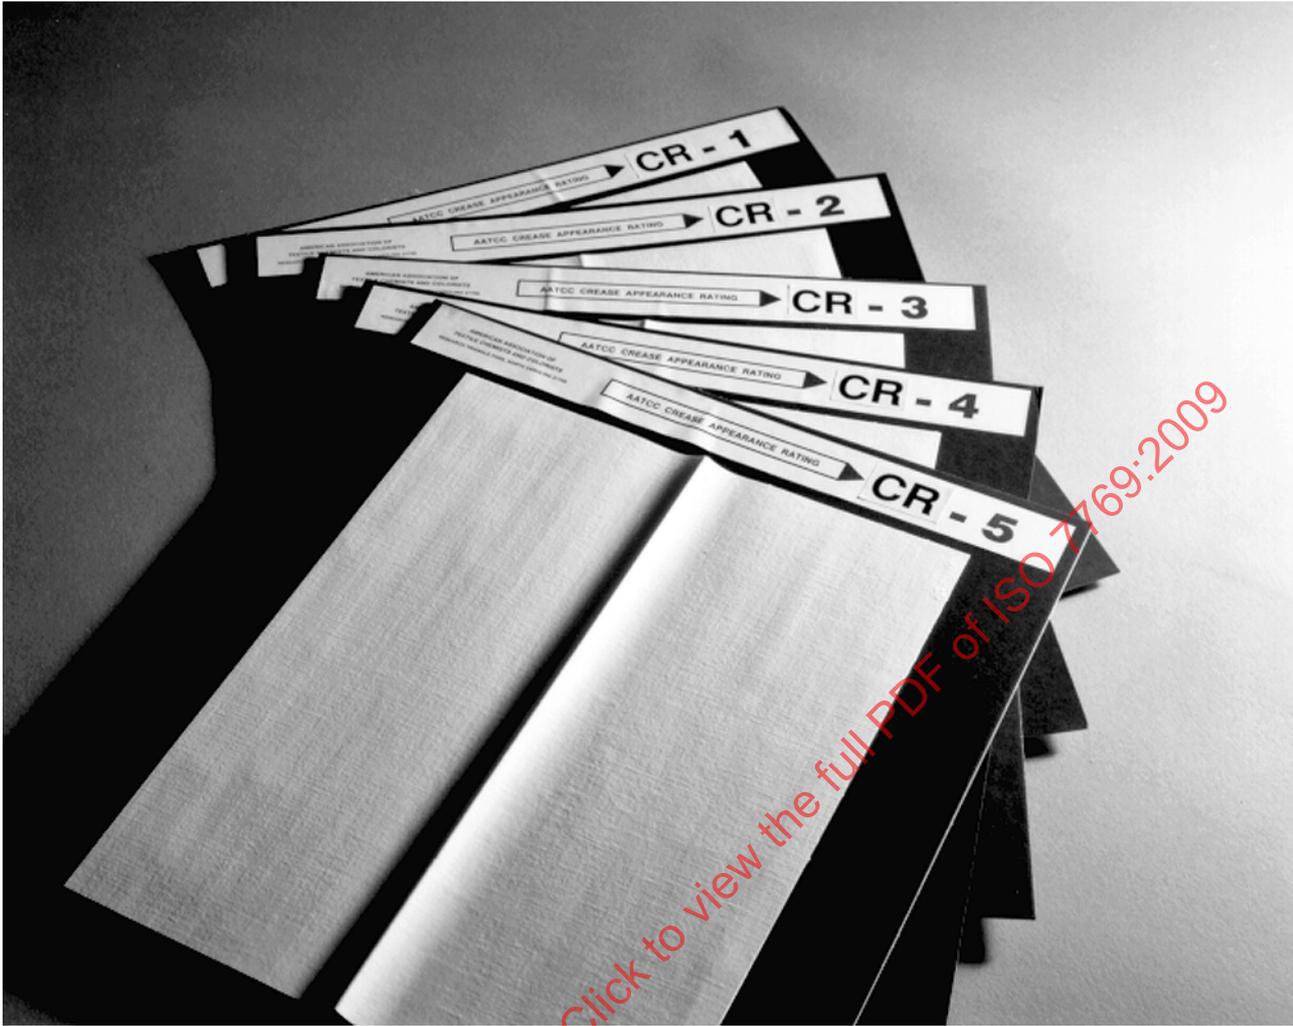


Figure 3 — Plastic crease replicas

5 Test specimens

Prepare three test specimens, each measuring 38 cm × 38 cm and pinked to prevent fraying, each with a press-in crease through the middle. If the fabric is wrinkled, it may be smoothed by appropriate ironing prior to testing. Care shall be taken to avoid altering the quality of the crease itself.

6 Procedure

- 6.1 Treat each specimen according to one of the procedures specified in ISO 6330 or ISO 3175, as agreed between the interested parties.
- 6.2 If required, repeat the selected treatment four times to give a total of five cycles.
- 6.3 Condition the test specimens for a minimum of 4 h and maximum of 24 h, according to ISO 139, by hanging each specimen by two corners with the crease vertical or, alternatively, using full-width clamps.
- 6.4 For the evaluation, carry out steps 6.4.1 to 6.4.5.
 - 6.4.1 Three observers shall rate each treated test specimen independently, as follows.

6.4.2 Mount the test specimen on the viewing board (4.3.3) as illustrated in Figure 1, with the crease in the vertical direction, taking care not to distort the crease. Place the plastic crease replicas (4.4) alongside to facilitate comparative rating. Place the most similar plastic crease replicas on each side of the test specimen. Mount replicas 1, 3 or 5 on the left and 2 or 4 on the right.

6.4.3 The observer shall stand directly in front of the specimen, 1,2 m away from the viewing board. It has been found that normal variations in the height of the observer above and below the arbitrary 1,5 m eye level have no significant effect on the rating given.

The overhead fluorescent light (4.3.1) and the side flood light shall be the only light source for the viewing board, and all other lights in the room shall be turned off. It has been the experience of many observers that the light reflected from the side walls near the viewing board can interfere with the rating results. It is recommended that the side walls be painted black or that blackout curtains be mounted on either side of the viewing board to eliminate the reflective interference.

6.4.4 Compare the retention of the specimen crease with the plastic crease replicas (see Figure 3), using the prescribed lighting arrangement in a darkened room as shown in Figures 1 and 2. Assign the number of the plastic crease replica that most nearly matches the appearance of the specimen crease (see Figure 3 and Table 1), or assign ratings midway between those whole-number standards, if the appearance of the specimens warrants it.

Table 1 — Crease appearance ratings

Class	Crease appearance
5	Equivalent to Standard CR-5
4,5	Midway between Standard CR-4 and CR-5
4	Equivalent to Standard CR-4
3,5	Midway between Standard CR-3 and CR-4
3	Equivalent to Standard CR-3
2,5	Midway between Standard CR-2 and CR-3
2	Equivalent to Standard CR-2
1,5	Midway between Standard CR-1 and CR-2
1	Equivalent to or worse than Standard CR-1

6.4.5 Similarly, the observer shall independently rate each of the other two test specimens. The other two observers shall proceed in the same manner, assigning ratings independently.

7 Expression of results

Average the nine observations made by the three observers on the set of three test specimens. Report the average to the nearest half of a rating.

8 Test report

The test report shall include the following information:

- a) a reference to this International Standard (ISO 7769:2009);
- b) details of the sample evaluated;

ISO 7769:2009(E)

- c) details of the cleansing procedures used;
- d) the number of cleansing cycles used;
- e) the crease appearance rating as calculated in accordance with Clause 7, and expressed according to Table 1;
- f) details of any deviation from the specified procedure.

STANDARDSISO.COM : Click to view the full PDF of ISO 7769:2009

Annex A (informative)

Precision and bias statement

A.1 Preliminary tests

A series of inter-laboratory tests was conducted during development of the set of five plastic replica standards. From this work, it was concluded that:

- a) replica standards were preferred over photographic standards;
- b) replica standards did not change the level of ratings;
- c) the absence of side-lighting raised the level of ratings;
- d) rating to half-units improved precision.

This was the basis for adopting the set of replica standards, retaining side-lighting and allowing rating to half-units.

A.2 Precision

Using the adopted set of replica standards, five fabrics spanning the range of ratings from 1 to 5, three specimens per fabric, were rated by six observers at a single laboratory location (December 1985). With all conditions identical for the six observers, this data set provided an unbiased estimate of the frequency distribution of observer ratings about an unexpected rating value (or the variability to be expected in observer ratings). Because of the limited and discontinuous scale of replica ratings, the analysis of variance technique was judged not to be applicable to this data set, but such a scale imposes no such restriction with regard to frequency distributions. From the data set, it was determined that observers rate individual specimens to an expected half-rating (E) on the following frequency:

Rated a whole unit under the expected value	0,011 11
Rated a half-unit under the expected value	0,133 34
Rated to expected value (E)	0,600 00
Rated a half-unit over the expected value	0,200 00
Rated a whole unit over the expected value	0,055 55
Total	1,000 00

Starting with the near-normal distribution for observer determinations [designated distribution 1)], it was used to calculate the following additional distributions: 2) the probability of differences between observers (single determination); 3) the distribution of observer totals of three determinations about an expected value; 4) the probability of differences between observers (three determinations per total); 5) the distribution of laboratory totals of three observer totals (nine rating determinations, three each by three observers) about an expected value; and 6) the probability of differences between laboratories (nine determinations per total).

Adhering to fiducial limits based on the usual $P = 0,05$ (or, in some instances, slightly more favourable), critical differences were established from three different distributions as given in Table A.1.

Table A.1 — Critical differences

Source	Critical difference (average)	Probability <i>P</i>
Between two observers (one determination each)	1	0,03
Between two observers (three determinations each)	0,67	0,02
Between two laboratories (nine determinations each)	0,33 0,50	0,05 0,01

The foregoing was based on observers and laboratories at the same level. When two or more laboratories wish to compare test results, it is recommended that laboratory level be established between them, through ratings of creases on fabrics of known history and performance. Differences greater than the critical differences (on the same fabric, with the same washing and drying conditions) suggest differences in laboratory levels and indicate a need for removing such bias.

A.3 Bias

The true value of appearance of creases in items after home laundering can be defined only in terms of a test method. There is no independent method for determining the true value.

Annex B (informative)

Digital description of the ISO crease replicas

B.1 Introduction

This annex provides the digital description of 3-dimensional (3D) replicas. The data are not intended to be used to assess specimens. When assessing specimens, the 3D replicas are to be used.

B.2 Processes of measurement and analysis

B.2.1 A 3-dimensional scanning system was used to measure digital images of ISO crease replicas as shown in Figure B.1. Specifications for the scanning system are shown in Table B.1.




Figure B.1 — 3-Dimensional scanning system

Table B.1 — Specification of the 3-dimensional scanning system

Camera	1 024 × 768 pixels, black and white (B/W)
Special pattern	Structural beam by halogen lamp
Adjustment of focus	Using the laser-point light source
Measurement time	Approximately 70 s to 80 s
Resolution	± 0,05 mm

B.2.2 The measuring area is shown in Figure B.2.

Dimensions in millimetres

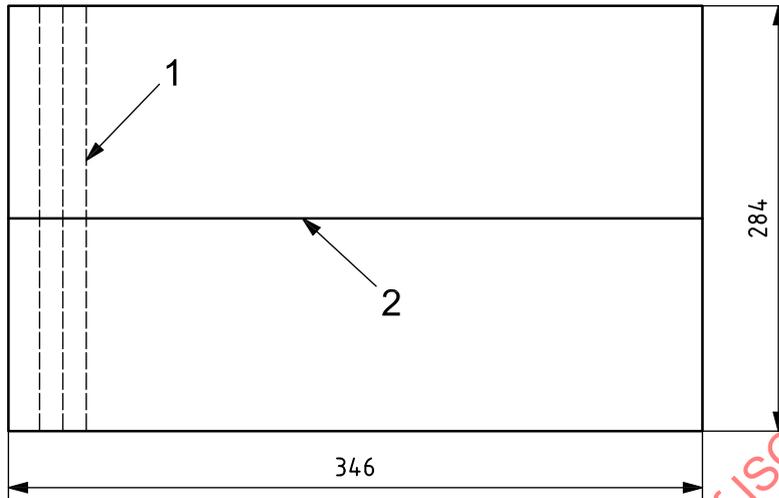

Key

- 1 measuring lines
- 2 crease line

Figure B.2 — Measuring area of crease replica

B.2.3 A geometric shape of each standard replica is measured using a 3-dimensional laser scanning system in a perpendicular direction with the crease line of the replicas at two intervals of 0,375 mm and 1 mm, respectively. The measuring point intervals along each line are the same as the line intervals, 0,375 mm and 1 mm, respectively. The number of measuring points along each line is determined by the intervals.

To analyse the replicas, the maximum value of height, which is the most important shape parameter having an influence on the grade of replica, was defined. This corresponds to the height of peak points of a crease line. For each line, the parameter can be obtained.

B.3 Analysis of crease with 1 mm measurements

B.3.1 Measured images of crease replicas

Figure B.3 shows measured images of crease replicas using a 3-dimensional scanning system at intervals of 1 mm.