
**Materials and articles in contact with
foodstuffs — Cutlery and table holloware —**

Part 7:

**Requirements for table cutlery made of
silver, other precious metals and their
alloys**

*Matériaux et objets en contact avec les denrées alimentaires — Coutellerie
et orfèvrerie de table —*

*Partie 7: Exigences relatives à la coutellerie de table en argent massif,
autres métaux précieux et leurs alliages*



PDF disclaimer

This PDF file may contain embedded typefaces. In accordance with Adobe's licensing policy, this file may be printed or viewed but shall not be edited unless the typefaces which are embedded are licensed to and installed on the computer performing the editing. In downloading this file, parties accept therein the responsibility of not infringing Adobe's licensing policy. The ISO Central Secretariat accepts no liability in this area.

Adobe is a trademark of Adobe Systems Incorporated.

Details of the software products used to create this PDF file can be found in the General Info relative to the file; the PDF-creation parameters were optimized for printing. Every care has been taken to ensure that the file is suitable for use by ISO member bodies. In the unlikely event that a problem relating to it is found, please inform the Central Secretariat at the address given below.

STANDARDSISO.COM : Click to view the full PDF of ISO 8442-7:2000

© ISO 2000

All rights reserved. Unless otherwise specified, no part of this publication may be reproduced or utilized in any form or by any means, electronic or mechanical, including photocopying and microfilm, without permission in writing from either ISO at the address below or ISO's member body in the country of the requester.

ISO copyright office
Case postale 56 • CH-1211 Geneva 20
Tel. + 41 22 749 01 11
Fax + 41 22 749 09 47
E-mail copyright@iso.ch
Web www.iso.ch

Printed in Switzerland

Foreword

ISO (the International Organization for Standardization) is a worldwide federation of national standards bodies (ISO member bodies). The work of preparing International Standards is normally carried out through ISO technical committees. Each member body interested in a subject for which a technical committee has been established has the right to be represented on that committee. International organizations, governmental and non-governmental, in liaison with ISO, also take part in the work. ISO collaborates closely with the International Electrotechnical Commission (IEC) on all matters of electrotechnical standardization.

International Standards are drafted in accordance with the rules given in the ISO/IEC Directives, Part 3.

Draft International Standards adopted by the technical committees are circulated to the member bodies for voting. Publication as an International Standard requires approval by at least 75 % of member bodies casting a vote.

Attention is drawn to the possibility that some of the elements of this part of ISO 8442 may be the subject of patent rights. ISO shall not be held responsible for identifying any or all such patent rights.

International Standard ISO 8442-7 was prepared by the European Committee for Standardization (CEN) in collaboration with ISO Technical Committee TC 186, *Cutlery and table and decorative metal hollow-ware*, in accordance with the Agreement on technical cooperation between ISO and CEN (Vienna Agreement).

Throughout the text of this standard, read "...this European Standard..." to mean "...this International Standard...".

ISO 8442 consists of the following parts, under the general title *Materials and articles in contact with foodstuffs — Cutlery and table holloware*:

- *Part 1: Requirements for cutlery for the preparation of food*
- *Part 2: Requirements for stainless steel and silver-plated cutlery*
- *Part 3: Requirements for silver-plated table and decorative holloware*
- *Part 4: Requirements for gold plated cutlery*
- *Part 5: Specification for sharpness and edge retention test of cutlery*
- *Part 6: Lightly silver-plated table holloware protected by lacquer*
- *Part 7: Requirements for table cutlery made of silver, other precious metals and their alloys*
- *Part 8: Requirements for silver table and decorative holloware*

Annexes A to C form a normative part of this part of ISO 8442. Annex D is for information only.

Contents

	Page
Foreword	v
1 Scope	1
2 Normative references	1
3 Terms and definitions	1
4 Materials	1
5 Construction	2
6 Precious metal-plating	3
7 Performance	3
8 Marking and labelling	5
Annex A (normative) Method of test for adhesion of precious metal coating	6
Annex B (normative) Method of test for corrosion resistance of knife blades	7
Annex C (normative) Test method for strength of knives with martensitic stainless steel blades	9
Annex D (informative) A-deviations	11

STANDARDSISO.COM : Click to view the full PDF of ISO 8442-7:2000

Foreword

The text of EN ISO 8442-7:1999 has been prepared by Technical Committee CEN/TC 194 "Utensils in contact with food", the secretariat of which is held by BSI, in collaboration with Technical Committee ISO/TC 186 "Cutlery and table and decorative metal hollow-ware".

This European Standard shall be given the status of a national standard, either by publication of an identical text or by endorsement, at the latest by January 2001, and conflicting national standards shall be withdrawn at the latest by January 2001.

Attention is drawn to the European Community Directives relative to materials in contact with foodstuffs, in particular Directive 89/109/EEC

EN ISO 8442 consists of the following parts:

- Part 1: Requirements for cutlery for the preparation of food
- Part 2: Requirements for stainless steel and silver-plated cutlery
- Part 3: Requirements for silver-plated table and decorative holloware
- Part 4: Requirements for gold-plated cutlery
- Part 5: Specification for sharpness and edge retention test of cutlery
- Part 6: Lightly silver plated table holloware protected by a lacquer
- Part 8: Requirements for silver table and decorative holloware

According to the CEN/CENELEC Internal Regulations, the national standards organizations of the following countries are bound to implement this European Standard: Austria, Belgium, Czech Republic, Denmark, Finland, France, Germany, Greece, Iceland, Ireland, Italy, Luxembourg, Netherlands, Norway, Portugal, Spain, Sweden, Switzerland and the United Kingdom.

1 Scope

This European Standard specifies material and performance requirements for table cutlery made of silver, other precious metals and their alloys (knives with stainless steel blades, forks, spoons, carving sets, ladles and other pieces).

It does not include requirements for design, size, type of finish, blade flexibility, or similar characteristics which are matters of personal choice or which can be readily assessed by the purchaser at the point of sale. No sampling provisions are included in this standard, the requirements specified are applicable for each and every item produced.

2 Normative references

This European Standard incorporates by dated reference, provisions from other publications. These normative references are cited at the appropriate places in the text and the publications are listed hereafter. For dated references, subsequent amendments to or revisions of any of these publications apply to this European Standard only when incorporated in it by amendment or revision (including amendments).

ISO 4481: 1977 Cutlery and flatware - Nomenclature

ISO 6508: 1986 Metallic materials - Hardness test - Rockwell test (scales A - B - C - D - E - F - G - H - K)

EN 10088-1: 1995 Stainless Steels, Part 1: List of stainless steels

prEN 1904:1995 Precious metals - Solders used with precious metal jewellery alloys

3 Terms and definitions

For the purposes of this European Standard the terms and definitions given in annex of ISO 4481: 1977 apply together with the following.

3.1

unsharpened knives

knives with an unsharpened blade used for cutting soft foods

NOTE They are not made of martensitic stainless steel. Examples are butter knife, fish serving knife, ice cream knife, fish knife, spreading knife, cheese knife.

4 Materials

4.1 General

The table cutlery shall be made of silver, other precious metals and their alloys with a minimum standard of fineness of 800 (expressed in parts per thousand) that enable the finished product to meet all of the performance requirements of this standard and which shall be neither detrimental to health nor have any detrimental organoleptic effects.

4.2 Metals

4.2.1 Silver plating

Any parts of silver table cutlery may be plated with a fine silver coating.

4.2.2 Soldering

Precious metals in an article shall be soldered according to prEN 1904:1995.

4.2.3 Stainless Steels

Knife blades and any parts of the table cutlery, which have to fulfil special requirements e.g. carving items, shall be made of stainless steels according to Table 1.

Table 1 — Stainless steel for table cutlery, limiting requirements

Application	Name	number of materials	structure
Carving items	X6CrMo 17-1	1.4113	ferritic
	X20Cr 13	1.4021	martensitic
The chemical composition shall be in accordance with EN 10088-1 : 1995			

4.3 Non-metals

Non-metal parts of table cutlery may be made of such materials as glass, ceramics, plastics or similar materials provided that the finished cutlery complies with the relevant performance requirements of 4. 1.

5 Construction

5.1 Alignment, uniformity and absence of defects

5.1.1 All surfaces shall be free from cracks, pits and other defects.

5.1.2 All cutlery shall be essentially straight and symmetrical except when the lack of straightness or symmetry is an intentional feature of the design.

5.1.3 Identical items within a batch shall, as far as is practicable, show no significant variation in dimension or form.

5.1.4 All edges, including the edges of spoons, forks, ladles and the insiders of fork prongs, shall be free from burrs and the roughness of blanked edges shall have been removed by a suitable operation.

5.1.5 Table knives shall be balanced such that when the knife is pivoted on its bolster, or at the junction of the handle and blade if no bolster is present, the handle shall be heavier than the blade.

5.1.6 Compliance with the requirements for 5.1.1 to 5.1.5 shall be checked by touch or by visual inspection

5.2 Hollow handles

The seams joining hollow handles together shall be watertight.

5.3 Knife edges

The cutting edge of sharpened table knives shall be either scalloped or serrated or shall be whetted to an included angle not greater than 60 °.

The cutting edges of a carving knife blade shall be whetted to an included angle not greater than 40° and shall not be thicker than 0,46 mm when measured 1 mm from the edge.

6 Precious metal-plating

6.1 Hardness of hard gold coatings

Gold coatings claimed to be hard shall contain 0,2 % minimum Co or Ni or Fe or any other element which increases the hardness.

6.2 Adhesion of precious metal coatings

When tested in accordance with annex A coatings shall show no signs of flaking, blistering or peeling.

NOTE Alternative methods of determining the adhesion of coatings may be used provided the results obtained are in correlation with those given by ball burnishing.

6.3 Fineness of precious metal coatings

The fineness of precious metal coatings should not be less than 925 ‰.

7 Performance

7.1 Resistance to corrosion

The surfaces of stainless steel parts of table cutlery shall comply with the requirements a) to c) when tested in accordance with the method described in annex B:

- a) no transverse cracks shall have developed and no longitudinal cracks of a length exceeding 1,5 mm shall have developed;
- b) there shall not be more than three pits or zones of intergranular corrosion each having an area greater than a circle of 0,4 mm diameter on the handle, and not more than three pits each having an area greater than a circle of 0,4 mm diameter (0,126 mm²) elsewhere;
- c) there shall be no pits or zones of intergranular corrosion having an area greater than a circle of 0,75 mm (0,442 mm²) on any part.


7.2 Strength

7.2.1 Knives with martensitic stainless steel blades

A knife shall not crack or break and shall not acquire a permanent deformation of more than $3^\circ \pm 0,5^\circ$ when tested in accordance with the method described in annex C. In addition, the handle blade joint shall not become loose.

7.2.2 Spoons, forks, ladles and unsharpened knives

An item shall not have a permanent deformation of more than 1mm when tested as follows; an item shall be laid on a plane with the highest point of the handle facing upward. A force shall be applied equivalent to 5,5 N for each centimetre of overall length or $80\text{N} \pm 10\text{N}$ whichever is the lesser for 10 s (see figure 1 for a spoon). During the application of this force the point of rest of the handle (A in figure 1) shall not be more than 10 mm from the edge of the supporting surface.

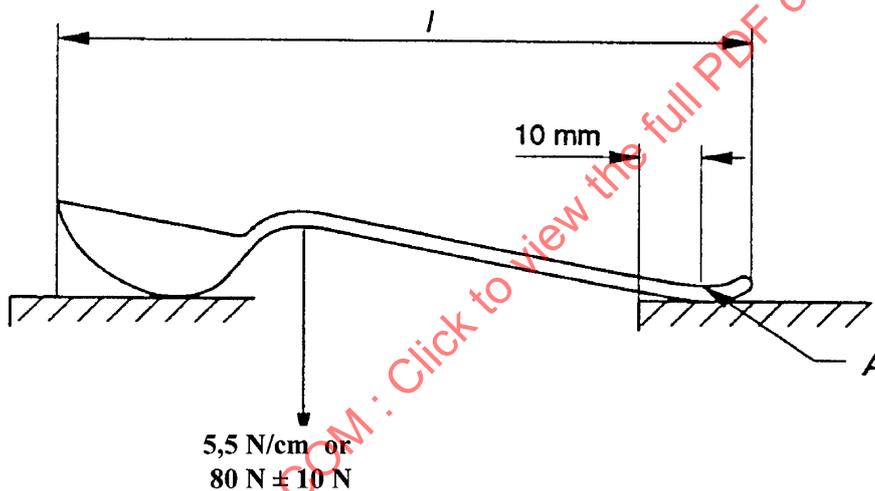

Key

- l length
- A point of rest

Figure 1 — Strength test for a spoon

7.2.3 Firmness of handle attachment

Handles that are not an integral part of the rest of the item shall be attached by a method that prevents the handle turning relative to the rest of the item or pulling away from the blade when, immediately after being immersed for 10 min in water at a temperature of (100 _{-5}^0) °C, the item is subjected to

- a) a pulling force of 180 _{-10}^0 for 10 s;
- b) a torque of $(4,5 \text{ }_{-0,2}^0)$ Nm for items whose handles have a surface area of 37 cm² or more, or a torque of $(3,7 \text{ }_{-0,2}^0)$ Nm for items whose handles have a surface area of less than 37 cm². The torque shall be applied for 10 s.

The pulling force and torque shall be applied successively.

7.3 Hardness of knife blades

Knife blades made from martensitic stainless steel shall have a minimum hardness of 48 HRC when tested in accordance with ISO 6508:1986. Readings shall be taken not less than 40 mm from the handle.

Carving knife blades shall have a minimum of 52 HRC.

8 Marking and labelling

Each item of cutlery shall be legibly and indelibly marked with the name and/or trade mark or other means of identifying the manufacturer or responsible supplier.

The following information shall be made available at the point of sale:

- the number of this European Standard,
- a statement that the cutlery meets the requirements of the standard.

This information may be provided as leaflets on the packaging or by means of labelling or on a display card or in any other suitable form.

Annex A
(normative)

Method of test for adhesion of precious metal coating

A.1 Principle

Cutlery items are examined after burnishing with steel balls by rotation in a rubber-lined drum containing soap solution.

A.2 Apparatus and materials

A.2.1 Rotatable drum, rubber-lined of hexagonal cross section measuring $250 \text{ mm} \pm 20 \text{ mm}$ across the flats capable of rotating at $25 \text{ r/min} \pm 2 \text{ r/min}$ and preferably fitted with transverse dividing panels so that compartments shorter than the items to be tested can be formed within the drum to prevent entanglement of the test items. The drum is half filled with hardened steel balls in the following size proportions (to prevent geometric bunching):

4,8 mm diameter: 50 % by mass;

4,0 mm diameter: 25 % by mass;

5,6 mm diameter: 25 % by mass.

A.2.2 Soap solution, 1,2 g of soap per litre of demineralized or distilled water.

A.3 Procedure

Sufficient cold soap solution (A.2.2) is added to the drum to cover the steel balls

NOTE The soap inhibits corrosion of the steel balls.

Place the test items in the drum (A.2.1) and rotate it at $25 \text{ r/min} \pm 2 \text{ r/min}$ for 40 min.

Remove the test items from the drum and carefully examine them

A.4 Expression of results

Report any signs of peeling or flaking of the coating.

Annex B (normative)

Method of test for corrosion resistance of knife blades

B.1 Principle

The test samples are intermittently immersed in a solution of sodium chloride (NaCl) maintained at $60^{\circ}\text{C} \pm 2^{\circ}\text{C}$ for 6 h. The number and size of any pits that have formed are measured visually with the aid of a microscope lens.

B.2 Reagents

Sodium chloride solution with a mass fraction of 1 % consisting of one part by mass sodium chloride in 99 parts demineralized/distilled water.

During the test, unless otherwise stated, use only reagents of recognised analytical grade and only distilled water or water of equivalent quality.

B.3 Apparatus

A suitable apparatus is shown in figure B.1, and comprises a glass or plastics container and a cover, which may be glass or plastics, and a plastics specimen rack with means to raise and lower this into the container.

NOTE Other methods of specimen support may be used provided that there is a minimal contact of the specimen with the supporting means.

Calibrated microscope or lens of at least 4 times magnification.

B.4 Procedure

B.4.1 Wash the selected samples thoroughly in hot soapy water. Thoroughly rinse and then degrease the samples in acetone or methylated spirits.

B.4.2 Fill the container with the sodium chloride solution (see B.2) using at least 1 litre of solution for every square decimetre of area of the stainless steel parts of the samples. Bring the container and contents to $60^{\circ}\text{C} \pm 2^{\circ}\text{C}$. Maintain at this temperature. Do not allow the temperature of the solution to exceed 62°C at any time, even before the start of the test. Use a fresh sodium chloride solution for each test.

NOTE The temperature of the sodium chloride solution can be conveniently maintained at $60^{\circ}\text{C} \pm 2^{\circ}\text{C}$ by positioning the apparatus in a thermostatically controlled water bath, the level of which is maintained at approximately the same level as that of the sodium chloride solution.

B.4.3 Place the sample in the rack and replace the cover.

B.4.4 Completely immerse and completely withdraw the samples from the solution at the rate of from two to three times per minute for 6 h.

B.4.5 At the conclusion of the test period, thoroughly wash and rinse the samples and examine for corrosion.

NOTE: Products of corrosion that impede visual examination of corrosion pits can be removed by hand rubbing the surface of the cutlery with a stainless steel polishing paste applied with a soft cloth.

B.5 Expression of results

Assess the size of pits and the length of longitudinal cracks per test specimen visually with the aid of a calibrated microscope or lens of at least four times magnification. Where two pits have obviously merged together they shall be assessed as two separate pits.

NOTE The use of wires of diameter 0,4 mm and 0,75 mm respectively, placed in contact with the sample surface, provides a convenient method of assessing the size of pits with a hand lens.

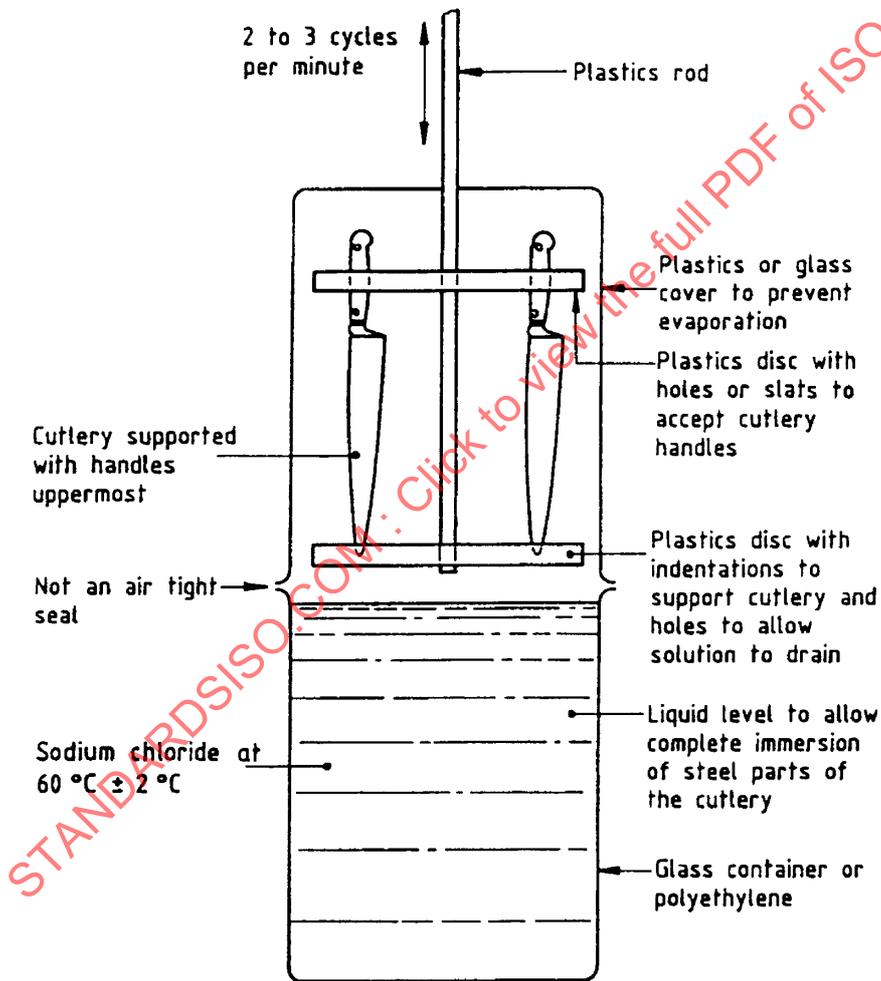


Figure B.1 — Apparatus for corrosion test