
**Glass-reinforced thermosetting plastics
(GRP) pipes and fittings — Test methods
to prove the design of cemented or
wrapped joints**

*Tubes et raccords en plastiques thermodurcissables renforcés de verre
(PRV) — Méthodes d'essai pour confirmer la conception des
assemblages scellés ou enrobés*

STANDARDSISO.COM : Click to view the PDF of ISO 8533:2003



PDF disclaimer

This PDF file may contain embedded typefaces. In accordance with Adobe's licensing policy, this file may be printed or viewed but shall not be edited unless the typefaces which are embedded are licensed to and installed on the computer performing the editing. In downloading this file, parties accept therein the responsibility of not infringing Adobe's licensing policy. The ISO Central Secretariat accepts no liability in this area.

Adobe is a trademark of Adobe Systems Incorporated.

Details of the software products used to create this PDF file can be found in the General Info relative to the file; the PDF-creation parameters were optimized for printing. Every care has been taken to ensure that the file is suitable for use by ISO member bodies. In the unlikely event that a problem relating to it is found, please inform the Central Secretariat at the address given below.

STANDARDSISO.COM : Click to view the full PDF of ISO 8533:2003

© ISO 2003

All rights reserved. Unless otherwise specified, no part of this publication may be reproduced or utilized in any form or by any means, electronic or mechanical, including photocopying and microfilm, without permission in writing from either ISO at the address below or ISO's member body in the country of the requester.

ISO copyright office
Case postale 56 • CH-1211 Geneva 20
Tel. + 41 22 749 01 11
Fax + 41 22 749 09 47
E-mail copyright@iso.org
Web www.iso.org

Published in Switzerland

Contents

Page

Foreword	iv
Introduction	v
1 Scope	1
2 Principle	1
3 Apparatus	2
4 Test pieces	4
4.1 Test arrangement	4
4.2 Number of test pieces	4
5 Conditioning	4
6 Test temperature	4
7 Procedure	4
7.1 General	4
7.2 Leaktightness when subjected to an external pressure differential	5
7.3 Initial leakage	5
7.4 Resistance of the joint to bending and pressure	5
7.5 Resistance to internal pressure	6
7.6 Testing excluding hydrostatic end thrust (see 7.1)	7
8 Test report	7
Annex A (normative) Equations for calculating the additional force, F , and limiting deflection, Δ , for the bending test described in 7.4	9

Foreword

ISO (the International Organization for Standardization) is a worldwide federation of national standards bodies (ISO member bodies). The work of preparing International Standards is normally carried out through ISO technical committees. Each member body interested in a subject for which a technical committee has been established has the right to be represented on that committee. International organizations, governmental and non-governmental, in liaison with ISO, also take part in the work. ISO collaborates closely with the International Electrotechnical Commission (IEC) on all matters of electrotechnical standardization.

International Standards are drafted in accordance with the rules given in the ISO/IEC Directives, Part 2.

The main task of technical committees is to prepare International Standards. Draft International Standards adopted by the technical committees are circulated to the member bodies for voting. Publication as an International Standard requires approval by at least 75 % of the member bodies casting a vote.

Attention is drawn to the possibility that some of the elements of this document may be the subject of patent rights. ISO shall not be held responsible for identifying any or all such patent rights.

ISO 8533 was prepared by Technical Committee ISO/TC 138, *Plastics pipes, fittings and valves for the transport of fluids*, Subcommittee SC 6, *Reinforced plastics pipes and fittings for all applications*.

STANDARDSISO.COM : Click to view the full PDF of ISO 8533:2003

Introduction

In a pipework system, pipes and fittings of different nominal pressures and stiffness may be used.

A joint may be made between pipes and/or fittings and should be designed such that its performance is equal to or better than the requirements of the pipeline, but not necessarily of the components being joined.

The requirements for the assembly of the joint are not included in this standard, but they should be in accordance with the manufacturer's recommendations.

STANDARDSISO.COM : Click to view the full PDF of ISO 8533:2003

Glass-reinforced thermosetting plastics (GRP) pipes and fittings — Test methods to prove the design of cemented or wrapped joints

1 Scope

This International Standard specifies methods of test for cemented or wrapped joints for plastics piping systems made of glass-reinforced thermosetting plastics (GRP) for buried and non-buried pipelines. This standard is only applicable to the joint and covers methods of test to prove its design. It assumes that the joint either is or is not intended to be subject to the effects of hydrostatic end thrust.

The tests detailed in 7.1 to 7.6 inclusive are applicable to cemented or wrapped joints intended to be used in either buried or non-buried applications. The bending tests detailed in 7.4 can be used to prove the design where joints are either intended to be used in buried applications or are intended to be used in particular above-ground situations where the tests may be considered appropriate.

With the exception of 7.4 these test procedures are applicable to joints between pipes and fittings of all nominal sizes. The tests detailed in 7.4 are applicable to joints between pipes and fittings up to and including DN 600. The tests are applicable to the evaluation of joints intended for the conveyance of liquids at temperatures specified in the referring standards (see Clause 2).

2 Principle

A joint is subjected to a specified internal pressure and, if applicable, longitudinal loading. The procedure includes prolonged static tests at elevated pressures and cyclic testing.

A joint is subjected to a specified internal negative pressure. This also simulates an external positive pressure.

NOTE 1 The only reason for testing the resistance to external pressure differential is to ensure adequate safety against infiltration of pollutants through the joint into the fluid carried in the piping system. Under these test conditions pipes with low stiffness may require support to prevent buckling.

A series of tests that are performed under bending is included.

At the end of each of the tests the joint is inspected for signs of leakage and damage and, unless otherwise specified, if either has occurred then the joint has failed.

If the joint is to be used in systems where the maximum operating temperature is higher than the value given in the referring standard the test conditions can be modified accordingly.

NOTE 2 It is assumed that the following test parameters are set by the standard making reference to this standard:

- a) length, L , of the assembled test piece (see 4.1);
- b) number of test pieces to be used (see 4.2);
- c) if applicable, conditioning other than as given in Clause 5;
- d) test temperature and its permissible deviations (see Clause 6);

- e) nominal pressure relevant to the joint under test (see 4.1 and Clause 7, as well as the introduction to this standard);
- f) if applicable, any criteria indicative of damage to the joint components [see Clause 7 and item j) of Clause 8];
- g) whether the joint is or is not to be tested with end loads;
- h) acceptable increase in pressure over 1 h for an external pressure differential test (see 7.2).

3 Apparatus

3.1 End-sealing devices

End-sealing devices shall be of a size and type appropriate to the joint system under test.

3.1.1 Capable of applying the end loads

If the joint is to be tested with the end load [see item g) of Note 2 of Clause 2] then the end-sealing devices shall be anchored to the pipes to transmit the end thrust loads.

3.1.2 Not capable of applying the end loads

If the joint is to be tested without the end load [see item g) of Note 2 of Clause 2 and 7.6] then the end-sealing devices shall not be anchored to the pipes.

3.2 Supports

3.2.1 End thrust supports

If required, the end thrust supports shall comprise part of the rig and shall be capable of supporting the end thrust induced by the internal pressure but shall not otherwise support the joint [see 7.6 and Figure 1b), item 3].

3.2.2 Straps and cradles

Straps or cradles for use as supports shall be of sufficient width for the pipe components of the test piece (see Figure 2) and shall not have a detrimental effect on the test piece, e.g. shall not apply point loads.

3.2.3 Special supports

Special supports may be used to prevent buckling of the pipe barrel during external pressure differential testing (see 7.2).

3.3 Source of hydrostatic pressure


A source of hydrostatic pressure capable of meeting the needs of the test.

3.4 Means of measuring the gauge pressure

A means of measuring the gauge pressure at the top of the pipe to an accuracy within $\pm 1\%$ and checking conformity to the specified pressures (see 7.2, 7.3, 7.4 and 7.5).

3.5 Vacuum pump or equivalent

A vacuum pump or equivalent capable of applying the required negative gauge pressure (see 7.2).

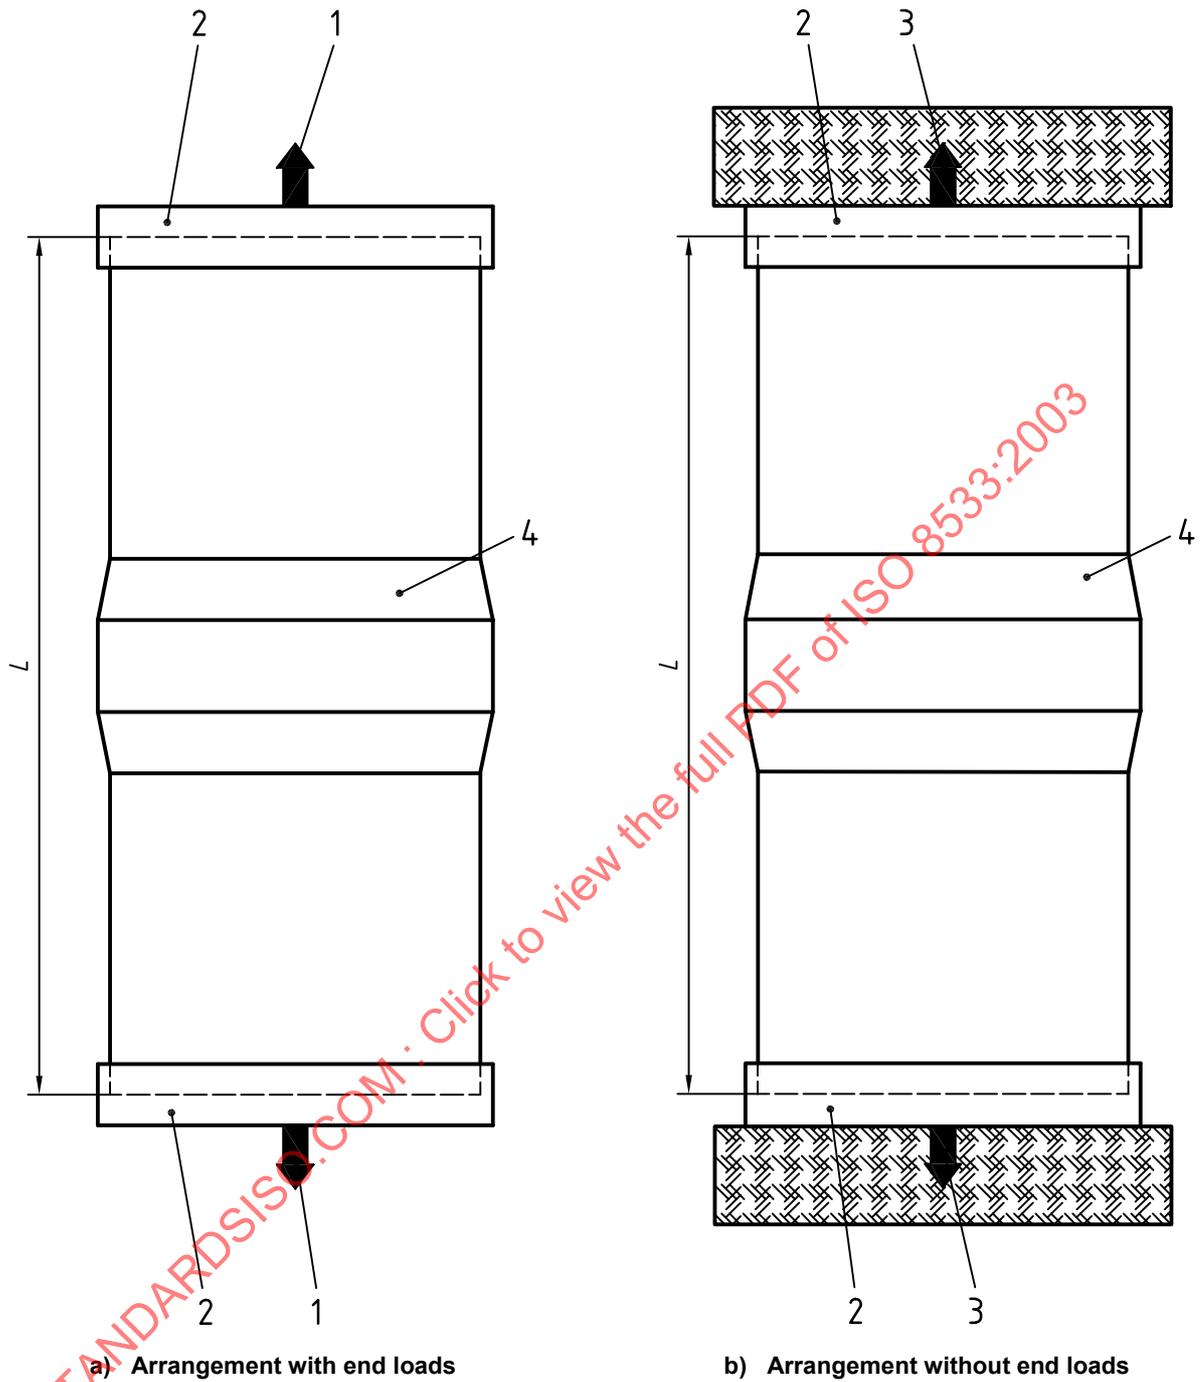

Key

- | | |
|--------------------------------|----------------------------|
| 1 thrust carried by test piece | 4 joint being tested |
| 2 end-sealing device | L length of the assembly |
| 3 thrust carried by test rig | |

Figure 1 — Typical test arrangements for the tests detailed in 7.2, 7.3 and 7.5

4 Test pieces

4.1 Test arrangement

The test piece shall comprise an assembly of two pieces of pipe of the correct size and pressure class, as specified in the referring standard, between which is located the joint to be tested.

For the tests detailed in 7.2, 7.3 and 7.5, the length of the assembly, L , shall be not less than that specified in the referring specification and shall allow, if required, the joint under test to be located in the middle of the test arrangement. For the test detailed in 7.4 the length, L , of the assembly shall be not greater than 8 m and the joint under test shall be located in the middle of the test arrangement.

For the tests detailed in 7.2, 7.3 and 7.5, the arrangement shall be as shown in Figure 1. For the test detailed in 7.4, the arrangement shall be as shown in Figure 2. For the tests detailed in 7.4, see Annex A for details on determining the maximum deflection, Δ (see item 6 in Figure 2), at mid-span and the magnitude of the force F . In all these arrangements a joint of the same size and design shall be used. The same test piece may be used for more than one test procedure providing it is undamaged and of sufficient size to enable the test conditions to be achieved.

The joint shall be assembled in accordance with the manufacturer's recommendations and the requirements of the referring standard.

4.2 Number of test pieces

The number of test pieces shall be as specified in the referring standard.

5 Conditioning

For any interval between assembly of the test piece in accordance with Clause 4 and conditioning performed in accordance with the following paragraph, store the test piece at a temperature which does not exceed the test temperature (see Clause 6).

Following assembly, unless otherwise specified in the referring standard, condition test pieces by storing at the test temperature (see Clause 6) for at least 24 h prior to testing.

6 Test temperature

Conduct the following procedures at the temperature specified in the referring standard.

7 Procedure

7.1 General

WARNING — When carrying out the procedures detailed in this clause, care should be taken to provide suitable protection from flying objects resulting from catastrophic failure.

Subject the test piece (see Clause 4) to either the tests in 7.2 to 7.5 summarized in Table 1, for joints intended to carry end thrust, or the tests detailed in 7.6 summarized in Table 1 for joints not intended to carry end thrust. In either case for the tests detailed in 7.4 the test piece shall have a length not exceeding 8 m and use a joint of the same size and design as that used for 7.2, 7.3 and 7.5.

NOTE Each reference to hydrostatic pressure specifies a positive internal gauge pressure (i.e. relative to atmospheric pressure) and the nominal pressure is that relevant to the joint under test.

If a test is interrupted, record the details in the test report and repeat the particular test before carrying on to the next in the series of tests, if applicable. Failure at the end caps or of the pipe shall not constitute failure of the joint but, if the test conditions are invalidated thereby, repeat the particular test after replacing the failed component.

7.2 Leaktightness when subjected to an external pressure differential

7.2.1 Assemble the test arrangement as shown in Figure 1a) and condition as described in Clause 5.

7.2.2 Connect to the vacuum pump (see 3.5).

7.2.3 Reduce the pressure to at least 0,8 bar below atmospheric pressure (approximately 0,2 bar absolute). Record the pressure achieved.

7.2.4 Close the valve between the test piece and the vacuum pump and leave for 1 h.

7.2.5 After this time record any increase in pressure.

7.2.6 If an increase in pressure in excess of the acceptable level specified in the referring standard [see item h) of Note 2 to Clause 2] has occurred then inspect for sources of leakage other than the joint. If any such sources are found then return the test piece to atmospheric pressure, seal the source of the leaks and repeat the test in 7.2.2 to 7.2.5. Otherwise stop the test and record the observations.

7.2.7 If an increase in pressure in excess of the acceptable level specified in the referring standard [see item h) of Note 2 to Clause 2] has not occurred then restore atmospheric pressure and inspect for and record any signs of damage to the joint [see item f) of Note 2 to Clause 2] and proceed to the next test.

7.3 Initial leakage

7.3.1 Fill the test piece with water and vent to remove any air.

7.3.2 Apply an internal pressure of 1,5 times the nominal pressure of the joint, expressed in bars¹⁾, and maintain within $\pm 2\%$ for 15 min (see Table 1).

7.3.3 Inspect the joint for signs of leakage or damage. If neither are present proceed to the next test. Otherwise stop the test and record the observations.

7.4 Resistance of the joint to bending and pressure

7.4.1 Assemble the test arrangement as shown in Figure 2 using a test piece conforming to Clause 4 and having a length L not exceeding 8 m. Determine the values of F and Δ in accordance with Annex A.

7.4.2 Connect the end caps to the pipes in such a way that the full loads induced by the internal pressure will be transmitted along the pipes to the joint under test.

7.4.3 Position the stop at mid-span to ensure a deflection up to Δ can occur and condition the test piece in accordance with Clause 5.

7.4.4 Fill the test piece with water, taking care to avoid entrapping air.

7.4.5 Apply the force F .

1) 1 bar = 10^5 N/m² = 0,1 MPa.

7.4.6 Apply an initial hydrostatic pressure of 1,5 times the nominal pressure of the joint, expressed in bars, and maintain within $\pm 2\%$ for 15 min. Inspect the joint for signs of leakage or damage. If either has occurred stop the test and empty the test piece. Otherwise continue in accordance with 7.4.7.


7.4.7 Maintain the hydrostatic pressure of 1,5 times the nominal pressure of the joint, expressed in bars, within $\pm 2\%$ for not less than 24 h.

7.4.8 Inspect the joint and record any signs of leakage or damage.

7.4.9 Check and record whether or not the joint is resting on the stop.

7.4.10 Remove the force F and reduce the pressure to atmospheric.

7.4.11 Inspect the joint and record any signs of damage.

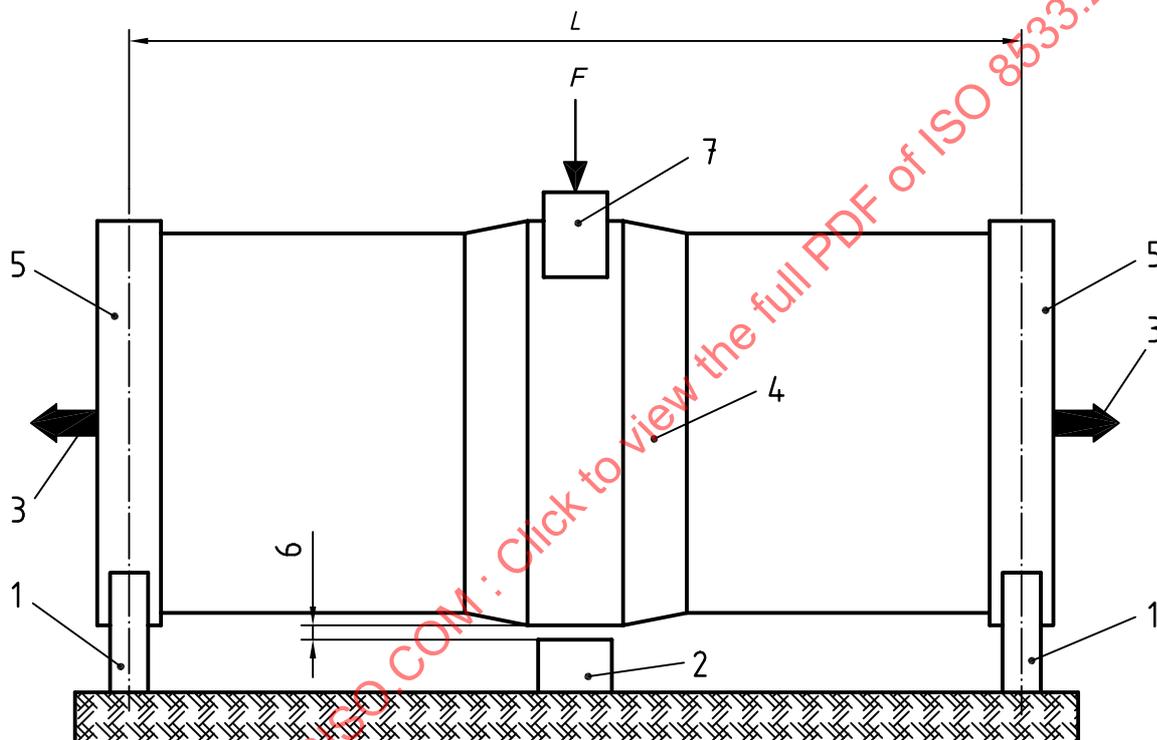

Key

- | | |
|--|--|
| 1 support | 6 limiting deflection at mid-span, Δ |
| 2 stop | 7 strap or cradle for the application of force F |
| 3 thrust carried by test piece | L length not exceeding 8 m |
| 4 joint being tested | F additional force (if required) |
| 5 end-sealing device fixed to test piece | |

Figure 2 — Typical test arrangement for tests detailed in 7.4

7.5 Resistance to internal pressure

7.5.1 Maintain an internal pressure of 1,5 times the nominal pressure of the joint, expressed in bars, for 24 h (see Table 1).

7.5.2 Inspect the joint for signs of leakage or damage. If neither are present proceed in accordance with 7.5.3. Otherwise stop the test and record the observations.

7.5.3 Reduce the pressure to atmospheric.