

---

---

**Ophthalmic optics — Uncut finished  
spectacle lenses —**

Part 5:

**Minimum requirements for spectacle lens  
surfaces claimed to be abrasion-resistant**

*Optique ophtalmique — Verres de lunettes finis non détourés —*

*Partie 5: Exigences minimales pour les surfaces de verres de lunettes  
déclarées être résistantes à l'abrasion*

STANDARDSISO.COM : Click to view the full PDF of ISO 8980-5:2005



**PDF disclaimer**

This PDF file may contain embedded typefaces. In accordance with Adobe's licensing policy, this file may be printed or viewed but shall not be edited unless the typefaces which are embedded are licensed to and installed on the computer performing the editing. In downloading this file, parties accept therein the responsibility of not infringing Adobe's licensing policy. The ISO Central Secretariat accepts no liability in this area.

Adobe is a trademark of Adobe Systems Incorporated.

Details of the software products used to create this PDF file can be found in the General Info relative to the file; the PDF-creation parameters were optimized for printing. Every care has been taken to ensure that the file is suitable for use by ISO member bodies. In the unlikely event that a problem relating to it is found, please inform the Central Secretariat at the address given below.

STANDARDSISO.COM : Click to view the full PDF of ISO 8980-5:2005

© ISO 2005

All rights reserved. Unless otherwise specified, no part of this publication may be reproduced or utilized in any form or by any means, electronic or mechanical, including photocopying and microfilm, without permission in writing from either ISO at the address below or ISO's member body in the country of the requester.

ISO copyright office  
Case postale 56 • CH-1211 Geneva 20  
Tel. + 41 22 749 01 11  
Fax + 41 22 749 09 47  
E-mail [copyright@iso.org](mailto:copyright@iso.org)  
Web [www.iso.org](http://www.iso.org)

Published in Switzerland

## Foreword

ISO (the International Organization for Standardization) is a worldwide federation of national standards bodies (ISO member bodies). The work of preparing International Standards is normally carried out through ISO technical committees. Each member body interested in a subject for which a technical committee has been established has the right to be represented on that committee. International organizations, governmental and non-governmental, in liaison with ISO, also take part in the work. ISO collaborates closely with the International Electrotechnical Commission (IEC) on all matters of electrotechnical standardization.

International Standards are drafted in accordance with the rules given in the ISO/IEC Directives, Part 2.

The main task of technical committees is to prepare International Standards. Draft International Standards adopted by the technical committees are circulated to the member bodies for voting. Publication as an International Standard requires approval by at least 75 % of the member bodies casting a vote.

Attention is drawn to the possibility that some of the elements of this document may be the subject of patent rights. ISO shall not be held responsible for identifying any or all such patent rights.

ISO 8980-5 was prepared by Technical Committee ISO/TC 172, *Optics and photonics*, Subcommittee SC 7, *Ophthalmic optics and instruments*.

ISO 8980 consists of the following parts, under the general title *Ophthalmic optics — Uncut finished spectacle lenses*:

- *Part 1: Specifications for single-vision and multifocal lenses*
- *Part 2: Specifications for progressive power lenses*
- *Part 3: Transmittance specifications and test methods*
- *Part 4: Specifications and test methods for anti-reflective coatings*
- *Part 5: Minimum requirements for spectacle lens surfaces claimed to be abrasion-resistant*



# Ophthalmic optics — Uncut finished spectacle lenses —

## Part 5: Minimum requirements for spectacle lens surfaces claimed to be abrasion-resistant

### 1 Scope

This part of ISO 8980 specifies the requirement and test method for spectacle lens surfaces that are claimed to provide a basic level of abrasion resistance including those with coatings.

A lens claimed to be abrasion-resistant shall meet the requirements on both front and back surfaces.

Lens powers and surface form is restricted for testing, however test results are applicable to claims for lenses and lens surfaces with identical properties other than the lens power or surface radius.

This part of ISO 8980 does not attempt to define the properties of lens surfaces with abrasion resistance better than the following defined criteria.

### 2 Normative references

The following referenced documents are indispensable for the application of this document. For dated references, only the edition cited applies. For undated references, the latest edition of the referenced document (including any amendments) applies.

ISO 48, *Rubber, vulcanized or thermoplastic — Determination of hardness (hardness between 10 IRHD and 100 IRHD)*

ISO 13666, *Ophthalmic optics — Spectacle lenses — Vocabulary*

ISO 8980-4, *Ophthalmic optics — Uncut finished spectacle lenses — Part 4: Specifications and test methods for anti-reflective coatings*

### 3 Terms and definitions

For the purposes of this document, the terms and definitions given in ISO 13666 and in ISO 8980-4 and the following apply.

#### 3.1

##### **abrasion resistance**

property of a spectacle lens surface to resist damage during normal use such as scratches caused by cleaning or wear

## 4 Requirement

Under the conditions described in the test method given in Clause 5, the surface tested shall be free of visible abrasion.

When used as a type test, 10 consecutively tested surfaces shall be free of visible abrasion.

## 5 Test method

### 5.1 Materials and equipment

#### 5.1.1 Abrasion tool

The abrasion tool<sup>1)</sup> allows the controlled positioning and movement of an eraser covered with cheesecloth against the test surface. The abrasion tool is calibrated to apply a force of  $(5 \pm 1)$  N. (A model of an abrasion tool is shown in Annex A.)

#### 5.1.2 Eraser

The eraser<sup>1)</sup> (see Annex A) shall be a uniform mixture of rubber and abrasive, formed by an extrusion process. It shall be composed of no less than 15 % by mass of pumice. All abrasive shall be fine-ground, such that 100 % will pass through a sieve with opening 45  $\mu$ m. The formulation shall not contain any ingredient that might leave a residue on the surface under test that would lubricate subsequent strokes during the test procedure. The finished eraser shall have an international rubber hardness degree (IRHD) in accordance with ISO 48 of  $75 \pm 5$  on both ends. The diameter of the eraser shall be from 6,5 mm to 7 mm with a usable flat surface of no less than 5,5 mm. It shall be of sufficient length so as to be held securely in the abrasion tester with no more than 3 mm exposed. The eraser shall be free from any excessive holes, cracks, splits, or foreign particles, which might adversely affect its use. In order to maintain specified hardness, the eraser shall periodically be checked and replaced as required.

#### 5.1.3 Cotton cheesecloth

The cheesecloth<sup>1)</sup> (see Annex A) shall be unbleached, the warp shall have 41 yarns to 47 yarns per 25 mm, and the weft shall have 33 yarns to 39 yarns per 25 mm. The total number of yarns in a 25 mm by 25 mm square shall be 76 to 84.

#### 5.1.4 Lens and surface form

The lenses to be tested shall have an optical power between  $-3,00$  D and  $+3,00$  D.

The tested surface shall have a numerical radius of curvature no less than 75 mm.

---


1) Abrasion tool, cheesecloth and eraser manufactured to the requirements in 5.1 may be available from:

Summers Optical	phone (215) 646 1477
321 Morris Road	fax (215) 646 8931
P.O. Box 162	e-mail <a href="mailto:sgkcck@aol.com">sgkcck@aol.com</a>
Fort Washington, PA 19034	<a href="http://www.emsdiasum.com">http://www.emsdiasum.com</a>
USA	

This information is given for the convenience of users of this part of ISO 8980 and does not constitute an endorsement by ISO of this supplier.

### 5.1.5 Inspection lighting

Use a fluorescent light source of at least 400 lm, which, for example can be achieved by one fluorescent tube of 15 W or a set of two fluorescent tubes of 8 W each. The light source and specimen shall be configured as shown in Figure 1 and Figure 2. Inspect the lens in a room with ambient lighting of about 200 lx.

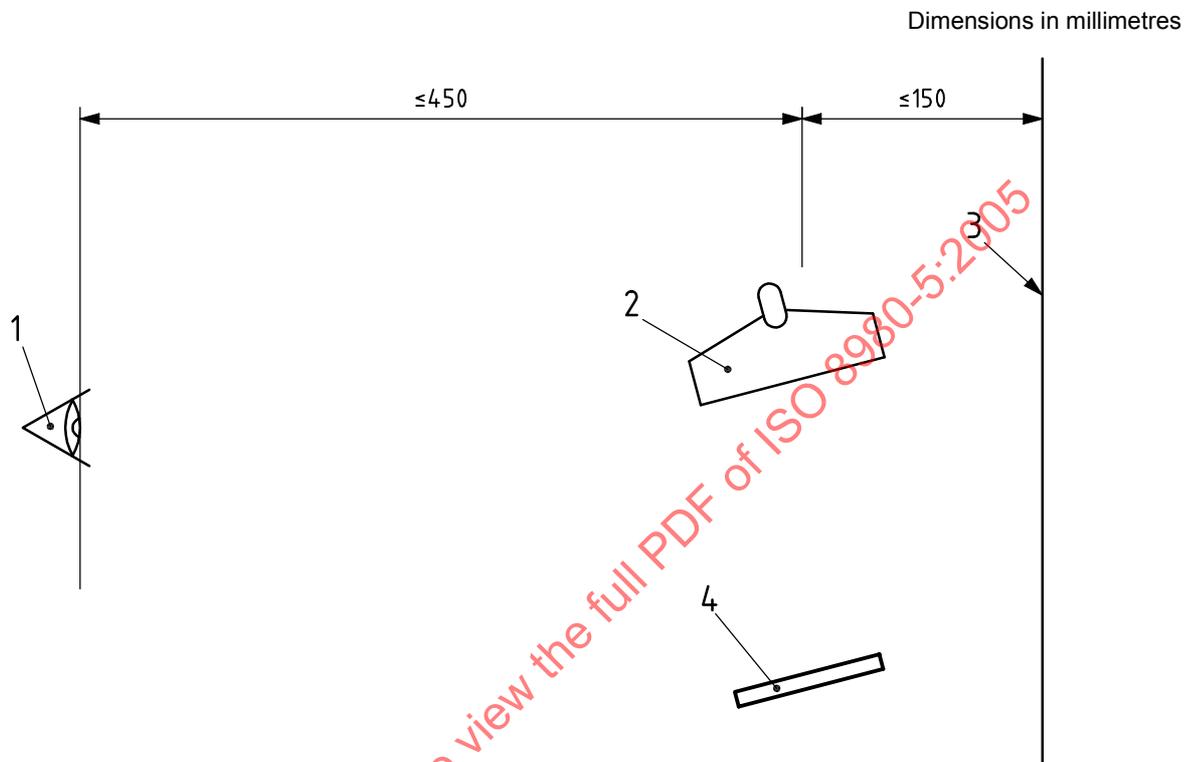

#### Key

- 1 observer
- 2 commercial fixture containing light source
- 3 matt black background
- 4 specimen

Figure 1 — Reflection inspection



Dimensions in millimetres

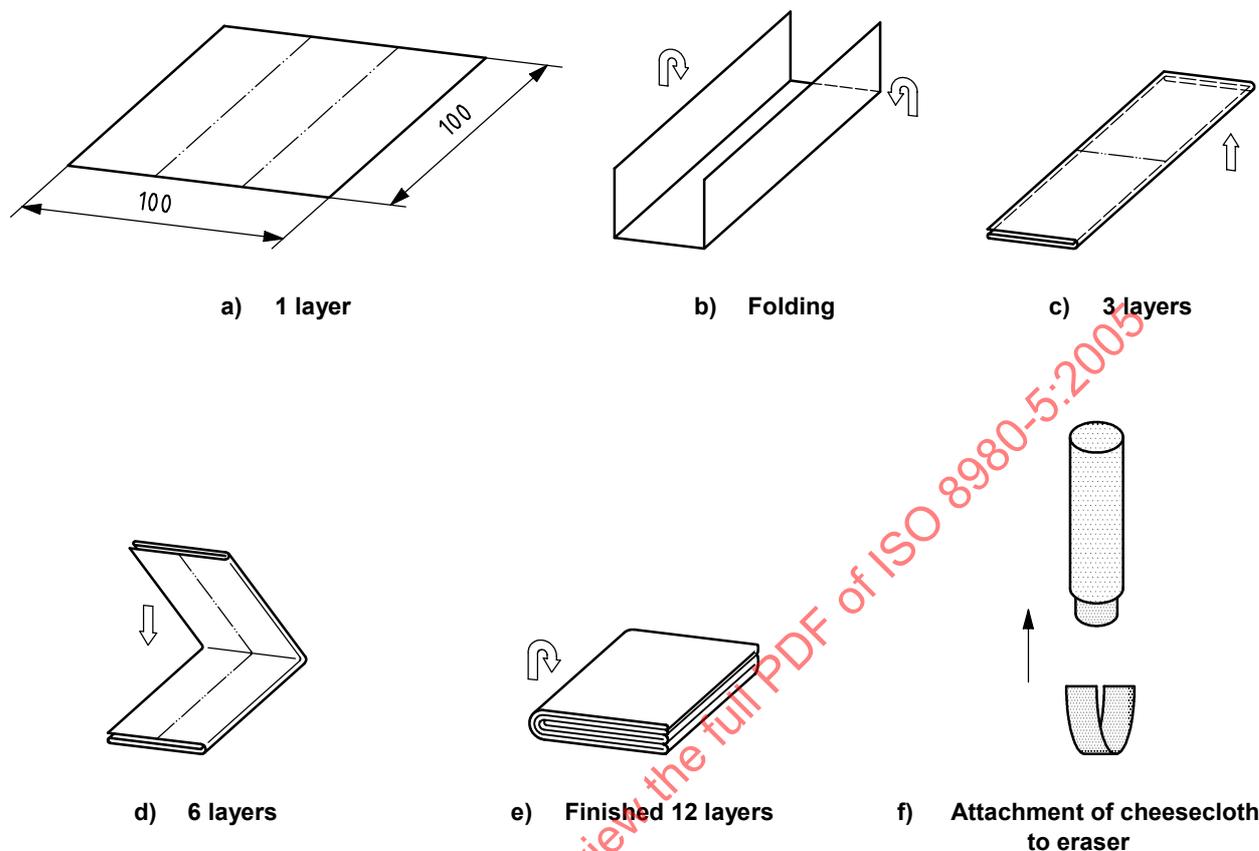


Figure 3 — Cheesecloth and tool assembly

### 5.3 Procedure

Rub the lens surface with the prepared tool applying the force of  $(5 \pm 1)$  N for 25 cycles. A cycle is defined as one stroke in one direction, followed by a return stroke in the opposite direction. A stroke is defined as one pass in one direction on the surface being tested. The centre of the abrasion track shall pass within  $\pm 2$  mm of the geometric centre, with a stroke length of  $(30 \pm 5)$  mm. The test shall be conducted at a rate of  $(1 \pm 0,1)$  cycle per second.

The lens sample shall be held firmly so that it does not move during the test. The tool shall follow the curvature of the lens during the rubbing operation to within  $\pm 5^\circ$  of the normal to the surface under test.


Inspect the lens surface tested by reflection and side illumination as described in Figures 1 and 2 for any visible scratches. If visible scratches are observed, refer to 5.2.

The use of mechanization can make it easier to perform the test (see Annex C).

## Annex A (informative)

### Model of an abrasion tool and components

The plunger, which can move longitudinally within the body of the tool, is fitted at one end with a chuck holding an eraser wrapped in cheesecloth, while the other end carries a scale or other marking indicating the position of the plunger within the body. The plunger is loaded by a spring to apply a force of  $(5 \pm 1)$  N when the body is held vertically to the specimen surface and the scale marking is in its required position.

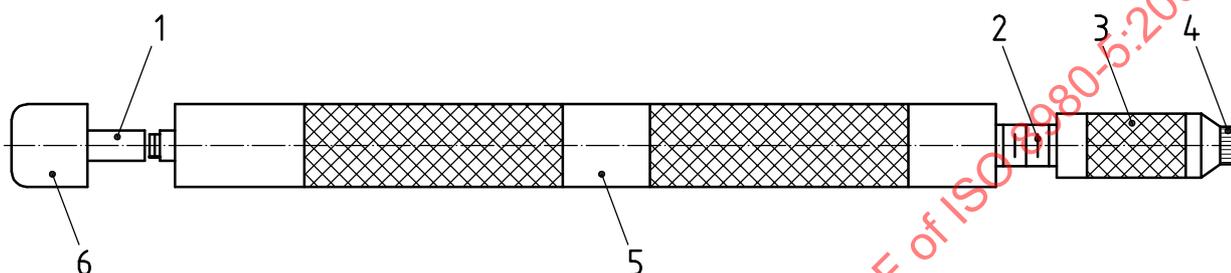

#### Key

- 1 indicator rod
- 2 plunger
- 3 chuck
- 4 eraser
- 5 body
- 6 cap

Figure A.1 — Model of an abrasion tool

## **Annex B** (normative)

### **Verification of test conditions**

The results of this test can be adversely affected by unwanted particulate contamination. The following can be used to determine the cleanliness of the test site.

10 uncoated fully cured ADC (allyl diethyleneglycol carbonate) lenses shall be tested using the method described in Clause 5. All tested lens surfaces shall have no visible abrasion.

If the requirements of evaluation are not met, clean the area in which the test is being performed or move the test to a cleaner site. Assure that the cloth used in the test is clean and is stored in a manner that it is protected from airborne dust.

STANDARDSISO.COM : Click to view the full PDF of ISO 8980-5:2005