
**Wood-based panels — Determination of
dimensions of panels**

*Panneaux à base de bois — Détermination des dimensions des
panneaux*

STANDARDSISO.COM : Click to view the full PDF of ISO 9426:2003



PDF disclaimer

This PDF file may contain embedded typefaces. In accordance with Adobe's licensing policy, this file may be printed or viewed but shall not be edited unless the typefaces which are embedded are licensed to and installed on the computer performing the editing. In downloading this file, parties accept therein the responsibility of not infringing Adobe's licensing policy. The ISO Central Secretariat accepts no liability in this area.

Adobe is a trademark of Adobe Systems Incorporated.

Details of the software products used to create this PDF file can be found in the General Info relative to the file; the PDF-creation parameters were optimized for printing. Every care has been taken to ensure that the file is suitable for use by ISO member bodies. In the unlikely event that a problem relating to it is found, please inform the Central Secretariat at the address given below.

STANDARDSISO.COM : Click to view the full PDF of ISO 9426:2003

© ISO 2003

All rights reserved. Unless otherwise specified, no part of this publication may be reproduced or utilized in any form or by any means, electronic or mechanical, including photocopying and microfilm, without permission in writing from either ISO at the address below or ISO's member body in the country of the requester.

ISO copyright office
Case postale 56 • CH-1211 Geneva 20
Tel. + 41 22 749 01 11
Fax + 41 22 749 09 47
E-mail copyright@iso.org
Web www.iso.org

Published in Switzerland

Foreword

ISO (the International Organization for Standardization) is a worldwide federation of national standards bodies (ISO member bodies). The work of preparing International Standards is normally carried out through ISO technical committees. Each member body interested in a subject for which a technical committee has been established has the right to be represented on that committee. International organizations, governmental and non-governmental, in liaison with ISO, also take part in the work. ISO collaborates closely with the International Electrotechnical Commission (IEC) on all matters of electrotechnical standardization.

International Standards are drafted in accordance with the rules given in the ISO/IEC Directives, Part 2.

The main task of technical committees is to prepare International Standards. Draft International Standards adopted by the technical committees are circulated to the member bodies for voting. Publication as an International Standard requires approval by at least 75 % of the member bodies casting a vote.

Attention is drawn to the possibility that some of the elements of this document may be the subject of patent rights. ISO shall not be held responsible for identifying any or all such patent rights.

ISO 9426 was prepared by Technical Committee ISO/TC 89, *Wood-based panels*.

STANDARDSISO.COM : Click to view the full PDF of ISO 9426:2003

Introduction

This edition is based on European Standards EN 324-1 and EN 324-2. It cancels and replaces ISO 9426-1:1989 which applied to the measurement of thickness, width and length. The scope was extended to include the determination of squareness and edge straightness of panels which were formerly included in ISO 9426-2. Furthermore, the determination of flatness of panels was added. Compared to ISO 9426-1:1989, for the thickness measurement, a range has been specified for the anvil diameter and for the distance of measuring points, from the edges.

STANDARDSISO.COM : Click to view the full PDF of ISO 9426:2003

Wood-based panels — Determination of dimensions of panels

1 Scope

This International Standard specifies methods for measuring the thickness, width and length, as well as the squareness, edge straightness and flatness of wood-based panels.

It applies to full-size flat panels.

2 Normative references

The following referenced documents are indispensable for the application of this document. For dated references, only the edition cited applies. For undated references, the latest edition of the referenced document (including any amendments) applies.

ISO 16979, *Wood-based panels — Determination of moisture content*

ISO 16999, *Wood-based panels — Sampling and cutting of test pieces*

3 Principle

The thickness, length and width of full-size panels are determined by linear measurement.

Squareness and edge straightness of full-size panels are determined by the measurement of deviation from a mechanical square or straight edge.

Flatness is determined by measuring the deviation of the panel surface from a taut string line placed across the whole surface and against the edge of the panel.

4 Sampling

Sampling of panels shall be in accordance with ISO 16999.

5 Moisture content at time of measurement

Normally the dimensions of panels are measured in the as-received state.

If necessary, the moisture content of the panels shall be determined in accordance with ISO 16979.

6 Conditioning

If necessary, the panels shall be conditioned to constant mass in an atmosphere with a relative humidity of $(65 \pm 5) \%$ and a temperature of $(20 \pm 2) ^\circ\text{C}$. Constant mass is considered as having been reached when the results of two successive weighing operations, carried out at an interval of 24 h, do not differ by more than 0,1 % of the mass of the panel.

For flatness measurement, allow newly made panels to reach room temperature and condition them for a minimum of 48 h in a well ventilated room at that temperature prior to testing.

7 Apparatus

7.1 Micrometer or similar measuring instrument, for thickness measurement, having flat and parallel circular anvils of diameter between 6,0 mm and 20,0 mm diameter and an operating pressure between 0,02 MPa and 0,05 MPa. The graduation of the apparatus shall allow a reading to 0,05 mm.

The anvil diameter selected will depend on the panel type. In principle, panels of low density and/or uneven surface should be measured using the larger anvil diameter.

7.2 Steel measuring tape, of scale interval 1 mm.

7.3 Mechanical square, having two arms of $(1\ 000 \pm 1)$ mm for measuring the deviation of the angles of adjacent sides of a panel from a right angle. It shall be accurate to 0,2 mm in 1 000 mm (see Figure 1).

Dimensions in millimetres

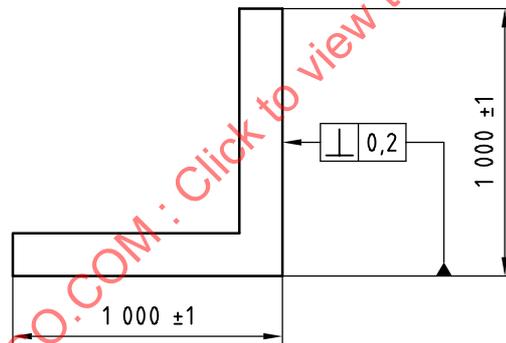


Figure 1 — Accuracy requirements of mechanical square

7.4 Straightedge, of length at least equal to the length of the board, or wire of constant cross-section and flexible enough to be stretched to assure linearity.

7.5 Steel rule, wedge or caliper, for deviation measurements graduated to allow reading to 0,5 mm.


7.6 String line, fine builders' string line for flatness measurement.

8 Procedure

8.1 Determination of thickness of panels

Measure the thickness between 24 mm and 50 mm from the edges, at points located in each corner and in the middle of each side, i.e. at eight points in all (see Figure 2), to an accuracy of 1 % of the thickness but to not less than 0,1 mm.

For measuring the thickness, apply the measuring surfaces of the instrument slowly to the panel surface.

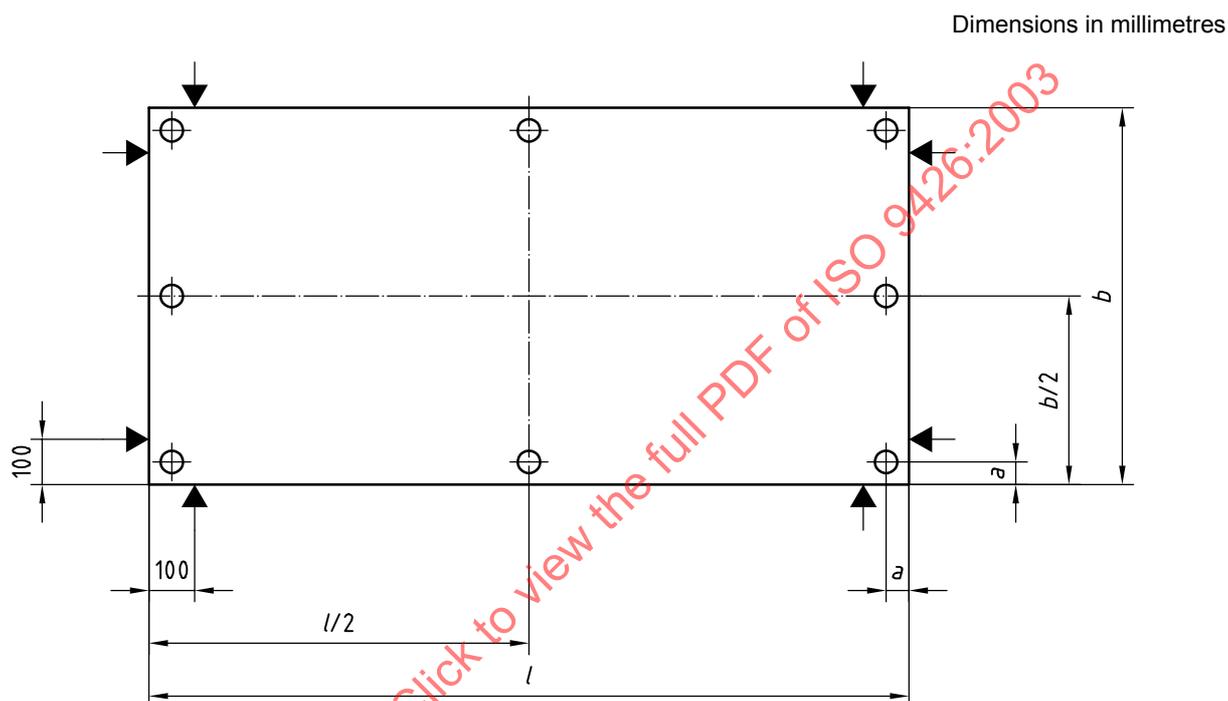

Key

- a = 24 to 50
- b Width
- l Length

Figure 2 — Points of measurement of thickness ⊕, length and width → of a board

8.2 Determination of length and width of panels

Measure both the length and width of each panel along two lines parallel to and at a distance of 100 mm from the edges (see Figure 1), to an accuracy of 0,1 % but not less than 1 mm.

8.3 Determination of squareness of panels

Place one side of the square (7.3) against one side of the panel, the squareness of which is to be measured (see Figure 3).

At a distance of $(1\,000 \pm 1)$ mm from the corner of the panel, measure the distance δ_1 between the panel edge and the side of the other arm of the square, by means of one of the measuring devices specified in 7.5 (see Figure 3).

Follow the same procedure for each of the other corners.

NOTE For factory-production control, the squareness may also be determined as the difference of the two diagonal lengths of the panel measured using the steel measuring tape if a valid correlation can be proven.

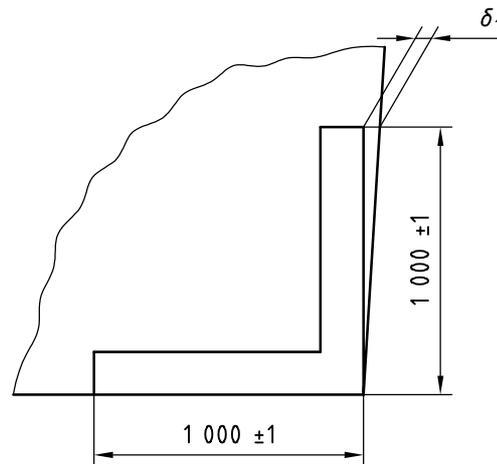


Figure 3 — Use of mechanical square to measure panel squareness

8.4 Determination of edge straightness of panels

Place the straightedge (7.4) against a panel edge, or locate the wire at the corners of the panel and stretch it.

Measure the largest deviation between the straight edge (or string line) and the edge of the panel using one of the measuring devices specified in 7.5 and read the result to 0,5 mm.

Follow the same procedure for each of the other edges.

8.5 Determination of flatness of panels

Place the panel without restraint on a flat horizontal surface. Span the whole surface to be tested with the string line (7.6) stretched taut. Measure the distance between the string line and surface at the point of greatest deformity in the panels, to the nearest 0,5 mm, using the steel rule (7.5).

9 Expression of results

9.1 Thickness

For each panel tested, the arithmetic mean of the measurements shall be calculated and expressed to the nearest 0,1 mm.

9.2 Length and width

For each panel tested, the arithmetic mean of the measurements shall be calculated and expressed, for the length and the width, to the nearest 1 mm.

9.3 Squareness of panels

The result is the largest measured value of the deviation of the side of square and the panel edge. It is expressed in millimetres per metre of board-edge length, to the nearest 0,5 mm/m.